

Footwear — Test methods for insoles — Dimensional stability

The European Standard EN 12800:2000 has the status of a
British Standard

ICS 61.060

National foreword

This British Standard is the English language version of EN 12800:2000.

The UK participation in its preparation was entrusted to Technical Committee TCI/69, Footwear and leather, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled “International Standards Correspondence Index”, or by using the “Find” facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 5 and a back cover.

The BSI copyright notice displayed throughout this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

This British Standard, having been prepared under the direction of the Sector Committee for Materials and Chemicals, was published under the authority of the Standards Committee and comes into effect on 15 May 2000

© BSI 05-2000

ISBN 0 580 34267 0

ICS 61.060

English version

Footwear — Test methods for insoles — Dimensional stability

Chaussures — Méthodes d'essai relatives aux
premières de montage — Stabilité dimensionnelle

Schuhe — Prüfverfahren von Brandsohlen —
Maßhaltigkeit

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 309, Footwear, the Secretariat of which is held by AENOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2000, and conflicting national standards shall be withdrawn at the latest by August 2000.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Contents

	Page
Foreword	2
1 Scope	3
2 Normative references	3
3 Definitions	3
4 Apparatus and material	3
5 Sampling and conditioning	3
6 Test method	3
7 Expression of results	4
8 Test report	4

1 Scope

This European Standard specifies a method for the determination of the dimensional stability of insoles, irrespective of the material, after immersion in water.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to, or revisions of, any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 12222, *Footwear — Standard atmospheres for conditioning and testing of footwear and components for footwear.*

prEN 13400:1998, *Footwear — Sampling location of components for footwear.*

3 Definitions

For the purposes of this standard the following definitions apply.

3.1

swelling

gain in thickness, expressed as a percentage, after leaving the test piece of insole material submerged in water for 6 h

3.2

increase in size

increase in length and in width, expressed as a percentage, after leaving the test piece of insole material in water for 6 h

3.3

shrinkage

reduction in length and width, expressed as a percentage, of a test piece of insole material after leaving the test piece in an oven at 35 °C for 24 h

3.4

dimensional stability

the change in the distance between two reference points on a test piece before and after specified test conditions (e.g. heat, moisture) expressed as a percentage of the initial distance

4 Apparatus and material

The following apparatus and material shall be used:

4.1 Dual micrometer gauge, standing on a firm base and loaded with a dead mass such that the presser foot applied a pressure of $50 \text{ kPa} \pm 5 \text{ kPa}^1$. The gauge has a presser foot which is flat, circular and 10,0 mm in diameter.

The gauge has scale divisions of 0,01 mm.

4.2 Measuring device — Vernier calipers or similar, capable of measuring to an accuracy of 0,1 mm.

4.3 Glass or flat bottomed container of an adequate size such that the test piece can be placed in the bottom.

4.4 Oven, for heating the test piece to 35 °C and thermostatically controlled so that the test piece is kept within 1 °C of the required temperature during the heating period.

4.5 Distilled water

5 Sampling and conditioning

From the shoe insoles, cut insoles, or component as supplied into two square or rectangular test pieces of $(60 \text{ mm} \pm 20 \text{ mm}) \times (60 \text{ mm} \pm 20 \text{ mm})$, one to determine swelling and size growth and the other to determine shrinking. According to the given dimensions, cut the test piece as big as the sample will allow.

If the test pieces are taken from the shoes or cut component, sampling shall be done according to prEN 13400:1998.

condition the test pieces according to EN 12222, for a minimum of 24 h.

6 Test method

6.1 Swelling and increase in size

On one of the conditioned test pieces trace parallel lines 5 mm in from each side. Label the corners of the square or rectangle formed A, B, C and D (see Figure 1). Trace diagonals AD and BC. Mark the centre E and the half way points of the diagonals AE, BE, CE and ED and label them F, G, H and I.

Measure the distances between the points A-B, C-D, A-C and B-D with a measuring device.

Measure the thickness at points E, F, G, H and I with the dial micrometer gauge.

Submerge the test piece in distilled water for 6 hours.

The test piece must be fully submerged in water being loaded with a small weight.

Take the test piece out of the water and eliminate superficial drops of water.

Measure the distances AB, CD, AC and BD again and the thickness at points E, F, G, H and I.

¹⁾ $1 \text{ Pa} = 1 \text{ N/m}^2$.

6.2 Shrinkage

On the other conditioned test piece mark parallel lines in the same way as in 6.1 (see Figure 1). Measure distances A-B, C-D, A-C and B-D.

Leave the test piece in the drying oven (see 4.4) for 24 h. Then measure again the distances A-B, C-D, A-C and B-D.

7 Expression of results

7.1 Swelling

Calculate the average value of the five thicknesses e_o .

Calculate the average value of the five thicknesses after removing the test piece from the water e_f .

Swelling, H , is calculated as a percentage (%) from the equation:

$$H = \frac{e_f - e_o}{e_o} \times 100$$

where

e_f is the thickness of test piece when wet.

e_o is the thickness of test piece when dry.

Express the result to the nearest 0,5 %.

7.2 Increase in size

Calculate the average value of the initial distances A-B and C-D measured in accordance with 6.1 and call it a_1 . In the same way find the average of the initial distances A-C and B-D and call it b_1 .

In the same way calculate the averages of the same distances measured after taking the test pieces out of the water and call it a_2 for the distances A-B and C-D and b_2 for distances A-C and B-D.

Calculate the increase in size, V , expressed as a percentage, from the equations:

$$V_a = \frac{a_2 - a_1}{a_1} \times 100$$

(Increase in size in direction a)

$$V_b = \frac{b_2 - b_1}{b_1} \times 100$$

(Increase in size in direction b)

Express the result to the nearest 0,5 %.

7.3 Shrinkage

Calculate the average of the distances A-B and C-D measured in accordance with 6.2 and call it a_o .

In the same way find the average of the distances A-C and B-D and call it b_o .

Calculate the averages of the same distances measured after leaving the test piece for 24 h in the oven at 35 °C and call them a_{24} and b_{24} .

Calculate the shrinkage S , as a percentage, from the equations:

$$S_a = \frac{a_o - a_{24}}{a_o} \times 100$$

and

$$S_b = \frac{b_o - b_{24}}{b_o} \times 100$$


Express the result to the nearest 0,5 %.

The result will be the average of the two values.

8 Test report

The test report shall include the following information:

- the results for swelling, increase in size and shrinkage expressed according to 7.1, 7.2 and 7.3;
- full description of the samples tested including commercial styles codes, colours, nature, etc.;
- description of sampling procedure, where relevant;
- reference to the method of test;
- details of any deviation from the standard test procedure;
- any deviations from the test method;
- date of testing.

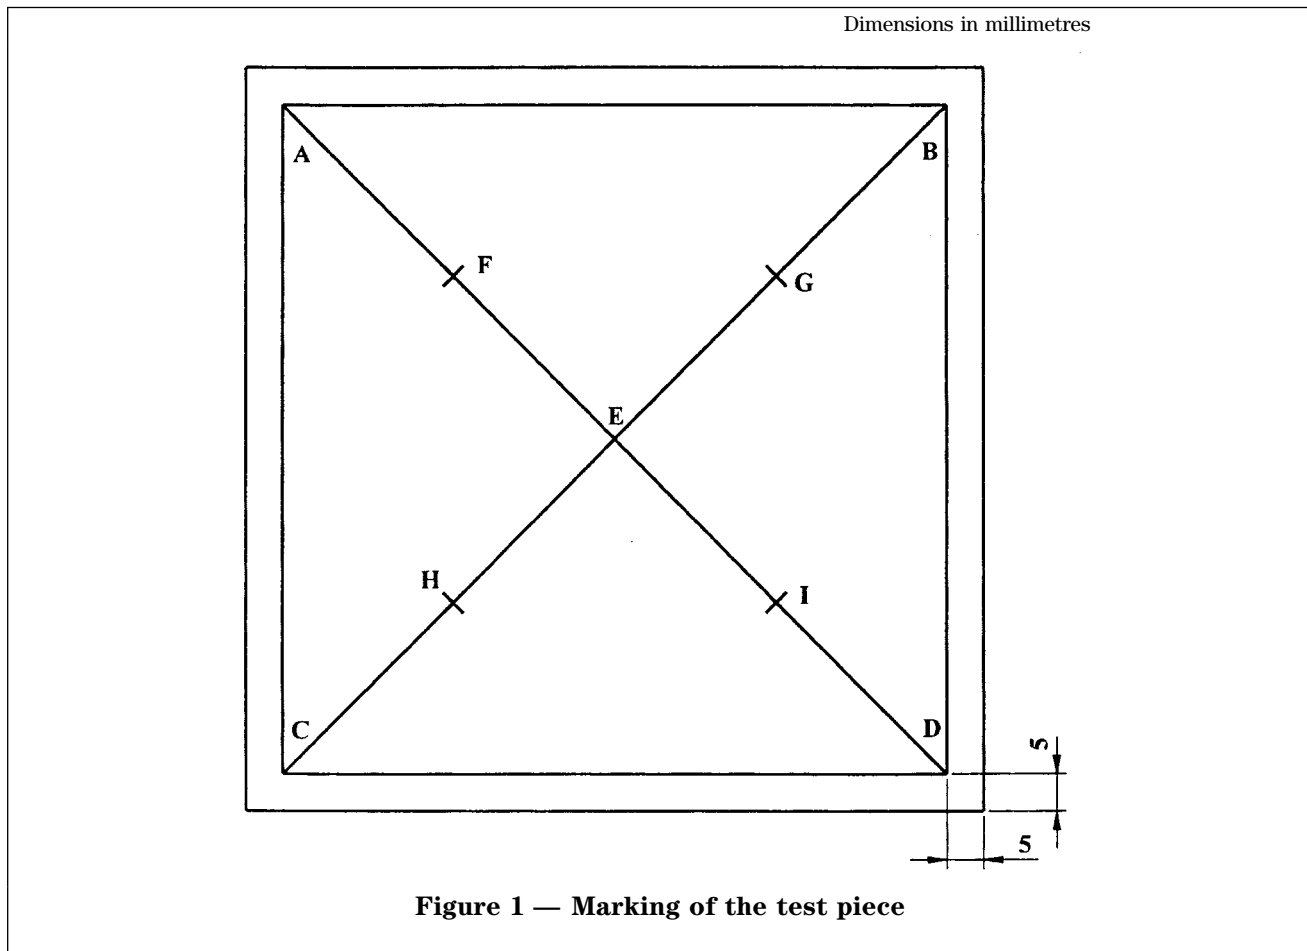

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.