

BS EN 13523-1:2017



BSI Standards Publication

Coil coated metals — Test methods

Part 1: Film thickness

National foreword

This British Standard is the UK implementation of EN 13523-1:2017. It supersedes BS EN 13523-1:2009 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee STI/21, Paint systems and surface preparation for metallic substrates.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2017.
Published by BSI Standards Limited 2017

ISBN 978 0 580 91551 2

ICS 17.040.20; 25.220.60

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 28 February 2017.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD

EN 13523-1

NORME EUROPÉENNE

EUROPÄISCHE NORM

February 2017

ICS 17.040.20; 25.220.60

Supersedes EN 13523-1:2009

English Version

Coil coated metals - Test methods - Part 1: Film thicknessTôles prélaquées - Méthodes d'essai - Partie 1 :
Épaisseur du revêtementBandbeschichtete Metalle - Prüfverfahren - Teil 1:
Schichtdicke

This European Standard was approved by CEN on 18 December 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG**CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels**

Contents		Page
European foreword		3
1	Scope	5
2	Normative references	5
3	Terms and definitions	5
4	Principle	5
4.1	Method A: Measurement on a magnetic substrate - magnetic induction	5
4.2	Method B: Measurement on a non-magnetic substrate - eddy current	6
4.3	Method C: Measurement on all substrates - micrometer method	6
4.4	Method D: Measurement on all substrates - optical method	6
5	Apparatus and materials	6
6	Sampling	6
7	Test panels	6
8	Procedure	6
8.1	Calibration	6
8.1.1	General	6
8.1.2	Calibration standards	7
8.2	Scale rating	7
8.3	Measurement	7
8.3.1	Ambient conditions	7
8.3.2	Number of measurements	7
8.3.3	Method A: Magnetic induction	7
8.3.4	Method B: Eddy current	8
8.3.5	Method C: Micrometer method	8
8.3.6	Method D: Optical method	8
9	Expression of results	9
10	Accuracy	9
11	Test report	9
Bibliography		10

European foreword

This document (EN 13523-1:2017) has been prepared by Technical Committee CEN/TC 139 “Paints and varnishes”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2017, and conflicting national standards shall be withdrawn at the latest by August 2017.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 13523-1:2009.

The main changes are:

- a) a reference to EN 13523-0 concerning conditioning of the test panels was added;
- b) the principle clause for methods A and B have been stated more precisely;
- c) the number of measurements has been added to methods C and D;
- d) the text has been editorially revised and the normative references have been updated.

The EN 13523 series, *Coil coated metals — Test methods*, consists of the following parts:

- *Part 0: General introduction*
- *Part 1: Film thickness*
- *Part 2: Gloss*
- *Part 3: Colour difference — Instrumental comparison*
- *Part 4: Pencil hardness*
- *Part 5: Resistance to rapid deformation (impact test)*
- *Part 6: Adhesion after indentation (cupping test)*
- *Part 7: Resistance to cracking on bending (T-bend test)*
- *Part 8: Resistance to salt spray (fog)*
- *Part 9: Resistance to water immersion*
- *Part 10: Resistance to fluorescent UV radiation and water condensation*
- *Part 11: Resistance to solvents (rubbing test)*
- *Part 12: Resistance to scratching*
- *Part 13: Resistance to accelerated ageing by the use of heat*

- *Part 14: Chalking (Helmen method)*
- *Part 15: Metamerism*
- *Part 16: Resistance to abrasion*
- *Part 17: Adhesion of strippable films*
- *Part 18: Resistance to staining*
- *Part 19: Panel design and method of atmospheric exposure testing*
- *Part 20: Foam adhesion*
- *Part 21: Evaluation of outdoor exposed panels*
- *Part 22: Colour difference — Visual comparison*
- *Part 23: Resistance to humid atmospheres containing sulfur dioxide*
- *Part 24: Resistance to blocking and pressure marking*
- *Part 25: Resistance to humidity*
- *Part 26: Resistance to condensation of water*
- *Part 27: Resistance to humid poultice (Cataplasm test)*
- *Part 29: Resistance to environmental soiling (Dirt pick-up and striping)*

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

1 Scope

This part of the EN 13523 series specifies the procedures for determining the dry-film thickness of an organic coating on a metallic substrate (coil coating).

Four appropriate methods are given in this European Standard:

- a) magnetic induction;
- b) eddy current;
- c) micrometer;
- d) optical.

The methods are applicable only to products with smooth and flat substrates but the coating itself may be textured. In that case, for methods a) and b) the average of a series of readings will represent an average of the thickness of the organic coating, while method c) will give the maximum thickness and method d) can provide the minimum, maximum and average thickness.

Non-destructive continuous-web methods on measurement of dry-film thickness (see EN ISO 2808) are not dealt with.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 13523-0:2014, *Coil coated metals - Test methods - Part 0: General introduction*

EN 23270, *Paints and varnishes and their raw materials - Temperatures and humidities for conditioning and testing (ISO 3270)*

EN ISO 3611, *Geometrical product specifications (GPS) - Dimensional measuring equipment: Micrometers for external measurements - Design and metrological characteristics (ISO 3611)*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 13523-0 and the following apply.

3.1

film thickness

distance between the surface of the film and the surface of the substrate

[SOURCE: EN ISO 2808:2007, 3.3]

4 Principle

4.1 Method A: Measurement on a magnetic substrate – magnetic induction

The film thickness on a magnetic substrate is determined by means of an electromagnetic probe placed on the coating and developing an electromagnetic field. The variation of this field is a function of the distance between the probe and the substrate. This signal is measured and converted to the film thickness reading.

4.2 Method B: Measurement on a non-magnetic substrate – eddy current

The film thickness on a non-magnetic conductive substrate is determined by means of an electromagnetic probe placed on the coating and generating eddy currents in the substrate. The magnitude of the eddy currents is a function of the distance between the probe and the substrate. This measuring signal is derived from the impedance change in the probe and converted to the film thickness reading.

4.3 Method C: Measurement on all substrates – micrometer method

The film thickness is determined by measuring the coated sample and then removing the organic coating and re-measuring the sample minus the coating or by measuring a film of organic coating that has been removed from the sample.

4.4 Method D: Measurement on all substrates – optical method

The film thickness is determined by microscopical measurement of a section cut through the film. The defined cut may be made in the coating using a special blade (symmetrical cut), a special paint borer (conical bore) or a milling tool (sloping cut).

5 Apparatus and materials

5.1 Instruments for measuring film thickness, using the principles described in Clause 4.

5.2 Solvent, suitable for removing organic coatings, for example methyl ethyl ketone (2-butanone).

5.3 Suitable abrasive and/or **blunt knife** or other means of removing softened organic coatings that do not damage the substrate.

5.4 Cutting tool, for Method D.

5.4.1 Blade, for making a symmetrical cut in the coating.

5.4.2 Paint borer, for making a conical bore in the coating.

5.4.3 Milling tool, for making a sloping cut in the coating.

6 Sampling

Shall be according to EN 13523-0.

7 Test panels

Shall be according to EN 13523-0.

8 Procedure

8.1 Calibration

8.1.1 General

For the measurement, the instructions of the manufacturer of the instrument shall be taken into account, in particular regarding the calibration and/or setting up procedure.

Before use, calibrate each instrument in accordance with the manufacturer's instructions using calibration standards. For instruments that cannot be calibrated, determine the deviation from the nominal value by comparison with calibration standards and take this into consideration for all measurements.

During use, check the calibration of the instrument as specified by the instrument's manufacturer.

8.1.2 Calibration standards

Calibration standards of known and uniform thickness are available either as foils or shims, or as coated standards with assigned values traceable to nationally recognized standards.

Calibration foils are generally made of plastics materials. They are subject to indentation and shall, therefore, be replaced frequently.

For methods A and B the surface and magnetic properties and the thickness of the metallic substrate of the coated calibration standards shall be similar to those of the test specimen.

For methods C and D the substrate of the test specimen and of the calibration standards shall be the same, provided the critical thickness (see Note) is not exceeded.

NOTE For each instrument, there is a critical thickness of metallic substrate above which instruments will not be affected by an increase in thickness.

8.2 Scale rating

For methods A and B, and if necessary, select the scale with a maximum above the estimated thickness of the coating and adjust the instrument to the thickness of a known non-metallic standard measured on the reference plate. The readings at several positions shall not vary by more than $\pm 5\%$. The thickness of the standard shall be greater than half the measuring scale used.

8.3 Measurement

8.3.1 Ambient conditions

Measure the film thickness at ambient temperature. For more accurate measurements, as required for instance in case of dispute, the temperature shall be $(23 \pm 2)^\circ\text{C}$ and the relative humidity $(50 \pm 5)\%$, in accordance with EN 23270. Conditioning is carried out in accordance with EN 13523-0:2014, Clause 6.

8.3.2 Number of measurements

For methods A and B, take at least five measurements on smooth surfaces, and at least 10 measurements on textured coatings.

For methods C and D, it is recommended that a minimum number of five measurements is taken.

8.3.3 Method A: Magnetic induction

The samples shall be measured on a non-metallic and non-conductive table.

Place the probe perpendicular to and in contact with the coated panel and read the film thickness on the standard scale.

In the case of metallic coated steel (e.g. galvanized steel), the electromagnetic probe cannot measure simultaneously the metallic and the organic coating. Therefore, determine first the total thickness of the metallic coating and organic coating and, after having removed the organic coating, measure the thickness of the metallic coating on the same place. The difference gives the thickness of the organic coating.

Remove the organic coating with a solvent (5.2). After an adequate period of contact with the solvent, remove the softened organic coating by abrasive action using an abrasive and/or blunt knife (5.3). This stripping process shall not remove any metallic coating.

8.3.4 Method B: Eddy current

The samples shall be measured on a non-metallic and non-conductive table.

Place the probe perpendicular to and in contact with the coated panel and read the film thickness on the standard scale.

8.3.5 Method C: Micrometer method

Operate all instruments so that the coated specimen side is facing the spindle. With the hand-held type, press the specimen against the fixed measuring tip. Carry out each measurement such that the spindle of the micrometer is pressed against the surface to be tested. Turn the spindle until the ratchet is activated.

Remove the organic coating with a solvent (5.2). After an adequate period of contact with the solvent, remove the softened organic coating by abrasive action using an abrasive and/or blunt knife (5.3). This stripping process shall not remove any metallic coating.

Repeat the second measurement after removing the film. Calculate the film thickness from the difference in the readings for the total thickness and the substrate thickness.

For measuring free films, remove a filmstrip and measure the thickness according to above.

The external micrometer gauge design shall conform to the requirements of EN ISO 3611. An example is shown in Figure 1. Both jaws shall be in the same plane.

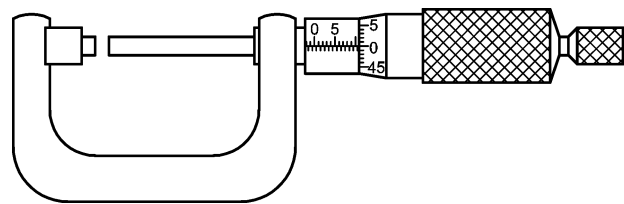


Figure 1 — Micrometer screw gauge

8.3.6 Method D: Optical method

Use the instrument (5.4) to make a cut in the organic coating down to the substrate, according to Figure 2. Examine using a microscope.


The cut is made with a specified angle in the coating. The film thickness t , is calculated either manually or by the device using the equation

$$t = b \times \tan \alpha$$

where

b is the projected width determined using a microscope;

α is the angle of cut.

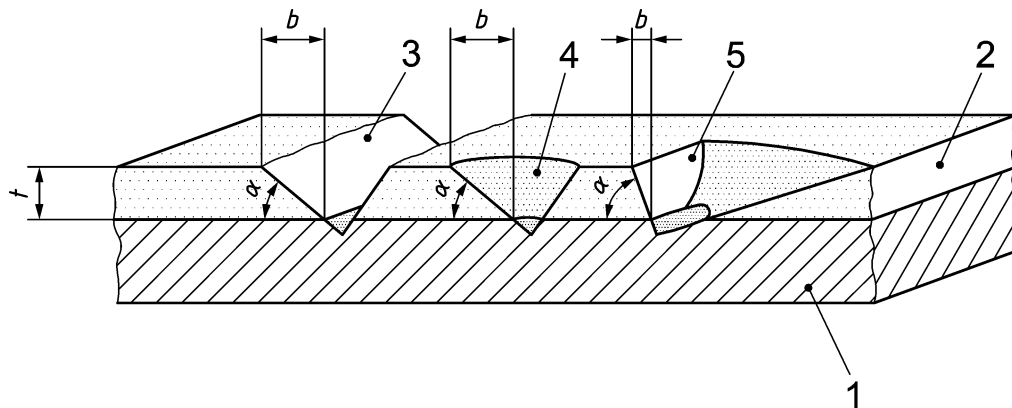

Key

- | | | | |
|---|-----------------|----------|-----------------|
| 1 | substrate | α | angle of cut |
| 2 | organic coating | b | projected width |
| 3 | symmetrical cut | t | film thickness |
| 4 | conical bore | | |
| 5 | sloping cut | | |

Figure 2 — Symmetrical cut, conical bore and sloping cut

NOTE For the conical bore method, see for instance ASTM D5796.

9 Expression of results

Express the results as the mean of the measurements taken, in micrometers (μm).

10 Accuracy

The accuracy depends on the equipment used. As a minimum, the instrument, its calibration and its operation shall be such that the film thickness can be determined to within 10 % or $\pm 1,5 \mu\text{m}$ of the true thickness of the coating, whichever is the greater of the two.

11 Test report

The test report shall contain at least the following information:

- a) all details necessary to identify the product tested;
- b) a reference to this part of the EN 13523 series (EN 13523-1);
- c) the method or combination of methods used;
- d) the results of the test, as indicated in Clause 9;
- e) any deviation from the test method specified;
- f) the date of the test.

Bibliography

- [1] EN 1396, *Aluminium and aluminium alloys - Coil coated sheet and strip for general applications - Specifications*
- [2] EN 10169, *Continuously organic coated (coil coated) steel flat products — Technical delivery conditions*
- [3] EN ISO 2178, *Non-magnetic coatings on magnetic substrates - Measurement of coating thickness - Magnetic method (ISO 2178)*
- [4] EN ISO 2360, *Non-conductive coatings on non-magnetic electrically conductive basis materials - Measurement of coating thickness - Amplitude-sensitive eddy current method (ISO 2360)*
- [5] EN ISO 2808:2007, *Paints and varnishes - Determination of film thickness (ISO 2808:2007)*
- [6] ASTM D5796, *Standard Test Method for Measurement of Dry Film Thickness of Thin-Film Coil-Coated Systems by Destructive Means Using a Boring Device*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK