

Pallet production specification —

Part 1: Construction specification for 800 mm x 1200 mm flat wooden pallets

The European Standard EN 13698-1:2003 has the status of a
British Standard

ICS 55.180.20

National foreword

This British Standard is the official English language version of EN 13698-1:2003.

The UK participation in its preparation was entrusted by Technical Committee PKW/5, Primary and transport packaging, to Subcommittee PKW/5/34, Pallets, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 27 and a back cover.

The BSI copyright date displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

This British Standard, was published under the authority of the Standards Policy and Strategy Committee on 9 July 2003

© BSI 9 July 2003

ISBN 0 580 42238 0

EUROPEAN STANDARD

EN 13698-1

NORME EUROPÉENNE

EUROPÄISCHE NORM

July 2003

ICS 55.180.20

English version

Pallet production specification - Part 1: Construction specification for 800 mm x 1200 mm flat wooden pallets

Spécification de produit pour les palettes - Partie 1:
Spécification de fabrication des palettes en bois, de
dimensions 800 mm x 1200 mm

Produktspezifikation für Paletten - Teil 1: Herstellung von
800 mm x 1200 mm Flachpaletten aus Holz

This European Standard was approved by CEN on 10 April 2003.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Slovakia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

	page
Foreword.....	3
Introduction	4
1 Scope	5
2 Normative references	5
3 Terms and definitions.....	5
4 Nominal and safe working loads.....	6
5 Construction.....	6
6 Inspections and marking.....	10
Annex A (normative) Materials.....	11
Annex B (informative) Wood shrinkage	17
Annex C (informative) Nail pattern.....	18
Annex D (normative) Joint separation test.....	20
Annex E (informative) Inspection (Quality control).....	22
Annex F (normative) Preservatives	25
Annex G (informative) Safe working loads under different loading situations.....	26
Bibliography	27

Foreword

This document (EN 13698-1:2003) has been prepared by Technical Committee CEN /TC 261 "Packaging", the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2004, and conflicting national standards shall be withdrawn at the latest by January 2004.

Annexes A, D and F are normative. Annexes B, C, E and G are informative.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Slovakia, Spain, Sweden, Switzerland and the United Kingdom.

Introduction

All general purpose re-usable pallets, irrespective of the material from which they are made, are required to conform to the dimensional requirements and performance criteria specified in the following standards:

EN 13382:2002	<i>Flat pallets for materials handling — Principal dimensions</i>
prEN ISO 8611-1	<i>Pallets for materials handling — Part 1: Test methods for flat pallets (ISO/DIS 8611-1:2000)</i>
prEN ISO/DIS 8611-2	<i>Pallets for materials handling - Flat pallets - Part 2: Performance requirements and selection of tests</i>
prEN ISO/DIS 8611-3	<i>Pallets for materials handling – Flat pallets - Part 3: Maximum working load</i>

Tests performed by various European railway companies, and over 30 years of experience in through transport of goods, have demonstrated that the design of pallet 'Europallet' conforms to the relevant dimensional requirements and appropriate tests specified in the above standards. This certifies that the quality of the pallet is suitable for normal purposes as regards the physical stresses involved in distribution and handling. Pallets in full conformity to this specification are therefore exempt from the load testing programs described in the standards relating to performance listed above.

This European Standard is largely based upon, but not identical to, UIC-Code 435-2:1994 *Standard of quality for a European flat pallet made of wood with four openings and measuring 800 mm × 1200 mm.*

1 Scope

This European Standard specifies the manufacturing characteristics of a flat re-usable wooden 800 mm × 1200 mm, double deck, non-reversible, 4-way entry, 9 block pallet suitable for transport, storage, handling or exchange use. It also gives some requirements for manufacture and marking and addresses the issue of safety.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text, and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

ENV 717-1, *Wood-based panels – Determination of formaldehyde release – Part 1: Formaldehyde emission by the chamber method*

EN 1087-1, *Particleboards – Determination of moisture resistance – Part 1: Boil test*

EN 1310:1997, *Round and sawn timber – Method of measurement of features*

EN 12246:1999, *Quality classification of timber used in pallets and packaging.*

EN 13183-1, *Moisture content of a piece of sawn timber - Part 1: Determination by oven dry method*

EN 13183-2, *Moisture content of a piece of sawn timber - Part 2: Estimation by electrical resistance method*

EN ISO 445:1998, *Pallets for materials handling – Vocabulary (ISO 445:1996)*

prEN ISO 8611-1:2000, *Pallets for materials handling - Part 1: Test methods for flat pallets (ISO/DIS 8611-1:2000)*

EN ISO 12777-3, *Methods of test for pallet joints – Part 3: Determination of strength of pallet joints (ISO 12777-3:2002).*

ISO 3133, *Wood – Determination of ultimate strength in static bending.*

3 Terms and definitions

For the purposes of this European Standard, the definitions given in EN ISO 445:1998 and the following apply.

3.1

stacking

placing of pallets with unit loads, one on the other, without recourse to intermediate shelves or racking

3.2

nominal load

reference load capacity, in kilograms, assuming a uniformly distributed load

3.3

safe working load

maximum load capacity, in kilograms, in a defined loading situation

3.4

concentrated load

load concentrated over an area between 30 % and 85 % of the pallet deck

EN 13698-1:2003 (E)

3.5 uniformly distributed load

load spread evenly across the full surface of the pallet deck

3.6 solid load

single, compact, rigid, homogeneous load, covering approximately the complete surface of the pallet

4 Nominal and safe working loads

The nominal load of pallets conforming to this standard is to be established by tests conducted under the review of ISO 8611:1991. Annex G gives general information on safe working loads under different loading conditions. The safe working load of the pallet is 1 500 kg for a uniformly distributed load.

5 Construction

5.1 Materials

5.1.1 Timber

5.1.1.1 Timber species

Timber species are given in annex A.

5.1.1.2 Timber quality grade

The timber quality grade shall conform to A.2.

5.1.1.3 Moisture content

Moisture content shall be determined in accordance with EN 13183-1 or EN 13183-2.

At the time of delivery the moisture content of the component parts of the pallets shall not exceed 22 %.

NOTE Dimensions at other moisture levels may be calculated using the correction factors given in annex B.

The reference moisture content shall be 20 %.

5.1.2 Particle board

High density, moisture resistant particle board conforming to A.3 is permitted for skid blocks.

5.1.3 Fasteners

Pallets shall be assembled with fasteners conforming to A.4.

5.2 Design and manufacture


5.2.1 Component parts

Component parts of pallets shall conform to Table 1 and Figure 1.

Table 1 - Dimensions and tolerances of pallet components

Part	Component ¹⁾	Number of components	Dimensions at 22 % moisture content mm		
			Length	Width ²⁾	Thickness ²⁾
1	Bottom deck lead board	2	1200 ± 3	100 ± 3	22 ⁺² ₀
2	Top deck lead board	2	1200 ± 3	145 ⁺⁵ ₋₃	22 ⁺² ₀
3	Central bottom deck board	1	1200 ± 3	145 ⁺⁵ ₋₃	22 ⁺² ₀
4	Stringer board	3	800 ± 3	145 ⁺⁵ ₋₃	22 ⁺² ₀
5	Central top deck board	1	1200 ± 3	145 ⁺⁵ ₋₃	22 ⁺² ₀
6	Intermediate top deck board	2	1200 ± 3	100 ± 3	22 ⁺² ₀
7	Outer skid block	6	145 ⁺⁵ ₋₃	100 ± 3	78 ⁺¹ ₀
8	Centre skid block	3	145 ⁺⁵ ₋₃	145 ⁺⁵ ₋₃	78 ⁺¹ ₀
9	Fasteners ³⁾				
10	Fasteners ³⁾				
11	Fasteners ³⁾				

¹⁾ See Figures 1, 2 and C.1
²⁾ See Annex B
³⁾ See A.4

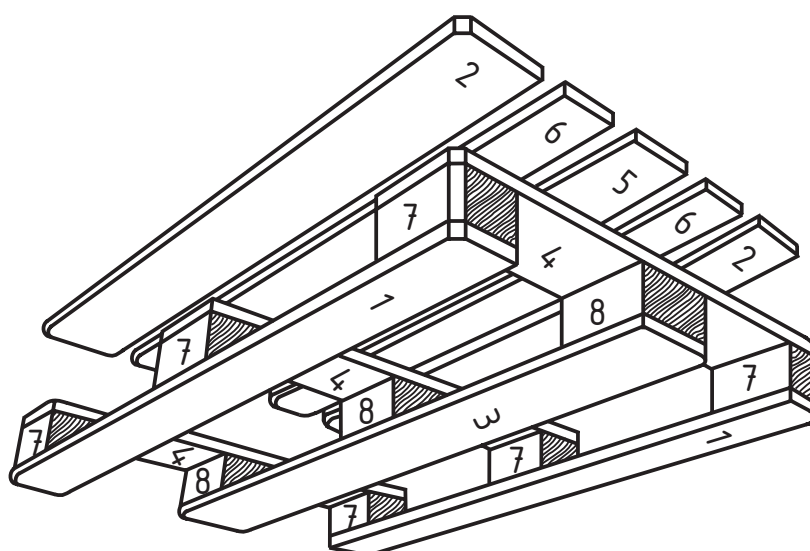

Key

See Table 1

Figure 1 — 800 mm × 1200 mm pallet component parts

EN 13698-1:2003 (E)

5.2.2 Boards and blocks

Boards and blocks shall meet the following requirements:

- a) All boards and natural timber blocks shall be of one piece.
- b) The outer surfaces of the top and bottom decks shall be unplanned.
- c) The wood fibres of the outer skid blocks shall be parallel to the longitudinal axis of the pallet.
- d) Skid blocks shall be of natural timber or particle board (see 5.1.2).

5.2.3 Pallet assembly and fastener positions

5.2.3.1 General

All fasteners shall be driven in vertically, at a minimum of 20 mm from the edges of the boards, and, for particle board blocks, a minimum of 20 mm from the centre hole if present. Fasteners shall not be inserted parallel with the wood grain (which may split the board), and shall be spaced as far apart as possible. Nail heads shall not protrude above the surface of the board (this also applies after drying the pallet), or be sunk below the board surface by more than 3 mm. Fasteners shall not pierce the sides of blocks.

No splits resulting from nailing shall be visible on the blocks or boards after assembly.

NOTE A recommended nail pattern for pallets is given in annex C.

5.2.3.2 Assembly top board block

For each block, a minimum of three fasteners shall be used on both the top and bottom surfaces.

5.2.3.3 Assembly top deck board /stringer board

A minimum of three fasteners shall be used for fixing each intermediate top deck board to a stringer board. The top deck leadboard, and if necessary the central deck board, shall be fixed to each stringer board by one fastener. Any fastener protruding below the stringer board shall be bent back.

NOTE A staple is considered to be a single fastener.


5.3 General assembly details

General assembly details of the pallet, including dimensions and tolerances, shall conform to Figure 2 and to Table 2. The chamfering section A–B shall be on all three bottom boards.

Table 2 – General assembly details — Overall tolerances in millimetres

Length	1200 ± 3
Width	800 ± 3
Height	144 ⁺⁷ ₀

Dimensions in millimetres

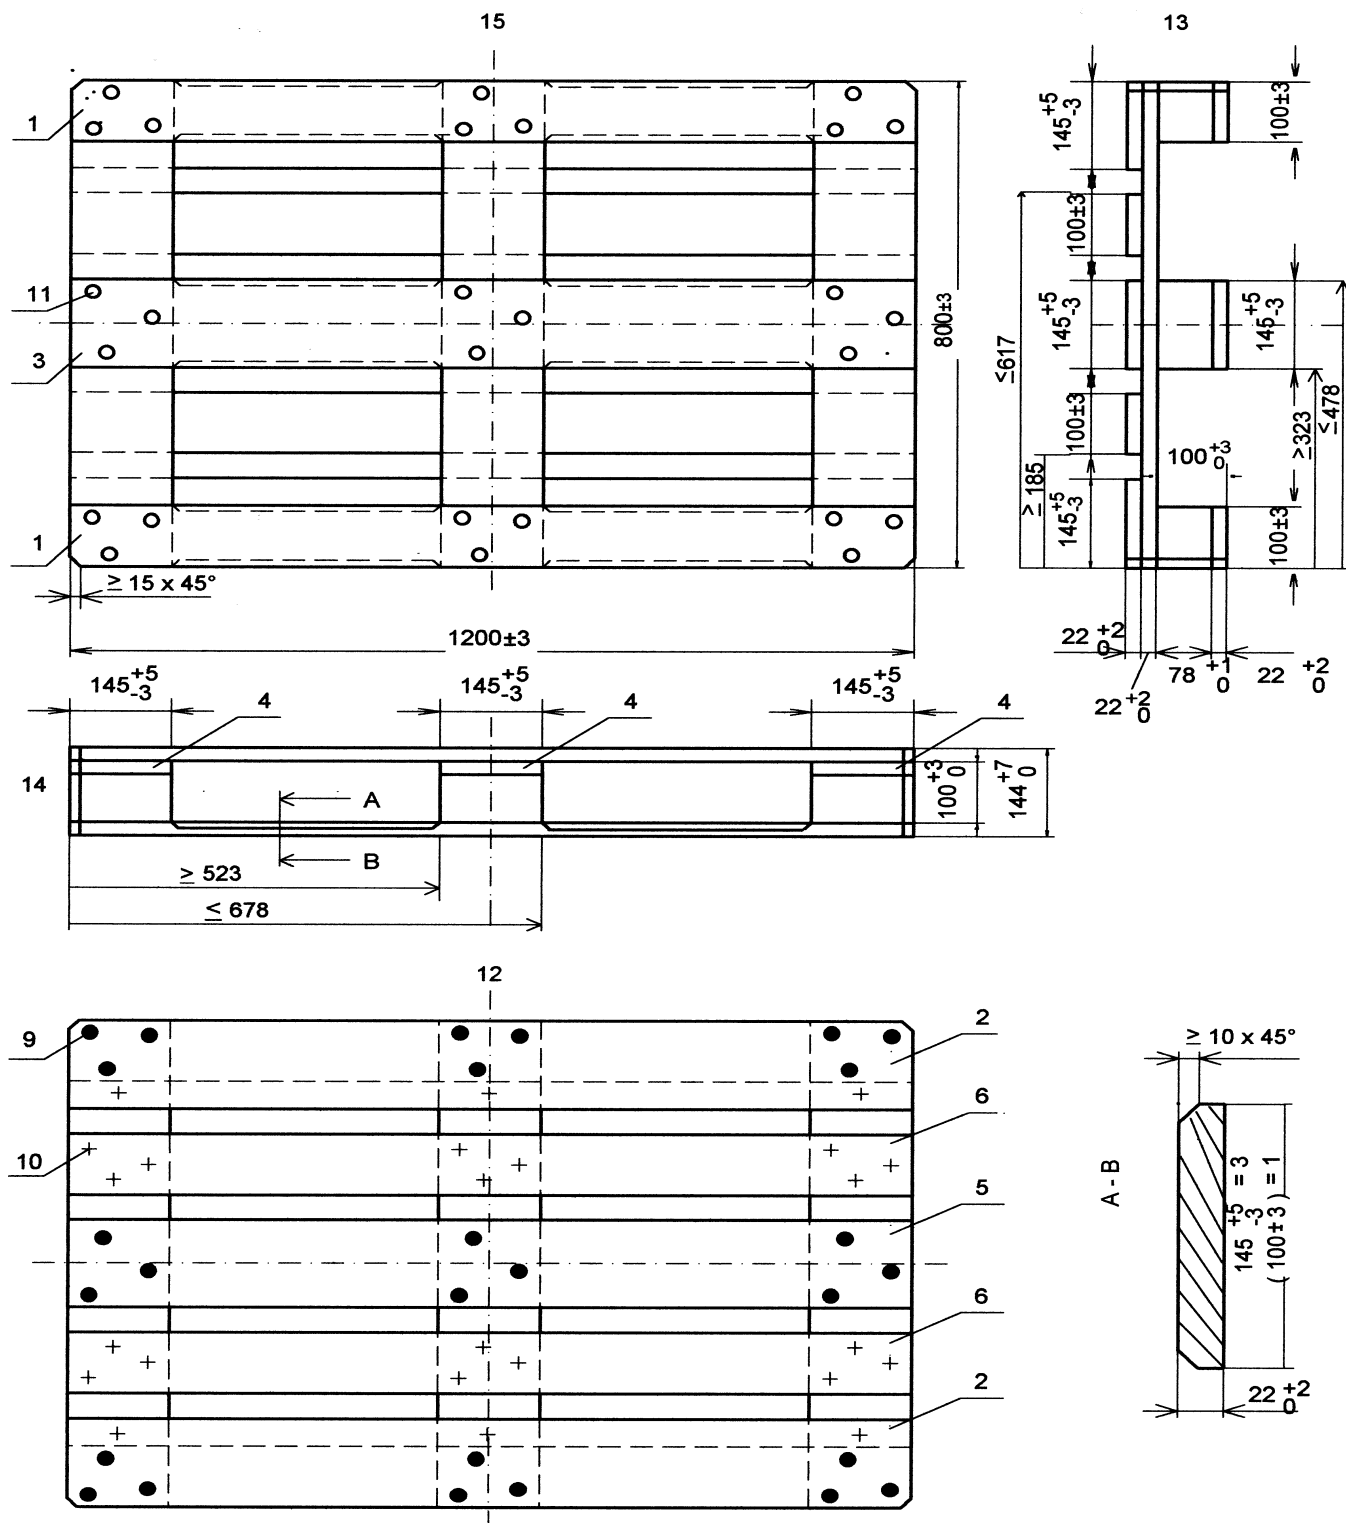

- Key**
- 1-11 See Table 1 and Table C.2
 - 12 Top view
 - 13 Side view
 - 14 Front view
 - 15 Bottom view

Figure 2 — General assembly details, dimensions and tolerances

5.4 Assembly strength

5.4.1 Diagonal rigidity

Test for diagonal rigidity in accordance with prEN ISO 8611-1:2000 (Test No 10) on three pallets with six corner drops on each pallet (same corner throughout). The drop height shall be 1 metre.

After the test, the pallets shall not be distorted by more than 3 % of the initial value (measured as the mean distortion for all three pallets).

5.4.2 Separation force

The joints of the pallet shall be tested using the joint separation test in accordance with annex D. The arithmetic mean of the recorded separation force, and at least 75 % of all recordings, shall be equal to or higher than the following:

- a) block/stringer board/top deck board: 5,5 kN;
- b) block/bottom deck board: 5,5 kN;
- c) stringer board/intermediate top deck board: 3,0 kN.

6 Inspections and marking

Before delivery, pallets shall be inspected for quality. For guidance on inspection (Quality control) see Annex E.

Pallets in conformity with this standard shall be marked on the outer side of the centre block with the number of this European Standard, the mark of the country and of the manufacturer.

NOTE 1 Pallets used in pooling or exchange systems may be marked in accordance with the guidelines defined at the pooling or exchange system.

NOTE 2: Pallets manufactured in conformity with this standard may be required to comply with National Authority marking requirements.

NOTE 3: Plant health recommendations are constantly under review and pallets may need to be marked accordingly.

Annex A (normative)

Materials

A.1 Timber

A.1.1 General

Pallets shall be constructed from the timber species listed in Table A.1 and in A.1.2.

Table A.1 — European grown wood

Softwood (conifer)	Hardwood (deciduous)
Douglas	acacia
Pine	alder
Fir	ash
Larch	beech
Spruce	birch
	chestnut
	elm
	maple
	oak
	plane
	poplar

A.1.2 Other timber species

If other timber species are taken into consideration for manufacturing pallets in conformity with this standard, this species shall have an ultimate strength in static bending of at least 42 N/mm², tested on small clear samples with a moisture content of 20 %, in accordance with ISO 3133, and the pallets manufactured from these species shall be tested according to prEN ISO 8611-1:2000 (bending test) before starting the production.

A.2 Timber quality grade

A.2.1 Pallet components

The quality of sawn timber for pallet components (except stringer boards) shall conform to Table A.2.

A.2.2 Stringer boards

The quality of sawn timber for stringer boards shall conform to Tables A.2 and A.3.

A.2.3 Bark

Timber containing bark shall not be used.

Table A.2 — Quality of sawn timber in pallets

Criterion	Requirement (EN 12246:1999, Class P1)
Knots:	On both faces, knots shall be measured in accordance with 4.1.2 of EN 1310:1997. Knots shall be disregarded on the edges. Knots less than 10 mm shall be disregarded. Knot clusters shall be considered as individual knots.
– intergrown, partially intergrown, dead	Shall be ≤ 33 % of the width of the piece.
– loose	Shall be ≤ 20 mm.
– unsound	Shall be ≤ 20 mm.
– branched	Permitted.
Exposed pith	Permitted on one face.
Boxed heart	Permitted.
Shakes:	Shakes shall be taken into account on the ends, faces and edges. Shakes shall be measured in accordance with EN 1310.
– surface shake	Permitted except at points of nailing.
– split (in boards)	One split permitted \leq width of the board.
– split (in blocks)	Not permitted.
Resin pocket	Permitted on one face only.
Bark pocket	Not permitted.
Blue stain ¹⁾	
Biodeterioration except blue stain	Not permitted.
Active timber infestation	Not permitted.
Black holes (non active)	Up to 5 holes of diameter ≤ 3 mm permitted.
Wane (without bark)	Wane shall be measured in accordance with 4.8 of EN 1310:1997. Permitted up to 25 % of the piece length, up to 33 % of the thickness and allowed both sides of one face if ≤ 10 mm from each side.
¹⁾ See Annex F	

Table A.3 — Quality of sawn timber for stringer boards

Criterion	Requirement
Knots– intergrown, partially intergrown, dead	≤ 25 % of piece width.
Wane	Not permitted.
Slope of grain	≤ 5 %.


A.3 Particle board

A.3.1 Particle board composition and dimensions

Particle board shall only be used for blocks. The material shall conform to the following:

- a) depending on the manufacturing process, blocks shall be rectangular or provided with chamfered edges of $15 \text{ mm} \times 45^\circ$ and with or without a central hole. The diameter of any hole shall not exceed 32 mm for blocks $145 \text{ mm} \times 100 \text{ mm}$ or 40 mm for blocks $145 \text{ mm} \times 145 \text{ mm}$.
- b) the mean weight per unit volume shall be $\geq 580 \text{ kg/m}^3$.
- c) the moisture content shall be between 7 % and 13 %.
- d) the material shall give a formaldehyde emission of $< 0,1 \text{ ml}$ per cubic metre of air, when determined in accordance with ENV 717-1.
- e) the efficiency of the bonding process shall be determined by the following tests:
 - 1) size variation test, after 24 h immersion in water at 20°C , measured on 10 test pieces:
 - the length and width shall not increase by more than 2 %;
 - the height shall not vary by more than 4,5 %, except that one of the ten blocks may vary between 4,5 % and 5,5 %.
 - 2) tests for retention of material strength, absence of splits, loss of cohesion after test cycle, and determination of bond quality, in accordance with EN 1087-1 involving:
 - a 2-h immersion in water at 100°C under ambient pressure,
 - 2 h in the oven at $(65 \pm 3)^\circ \text{C}$.

Dimensions in millimetres

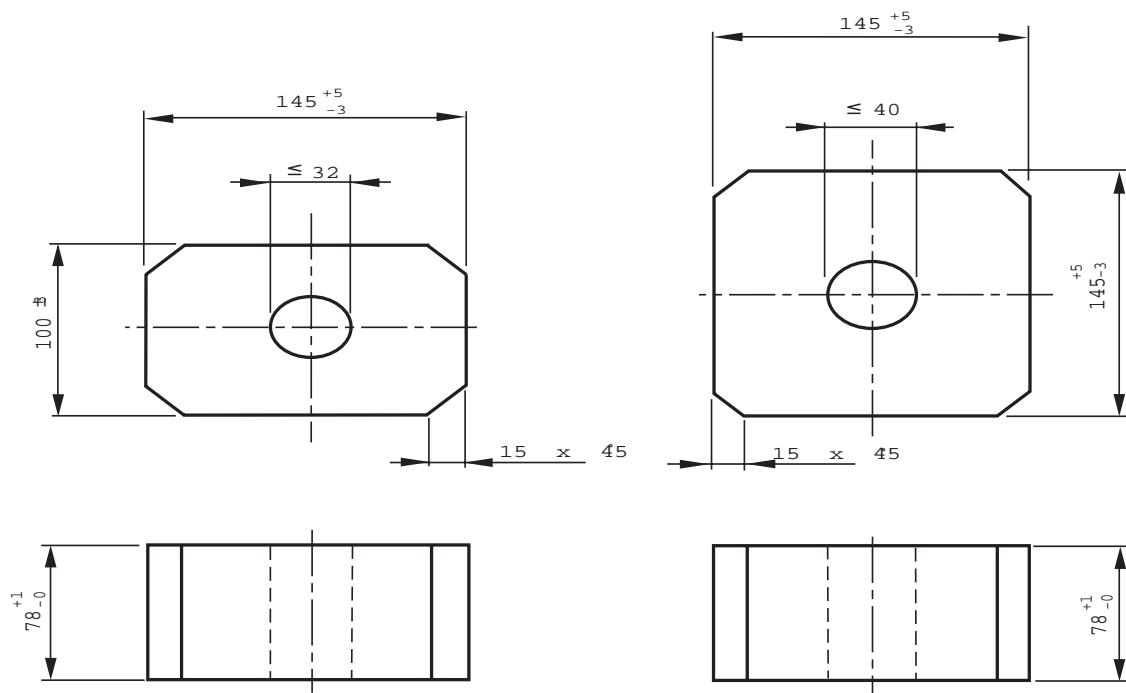

NOTE The examples in this diagram are shown with both hole and chamfer. Blocks are not required to have either.

Figure A.1 — Particle board blocks

A.4 Fasteners

A.4.1 Nails for block/stringer board/top deck board assemblies (part No 9)

Nails for block/stringer board/top deck board assemblies shall conform to Table A.4.

Table A.4 — Nails for block/stringer board/top deck board assemblies

Property	Specification
Minimum length	88 mm ¹⁾
Dimension of nail head	min 8,4 mm (diameter) or min 55 mm ²
Ratio of head diameter to shank diameter	≥ 2
Nail shank type	spiral rolled, annular ring rolled, square twisted, indented shank
Minimum tensile strength	700 N/mm ²
Nail point type	diamond or chisel point
¹⁾ This value is valid for a standard nominal dimension of (90 ± 2) mm.	

A.4.2 Nails for block/bottom deck board assemblies (part No 11)

For block/bottom deck board assemblies shall conform to Table A.5.

Table A.5 — Nails for block/bottom deck board assemblies

Property	Specification
Minimum length	68 mm ¹⁾
Dimension of nail head	min 8,4 mm (diameter) or min 55 mm ²
Ratio of nail head diameter to shank diameter	≥ 2
Nail shank type	spiral rolled, annular ring rolled, square twisted, indented shank
Minimum tensile strength	650 N/mm ²
Nail point type	diamond or chisel point
¹⁾ This value is valid for a standard nominal dimension of (70 ± 2) mm.	

A.4.3 Fasteners for stringer board/top deck board assemblies (part No 10)

Fasteners for stringer board/top deck board assemblies shall conform to Tables A.6, A.7, or A.8 as appropriate.

Table A.6 — Nails bent back on the lower surface of the stringer board

Property	Specification
Minimum length	50 mm ¹⁾
Dimension of nail head	min 5,5 mm (diameter) or min 24 mm ²
Ratio of nail head diameter to shank diameter	≥ 2
Nail shank type	plain, spiral rolled, annular ring rolled, square twisted, indented shank
Minimum tensile strength	800 N/mm ²
Nail point type	diamond or diamond offset
¹⁾ This value is valid for standard nominal dimensions of $(55 \begin{smallmatrix} +2 \\ -5 \end{smallmatrix})$ mm and (60 ± 2) mm.	

Table A.7 — Nails that do not pierce the stringer board

Property	Specification
Length	min 36 mm , max 41 mm ¹⁾
Dimension of nail head	min 5,5 mm (diameter) or min 24 mm ²
Ratio of nail head diameter to shank diameter	≥ 2
Nail shank type	spiral rolled, annular ring rolled, square twisted, indented shank
Minimum tensile strength	600 N/mm ²
Nail point type	diamond or chisel point
¹⁾ This value is valid for a standard nominal dimension of $(38 \begin{smallmatrix} +3 \\ -2 \end{smallmatrix})$ mm.	

Table A.8 - Staples bent back on the lower surface of the stringer board

Property	Specification
Length	Min 53 mm
Width (inside)	Min 14 mm
Thickness of wire	Min 2,2 mm
Shank type	Plain
Tensile strength	760 N/mm ²
Point type	Diamond offset

Annex B (informative)

Wood shrinkage

Comparative wood shrinkage/expansion rates

At the saw milling stage, it is necessary to consider the machining allowances taking into account the moisture content, consequent shrinkage of the wood, and dressing, smoothing or planing operations.

Table B.1 gives comparative wood shrinkage/expansion rates, valid for all species, for determination of dimensions at alternative moisture contents to 22 %.

Table B.1 - Minimum dimensions in relation to moisture content

Moisture content	Minimum actual dimension of nominal width and thickness ¹⁾				
	(22 ⁺² ₀) mm (nominal)	(78 ⁺¹ ₀) mm (nominal)	(100 ⁺³ ₋₃) mm (nominal)	(100 ⁺³ ₀) mm (nominal)	(145 ⁺⁵ ₋₃) mm (nominal)
%	mm	mm	mm	mm	mm
30	22,5	79,5	99,0	102,0	145,0
29	22,5	79,5	98,5	102,0	144,5
28	22,5	79,0	98,5	101,5	144,0
27	22,5	79,0	98,0	101,5	144,0
26	22,0	79,0	98,0	101,0	143,5
25	22,0	78,5	97,5	100,5	143,0
24	22,0	78,5	97,5	100,5	142,5
23	22,0	78,0	97,0	100,0	142,5
22	22,0	78,0	97,0	100,0	142,0
21	22,0	78,0	97,0	99,5	141,5
20	22,0	77,5	96,5	99,5	141,5
19	22,0	77,5	96,5	99,0	141,0
18	22,0	77,0	96,0	99,0	140,5
17	21,5	77,0	96,0	98,5	140,0
16	21,5	77,0	95,5	98,5	140,0
15	21,5	76,5	95,5	98,0	139,5
14	21,5	76,5	95,0	98,0	139,0
13	21,5	76,0	95,0	97,5	139,0
12	21,5	76,0	94,5	97,5	138,5


¹⁾ The thickness and the width of a piece of timber increase by 0,25 % for every 1 % of moisture content from 20 % up to 30 %, and decrease by 0,25 % for every 1 % of moisture content. below 20 %. The above values are typical, regardless of the species (see EN 1313-1 and EN 1313-2).

Annex C (informative)

Nail pattern

Recommended nail pattern

The recommended nail pattern for pallets are as shown in Figure C.1 and the recommended fasteners in Table C.1.

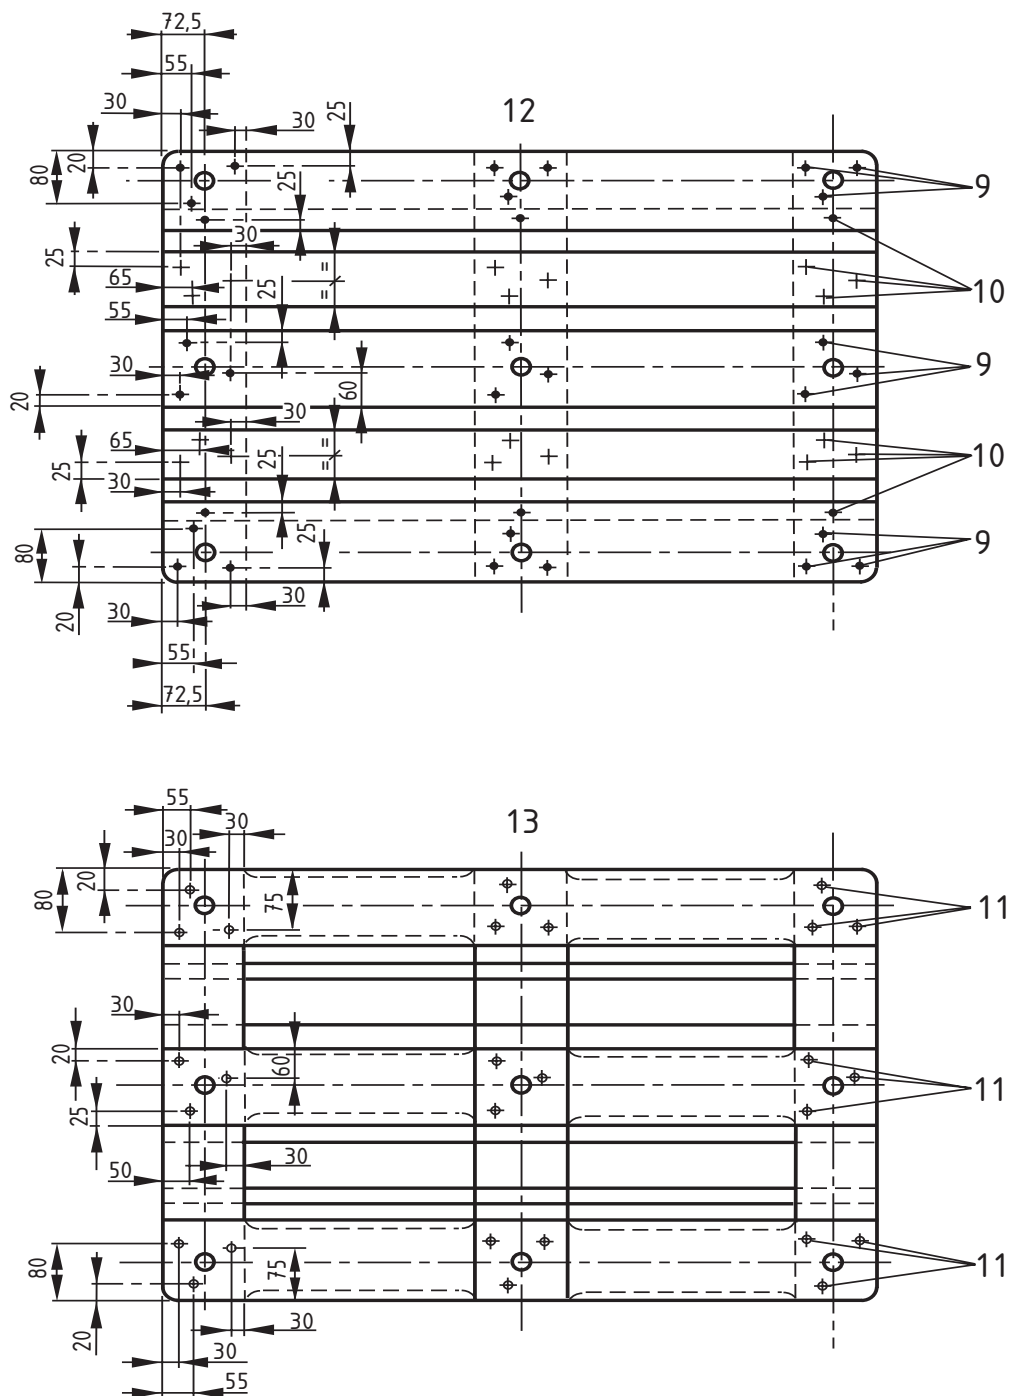

- Key**
- 9-11 See Table C.1
 - 12 View from above
 - 13 View from below

Figure C.1 — Recommended nail pattern for pallets

Table C.1 — Recommended fasteners for pallets

Minimum quantity ¹⁾	Part no. ²⁾	Type of nail	Nominal dimensions mm	Minimum tensile strength ³⁾ N/mm ²	use for
27	9	Annular ring rolled nail	4,2 × 90	700	blocks of softwood (conifer), chipboard and poplar
27	9	Spiral rolled nail with chisel point	5,2 × 90	700	blocks of hardwood (deciduous)
24	10	Annular ring rolled nail	4,2 × 38	600	stringer board of hardwood (deciduous)
24	10	Annular ring rolled nail with diamond point offset	2,8 × 55	800	fixed nailing bar
24	10	a) Plain shank nail	2,5 × 60	800	movable nailing bar
24	10	Staple	14 × 2,2 × 53	760	fixed nailing bar
27	11	Annular ring rolled nail	4,2 × 70	650	blocks of softwood (conifer), particle board and poplar
27	11	Spiral rolled nail with chisel point	5,2 × 70	650	blocks of hardwood (deciduous)
¹⁾ See 5.2.3 and Figure C.1 ²⁾ See Figure 2 and Figure C.1 ³⁾ See EN 10002-1					

Annex D (normative)


Joint separation test

D.1 Test apparatus

The test apparatus shall conform to Figure D.1 in accordance with prEN ISO 12777-3. Two stirrups shall be prepared, with stirrup B attached to a pallet block (or stringer board), and stirrup C pressing on to an adjoining board.

A gauge shall be positioned to measure the force (at A) required to separate the block and board.

The accuracy of the measuring gauge shall be at least 4 % of the nominal separation force.

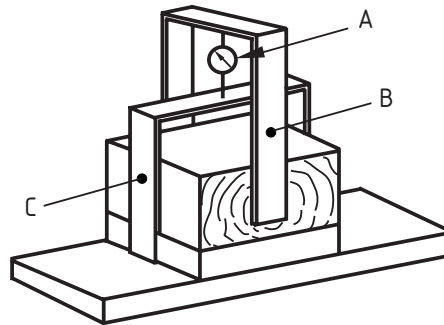

Key

- A Force indicator
- B Stirrup
- C Stirrup

Figure D.1 — Joint separation test apparatus


D.2 Test pieces

Cut test pieces conforming to figure D.2 from workable pallets.

NOTE The moisture content of the wood should be (20 ± 2) %.

For each type of assembly, wood and fastener, perform the following tests:

- a new assembly test (20 test pieces);
- production control tests (10 test pieces; at the start of production, if changing the type of wood or fasteners, or changing production methods).

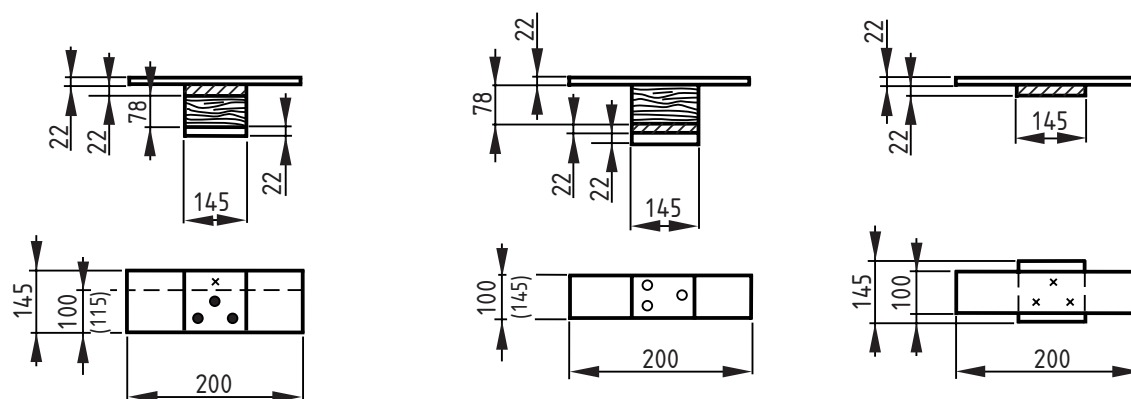

A	B	C
---	---	---

Key (Dimensions in mm)

- A. Block/stringerboard/top deckboard
- B. Block/bottom deckboard
- C. Intermediate top deckboard/stringerboard

Figure D.2 — Test pieces

D.3 Procedure

Apply a separating force across the block and board slowly and smoothly, and measure the resulting separation force.

D.4 Test results

The test pieces shall conform to 5.4.2.

D.5 Report

The test report shall contain:

- a) the type, dimensions material and tensile strength of the fasteners, with tolerances and drawings;
- b) the wood species used for the blocks and boards;
- c) the moisture content of each test piece;
- d) the separation force of each test piece;
- e) the arithmetic mean separation force for each type of assembly.

Annex E (informative)

Inspection (Quality control)

E.1 General policy

Quality control of each batch of pallets should be executed at least in accordance with the random survey schedule given in E.1.1 to E.1.6.

E.1.1 Quality control of a submitted batch of pallets involves inspection of a statistically selected sample on the basis of quality characteristics described in the survey schedule.

NOTE The inspection carried out in accordance with the survey schedule should only be used provided a constant manufacturing standard is guaranteed.

E.1.2 The number n of pallets in the quality control sample should vary with the number N of pallets in the batch as shown in Table E.1.

If N exceeds 10000, the pallets should be divided into smaller batches.

Table E.1 Sample sizes

Size of batch N	Sample size n
< 150	8
$151 < 280$	13
$281 < 500$	20
$501 < 1200$	32
$1201 < 3200$	50
$3201 < 10000$	80

E.1.3 Prior to inspection, a random sample of n pallets should be selected.

E.1.4 A visual inspection should be carried out on the sample, and the main dimensions of the pallet and its component parts measured. An inspection report conforming to the example in Table E.2 should be completed, with all defects (critical, major or minor) recorded.

NOTE A critical defect is one that, from experience, is likely to reduce the level of safety or increase the risk of accidents to users or persons depending on the unit. A major defect is one that could result in failure of the unit or considerably reduce its performance. A minor defect is one that does not affect the performance or efficient operation of the unit.

Table E.2 — Example of a typical inspection report

Defect	Number in sample
Critical defects:	
– pallet length exceeding 1200_{-5}^8 mm	
– pallet width exceeding 800_{-5}^8 mm	
– stringer board thickness exceeding 22_0^3 mm	
– unacceptable timber species, knots and waness in stringer boards (see annex A)	
– unacceptable fasteners	
Total critical defects	
Major defects:	
– pallet length exceeding 1200 ± 3 mm	
– pallet width exceeding 800 ± 3 mm	
– height of entry exceeding 100_0^3 mm	
– width of stringer board exceeding 145_{-3}^5 mm	
– board thickness exceeding 22_0^2 mm	
– insect damage, decay, bark pocket	
– moisture content > 26 %	
– unacceptable knots (see annex A)	
– assembly splits	
– chamfers	
– missing or twisted fasteners	
– unacceptable distance between fasteners	
– marking incomplete	
Total major defects	
Minor defects:	
– deck/lead board length exceeding 1200 ± 3 mm	
– stringer board length exceeding 800 ± 3 mm	
– board width exceeding 145_{-3}^5 mm (except stringer boards)	
– board width exceeding 100_{-3}^3 mm	
– block length exceeding 145_{-3}^5 mm	
– centre skid block width exceeding 145_{-3}^5 mm	
– outer skid block width exceeding 100_{-3}^3 mm	
– block height exceeding 78_0^1 mm	
– moisture content 22 % to 26 %	
– waness > 15 mm	
– unacceptable knots (see annex A)	
– Biodeterioration	
– resin pockets > 50 mm	
– slope of grain exceeding 5 %	
– black holes	
– protruding fasteners	
Total minor defects	

E.1.5 If the sample does not exceed the maximum permitted number of defects given in Table E.3, the batch should be accepted.

EN 13698-1:2003 (E)

If any of the maximum number of critical, major or minor defects is exceeded, the batch should be rejected. Markings should be removed from all pallets that do not conform to this standard.

Table E.3 — Maximum number of defects

Sample size n	Maximum permitted number of defects		
	Critical defects	Major defects	Minor defects
8	0	5	10
13	0	7	14
20	0	10	21
32	0	14	30
50	0	21	44
80	0	30	70

E.1.6 With approval of the inspector, an initially rejected batch should be resubmitted, after elimination of the defective pallets and replenishing of the batch. The eliminated pallets should be re-tested separately after repair if possible.

Procedures E.1.3 to E.1.5 should be repeated on the new batch.

Annex F **(normative)**

Preservatives

General policy

Blue stain does affect only the appearance of the wood, but not the mechanical properties. Blue stain can be avoided by kiln drying or other means.

If some species have to be protected in view to avoid blue stain, products used have to be in respect of the requirements of the directive BIOCIDES (98-8-CE). The directive has taken into account (clause 3) human and animal health and environmental risks. This directive is therefore in line with one of the first considerations fixed in the Directive 94/62 CE concerning packaging and packaging waste.



Annex G (informative)

Safe working loads under different loading situations

General policy

Pallets conforming to this standard should have a safe working load as described in the Table G.1.

Table G.1 - Safe working load in racking conditions

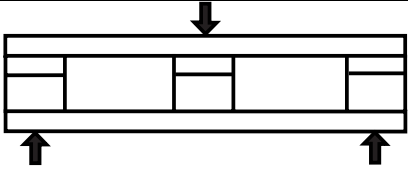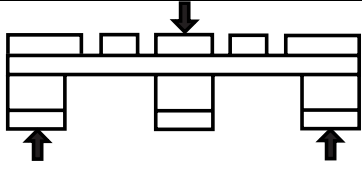		
Concentrated load	*)	*)
uniformly distributed load	*)	*)
uniformly distributed bonded load	*)	*)
solid load	*)	*)

*) Values will be checked after the completion of studies for prEN ISO/DIS 8611-3.

Bibliography

EN 1313-1, *Round and sawn timber - Permitted deviations and preferred sizes - Part 1: Softwood sawn timber*

EN 1313-2, *Round and sawn timber - Permitted deviations and preferred sizes - Part 2: Hardwood sawn timber.*

EN 10002-1, *Metallic materials - Tensile testing - Part 1: Method of test at ambient temperature.*

EN 13382, *Flat pallets for materials handling - Principal dimensions.*

prEN ISO/DIS 8611-2, *Pallets for materials handling - Part 2: Performance requirements (ISO/DIS 8611-2:1997).*

prEN ISO/DIS 8611-3, *Pallets for materials handling - Part 3: Design rating and maximum working load (ISO/DIS 8611-3:1997).*

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.
Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.