

# Hydraulically bound mixtures — Specifications —

## Part 13: Soil treated by hydraulic road binder

The European Standard EN 14227-13:2006 has the status of a  
British Standard

ICS 93.080.20

## National foreword

This British Standard is the official English language version of EN 14227-13:2006.

The UK participation in its preparation was entrusted by Technical Committee B/510, Road materials, to Subcommittee B/510/4, Cementitious bound materials, unbound granular materials, waste materials and marginal materials, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

### Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

### Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 23 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

### Amendments issued since publication

| Amd. No. | Date | Comments |
|----------|------|----------|
|          |      |          |
|          |      |          |
|          |      |          |
|          |      |          |

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 June 2006

© BSI 2006

ISBN 0 580 48684 2

EUROPEAN STANDARD

EN 14227-13

NORME EUROPÉENNE

EUROPÄISCHE NORM

May 2006

ICS 93.080.20

English Version

## Hydraulically bound mixtures - Specifications - Part 13: Soil treated by hydraulic road binder

Mélanges traités aux liants hydrauliques - Spécifications -  
Partie 13: Sol traité au liant hydraulique routier

Hydraulisch gebundene Gemische - Anforderungen - Teil  
13: Bodenverbesserung mit hydraulischem  
Tragschichtbinder

This European Standard was approved by CEN on 3 February 2006.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

## Contents

Page

|  |    |
|--|----|
| Foreword.....  | 4  |
| 1 Scope .....  | 5  |
| 2 Normative references .....   | 5  |
| 3 Terms and definitions .....  | 6  |
| 4 Symbols and abbreviated terms .....  | 6  |
| 5 Constituents.....  | 7  |
| 5.1 Hydraulic road binder.....   | 7  |
| 5.2 Soil .....   | 7  |
| 5.3 Water .....  | 7  |
| 5.4 Other constituents .....   | 7  |
| 6 Mixture .....  | 7  |
| 6.1 General.....   | 7  |
| 6.2 Proportioning and dry density .....  | 7  |
| 7 Requirements for the fresh mixture.....  | 8  |
| 7.1 Water content.....   | 8  |
| 7.2 Degree of pulverization .....  | 8  |
| 7.3 Immediate bearing index.....   | 8  |
| 7.4 Moisture condition value .....   | 9  |
| 8 Laboratory mechanical performance classification.....  | 9  |
| 8.1 General.....   | 9  |
| 8.2 Classification by California bearing ratio.....  | 9  |
| 8.3 Classification by compressive strength.....  | 10 |
| 8.4 Classification by $R_t$ , $E$ .....  | 11 |
| 8.4.1 General.....   | 11 |
| 8.4.2 Method by direct tensile testing.....  | 11 |
| 8.4.3 Method by indirect tensile testing.....  | 11 |
| 8.4.4 Method by indirect tensile and compression testing.....  | 12 |
| 9 Resistance to water and other requirements for the mixture .....   | 12 |
| 9.1 Resistance to water .....  | 12 |
| 9.1.1 General.....   | 12 |
| 9.1.2 Strength after immersion in water .....  | 12 |
| 9.1.3 Linear swelling after soaking in water.....  | 13 |
| 9.1.4 Volumetric swelling after immersion in water .....   | 13 |
| 9.2 Strength at trafficking .....  | 13 |
| 9.3 Resistance to frost.....   | 13 |
| 9.4 Workability period.....  | 13 |
| 10 Production control.....   | 14 |
| 11 Designation and description .....   | 14 |
| 12 Labelling .....   | 14 |
| Annex A (informative) Examples of 'age of classification' and curing regimes for $R_c$ , $R_t$ and $E$ testing of treated soils including resistance to water testing by full immersion in water ..... | 16 |
| Annex B (informative) Production control for hydraulically treated mixtures .....  | 17 |
| B.1 General.....   | 17 |
| B.2 Quality Manual .....   | 17 |
| B.3 Organization.....  | 17 |

|       |  |    |
|-------|--|----|
| B.3.1 | Responsibility and authority .....   | 17 |
| B.3.2 | Management representative .....  | 17 |
| B.3.3 | Internal audits .....  | 17 |
| B.3.4 | Management review .....  | 18 |
| B.3.5 | Sub-contract services .....  | 18 |
| B.3.6 | Records .....  | 18 |
| B.3.7 | Training.....  | 18 |
| B.4   | Control procedures .....   | 18 |
| B.4.1 | Production management .....  | 18 |
| B.4.2 | Composition of the mixture.....  | 19 |
| B.4.3 | Constituents.....  | 19 |
| B.4.4 | Process control .....  | 19 |
| B.4.5 | Inspection, calibration and control of process equipment.....              | 19 |
| B.4.6 | Handling and delivery .....  | 20 |
| B.5   | Inspection and testing of constituents and mixtures during production..... | 20 |
| B.5.1 | General .....  | 20 |
| B.5.2 | Characteristics that require control during production .....               | 20 |
| B.5.3 | Frequency of sampling the mixture.....                                     | 21 |
| B.6   | Inspection and testing equipment .....                                     | 21 |
| B.6.1 | General .....  | 21 |
| B.6.2 | Measuring and testing equipment .....                                      | 21 |
| B.6.3 | Measuring and testing equipment in the process .....                       | 21 |
| B.6.4 | Measuring and testing equipment in laboratory .....                        | 21 |
| B.7   | Non-conformity.....  | 22 |
| B.7.1 | General .....  | 22 |
| B.7.2 | Non-conformity of constituents.....  | 22 |
| B.7.3 | Non-conformity of the mixture.....   | 22 |

## Foreword

This European Standard (EN 14227-13:2006) has been prepared by Technical Committee CEN/TC 227 “Road materials”, the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2006, and conflicting national standards shall be withdrawn at the latest by November 2006.

This European Standard is one of a series of standards for hydraulically bound mixtures:

EN 14227-1, *Hydraulically bound mixtures — Specifications — Part 1: Cement bound granular mixtures.*

EN 14227-2, *Hydraulically bound mixtures — Specifications — Part 2: Slag bound mixtures.*

EN 14227-3, *Hydraulically bound mixtures — Specifications — Part 3: Fly ash bound mixtures.*

EN 14227-4, *Hydraulically bound mixtures — Specifications — Part 4: Fly ash for hydraulically bound mixtures.*

EN 14227-5, *Hydraulically bound mixtures — Specifications — Part 5: Hydraulic road binder bound mixtures.*

EN 14227-10, *Hydraulically bound mixtures — Specifications — Part 10: Soil treated by cement.*

EN 14227-11, *Hydraulically bound mixtures — Specifications — Part 11: Soil treated by lime.*

EN 14227-12, *Hydraulically bound mixtures — Specifications — Part 12: Soil treated by slag.*

EN 14227-13, *Hydraulically bound mixtures — Specifications — Part 13: Soil treated by hydraulic road binder.*

EN 14227-14, *Hydraulically bound mixtures — Specifications — Part 14: Soil treated by fly ash.*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

## 1 Scope

This European Standard specifies soils treated by hydraulic road binder for roads, airfields and other trafficked areas and specifies the requirements for their constituents, composition and laboratory performance classification.

## 2 Normative references

The following referenced documents are indispensable for the application of this European Standard. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 933-1, *Tests for geometrical properties of aggregates — Part 1: Determination of particle size distribution — Sieving method*

ENV 13282, *Hydraulic road binders — Composition, specifications and conformity criteria*

EN 13286-2, *Unbound and hydraulically bound mixtures — Part 2: Test methods for the determination of the laboratory reference density and water content — Proctor compaction*

EN 13286-3, *Unbound and hydraulically bound mixtures — Part 3: Test methods for laboratory reference density and water content — Vibrocompression with controlled parameters*

EN 13286-4, *Unbound and hydraulically bound mixtures — Part 4: Test methods for laboratory reference density and water content — Vibrating hammer*

EN 13286-5, *Unbound and hydraulically bound mixtures — Part 5: Test methods for laboratory reference density and water content — Vibrating table*

EN 13286-40, *Unbound and hydraulically bound mixtures — Part 40: Test method for the determination of the direct tensile strength of hydraulically bound mixtures*

EN 13286-41, *Unbound and hydraulically bound mixtures — Part 41: Test method for the determination of the compressive strength of hydraulically bound mixtures*

EN 13286-42, *Unbound and hydraulically bound mixtures — Part 42: Test method for the determination of the indirect tensile strength of hydraulically bound mixtures*

EN 13286-43, *Unbound and hydraulically bound mixtures — Part 43: Test method for the determination of the modulus of elasticity of hydraulically bound mixtures*

EN 13286-45, *Unbound and hydraulically bound mixtures — Part 45: Test method for the determination of the workability period of hydraulically bound mixtures*

EN 13286-46, *Unbound and hydraulically bound mixtures — Part 46: Test method for the determination of the moisture condition value*

EN 13286-47, *Unbound and hydraulically bound mixtures — Part 47: Test method for the determination of the California bearing Ratio, immediate bearing index and linear swelling*

EN 13286-48, *Unbound and hydraulically bound mixtures — Part 48: Test method for the determination of the degree of pulverisation*

EN 13286-49, *Unbound and hydraulically bound mixtures — Part 49: Accelerated swelling test for of soil treated by lime and/or hydraulic binder*

## EN 14227-13:2006 (E)

EN 13286-50, *Unbound and hydraulically bound mixtures — Part 50: Method for the manufacture of test specimens of hydraulically bound mixtures using Proctor equipment or vibrating table compaction*

EN 13286-51, *Unbound and hydraulically bound mixtures — Part 51: Method for the manufacture of test specimens of hydraulically bound mixtures using vibrating hammer compaction*

EN 13286-52, *Unbound and hydraulically bound mixtures — Part 52: Method for the manufacture of test specimens of hydraulically bound mixtures using vibrocompression*

EN 13286-53, *Unbound and hydraulically bound mixtures — Part 53: Methods for the manufacture of test specimens of hydraulically bound mixtures using axial compression*

EN 14227-11, *Hydraulically bound mixtures — Specifications — Part 11: Soil treated by lime*

### 3 Terms and definitions

For the purpose of this European Standard, the following terms and definitions apply.

#### 3.1

##### **soil**

natural, artificial or recycled material or any combination of these

#### 3.2

##### **soil treated with hydraulic road binder**

mixture of soil, hydraulic road binder, other constituents if appropriate, and water, that sets and hardens by hydraulic reaction

#### 3.3

##### **slenderness ratio**

height to diameter ratio of the specimen

### 4 Symbols and abbreviated terms

For the purpose of this European Standard, the following symbols and abbreviations apply.

W is the water content;

P is the pulverization;

IPI is the immediate bearing index;

MCV is the moisture condition value;

CBR is the California bearing ratio, expressed in percent (%);

$R$  is the compressive or tensile strength, expressed in megapascals (MPa);

$R_c$  is the compressive strength, expressed in megapascals (MPa);

$R_t$  is the direct tensile strength, expressed in megapascals (MPa);

$R_{it}$  is the indirect tensile strength, expressed in megapascals (MPa);

$R_i$  is the compressive or tensile strength after immersion in water, expressed in megapascals (MPa);

$E$  is the modulus of elasticity, expressed in megapascals (MPa);



- $E_c$  is the modulus of elasticity  $E$  determined in compression, expressed in megapascals (MPa);
- $E_t$  is the modulus of elasticity  $E$  determined in direct tension, expressed in megapascals (MPa);
- $E_{it}$  is the modulus of elasticity  $E$  determined in indirect tension, expressed in megapascals (MPa);
- $I$  is the 'strength after immersion' ratio;
- LS is the linear swelling of a CBR specimen, expressed in millimetres (mm);
- $G_v$  is the volumetric swelling of a specimen, expressed in percent (%).

## 5 Constituents

### 5.1 Hydraulic road binder

Hydraulic road binder shall be selected from and conform to ENV 13282 or to an European Technical Approval or equivalent or to provisions valid in the place of use.

### 5.2 Soil

Not less than 95 % of the soil shall pass the 63 mm sieve when tested using wet sieving in conformity with EN 933-1.

The soil shall conform to classification and homogeneity requirements at the place of use.

NOTE 1 Organic matter can delay the setting and hardening process. Laboratory mixture design work will determine whether soil/material containing organic matter can be accommodated. The amount of organic matter that can be accommodated depends on the type of organic matter.

NOTE 2 Soil containing or suspected of containing sulphates can result in expansion of the mixture. Laboratory mixture design work including 'resistance to water testing' in accordance with this European Standard will determine if sulfates or other material with the potential to cause swelling can be accommodated.

### 5.3 Water

The water used shall not adversely affect the setting, hardening and performance of the mixture.

### 5.4 Other constituents

Where appropriate, lime in conformity with EN 14227-11, and/or other constituents, for example aggregate, shall be added to improve workability, traffickability or performance.

## 6 Mixture

### 6.1 General

The mixture shall comprise constituents specified in Clause 5.

### 6.2 Proportioning and dry density

The proportioning of the constituents including water content, expressed as percentages by dry mass of the total dry mass of the mixture, and the dry density of the mixture, shall be declared. The declared proportions

shall be based on the laboratory mixture design and/or practical experiences with mixtures produced with the same constituents and under the same conditions.

## 7 Requirements for the fresh mixture

### 7.1 Water content

The water content shall be selected to permit compaction on site and to optimize the mechanical performance of the mixture. The water content shall be determined by the Proctor or other test in conformity with EN 13286-2 to EN 13286-5, and limits set to give a workable range of water content on site compatible with the compaction and the desired performance of the mixture.

When required, the water content of the mixture shall conform to one of the categories in Table 1.

**Table 1 — Minimum water content categories**

| Minimum water content of the mixture  | Category   |
|---|------------|
| 0,9 optimum water content of the mixture determined in accordance with the selected method of compaction from EN 13286-2 to EN 13286-5  | $W_{0,9}$  |
| 0,95 optimum water content of the mixture determined in accordance with the selected method of compaction from EN 13286-2 to EN 13286-5 | $W_{0,95}$ |
| The optimum water content of the mixture determined in accordance with the selected method of compaction from EN 13286-2 to EN 13286-5  | $W_{1,0}$  |
| Declared value  | $W_{DV}$   |

### 7.2 Degree of pulverization

When required, the degree of pulverization of the mixture, determined in accordance with EN 13286-48, shall conform to one of the categories in Table 2.

**Table 2 — Degree of pulverization**

| Degree of pulverization | Category |
|-------------------------|----------|
| $\geq 30\%$             | $P_{30}$ |
| $\geq 40\%$             | $P_{40}$ |
| $\geq 50\%$             | $P_{50}$ |
| $\geq 60\%$             | $P_{60}$ |
| Declared value          | $P_{DV}$ |

### 7.3 Immediate bearing index

When required, the immediate bearing index of the mixture at the declared water content, determined in accordance with EN 13286-47, shall conform to one of the categories in Table 3 observing the following testing procedure. After mixing, the mixture shall be stored in bags in a sealed condition for 60 min. The specimen(s) shall then be manufactured and the determination of the index carried out immediately or no later than 90 min after mixing.

Table 3 — Immediate bearing index category

| Immediate bearing index | Category          |
|-------------------------|-------------------|
| $\geq 10$               | IPI <sub>10</sub> |
| $\geq 15$               | IPI <sub>15</sub> |
| $\geq 20$               | IPI <sub>20</sub> |
| $\geq 25$               | IPI <sub>25</sub> |
| $\geq 30$               | IPI <sub>30</sub> |
| $\geq 40$               | IPI <sub>40</sub> |
| $\geq 50$               | IPI <sub>50</sub> |
| Declared value          | IPI <sub>DV</sub> |

#### 7.4 Moisture condition value

When required, the moisture condition value of the mixture, determined in accordance with EN 13286-46, shall conform to one of the categories in Table 4.

Table 4 — Moisture condition value category

| Moisture condition value | Category            |
|--------------------------|---------------------|
| 6 minimum, 10 maximum    | MCV <sub>6/10</sub> |
| 7 minimum, 11 maximum    | MCV <sub>7/11</sub> |
| 8 minimum, 12 maximum    | MCV <sub>8/12</sub> |
| 9 minimum, 13 maximum    | MCV <sub>9/13</sub> |
| Declared values          | MCV <sub>DV</sub>   |

## 8 Laboratory mechanical performance classification

### 8.1 General

The laboratory mechanical performance of the mixture shall be characterized and classified by one of the following three methods:

- by California bearing ratio CBR;
- by compressive strength  $R_c$ ;
- by the combination  $R_t, E$  of tensile strength  $R_t$  and modulus of elasticity  $E$ .

NOTE No correlation is intended nor should be assumed between the 3 methods of characterization.

### 8.2 Classification by California bearing ratio

The CBR of the mixture, determined in accordance with EN 13286-47 and the following, shall conform to the selected class from Table 5.

- a) After manufacture, the specimens shall be subjected to a conditioning period of either 1 h, 3 days, or other selected period, during which the specimens shall be prevented from drying out and shall be maintained at a temperature of  $(20 \pm 2)$  °C or other specified temperature.
- b) After conditioning, the specimens shall undergo a soaking period of either 4 days or other longer period before testing, during which they shall be maintained at a temperature of  $(20 \pm 2)$  °C or other specified temperature.
- c) The length of conditioning and soaking periods shall be noted in the test report.

**Table 5 — California bearing ratio classes and requirements**

| CBR requirement after 4 days soaking<br>(or other longer specified period) | Class             |
|--|-------------------|
| $\geq 15$ and the immediate bearing index                                  | CBR <sub>15</sub> |
| $\geq 20$ and the immediate bearing index                                  | CBR <sub>20</sub> |
| $\geq 30$ and the immediate bearing index                                  | CBR <sub>30</sub> |
| $\geq 40$ and the immediate bearing index                                  | CBR <sub>40</sub> |
| $\geq 50$ and the immediate bearing index                                  | CBR <sub>50</sub> |
| Declared value   | CBR <sub>DV</sub> |

### 8.3 Classification by compressive strength

Mixtures shall be classified by compressive strength determined in accordance with EN 13286-41 carried out on specimens manufactured in accordance with EN 13286-50 to EN 13286-53.

The class of compressive strength shall be selected from Table 6 in combination with the selected method of specimen manufacture.

NOTE 1 The permitted methods of specimen manufacture produce different specimen shapes and density, and thus for the same mixture, different strengths. Hence it is important, on the basis of experience and utilization, not to separate strength from the method of specimen manufacture.

The age of classification and curing conditions shall be specified in accordance with practice at the place of use.

NOTE 2 For information, Annex A gives examples of age of classification and curing regimes.

For characterization or mixture design testing in the laboratory, compressive strength shall be the average result from at least three specimens. If one value varies by more than 20 % of the average, it shall be discarded and compressive strength taken as the average of the other values.

Table 6 — Compressive strength classification

| Minimum $R_c$ in MPa for cylinders of slenderness ratio 2 <sup>a</sup>  | Minimum $R_c$ in MPa for cylinders of slenderness ratio 1 <sup>a</sup> and cubes | $R_c$ Class          |
|---|--|----------------------|
| 0,4   | 0,5  | C <sub>0,4/0,5</sub> |
| 0,8   | 1  | C <sub>0,8/1</sub>   |
| 1,5   | 2  | C <sub>1,5/2</sub>   |
| 3   | 4  | C <sub>3/4</sub>     |
| 6   | 8  | C <sub>6/8</sub>     |
| 9   | 12   | C <sub>9/12</sub>    |
| Declared value  | Declared value   | C <sub>DV</sub>      |
| <sup>a</sup> If cylinders with slenderness ratios other than 1 or 2 are used, then the correlation with cylinders of either slenderness ratio 1 or 2 shall be established before use, except for Proctor cylinders of slenderness ratio 1,2 and 0,83, which shall be considered equal to slenderness ratio 1. |  |                      |

## 8.4 Classification by $R_t$ , $E$

### 8.4.1 General

The class of  $R_t$ ,  $E$  shall be selected from Figure 1.

The age of classification and curing conditions shall be specified in accordance with practice at the place of use.

NOTE For information, Annex A gives examples of age of classification and curing regimes.

For characterization or mixture design testing in the laboratory,  $R_t$  and  $E$  shall be the average result from at least three specimens. If one value varies by more than 20 % of the average, it shall be discarded and  $R_t$  and  $E$  taken as the average of the other values.

$R_t$  and  $E$  shall be established using one of the equivalent methods described in 8.4.2 to 8.4.4.

### 8.4.2 Method by direct tensile testing

$R_t$  shall be determined in accordance with EN 13286-40.

$E$  shall be determined in direct tension  $E_t$  in accordance with EN 13286-43.

For both, specimens shall be manufactured using vibrocompression in accordance with EN 13286-52.

### 8.4.3 Method by indirect tensile testing

$R_t$  shall be derived from  $R_{it}$  determined in accordance with EN 13286-42 using the relationship  $R_t = 0,8 R_{it}$ .

$E$  shall be derived from  $E_{it}$  ( $E$  measured in indirect tension) determined in accordance with EN 13286-43 using the relationship  $E = E_{it}$ .

Specimens shall be manufactured using

- either Proctor compaction for both in accordance with EN 13286-50,
- or vibrating hammer for both in accordance with EN 13286-51,
- or vibrocompression for both in accordance with EN 13286-52,
- or axial compression for both in accordance with EN 13286-53.

NOTE The permitted methods of specimen manufacture produce different specimen shapes and density, and thus for the same mixture, different strengths. Hence it is important, on the basis of experience and utilization, not to separate strength from the method of specimen manufacture.

#### 8.4.4 Method by indirect tensile and compression testing

$R_t$  shall be derived from  $R_{it}$  determined in accordance with EN 13286-42 using the relationship  $R_t = 0,8 R_{it}$ .

$E$  shall be derived from  $E_c$  ( $E$  measured in compression) determined in accordance with EN 13286-43 using the relationship  $E = E_c$ .

Specimens shall be manufactured using

- either Proctor compaction for both in accordance with EN 13286-50,
- or vibrating hammer for both in accordance with EN 13286-51,
- or vibrocompression for both in accordance with EN 13286-52,
- or axial compression for both in accordance with EN 13286-53.

NOTE The permitted methods of specimen manufacture produce different specimen shapes and density, and thus for the same mixture, different strengths. Hence it is important, on the basis of experience and utilization, not to separate strength from the method of specimen manufacture.

## 9 Resistance to water and other requirements for the mixture

### 9.1 Resistance to water

#### 9.1.1 General

Resistance to water shall be examined in accordance with 9.1.2, 9.1.3 or 9.1.4.

#### 9.1.2 Strength after immersion in water

The mixture shall satisfy the selected class for immersion from Table 7.

NOTE 1 The selected class shall reflect the nature of the main constituent, in particular materials containing sulfates or other potentially expansive material, the intended use of the mixture, the climate and weather conditions during construction.

In Table 7,  $R_i$  shall mean the average strength of not less than 3 specimens after  $Z$  days sealed curing followed by  $W$  days full immersion curing in aerated water, and  $R$  shall mean the average strength of not less than 3 specimens after  $(Z + W)$  days sealed curing. All the specimens shall be manufactured from the same batch of mixture, using the same method of manufacture, and shall be cured at the same temperature.  $Z$  and  $W$  shall be specified in accordance with the practice and requirements at the place of use.

NOTE Annex A gives examples of Z and W.

**Table 7 — Strength after immersion**

| $R_i/R$ ratio  | Category  |
|----------------|-----------|
| $\geq 0,6$     | $I_{0,6}$ |
| $\geq 0,7$     | $I_{0,7}$ |
| $\geq 0,8$     | $I_{0,8}$ |
| Declared value | $I_{DV}$  |

### 9.1.3 Linear swelling after soaking in water

Linear swelling, determined on at least 3 fully soaked (immersed) CBR specimens in accordance with EN 13286-47, using water that is continuously aerated, shall conform to the selected category from Table 8. The soaking shall follow a conditioning period. The swelling shall be examined for at least 28 days or until swelling ceases if longer.

NOTE The conditioning period will usually be the same as that selected for the determination of CBR in 8.2.

**Table 8 — Linear swelling**

| Average maximum swelling of the specimens<br>mm | Maximum swelling of any individual specimen<br>mm | Class           |
|---|---|-----------------|
| 5   | 10  | LS <sub>5</sub> |
| 3   | 6   | LS <sub>3</sub> |
| 1   | 2   | LS <sub>1</sub> |

### 9.1.4 Volumetric swelling after immersion in water

Volumetric swelling,  $G_v$ , shall not exceed 5 % when tested in accordance with EN 13286-49.

NOTE Where the volumetric swelling is greater than 5 % but does not exceed 10 %, the use of the mixture is generally not possible; however a complementary study can be made according to experience at the place of use.

## 9.2 Strength at trafficking

'Strength at trafficking' shall be specified in accordance with provisions valid at the place of use.

## 9.3 Resistance to frost

Frost resistance shall be examined in accordance with provisions valid at the place of use.

NOTE Currently, there is insufficient experience to define a method for frost resistance that can be used in all parts of Europe.

## 9.4 Workability period

Where appropriate, the workability period determined in accordance with EN 13286-45 shall be declared.

## 10 Production control

See Annex B (informative).

## 11 Designation and description

11.1 The product shall be designated by:

- a) producer, place of production and producer code;
- b) reference to this European Standard, i.e. EN 14227-13;
- c) mixture description and mechanical performance class (e.g. Soil treated by hydraulic road binder – T2).

11.2 In addition, the product shall be described by:


- a) description of the constituents including, if applicable, the characteristics and homogeneity of the soil;
- b) mixture proportions including water content;
- c) appropriate fresh mixture requirements with selected categories (e.g. W, P, IPI, MCV) including the compaction energy used to determine W and IPI;
- d) laboratory mechanical performance values together with the method of manufacture, curing conditions, curing period, dry density and water content of the mechanical performance specimens;
- e) 'resistance to water' category (e.g. I, LS or G<sub>v</sub>).
- f) appropriate 'other requirements' from Clause 9.

## 12 Labelling

When appropriate, the delivery ticket shall contain at least the following:

- a) designation;
- b) date of despatch;
- c) quantity;
- d) serial number.

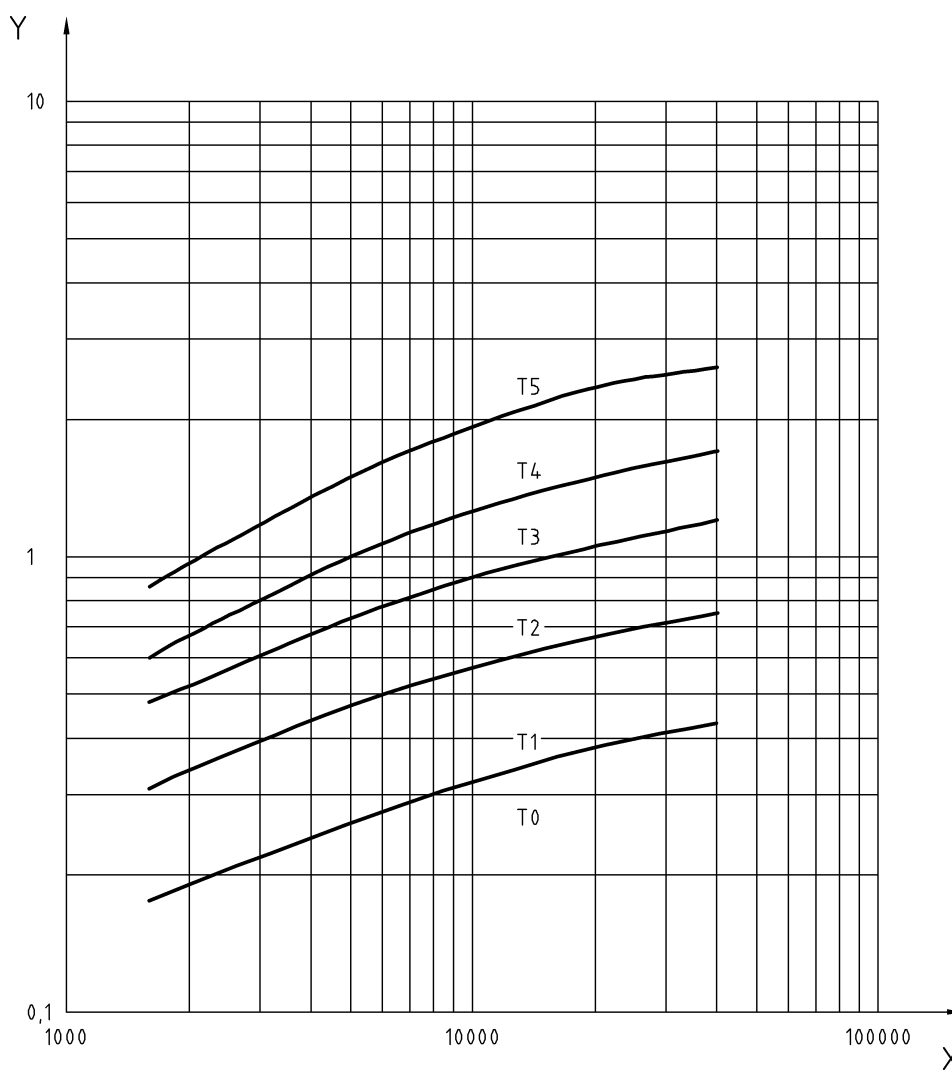

**Key**Y direct tensile strength  $R_t$ , in MPaX elastic modulus  $E$ , in Mpa

| $E$<br>MPa                   | 2 000        | 5 000 | 10 000 | 20 000 | 40 000 |
|------------------------------|--------------|-------|--------|--------|--------|
| <b>Low limit of category</b> | $R_t$<br>MPa |       |        |        |        |
| T5                           | 0,97         | 1,50  | 1,93   | 2,35   | 2,60   |
| T4                           | 0,67         | 1,00  | 1,26   | 1,49   | 1,70   |
| T3                           | 0,52         | 0,73  | 0,90   | 1,05   | 1,20   |
| T2                           | 0,34         | 0,47  | 0,57   | 0,67   | 0,75   |
| T1                           | 0,19         | 0,26  | 0,32   | 0,38   | 0,43   |

NOTE The table gives the values of  $R_t$  and  $E$  used to draw the curves limiting the categories T5, T4, T3, T2 and T1.

Figure 1 — Classification by  $R_t$ ,  $E$

## Annex A (informative)

### Examples of 'age of classification' and curing regimes for $R_c$ , $R_t$ and $E$ testing of treated soils including resistance to water testing by full immersion in water

Table A.1

| Sealed curing (days) Note 1<br>(Z in 9.1.2) | Immersion in water curing<br>(days) Note 2<br>(W in 9.1.2) | Total (days) |
|---|--|--------------|
| 7   | –  | 7            |
| 7   | 7  | 14           |
| 14  | –  | 14           |
| 21  | 7  | 28           |
| 28  | –  | 28           |
| 28  | 28   | 56           |
| 56  | –  | 56           |
| 28  | 63   | 91           |
| 91  | –  | 91           |
| 182   | –  | 182          |
| 364   | –  | 364          |

NOTE 1 Sealed curing, which is generally used for classification purposes, designates a condition that prevents loss or gain of water and also applies to the time in the mould.

NOTE 2 The water for 'immersion in water curing' can be still or aerated.

NOTE 3 Temperature during sealed or immersion curing is typically  $(20 \pm 2) ^\circ\text{C}$  or  $(40 \pm 2) ^\circ\text{C}$ .

## **Annex B** (informative)

### **Production control for hydraulically treated mixtures**

#### **B.1 General**

This annex describes recommendations for a production control system for producers of hydraulically treated mixtures (e.g. aggregates and soils treated by lime, hydraulic binders or hydraulic combinations).

The objective of production control is to give assurance that the mixture conforms to the specification.

#### **B.2 Quality Manual**

The producer should establish and maintain his policy and procedures for production control in a Quality Manual that should include:

- producer's organizational structure relating to quality;
- control of constituents and mixtures;
- process control, calibration and maintenance;
- requirements for the handling and storage of the mixture when appropriate;
- inspection, calibration and control of the measuring equipment in the process, and laboratory testing equipment for the mixture;
- procedures for handling non-conforming mixture.

#### **B.3 Organization**

##### **B.3.1 Responsibility and authority**

The responsibility, authority and interrelation of all personnel who manage, perform and verify work affecting quality should be defined in the Quality Manual, particularly personnel who have authority to identify, record and rectify any mixture quality problems.

##### **B.3.2 Management representative**

The producer should appoint a person with appropriate authority, knowledge and experience of production control and to ensure that the requirements of the Quality Manual are implemented and maintained.

##### **B.3.3 Internal audits**

The producer should carry out internal quality audits to verify compliance with the planned arrangements and the effectiveness of the quality system. Audits should be scheduled on the basis of the status and importance of the activity. The audits and follow up action should be carried out in accordance with documented procedures. The results of the audits should be documented and brought to the attention of the personnel

having responsibility in the area audited. The management personnel responsible for the area should take timely corrective action on the deficiencies found by the audit and should keep a record of the action taken.

### **B.3.4 Management review**

The production control system should be reviewed at appropriate intervals by management to ensure its continuing suitability and effectiveness. Records of such reviews should be maintained.

### **B.3.5 Sub-contract services**

Where any services are supplied from outside the producer's resources, means of control should be established.

### **B.3.6 Records**

The production control system should contain adequately documented procedures and instructions.

The intended frequencies of tests and inspections by the producer should be documented and the results of tests and inspections recorded.

Sampling location, date and time, as well as details of the mixture or constituents tested, should be recorded together with any other relevant information.

Where the constituent or mixture examined does not satisfy the requirements of the appropriate specification and this European Standard, records should be kept of corrective actions taken to ensure the quality of the mixture is maintained.

Records should be kept in such a way that they are retrievable and be retained for the period stated in the Quality Manual, usually a minimum of 3 years or longer if legally required.

### **B.3.7 Training**

The producer should establish and maintain procedures for the training of all personnel involved in activities affecting quality. Personnel performing specific assigned tasks should be suitably qualified on the basis of appropriate education, training or experience, as required. Training records should be kept.

## **B.4 Control procedures**

### **B.4.1 Production management**

The production control system should contain the following:

- a) composition of the mixture to be produced;
- b) procedures to adjust mixture composition;
- c) procedures to ensure that constituents comply with requirements;
- d) procedures to ensure that production equipment, including mixture storage facilities, maintain the composition, homogeneity, and consistency of the mixture;
- e) procedures for
  - calibrating, maintaining and adjusting the process and testing equipment,

- sampling the constituents and mixture,
  - data recording during processing,
  - adjusting the process according to weather conditions;
- f) instructions so that the mixture is identifiable up to the point of delivery as regards source and type.

#### **B.4.2 Composition of the mixture**

The composition of the mixtures should be established from a laboratory mixture design procedure intended to ensure the mixture will have properties conforming to the relevant standard.

Where applicable, the composition of regularly produced mixtures should be included in a catalogue of mixtures compositions and considered as the mixture base line or target composition.

The compositions should be re-established in case of significant change in constituents and should be reviewed periodically to ensure the mixture conforms to requirements taking account any change in properties of constituents.

#### **B.4.3 Constituents**

Documentation should detail the source and type of each constituent of the mixture for use at the production location.

Adequate supplies of constituent should be available to ensure that the planned rates of production and delivery can be maintained.

The specifications for incoming constituents should be established and communicated to suppliers by means of written orders.

The control procedures should check that constituents are capable of providing the required quality.

Constituents should be transported and stored in such a manner as to avoid intermingling, contamination or deterioration that may affect the quality of the product.

#### **B.4.4 Process control**

The Quality Manual should include:

- description of equipment and installation;
- description of the flow of constituents and the processes carried out on them. If appropriate this should incorporate a flow diagram;
- schedule for monitoring the performance of the process, (manual or automatic systems), including a record of equipment performance against the stated tolerances.

#### **B.4.5 Inspection, calibration and control of process equipment**

The Quality Manual should identify items of measuring devices that require calibration and the frequency of such calibration.

Calibration procedures should be provided, including the permitted tolerances for the devices to remain in service. The Quality Manual should state the required accuracy of all calibrations.

The equipment should be adequately maintained to ensure that it continues to be capable of producing mixture to the required specifications and tolerances.

#### **B.4.6 Handling and delivery**

The Quality Manual should contain procedures to ensure that the mixture is handled and (where appropriate) delivered with the minimum of segregation or degradation and within the permitted water content range and time limit.

At the point of delivery, the mixture should be identifiable and traceable with regard to its production data. The producer should maintain records of relevant data of production, which can be referenced from information when appropriate on the delivery ticket.

If appropriate the producer's Quality Manual should describe the characteristics of any mixture storage system and define its mode of operation. The producer should ensure through checks, inspections and records that such systems are used correctly and that mixtures maintain their suitability for use.

### **B.5 Inspection and testing of constituents and mixtures during production**

#### **B.5.1 General**

At the start of the production process, the homogeneity of the mixture should be considered with regard to the specification, the type and quality of the production plant and the quality and homogeneity of the constituents. This can be appreciated either from past production experience or by undertaking specific tests.

The Quality Manual should specify the frequency and nature of regular tests/checks/inspections that should be carried out during production. The producer should prepare a schedule of frequencies considering:

- test frequencies in relation to periods of actual production of each mixture;
- test frequency where automated surveillance and monitoring of the production process exists;
- statistical approach for testing.

Reasons for changing the test frequencies and analysis should be stated in the Quality Manual.

**NOTE** If appropriate, long-term experience of the consistency of a particular property as well as mixtures with an established record for conformity should be taken into account.

#### **B.5.2 Characteristics that require control during production**

These may include:

- properties of the constituents including water content (before production);
- proportioning of the constituents including added water;
- grading of the fresh mixture;
- water content of the fresh mixture.

The above characteristics should comply with the requirements of the target composition of the mixture (see B.4.2).

### B.5.3 Frequency of sampling the mixture

During the regular production of the mixture, the sample frequency may be as follows:

- In the case of plants with a validated and accepted automated surveillance and data collection system giving computerized composition for every truck or every batch, one sample should be taken every 2 000 t or 1 000 m<sup>3</sup> or one per day for lesser quantities.
- In the case of other types of plants or production, one sample should be taken every 300 t or 150 m<sup>3</sup>, with a minimum of 1 sample per day.
- Alternatively and independent of the type of mixing plant, the frequency of sampling can be on a time related rather than a quantity related basis such as a minimum of 1 sample per week or 1 sample per day depending on the characteristic being measured.

In the case of occasional production of a standard mixture, the production should be assessed cumulatively with previous production with the same or similar criteria. The frequency of sampling can be adjusted on a contract-by-contract basis according to the overall quantity of production required.

## B.6 Inspection and testing equipment

### B.6.1 General

All necessary facilities, equipment and personnel should be available to carry out the required inspections and tests.

Normally the testing should be performed according to the specified test methods given in the relevant standard.

Other test methods may be used, if correlations or safe relationships between the results of these test methods and the reference methods have been established.

### B.6.2 Measuring and testing equipment

The producer should be responsible for the control, calibration and maintenance of his inspection, measuring and testing equipment.

### B.6.3 Measuring and testing equipment in the process

The points in the process where measuring equipment needs to be deployed should be stated in the Quality Manual.

The Quality Manual should indicate when control is carried out automatically or manually. There should be a description of how equipment is maintained and calibrated.

### B.6.4 Measuring and testing equipment in laboratory

The testing equipment should be in a known state of calibration and accuracy, consistent with the required measurement capability.

The following points should be addressed:

- accuracy and frequency of calibration, which should be in accordance with the standard(s) for the relevant test(s);

## EN 14227-13:2006 (E)

- equipment to be used in accordance with documented procedures;
- equipment to be uniquely identified and calibration records should be retained;
- keeping of calibration records.

### B.7 Non-conformity

#### B.7.1 General

Non-conformity can arise at the following stages:

- constituent delivery;
- constituent in storage;
- mixture production;
- handling, storage and delivery of the mixture if appropriate.

In the event that a non-conforming constituent, process or mixture is identified, investigations should be initiated to determine the reasons for non-conformity and effective corrective action should be implemented to prevent recurrence in accordance with procedures documented in the Quality Manual.

#### B.7.2 Non-conformity of constituents

In the case of non-conforming constituents, corrective action may involve:

- reclassifying the constituent;
- reprocessing;
- adjusting process control to allow for constituent non-conformity;
- rejection and disposal of the non-conforming constituent.

#### B.7.3 Non-conformity of the mixture

Non-conforming mixture should be evaluated and procedures for taking action should be followed.

The Quality Manual should identify the action to be taken when a non-conforming product is identified and should state the circumstances under which the customer will be notified of non-conforming results.

Such action may involve:

- corrective action (for example modification of the mixture and or adjustment of equipment);
- acceptance of the mixture following the agreement of the customer to accept a non-conforming mixture;
- if the mixture produced is incorrect it can be redirect to an alternative customer if appropriate;
- rejection of the mixture.



## Bibliography

- [1] EN 14227-5, *Hydraulically bound mixtures — Specifications — Part 5: Hydraulic road binder bound mixtures*

---

---

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.  
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.  
Fax: +44 (0)20 8996 7001. Email: [orders@bsi-global.com](mailto:orders@bsi-global.com). Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.  
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: [info@bsi-global.com](mailto:info@bsi-global.com).

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.  
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.  
Email: [membership@bsi-global.com](mailto:membership@bsi-global.com).

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.  
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.  
Email: [copyright@bsi-global.com](mailto:copyright@bsi-global.com).