



BSI Standards Publication

**Flexible sheets for
waterproofing —
Waterproofing of concrete
bridge decks and other
concrete surfaces trafficable
by vehicles — Determination
of resistance to dynamic water
pressure after damage by pre-
treatment**

National foreword

This British Standard is the UK implementation of EN 14694:2017. It supersedes BS EN 14694:2005 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee B/546, Flexible sheets for waterproofing and water vapour control.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2017.
Published by BSI Standards Limited 2017

ISBN 978 0 580 94823 7

ICS 91.100.50

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 April 2017.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD

EN 14694

NORME EUROPÉENNE

EUROPÄISCHE NORM

March 2017

ICS 91.100.50

Supersedes EN 14694:2005

English Version

**Flexible sheets for waterproofing - Waterproofing of
concrete bridge decks and other concrete surfaces
trafficable by vehicles - Determination of resistance to
dynamic water pressure after damage by pre-treatment**

Feuilles souples d'étanchéité - Étanchéité des tabliers
de ponts en béton et autres surfaces en béton
circulables par les véhicules - Détermination de la
résistance à la pression hydraulique dynamique après
dégradation par prétraitement

Abdichtungsbahnen - Abdichtung von Betonbrücken
und anderen Verkehrsflächen auf Beton - Bestimmung
des Widerstandes gegenüber dynamischem
Wasserdruck nach Schäden infolge Vorbeanspruchung

This European Standard was approved by CEN on 6 February 2017.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents		Page
European foreword		3
Introduction		4
1	Scope	5
2	Normative references	5
3	Terms and definitions	5
4	Test methods	5
4.1	Principle	5
4.2	Apparatus and materials	5
4.3	Preparation of test specimens	5
4.4	Procedure	6
4.5	Expression of results	6
4.6	Test report	7

European foreword

This document (EN 14694:2017) has been prepared by Technical Committee CEN/TC 254 “Flexible sheets for waterproofing”, the secretariat of which is held by NEN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2017, and conflicting national standards shall be withdrawn at the latest by September 2017.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 14694:2005.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association.

The significant technical changes are the new reference to prEN 17048 in Clause 2, Normative references, and further information about test specimens in Clause 4.3, Preparation of test specimens.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Introduction

The purpose of this test is to determine the resistance to pre-treatment by impact puncturing followed by dynamic water pressure testing for sheets in the waterproofing system.

The test is normally performed for single sheets but may also be performed for double sheet systems.

1 Scope

This European Standard specifies a test method for the evaluation of the resistance to impact puncturing of a sheet or sheet system.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 13375, *Flexible sheets for waterproofing - Waterproofing of concrete bridge decks and other concrete surfaces trafficable by vehicles - Specimen preparation*

EN 13416, *Flexible sheets for waterproofing - Bitumen, plastic and rubber sheets for roof waterproofing - Rules for sampling*

EN 14695, *Flexible sheets for waterproofing - Reinforced bitumen sheets for waterproofing of concrete bridge decks and other trafficked areas of concrete - Definitions and characteristics*

prEN 17048, *Flexible sheets for waterproofing - Plastic and rubber sheets for waterproofing of concrete bridge decks and other trafficked areas of concrete - Definitions and characteristics*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 13416, EN 14695 and prEN 17048 apply.

4 Test methods

4.1 Principle

Pre-treatment impact puncturing is carried out at room temperature, where a conical weight is allowed to fall freely on to the waterproofing sheet. The degree of penetration is then assessed with the aid of dynamic water pressure testing.

4.2 Apparatus and materials

Equipment for impact puncturing, with a puncturing tool consisting of $(1,0 \pm 0,01)$ kg of steel with a 90° conical point (see Figures 2 and 3).

Concrete slab, according to EN 13375 for supporting the test specimen during impact puncturing.

Suitable frame, for holding the test specimen firmly to the concrete slab.

Equipment for the water pressure test, with a dynamic water pressure applied (see Figures 4 and 5).

4.3 Preparation of test specimens

Take test samples and test pieces in accordance with EN 13416.

Select one test specimen of 400 mm × 200 mm for testing.

In the case of a double sheet system, weld or glue the two sheets together according to manufacturer instructions. Ensure that the sheet or sheet system thickness is within the limits of the equipment used.

Condition the test specimen for at least 24 h at a temperature of (23 ± 2) °C.

4.4 Procedure

4.4.1 Carry out the testing at a temperature of (23 ± 2) °C.

4.4.2 Select on the test specimen of 400 mm × 200 mm two circular sections of diameter 135 mm approximately.

4.4.3 Lay the test specimen on the horizontal concrete slab, with the upper side of the sheet facing upwards. Hold the test specimen down and in place with a suitable frame. The sheet shall not be bonded to the concrete.

4.4.4 Impact the test specimen at 4 points in each circular section, ensuring that the 4 points are diametrically positioned within each circular section so that each point will fit into a disc slot according to Figure 5. Allow the puncturing tool to fall freely and vertically from a specified height of (200 ± 2) mm onto the surface of the test specimen.

4.4.5 Cut the two circular test specimens (diameter 135 mm approximately) from the pre-treated test specimen for water pressure testing.

4.4.6 Fill the apparatus for the water pressure test with water till overflowing. In testing, mount the circular test specimen firmly with the upper side of the sheet facing upwards in the equipment (see Figure 4). Place the slotted disc (see Figure 5), on top of the test specimen so that a punctured point appears in the middle of each slot, with one of the slots being parallel to the longitudinal direction of the sheet. Progressively tighten until the test specimen is firmly in place, and dry where necessary with a cloth or with compressed air.

4.4.7 Under the influence of a specified dynamic water pressure, examine the circular test specimen to determine whether it remains impervious for a specified number of pulses. The dynamic pressure is defined in Figure 1. The water pressure is increased from 0 kPa to (500 ± 5) kPa within 0,5 s, kept at that pressure for 2,5 s, decreased again within 0,5 s to 0 kPa and kept there for another 2,5 s. The total time of a pulse is 5 s to 6 s. Perform 1 000 pulses of the dynamic water pressure test on both circular test specimens. If a visual inspection identifies a leakage in the test specimen, terminate the test and record the number of pulses.

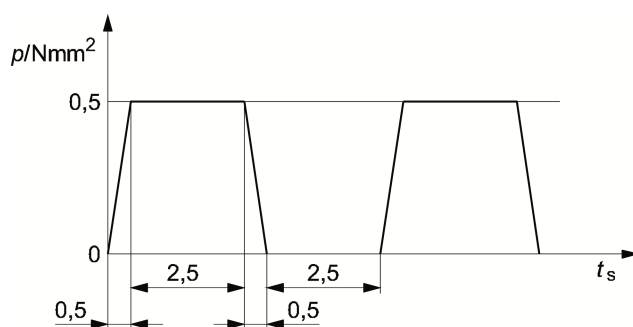


Figure 1 — Dynamic pressure load function

4.5 Expression of results


If both circular test specimens are watertight, the result is “pass”. Repeat the test once if one of the two circular test specimens has leaked, and report the test results. If both circular test specimens of this repeated test are watertight, the result is “pass”, if not “not pass”.

NOTE There is no precision data currently available.

4.6 Test report

The test report shall include at least the following information:


- a) all details necessary to identify the product tested;
- b) a reference to this document and any deviation from it;
- c) the dates of delivery of sample and preparation of test specimens;
- d) information about preparation of test specimens in accordance with 4.3;
- e) information about the procedure in accordance with 4.4;
- f) the test results in accordance with 4.5 and, in case of leakage, the number of pulses before leakage;
- g) the date of tests.

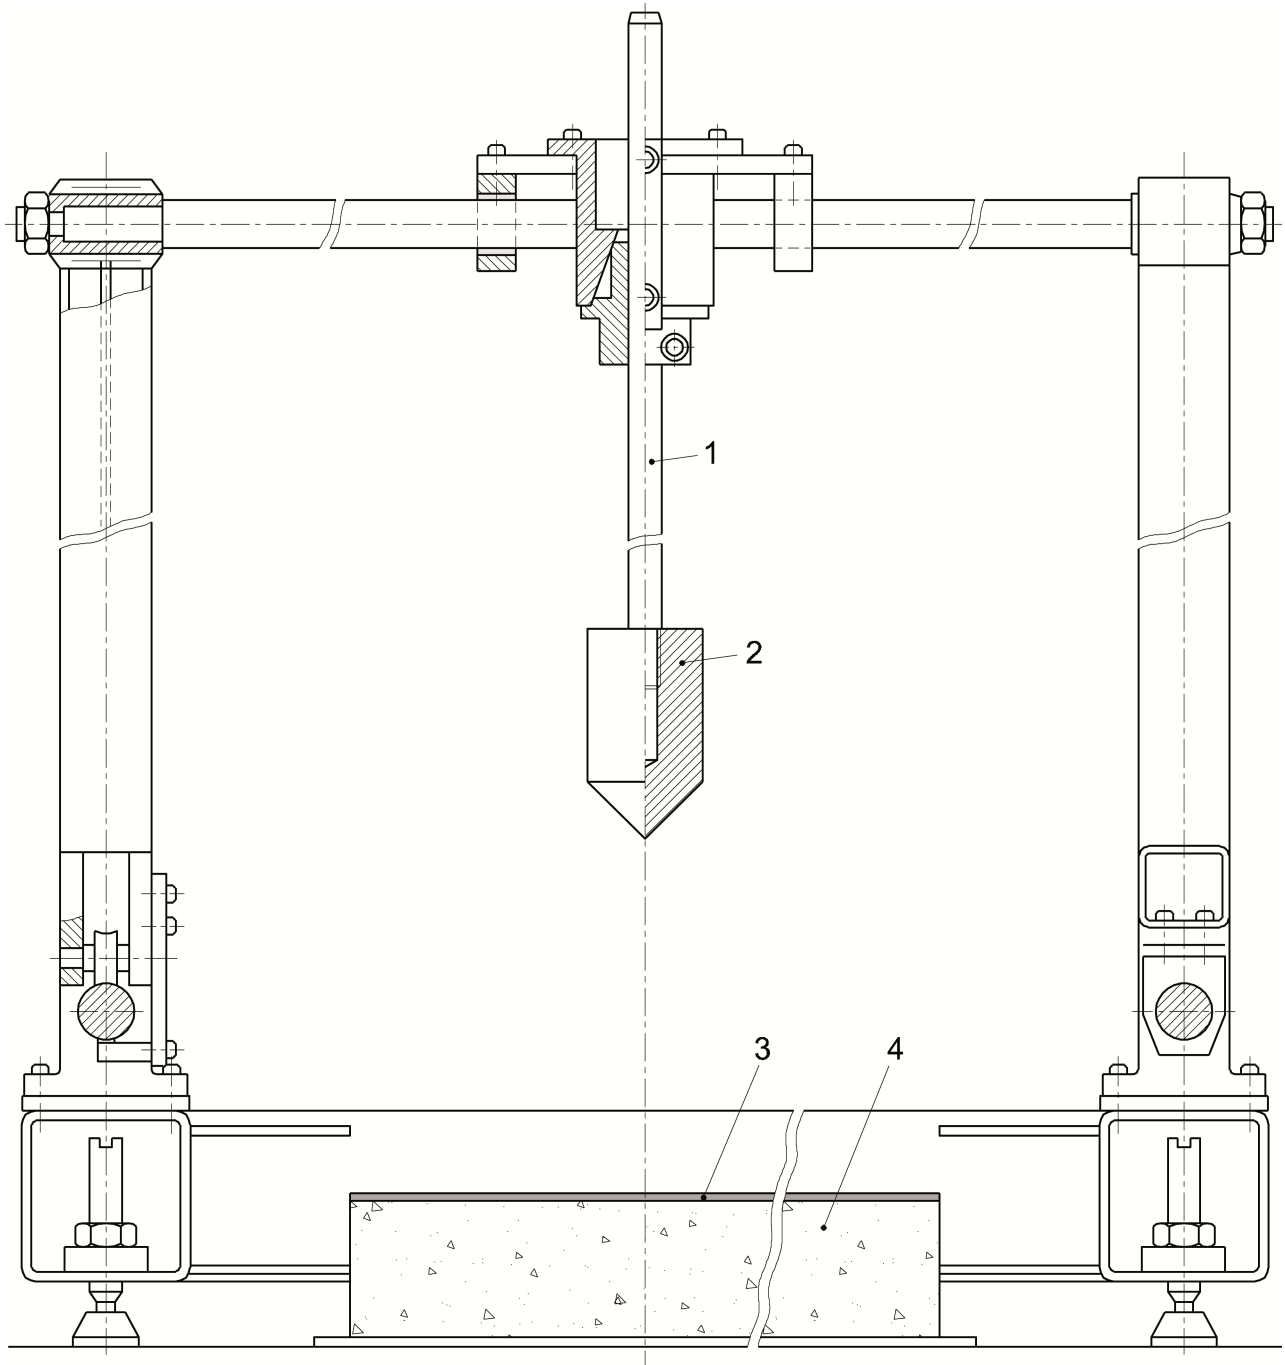

Key

- 1 Shaft
- 2 Puncturing tool
- 3 Test specimen
- 4 Concrete slab


Figure 2 — Example of equipment for impact puncturing

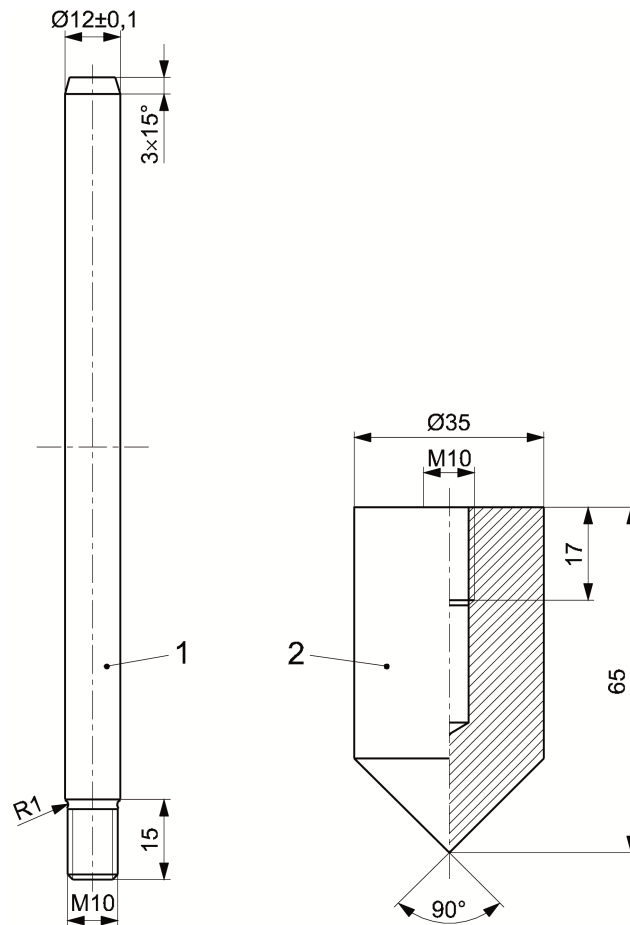

Key

- 1 Shaft with diameter $(12 \pm 0,1)$ mm
- 2 Puncturing tool
Cone hardened to 26 HRC to 31 HRC, surface even and unmarked
Cone diameter $(35 \pm 0,1)$ mm
Cone height $(65 \pm 0,1)$ mm
Cone end point diameter $(0,5 \pm 0,05)$ mm

Figure 3 — Puncturing tool

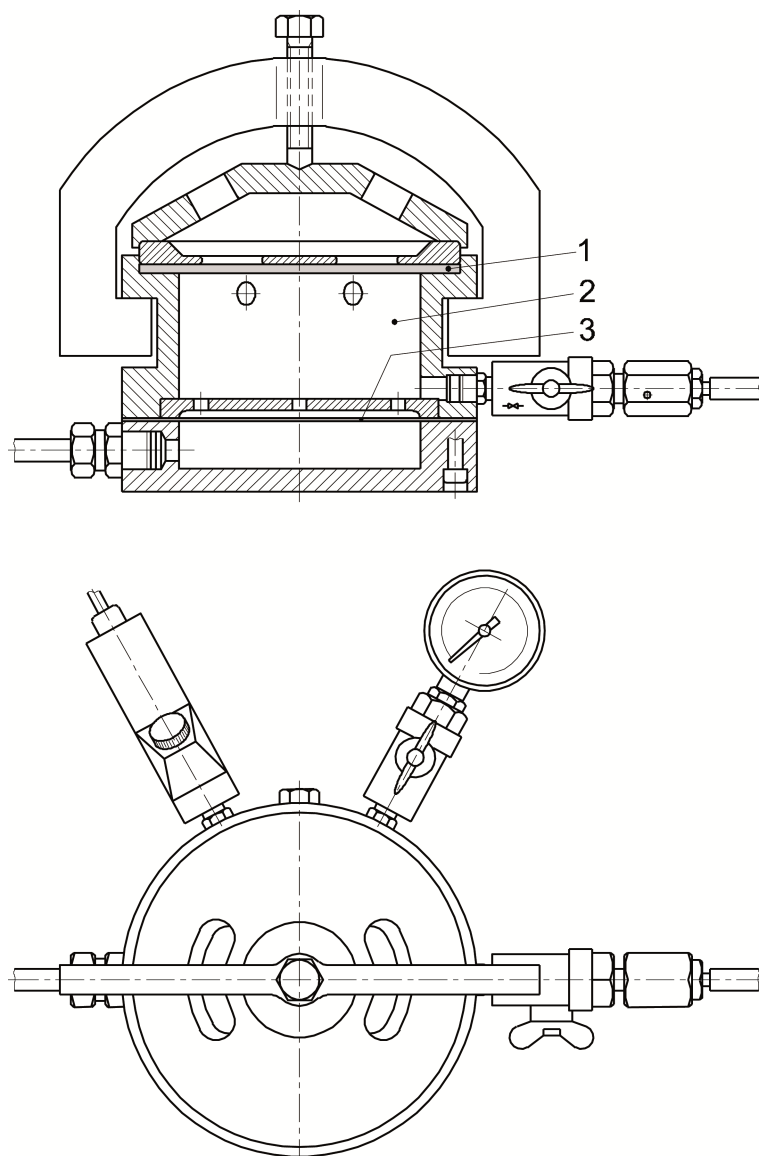

Key

- 1 Test specimen
- 2 Water
- 3 Membrane

Figure 4 — Example of equipment for determination of the resistance to dynamic water pressure

Dimensions in millimetres

Section A — A

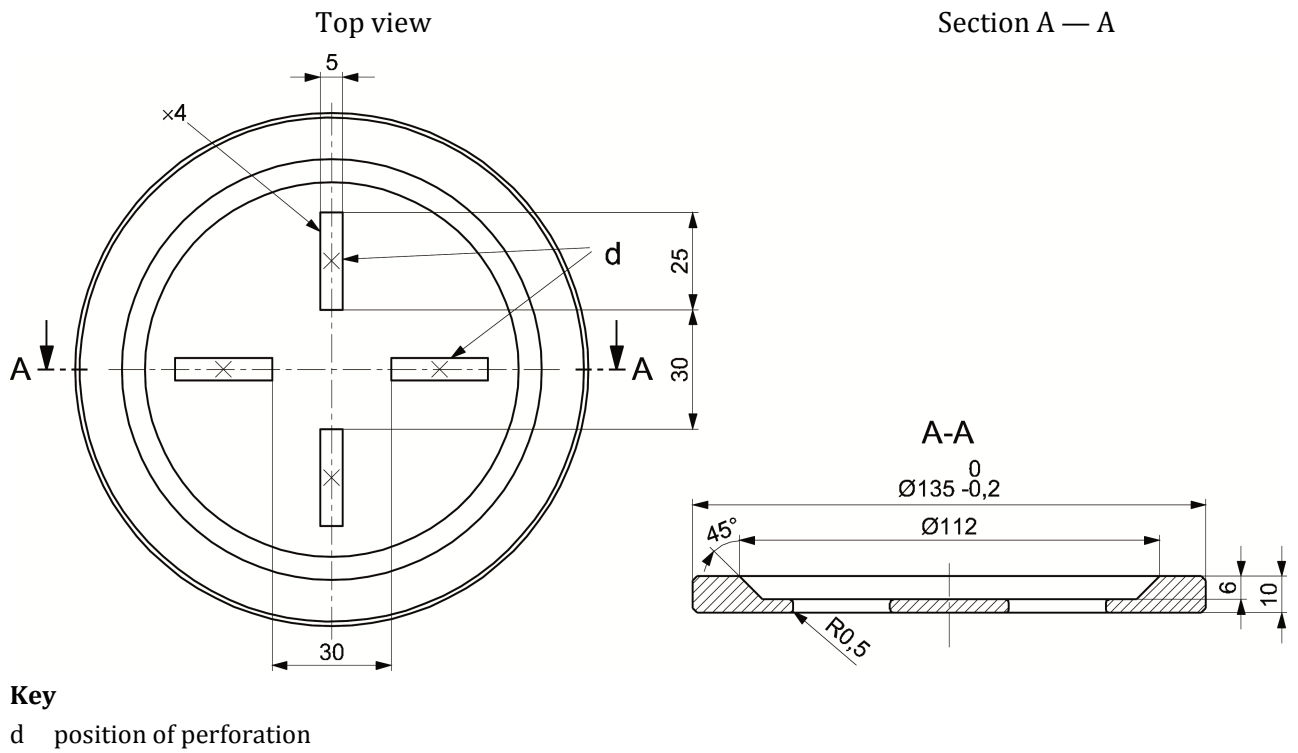


Figure 5 — Slotted disc of the slit pressure-testing device

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK