



BSI Standards Publication

Thermal insulating products for building equipment and industrial installations — Determination of maximum service temperature

National foreword

This British Standard is the UK implementation of EN 14706:2012. It supersedes BS EN 14706:2005 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee B/540, Energy performance of materials components and buildings.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013. Published by BSI Standards Limited 2013

ISBN 978 0 580 77439 3

ICS 91.100.60

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 28 February 2013.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Thermal insulating products for building equipment and industrial installations - Determination of maximum service temperature

Produits isolants thermiques pour l'équipement du bâtiment et les installations industrielles - Détermination de la température maximale de service

Wärmedämmstoffe für die Haustechnik und für betriebstechnische Anlagen - Bestimmung der oberen Anwendungsgrenztemperatur

This European Standard was approved by CEN on 24 August 2012.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

Foreword.....	4
1 Scope	5
2 Normative references	5
3 Terms and definitions	5
4 Principle.....	5
5 Apparatus	6
6 Test specimens	7
6.1 Dimensions of test specimens	7
6.2 Number of test specimens	7
6.3 Conditioning of test specimens	8
7 Procedure	8
7.1 Test conditions	8
7.2 Test procedure	8
8 Calculation and expression of results.....	9
8.1 Thickness deformation versus time	9
8.2 Dimensional changes.....	9
8.3 Additional tests and/or observations	10
8.4 Internal self heating.....	10
9 Accuracy of measurement.....	11
10 Test report	12
Annex A (normative) Modifications of and additions to the general test method for mineral wool products.....	13
A.1 General.....	13
A.2 Test specimens	13
A.2.1 Conditioning of test specimens	13
A.2.2 Dimensions of test specimens	13
A.3 Procedure	13
A.3.1 Test conditions	13
A.3.2 Test procedure	13
A.4 Additional tests and/or observations	14
A.5 Test for internal self-heating	14
Annex B (normative) Modifications of and additions to the general test method for cellular glass products.....	16
B.1 General.....	16
B.2 Apparatus	16
B.3 Test specimens	16
B.3.1 Conditioning of test specimens	16
B.3.2 Dimensions of test specimens	16
B.4 Test procedure	16
B.5 Additional tests and/or observations	16
B.5.1 Observations	16
B.5.2 Additional tests	16
Annex C (normative) Modifications of and additions to the general test method for phenolic foam products.....	17
C.1 General.....	17
C.2 Test specimens	17
C.2.1 Dimensions of test specimens	17

C.2.2	Conditioning of test specimens	17
C.3	Test procedure	17
C.4	Additional tests and/or observations	17
Annex D	(normative) Modifications of and additions to the general test method for polyethylene foam (PEF) and flexible elastomeric foam (FEF) products	19
D.1	General	19
D.2	Apparatus	19
D.3	Dimensions of the test specimens	19
D.4	Test procedure	19
D.5	Calculation and expression of results	20
	Bibliography	21

Foreword

This document (EN 14706:2012) has been prepared by Technical Committee CEN/TC 88 "Thermal insulating materials and products", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2013, and conflicting national standards shall be withdrawn at the latest by April 2013.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 14706:2005.

The main technical changes that have been made in this new edition of EN 14706 are the following:

- a) Normative references have been updated;
- b) Figure 1 has been corrected;
- c) Clause 9, Accuracy of measurements has been revised;
- d) 5.1, Flat square or circular hot plate has been supplemented;
- e) 6.1, Dimensions of test specimens has been revised;
- f) A.3.1, Test conditions has been revised;
- g) A.5, Test for internal self-heating has been completed;
- h) C.4, Additional tests and/or observations has been completed;
- i) D.3, Dimensions of test specimens has been revised.

This European Standard is one of a series of standards which specify test methods for determining dimensions and properties of thermal insulating materials and products. It supports a series of product standards for thermal insulating materials and products which derive from the Council Directive of 21 December 1988 on the approximation of laws, regulations and administrative provisions of the Member States relating to construction products (Directive 89/106/EEC) through the consideration of the essential requirements.

This European Standard has been prepared for products used to insulate building equipment and industrial installations, but it may also be applied to products used in other areas.

A similar standard is available for testing of preformed pipe insulation EN 14707, *Thermal insulating products for building equipment and industrial installations — Determination of maximum service temperature for preformed pipe insulation*.

According to the CEN/CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

1 Scope

This European Standard specifies the equipment and procedures for determining the maximum service temperature of flat insulation products. It is applicable to thermal insulating products.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 823, *Thermal insulating products for building applications — Determination of thickness*

EN 12085, *Thermal insulating products for building applications — Determination of linear dimensions of test specimens*

EN 12429, *Thermal insulating products for building applications — Conditioning to moisture equilibrium under specified temperature and humidity conditions*

EN 14303, *Thermal insulation products for building equipment and industrial installations — Factory made mineral wool (MW) products - Specification*

ISO 5725-2:1994, *Accuracy (trueness and precision) of measurement methods and results — Part 2: Basic method for the determination of repeatability and reproducibility of a standard measurement method*

ISO 7884-1, *Glass — Viscosity and viscometric fixed points — Part 1: Principles for determining viscosity and viscometric fixed points*

ISO 7884-7, *Glass — Viscosity and viscometric fixed points — Part 7: Determination of annealing point and strain point by beam bending*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

maximum service temperature

highest temperature at which the insulation product, when installed at the recommended thickness in a given application, continues to function within specified limits of performance

[SOURCE: EN ISO 9229:2007, 2.6.9.1]

Note 1 to entry: The required performance may be in the areas of dimensional stability, thermal properties, and mechanical properties as well as changes in appearance and resistance against creation of hazards such as internal self heating (see Annexes A and C and possible requirements in the relevant product standard).

Note 2 to entry: In the present test procedure, which is used as a reference, the test specimen is exposed to a temperature difference going from ambient to the maximum service temperature. This may not reflect the actual application conditions when products are exposed to different temperatures on the two main faces, e.g. in multilayer systems or for faced products where the facing may limit the maximum service temperature.

4 Principle

Measure thickness, length, and width after one sided heat treatment for a specified time period, at the maximum service temperature, achieved using a specified rate of temperature increase. The thickness of the test specimen is measured during heat treatment, and the length and width only after cooling to ambient temperature.

The procedure may be an iterative process.

Additional requirements for assessing the maximum service temperature of specific materials are described in normative annexes to this European Standard or the relevant product standard or any other European Technical Specification.

5 Apparatus

A general arrangement of the apparatus is indicated in Figure 1 and comprises:

5.1 Flat square or circular hot plate, with a uniform temperature distribution in the measuring zone on the hot face and a heat flux perpendicular to the face of the hot plate.

The deviation from flatness of the hot plate shall not exceed 1 mm in the measuring zone at ambient temperature.

The hot plate shall be capable of being controlled to within $\pm 2\%$ of a predetermined temperature or $\pm 10\text{ }^{\circ}\text{C}$, whichever is smaller.

The hot plate shall be capable of being heated at $50\text{ }^{\circ}\text{C/h}$ and/or $300\text{ }^{\circ}\text{C/h}$.

If a small size equipment (e.g. $\varnothing 100\text{ mm}$) is used, the free movement of the test specimen during the test is critical and shall be controlled strictly.

5.2 Edge insulation, with a gap as small as possible (e.g. $\leq 1\text{ mm}/100\text{ mm}$ test specimen size) which will permit free movement during the test of the test specimen and of the pressure plate.


5.3 Square or circular pressure plate, with the same dimensions as the test specimen exerting the required load on the test specimen.

5.4 Device, e.g. electromechanical, for measuring the thickness of the test specimen during the test to the nearest 0,1 mm.

When determining the thickness of the test specimen, the thermal movement of the apparatus (e.g. quartz rod) shall be taken into account up to the maximum service temperature.

5.5 Temperature sensors (e.g. thermocouples) capable of recording the hot plate temperature to the nearest $\pm 1\%$ in centigrade but not less than $\pm 1\text{ }^{\circ}\text{C}$, which are placed within grooves on the hot plate.

Dimensions in millimetres

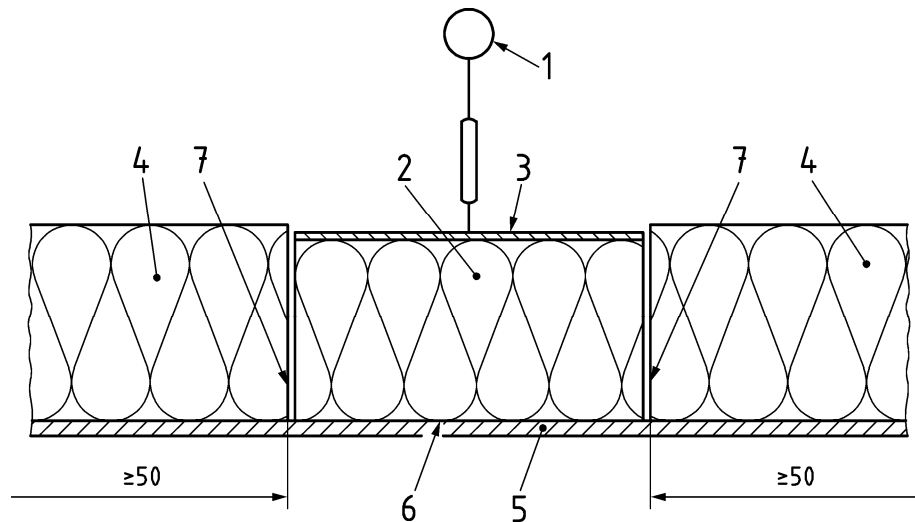

Key

- | | | | |
|---|---|---|--------------|
| 1 | device for measuring thickness, e.g. electromechanical device | 5 | hot plate |
| 2 | test specimen | 6 | thermocouple |
| 3 | pressure plate | 7 | small gap |
| 4 | edge insulation | | |

Figure 1 — Example of an apparatus for determining maximum service temperature

6 Test specimens

6.1 Dimensions of test specimens

a) **Length and width:** Test specimens shall be cut as squares or cylinders (as appropriate) and the cross section dimensions shall be as follows:

- 1) 100 mm × 100 mm (or diameter 100 mm) or
- 2) 150 mm × 150 mm (or diameter 150 mm) or
- 3) 200 mm × 200 mm (or diameter 200 mm) or
- 4) 300 mm × 300 mm (or diameter 300 mm).

The length and width or diameter shall be as specified in the relevant product standard or in annexes to this European Standard.

b) **Thickness:** The test specimen thickness shall be (100 ± 5) mm prepared by slicing if needed.

In the absence of a product standard or any other European Technical Specification the dimensions may be agreed between parties.

Testing may be performed on multilayer systems to simulate the conditions existing in the application.

6.2 Number of test specimens

The number of test specimens shall be as specified in the relevant product standard. If the number is not specified, then at least three test specimens shall be used.

In the absence of a product standard or any other European Technical Specification the number of test specimens may be agreed between parties.

6.3 Conditioning of test specimens

The test specimens shall be stored for at least 6 h at (23 ± 5) °C. In case of dispute they shall be stored at (23 ± 2) °C and (50 ± 5) % relative humidity for the time specified in the relevant product standard or at least 24 h.

7 Procedure

7.1 Test conditions

The initial temperature of the test specimen and the hot plate shall be (23 ± 5) °C.

7.2 Test procedure

Measure the length and width of the test specimen, l_1 , b_1 , (or diameter) in accordance with EN 12085, read to the nearest 0,5 mm.

Measure the thickness of the test specimen, d_0 , in accordance with EN 823 using the load specified in the relevant product standard.

Install the test specimen in the apparatus ensuring contact between the test specimen and the hot plate.

Load the test specimen with a pressure of 500 Pa and record the thickness, d_1 , to the nearest 0,1 mm.

For polyethylene foam and flexible elastomeric foam products, see Annex D.

Heat the test specimen using a temperature rate of increase of 50 °C/h or 300 °C/h, as specified in the relevant product standard or annex of this European Standard.

Maintain the temperature of the hot side, at the expected maximum service temperature, for 72 hours within ± 2 % of this temperature or ± 10 °C, whichever is smaller.

Record the thickness continuously during the test and at the end of the 72 h period, d_2 , to the nearest 0,1 mm.

Cool the test specimen in the equipment, to a temperature of < 35 °C and remeasure the thickness, d_3 , to the nearest 0,1 mm, unless otherwise specified in the relevant product standard or annex of this European Standard.

Take the test specimen from the apparatus and re-measure the length, l_2 , and the width, b_2 , (or diameter) of the test specimen as before to the nearest 0,5 mm.

In the case of non-rectangular edges, this shall be taken into account when measuring l_2 and b_2 (or diameter).

Examine the test specimen visually and note any changes caused by the test.

If the relevant product standard or annex of this European Standard specifies additional requirements, the observations and/or tests shall be performed accordingly.

Repeat the test procedure for the other test specimens.

8 Calculation and expression of results

8.1 Thickness deformation versus time

The curves thickness deformation versus time and temperature versus time recorded during testing shall be given. An example is shown in Figure 2.

8.2 Dimensional changes

Calculate the dimensional changes of thickness, $\Delta\varepsilon_d$, length, $\Delta\varepsilon_l$, and width, $\Delta\varepsilon_b$, in percentage, using the following formulae:

$$\Delta\varepsilon_d = 100 \times \frac{d_{2(\text{or } 3)} - d_1}{d_1} \quad (1)$$

$$\Delta\varepsilon_l = 100 \times \frac{l_2 - l_1}{d_1} \quad (2)$$

$$\Delta\varepsilon_b = 100 \times \frac{b_2 - b_1}{b_1} \quad (3)$$

where:

- d_1 is the measured thickness installed before heating, in millimetres;
- d_2 is the measured thickness installed after the 72 h at constant temperature, in millimetres;
- d_3 is the measured thickness after cooling down to a temperature of < 35 °C, in millimetres;
- l_1, b_1 are the measured length and width before heating, in millimetres;
- l_2, b_2 are the measured length and width after the 72 h at constant temperature and after cooling down, in millimetres.

In case of circular test specimens, the diameter/diameter change is calculated instead of length and width. Formula (2) can be used by inserting diameter instead of length.

If the dimensional change in thickness is larger by using d_3 instead of d_2 in Formula (1), this thickness shall be used in the calculation of the test result.

Calculate the test result as the mean values of dimensional changes, $\overline{\Delta\varepsilon_d}$, $\overline{\Delta\varepsilon_l}$, $\overline{\Delta\varepsilon_b}$, as a percentage rounded to the nearest 0,5 % from the test results of the individual test specimens.

If the change in the mean value (test result) for any of the dimensions exceeds the value specified in the relevant product standard, the test shall be repeated at a lower temperature until the dimensional changes are smaller than or equal to the specified value. This temperature is then considered as the maximum service temperature (see Figure 3), providing that the requirements given in 8.3 and 8.4 are also fulfilled.

The steps in centigrade for the indication of the maximum service temperature shall be as specified in the relevant product standard or annex to this European Standard. If the steps are not specified, the maximum service temperature shall be declared in steps of not less than 5 °C for temperatures up to 100 °C and in steps of not less than 10 °C for temperatures above 100 °C.

NOTE Results may not be comparable for a product tested at different thicknesses and/or different loads.

8.3 Additional tests and/or observations


The result of the visual examination shall be noted.

If a relevant annex of this European Standard and/or the relevant product standard specifies additional requirements, the calculations and/or observations shall be noted accordingly.

8.4 Internal self heating

Evidence of internal self heating is found when the test specimen temperature at any time during the test exceeds the temperature of the hot plate.


The test procedure is described in the relevant annexes of this European Standard.

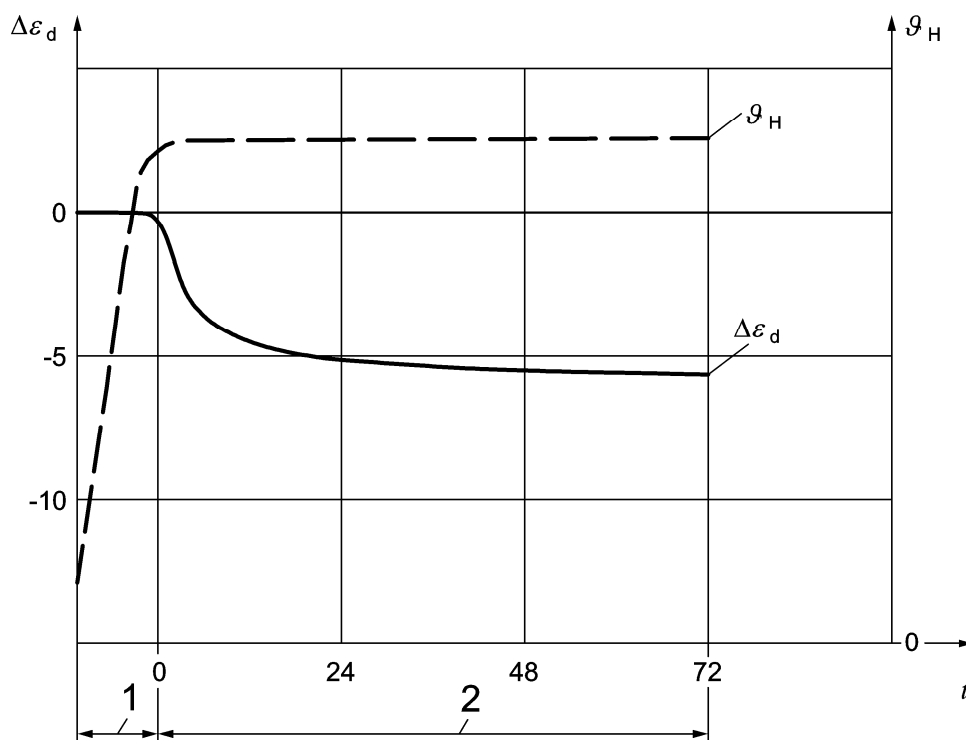

Key

- 1 period of heating
- 2 period of testing
- $\Delta\epsilon_d$ change in thickness in percentage
- ϑ_H temperature of the hot plate in centigrade
- t time in hours

Figure 2 — Example of hot plate temperature and thickness change versus time curves

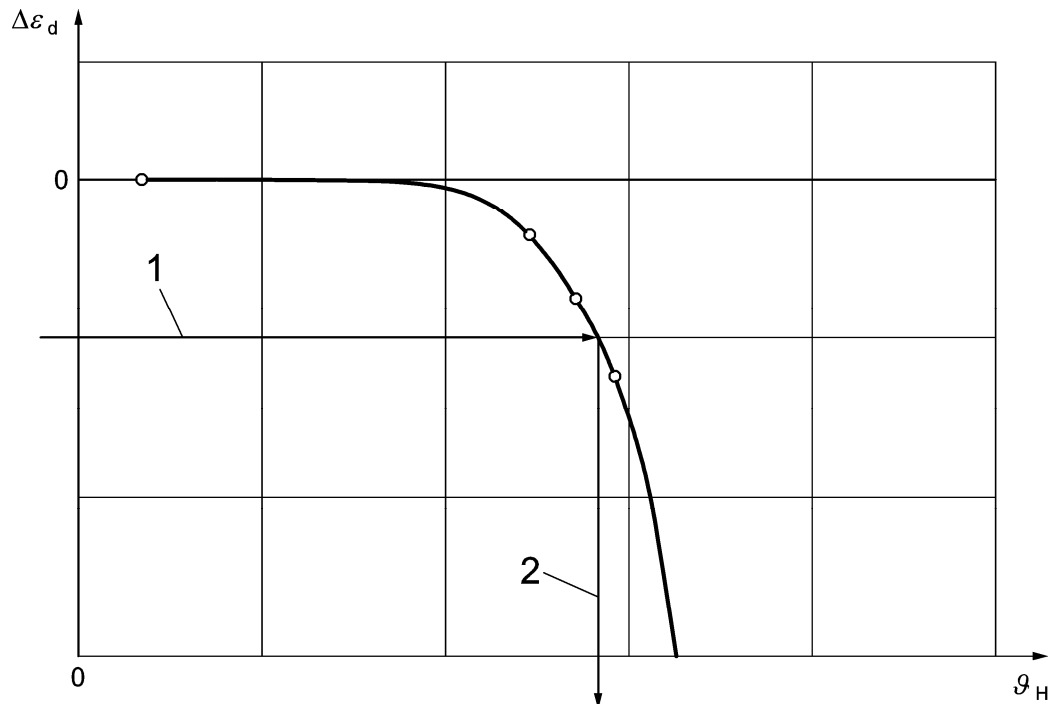

Key

- 1 maximum change of thickness of the relevant product standard in percentage
- 2 maximum service temperature in centigrade
- $\Delta\varepsilon_d$ change in thickness in percentage
- ϑ_H temperature of the hot plate in centigrade

Figure 3 — Example of determination of the maximum service temperature (after 72 h)

9 Accuracy of measurement

An interlaboratory test was performed with ten equipments from seven laboratories. Two products were tested.

The results, analysed according to ISO 5725-2:1994, are given in Table 1.

Table 1 — Relative change of thickness at a chosen temperature (equipment verification in comparative testing)

Temperature levels used °C	340 °C and 690 °C
Estimate of repeatability variance s_r 95 % repeatability limit	0,1 % 0,4 %
Estimate of reproducibility variance s_R 95 % reproducibility limit	0,3 % 0,9 %

All values given in the tables are expressed in percentage of the test specimen thickness.

The above mentioned terms are applied as described in ISO 5725-2:1994.

Bias cannot be determined in this test method as there is not any accepted reference material for it.

NOTE The choice of products was made to get a wide range of temperatures and also test a worst case situation (for the most complicated test specimen preparation see Figure A.1).

10 Test report

The test report shall include the following information:

- a) reference to this European Standard (EN 14706);
- b) product identification:
 - 1) product name, factory, manufacturer or supplier;
 - 2) production code number;
 - 3) type of product;
 - 4) packaging;
 - 5) form in which the product arrived at the laboratory;
 - 6) other information as appropriate, e.g. nominal dimensions, nominal density;
- c) test procedure:
 - 1) pre-test history and sampling, e.g. who sampled and where;
 - 2) conditioning;
 - 3) if any deviation from Clauses 6 and 7;
 - 4) date of testing;
 - 5) dimensions and number of test specimens;
 - 6) chosen temperature increase rate;
 - 7) general information relating to the test;
 - 8) events which may have affected the results;

Information about the apparatus and identity of the technician should be available in the laboratory but it need not be recorded in the report.

- d) Results:
 - 1) all individual curves deformation and temperature versus time;
 - 2) all individual values and the mean values of the dimensional changes. Note whether dimensional changes are shrinkage or expansion;
 - 3) all individual values and the mean value of the maximum service temperature;
 - 4) note the visual evaluation;
 - 5) additional results as specified in the annexes of this European Standard or the relevant product standard or any other European Technical Specification.

Annex A (normative)

Modifications of and additions to the general test method for mineral wool products

A.1 General

For mineral wool products, the test method described in this European Standard shall be modified in accordance with the following clauses.

A.2 Test specimens

A.2.1 Conditioning of test specimens

For wired mats, the wire and the stitching are removed before testing. Any existing profile on the surface of boards has to be cut off. Facings are not removed.

A.2.2 Dimensions of test specimens

Test specimens may be prepared by slicing or layering to obtain the thickness (d_0) of (100 ± 5) mm (necessary for thicknesses (d_0) other than 100 mm to obtain the thickness of 100 mm under the load specified in EN 14303). If slicing, the density of the test specimen shall be as for the unsliced test specimen.

A.3 Procedure

A.3.1 Test conditions

The test shall be started at an initial temperature of the test specimen and the hot plate between 20 °C and 50 °C. In case of dispute the test shall be started at (23 ± 5) °C.

The test load shall be 500 Pa. If necessary, the test load shall be reduced stepwise to 250 Pa or 100 Pa to ensure that the thickness (d_1) is at least 95 % of the thickness (d_0) and the load used shall be declared.

For special applications, different test loads may be agreed between parties. The thickness (d_1) is measured under the agreed load.


A.3.2 Test procedure

Measure dimensional changes in thickness only.

For wired mats, where d_1 is larger than the thickness d_0 , the test specimen shall be compressed to thickness d_0 by using the equipment shown in figure A.1. In this way, any expansion in the thickness during testing is avoided.

Heat the test specimen using a temperature rate of increase of 300 °C/h.

The thickness d_3 after cooling the test specimen down to a temperature of less than 35 °C need not be measured.

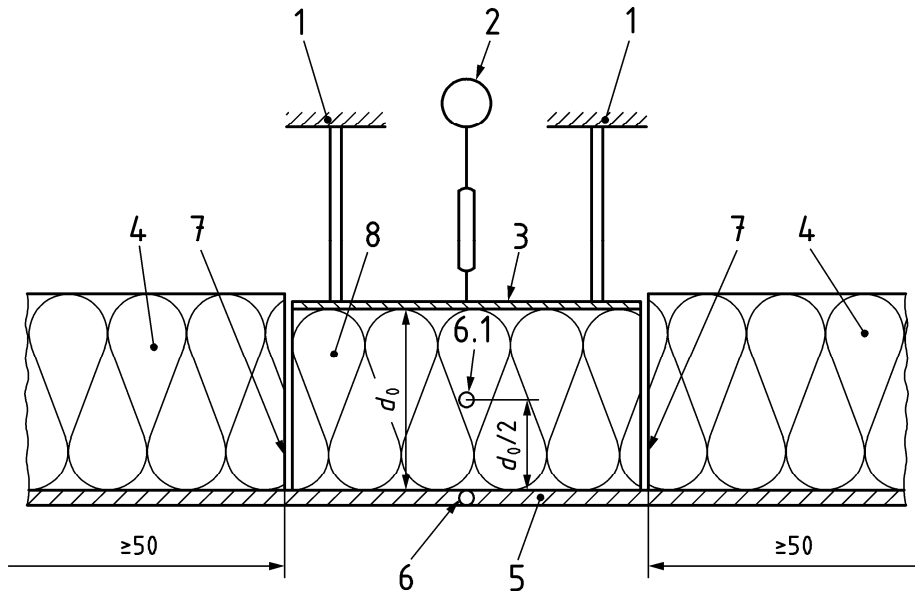

Key

- 1 height adjustable clamps to install the thickness d_0
- 2 device for measuring the thickness
- 3 pressure plate (500 Pa)
- 4 edge insulation
- 5 heated plate
- 6 thermocouple
- 6.1 additional thermocouple for testing for internal self-heating (A.5)
- 7 small gap
- 8 test specimen
- d_0 thickness of the test specimen

Figure A.1 — Example of an apparatus for determining maximum service temperature for wired mats

A.4 Additional tests and/or observations

After the measurement of d_2 and cooling down, remove the test specimen, cut the test specimen vertically through the centre and examine visually the cut edges to establish whether the fibrous structure has deteriorated. If cavities have been formed or if the test specimen has visually collapsed, this shall be reported as evidence of failure.


If failure occurs, the test shall be repeated at a lower temperature.

NOTE Any organic binder present is likely to have been removed from parts of the test specimen that have exceeded about 250 °C. This in itself does not impair the thermal performance of the product and is not a cause of failure in the test.

A.5 Test for internal self-heating

If required the test for internal self-heating has to be carried out. For that purpose, an additional thermocouple has to be installed at half the thickness of the test specimen (see Figure A.1, key symbol 6.1). The temperature $\vartheta_{1/2}$, in the middle of the thickness of the test specimen below the device for measuring the thickness, during the test of the maximum service temperature should not exceed the temperature of the heated plate ϑ_H . The appraisal of the test results is carried out according to Figure A.2, a) to c). The test has failed if $\vartheta_{1/2} > \vartheta_H$ (Figure A.2 c) extensive internal self-heating). If failure occurs, the test shall be repeated at a lower temperature.

NOTE Ideally the thermocouple should be moved to the centre along the isotherm at the 50% thickness level. If the thermocouple is placed at the 50% level directly vertically from the centre of the top of the test specimen a deviation of up to 20 °C may be found. This difference between vertically and horizontally placing is normally not critical as the aim is only to determine a possible exothermic reaction. In case of dispute, the thermocouple should be moved to the centre along the isotherm at the 50% thickness level.

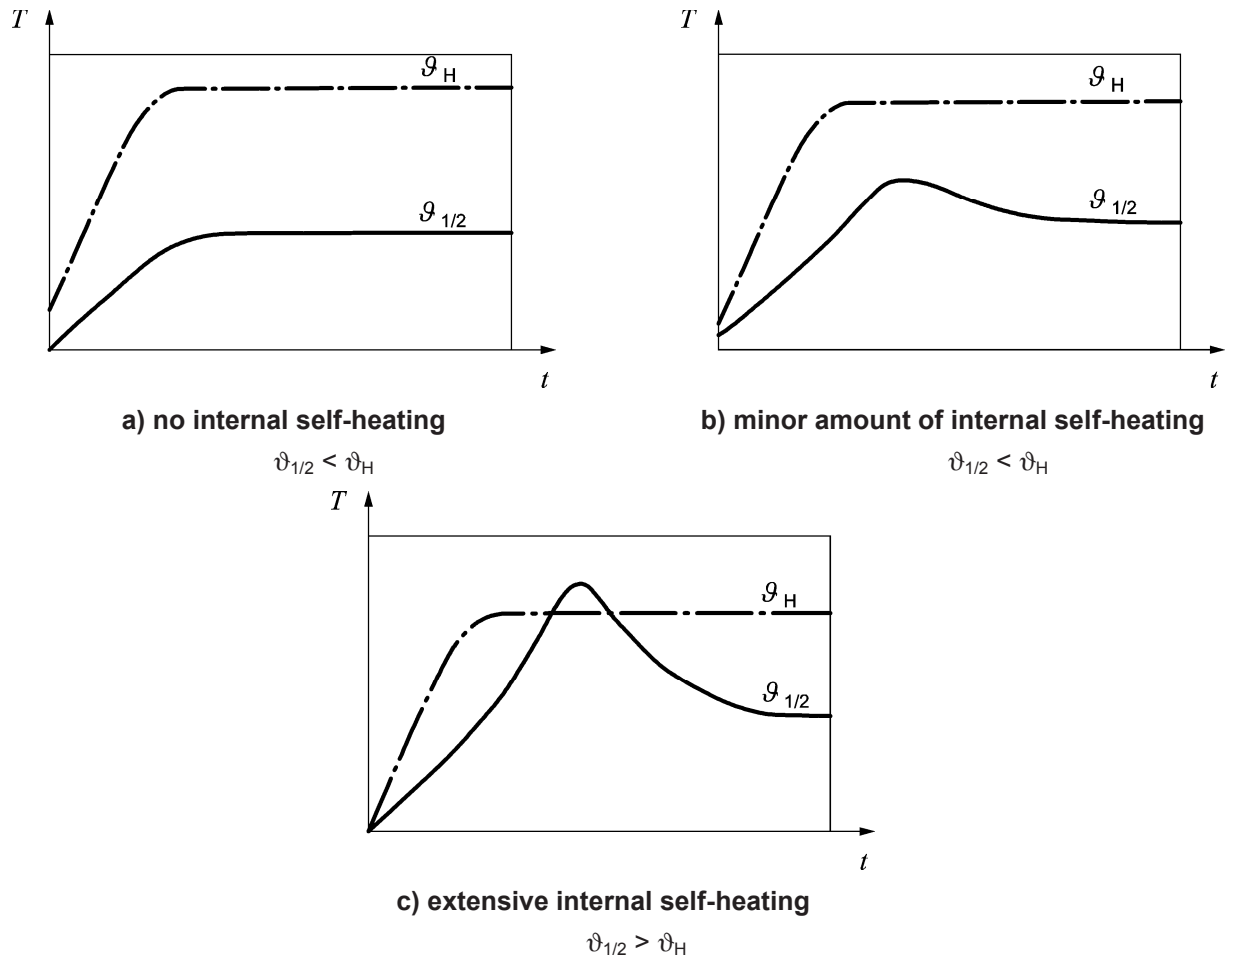

Key

T temperature in centigrade
 t time

Figure A.2 — Typical temperature profiles during the test for the internal self-heating versus time

Annex B (normative)

Modifications of and additions to the general test method for cellular glass products

B.1 General

For cellular glass products the test method described in this European Standard shall be modified in accordance with the following clauses.

B.2 Apparatus

The edge insulation shall be at least 100 mm wide.

B.3 Test specimens

B.3.1 Conditioning of test specimens

Facings are not removed.

B.3.2 Dimensions of test specimens

The test specimens shall have dimensions of 150 mm × 150 mm.

B.4 Test procedure

Heat the test specimens using a temperature rate of increase of 50 °C/h.

B.5 Additional tests and/or observations

B.5.1 Observations

After the measurement of d_2 and cooling down to a temperature lower than 35 °C, remove the test specimen and examine it visually. If cavities have been formed or if the test specimen has visually collapsed, this shall be reported as evidence of failure.

If failure occurs, the test shall be repeated at a lower temperature.

NOTE Discoloration is a normal phenomenon at temperatures in excess of 250 °C. This in itself does not impair the thermal performance of the product and is not a cause of failure in the test.

B.5.2 Additional tests

Determine the strain point of the glass in accordance with ISO 7884-1 and ISO 7884-7.

Annex C (normative)

Modifications of and additions to the general test method for phenolic foam products

C.1 General

For phenolic foam products the test method described in this European Standard shall be modified in accordance with the following clauses.

C.2 Test specimens

C.2.1 Dimensions of test specimens

The test specimens shall be square with dimensions of 100 mm × 100 mm.

C.2.2 Conditioning of test specimens

The test specimens shall be conditioned in accordance with EN 12429 at $(70 \pm 2) ^\circ\text{C}$ and then at $(23 \pm 2) ^\circ\text{C}$ and $(50 \pm 5) \%$ relative humidity prior to test.


C.3 Test procedure

During the test, the test specimens shall be heated at a temperature rate of $50 ^\circ\text{C/h}$ up to the manufacturer's claimed maximum service temperature.

C.4 Additional tests and/or observations

If required the test for internal self-heating has to be carried out. For that purpose, an additional thermocouple has to be installed at half the thickness of the test specimen (see Figure A.1, key symbol 6.1). The temperature $\vartheta_{1/2}$, in the middle of the thickness of the test specimen below the device for measuring the thickness, during the test of the maximum service temperature should not exceed the temperature of the heated plate ϑ_H . The appraisal of the test results is carried out according to Figure C.1 a) to c). The test has failed if $\vartheta_{1/2} > \vartheta_H$ (Figure C.1 c) extensive internal self-heating). If failure occurs, the test shall be repeated at a lower temperature.

NOTE Ideally the thermocouple should be moved to the centre along the isotherm at the 50% thickness level. If the thermocouple is placed at the 50% level directly vertically from the centre of the top of the test specimen a deviation of up to $20 ^\circ\text{C}$ may be found. This difference between vertically and horizontally placing is normally not critical as the aim is only to determine a possible exothermic reaction. In case of dispute the thermocouple should be moved to the centre along the isotherm at the 50% thickness level.

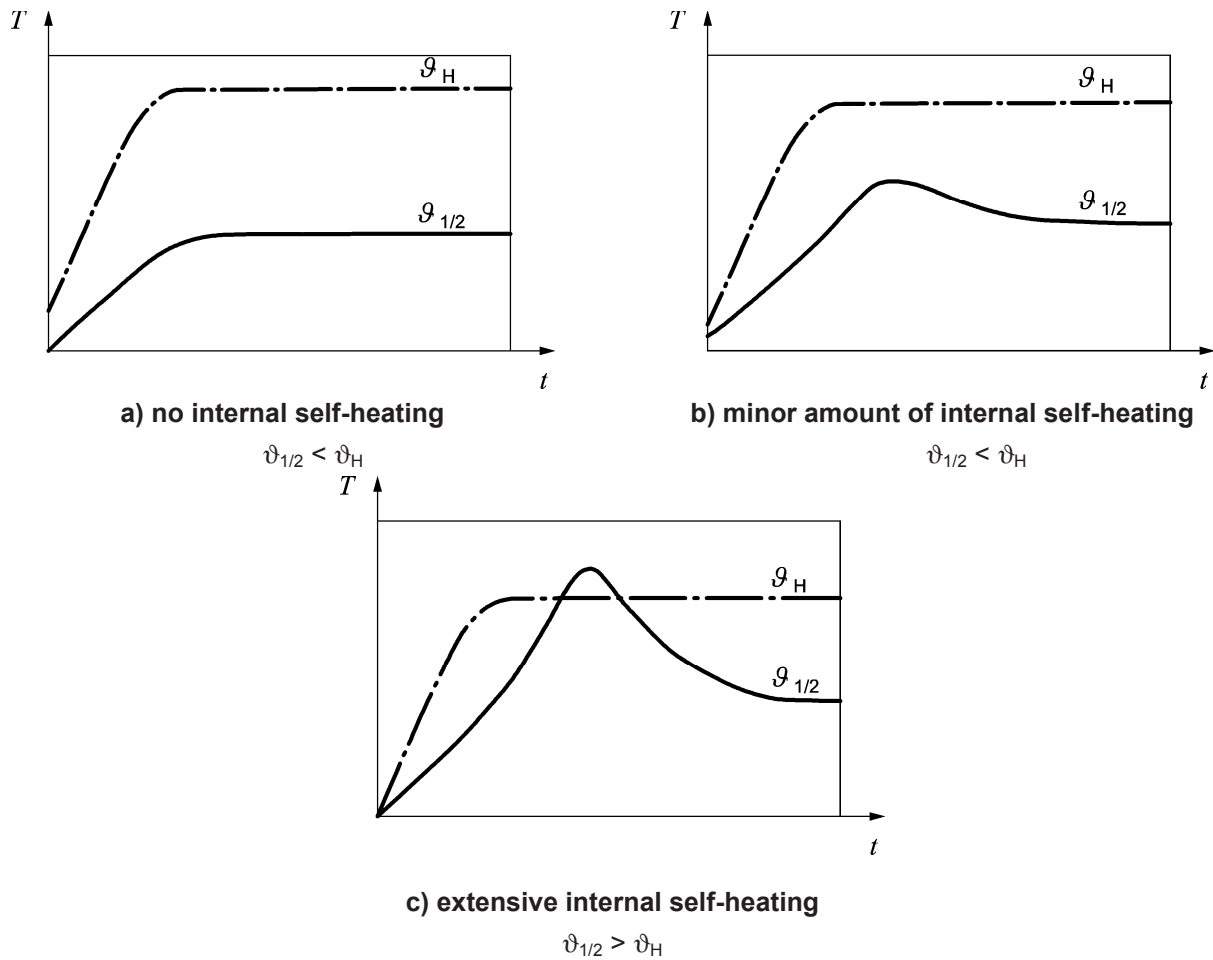

Key

T temperature in centigrade
 t time

NOTE Discoloration/change of colour does not impair the thermal performance of the product and is not a cause of failure in the test.

Figure C.1 — Typical temperature profiles during the test for the internal self-heating versus time

Annex D (normative)

Modifications of and additions to the general test method for polyethylene foam (PEF) and flexible elastomeric foam (FEF) products

D.1 General

For polyethylene foam and flexible elastomeric foam products the test method described in this European Standard shall be modified in accordance with the following clauses.

D.2 Apparatus

The edge insulation shall be at least 20 mm wide. The gap of the insulation shall be as small as possible e.g. ≤ 3 mm.

D.3 Dimensions of the test specimens

The test specimen shall be square with dimensions 100 mm \times 100 mm or alternatively 200 mm \times 200 mm.

The largest product thickness shall be tested. Multilayered products may be used for thickness up to 100 mm.

D.4 Test procedure

Measure the dimensional changes in thickness only.

The thickness shall be measured with d_0 being the initial thickness measured according to EN 823 and d_1 being the thickness taken at ambient temperature 24 h after the pressure plate has been applied to flatten the surface. d_2 is the thickness as stated in 7.2 of this European Standard. d_3 shall not be measured.

In case there is not a perfect thermal contact to the hot plate, glue the test specimen directly onto the hot plate or alternatively to a flat and stable metal plate using a suitable adhesive. Lay the test specimen on the heating plate with the metal plate face down. Make sure that the metal plate is in perfect thermal contact with the hot plate. Load the test specimen with a flat and stable metallic pressure plate exerting a load of 50 Pa for FEF and 250 Pa for PEF.


Leave the test specimen for 24 h at ambient temperature to ensure that small initial surface unevenness is flattened out. Measure d_1 .

Heat the test specimen using a temperature rate of 50 °C/h.

Maintain the temperature of the hot side, at the expected maximum service temperature, for 72 h within ± 2 % of this temperature or ± 10 °C whichever is smaller.

Record the thickness continuously during the test and at the end of the 72 h period, d_2 , to the nearest 0,1 mm (at least after 0, 0,5, 1, 6, 24, 48, 72 h).

NOTE Because of the thermal expansion of the entrapped cell gas when heating the foam from the start to the expected maximum service temperature (gas law), the thickness of the test specimen may initially increase (typical curve; see Figure D.1).

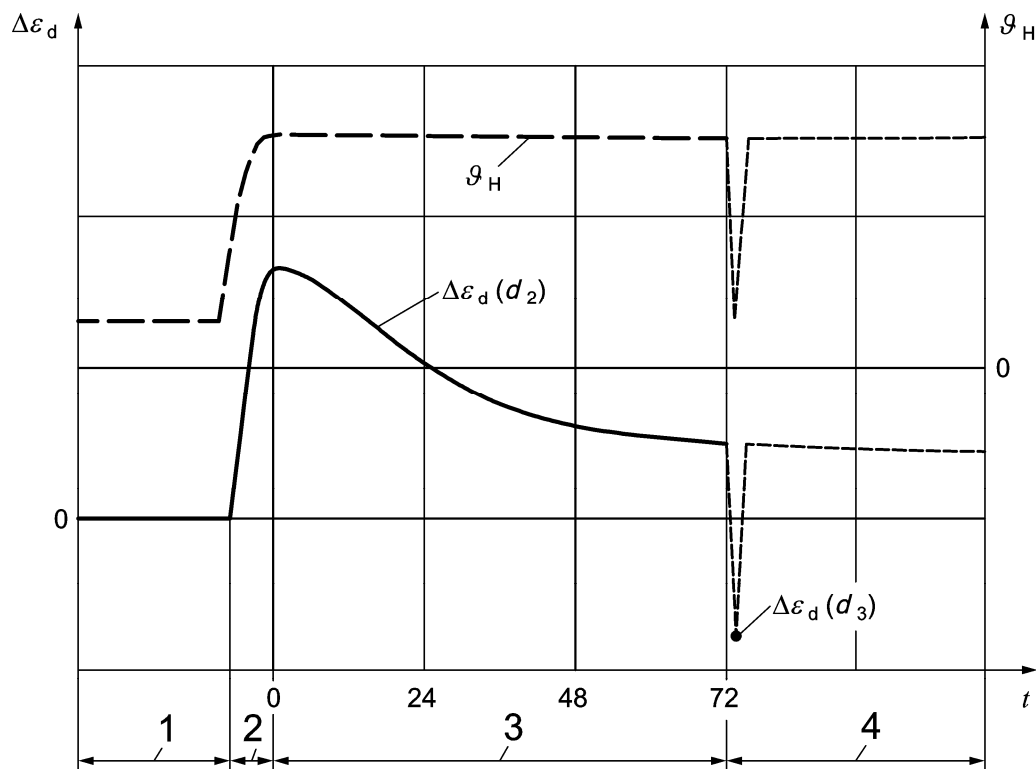

Key

- 1 ambient conditions, load installed
- 2 period of heating
- 3 period of testing
- 4 extra period of cooling down and heating up (exemplary only)

$\Delta\varepsilon_d$ change of thickness in %

ϑ_H temperature of the hot plate in °C

t time in h

Figure D.1 — Typical example of temperature and thickness deformation versus time curves

D.5 Calculation and expression of results

Calculate the dimensional changes using Formula (1) of Clause 8 of this European Standard.

NOTE The thickness d_3 at room temperature is not of interest for this kind of product because the reduction in temperature causes a reduction of the pressure inside the cells which leads to a reversible reduction in thickness. Heating up again leads to a similar thickness as before under temperature load.

Bibliography

- [1] EN ISO 9229:2007, *Thermal insulation — Vocabulary (ISO 9229:2007)*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™