

BS EN 15414-3:2011



BSI Standards Publication

# Solid recovered fuels — Determination of moisture content using the oven dry method

Part 3: Moisture in general analysis sample

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of EN 15414-3:2011. It supersedes DD CEN/TS 15414-3:2006 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PTI/17, Solid biofuels.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 68167 7

ICS 75.160.10

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2011.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

EUROPEAN STANDARD

**EN 15414-3**

NORME EUROPÉENNE

EUROPÄISCHE NORM

March 2011

ICS 75.160.10

Supersedes CEN/TS 15414-3:2006

English Version

## Solid recovered fuels - Determination of moisture content using the oven dry method - Part 3: Moisture in general analysis sample

Combustibles solides de récupération - Détermination de l'humidité par la méthode de séchage à l'étuve - Humidité de l'échantillon pour analyse générale

Feste Sekundärbrennstoffe - Bestimmung des Wassergehaltes unter Verwendung des Verfahrens der Ofentrocknung - Teil 3: Wassergehalt in gewöhnlichen Analysenproben

This European Standard was approved by CEN on 22 January 2011.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: Avenue Marnix 17, B-1000 Brussels**

## Contents

	Page
Foreword.....	3
1 Scope .....	4
2 Normative references .....	4
3 Terms and definitions .....	4
4 Principle .....	4
5 Apparatus .....	4
6 Sample preparation .....	5
7 Procedure .....	5
8 Calculation.....	5
9 Precision.....	6
10 Test report .....	6
Annex A (informative) Interlaboratory test results .....	7
Bibliography .....	10

## Foreword

This document (EN 15414-3:2011) has been prepared by Technical Committee CEN/TC 343 “Solid recovered fuels”, the secretariat of which is held by SFS.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2011, and conflicting national standards shall be withdrawn at the latest by September 2011.

This document supersedes CEN/TS 15414-3:2006.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association.

CEN/TS 15414/EN 15414 *Solid recovered fuels — Determination of moisture content using the oven dry method* consists of the following parts:

- *Part 1: Determination of total moisture by a reference method*
- *Part 2: Determination of total moisture content by a simplified method*
- *Part 3: Moisture in general analysis sample*

This document differs from CEN/TS 15414-3:2006 mainly as follows:

- a) use of automatic equipments under specific conditions permitted;
- b) specification to observe a defined repeatability limit deleted;
- c) results of interlaboratory tests supplemented as an informative Annex A;
- d) whole document editorially revised.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

## 1 Scope

This European Standard specifies a method for the determination of moisture in an analysis sample by drying the sample in an oven. This method is suitable for use for general analysis samples in accordance with CEN/TS 15414-1. It is applicable to all solid recovered fuels.

NOTE 1 The term moisture content when used with recovered materials can be misleading since solid recovered materials e.g. biomass frequently contain varying amounts of volatile compounds (extractives) which can evaporate when determining the moisture content of the general analyses sample by oven drying.

NOTE 2 This European Standard is based on EN 14774-3.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 15357:2011, *Solid recovered fuels — Terminology, definitions and descriptions*

EN 15443, *Solid recovered fuels — Methods for the preparation of the laboratory sample*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 15357:2011 apply.

## 4 Principle

The analysis sample of recovered fuel is dried at a temperature of 105 °C under air atmosphere, nitrogen atmosphere or vacuum conditions. The percentage of moisture is calculated from the loss in mass of the test sample. If the sample material is susceptible to oxidation (at 105 °C), drying in nitrogen atmosphere or vacuum conditions is performed.

## 5 Apparatus

**5.1 Drying oven**, capable of being controlled at  $(105 \pm 2)$  °C (see declaration of the manufacturer) and in which the air atmosphere changes between three and five times per hour. The air velocity shall be such that the sample particles are not dislodged from their weighing dish (5.2).

NOTE For the use of vacuum drying oven, see EN 14774-3.

**5.2 Weighing dish**, of glass or corrosion resistant and temperature resistant material, with a well-fitting lid and of such a size that the sample layer does not exceed 0,2 g/cm<sup>2</sup>.

**5.3 Balance**, with a sufficient accuracy to weigh the sample to the nearest 0,1 mg.

**5.4 Dessicator**, to avoid absorption of moisture from the atmosphere to the sample.

## 6 Sample preparation

The sample used for the determination shall be the general analysis test sample with a particle size  $\leq 1$  mm prepared in accordance with EN 15443.

Before commencing the determination, mix the analysis sample preferably by mechanical means.

## 7 Procedure

A minimum of two determinations shall be carried out on the test sample.

Dry an empty weighing dish (5.2) with its lid at  $(105 \pm 2)$  °C until constant mass is reached and allow it to cool to room temperature in the dessicator (5.4).

NOTE 1 Several weighing dishes can be handled at the same time.

Weigh the weighing dish (5.2) with its lid to the nearest 0,1 mg.

Add minimum 1 g of the analysis sample into the weighing dish (5.2) in an even layer and weigh the weighing dish with its lid plus sample to the nearest 0,1 mg.

Heat the uncovered weighing dish (5.2) and its lid together with the sample at  $(105 \pm 2)$  °C until constant mass is reached. Constancy in mass is defined as a change not exceeding 1 mg in mass during a further period of heating at  $(105 \pm 2)$  °C over a period of 60 min. If the sample material is susceptible to oxidation at the given temperature, dry in nitrogen atmosphere or under vacuum conditions (see EN 14774-3 for vacuum conditions). Report the drying atmosphere.

NOTE 2 The drying time required is usually between 2 h to 3 h.

**WARNING — For some materials present in solid recovered fuels there can be a risk of self-ignition when drying at 105 °C.**

Replace the lid while the weighing dish (5.2) is still in the drying oven (5.1). Transfer the weighing dish and its contents to the dessicator (5.4). Allow it to cool to room temperature.

Weigh the weighing dish (5.2) and its lid with the sample to the nearest 0,1 mg. Since small particle size recovered fuels are very hygroscopic, weigh rapidly once the sample is cooled.

NOTE 3 Since recovered fuels in small particle size are very hygroscopic, their moisture content will vary with change of humidity of the atmosphere and therefore, the moisture of the analyses sample should always be determined simultaneously when portions are weighed out for other analytical determinations, for example, calorific value, carbon, nitrogen.

Automatic equipments may be used if the method is validated by parallel measurements. These automatic equipments shall fulfil all the requirements regarding sample size, heating procedure, temperature, atmosphere and weighing accuracy. Deviations from this paragraph shall be reported and justified.

## 8 Calculation

For each determination, the moisture content,  $M_{ad}$ , in the analysis sample, as analysed, expressed as mass fraction in percent, shall be calculated using Equation (1):

$$M_{ad} = \frac{(m_2 - m_3)}{(m_2 - m_1)} \times 100 \quad (1)$$

where

- $m_1$  is the mass of the empty weighing dish (5.2) plus lid, in grams;
- $m_2$  is the mass of the weighing dish (5.2) plus lid plus sample before drying, in grams;
- $m_3$  is the mass of the weighing dish (5.2) plus lid plus sample after drying, in grams.

The test result for each individual determination shall be calculated on analysed basis to two decimal places and for reporting purposes, the mean value of the individual test results shall be calculated and rounded to the nearest 0,1 %.

## 9 Precision

### 9.1 Repeatability

The maximum difference to be expected between two independent single test results of one laboratory at a confidence level of 95 % will not exceed the repeatability limit in more than 5 % of cases when measuring the same measurand in the same medium, using the same facilities and fulfilling all requirements of the test method (interlaboratory testing).

Precision data derived from the interlaboratory test are given in Annex A.

### 9.2 Reproducibility

The maximum difference to be expected between two independent single test results of different laboratories at a confidence level of 95 % will not exceed the reproducibility limit in more than 5 % of cases when measuring the same measurand in the same medium, each laboratory using their own facilities and fulfilling all requirements of the test method (interlaboratory testing).

Precision data derived from the interlaboratory test are given in Annex A.

## 10 Test report

The test report shall include at least the following information:

- a) identification of the laboratory and the testing date;
- b) identification of the product or sample tested;
- c) a reference to this document, i.e. EN 15414-3;
- d) any deviation from this document;
- e) drying atmosphere used;
- f) test results on wet basis as specified in Clause 8;
- g) any unusual features observed during the test procedure which may have affected the test result.



## Annex A (informative)


### Interlaboratory test results

The statistic evaluation of the interlaboratory test results was carried out in accordance with ISO 5725-5. The precision data obtained are shown in Table A.1.


**Table A.1 — Precision data**

Designation	Shredded tyre	Demolition wood	Dried sludge	Municipal waste	Plastic/ paper fluff
Number of laboratories participated	14	14	14	14	14
Total number of values (without outliers)	50	50	50	52	50
Mean value, in % mass fraction	2,48	11,79	2,13	5,96	6,49
Laboratory effect, in % mass fraction	0,11	—	0,43	0,45	0,18
Sample effect, in % mass fraction	0,47	—	0,14	0,16	0,25
Repeatability standard deviation, $s_r$ , in % mass fraction	0,19	0,29	0,08	0,14	0,14
Repeatability limit, $r$ : ( $r = 2,8 \times s_r$ ) in % mass fraction	0,53	0,81	0,22	0,39	0,39
Reproducibility standard deviation, $s_R$ in % mass fraction	0,22	0,29	0,44	0,47	0,23
Reproducibility limit, $R$ : ( $R = 2,8 \times s_R$ ) in % mass fraction	0,62	0,81	1,23	1,32	0,64


The deviations of the test results between the individual laboratories for each sample type are shown in Figures A.1 a) to A.1 e).

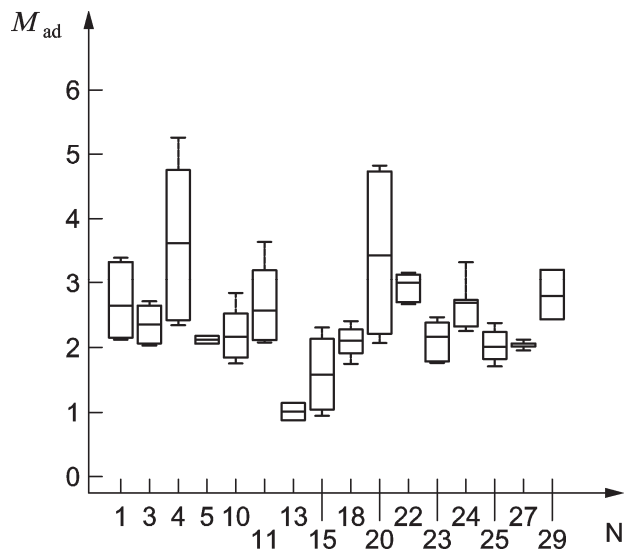


a) Shredded tyre

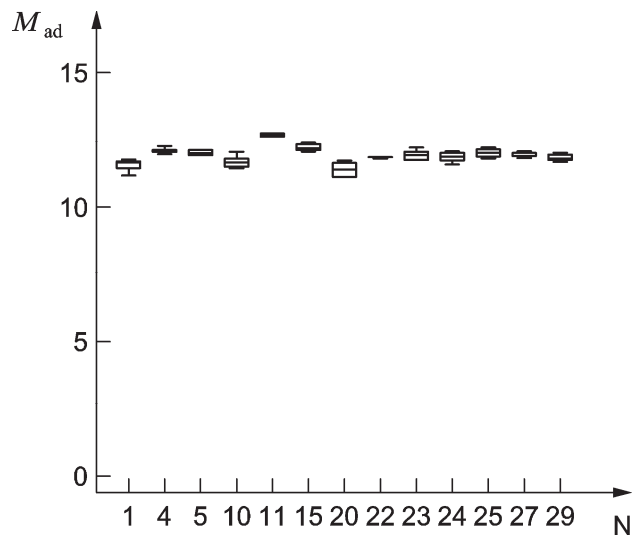


b) Demolition wood

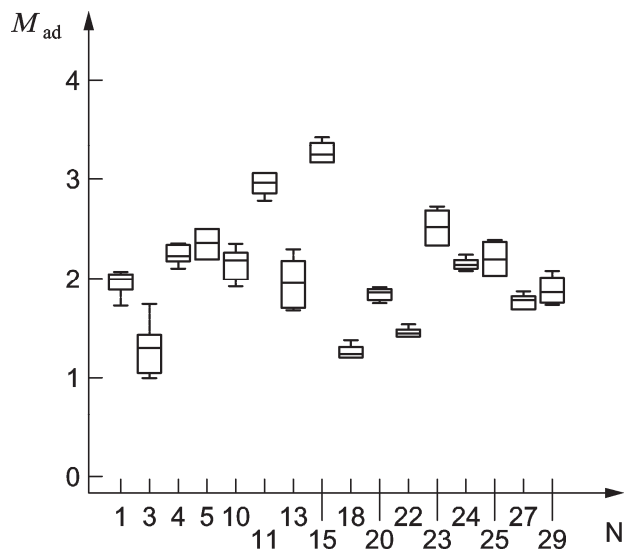

c) Dried sludge

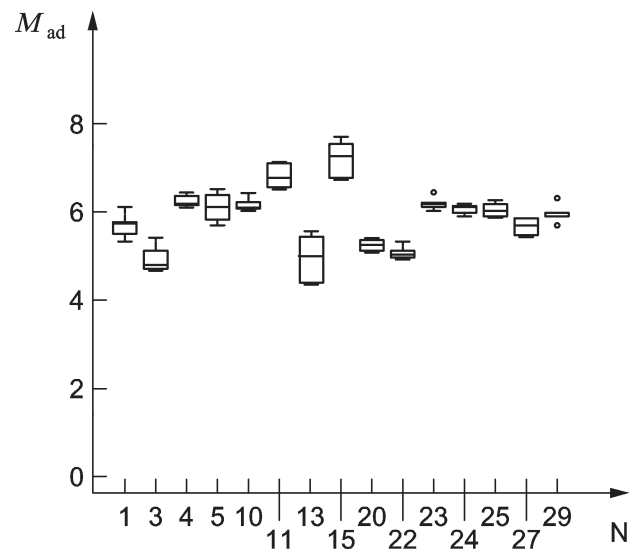

d) Municipal waste

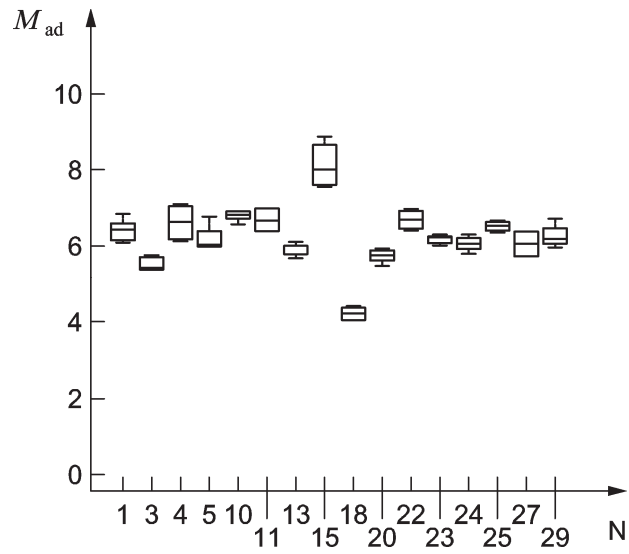

e) Plastic and paper fluffs

**Key**

$M_{ad}$  mass fraction of moisture in %  
 $N$  number of the individual laboratory

**Figure A.1 — Deviations of the test results between the individual laboratories**

## Bibliography

- [1] Horwitz, W.: *Moisture (loss of drying) in Roasted Coffee*, AOAC Official Method 979.12, Official Methods of Analysis of AOAC International 2000, 17<sup>th</sup> Edition, Volume II, ISBN: 0-935584-67-6
- [2] EN 14774-3, *Solid biofuels — Determination of moisture content — Oven dry method — Part 3: Moisture in general analysis sample*
- [3] ISO 5725-5, *Accuracy (trueness and precision) of measurement methods and results — Part 5: Alternative methods for the determination of the precision of a standard measurement method*



# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™