

BS EN 16732:2015



BSI Standards Publication

Slide fasteners (zips) — Specification

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN 16732:2015.

The UK participation in its preparation was entrusted to Technical Committee TCI/66, Apparel and interior textiles.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015. Published by BSI Standards Limited 2015

ISBN 978 0 580 82146 2

ICS 61.040

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 December 2015.

Amendments issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD

EN 16732

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 2015

ICS 61.040

English Version

Slide fasteners (zips) - Specification

Fermetures à glissière - Spécifications

Reißverschlüsse - Spezifikation

This European Standard was approved by CEN on 7 November 2015.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents

Page

European foreword.....	5
Introduction	6
1 Scope.....	7
2 Normative references.....	7
3 Terms and definitions	8
4 Requirements.....	10
5 Conditioning and testing	12
5.1 Conditioning of test samples.....	12
5.2 Slide fastener length measurement.....	12
5.3 Strength of puller attachment	12
5.4 Strength of closed-end.....	12
5.5 Strength of top stop	12
5.6 Strength of open-end slide fastener box.....	13
5.7 Resistance to reciprocation.....	13
5.8 Lateral strength of slide fastener	13
5.9 Lateral strength of open-end attachment	13
5.10 Strength of slider locking device	13
5.11 Open-end slide fastener single stringer slider retention	13
5.12 Torque strength.....	13
6 Washing and dry cleaning test	13
7 Test report.....	14
8 Marking.....	14
Annex A (informative) Guidance on factors to be taken into consideration when specifying slide fasteners	18
Annex B (normative) Test for strength of puller attachment	19
B.1 Principle	19
B.2 Apparatus.....	19
B.2.1 Constant rate of extension tensile testing machine.....	19
B.2.2 Fixture to retain the slider body rigidly	19
B.3 Procedure.....	19
Annex C (normative) Test for strength of closed-end.....	21
C.1 Principle	21
C.2 Apparatus.....	21
C.2.1 Constant rate of extension tensile testing machine.....	21
C.2.2 Clamping device.....	21
C.3 Procedure.....	22
Annex D (normative) Test for strength of top stop.....	23

D.1	Principle.....	23
D.2	Apparatus	23
D.3	Procedure.....	24
Annex E (normative) Test for strength of open-end slide fastener box.....		25
E.1	Principle.....	25
E.2	Apparatus	25
E.2.1	Constant rate of extension tensile testing machine	25
E.2.2	Slotted plate.....	25
E.3	Procedure	26
Annex F (normative) Test for resistance to reciprocation		27
F.1	Principle.....	27
F.2	Apparatus	27
F.3	Procedure.....	28
F.3.1	Preparation of the specimens	28
F.3.2	Method.....	29
Annex G (normative) Test for lateral strength of slide fastener.....		31
G.1	Principle.....	31
G.2	Apparatus	31
G.2.1	Constant rate of extension tensile testing machine	31
G.2.2	Jaws.....	31
G.3	Procedure	31
Annex H (normative) Test for lateral strength of open-end attachment.....		32
H.1	Principle.....	32
H.2	Apparatus	32
H.2.1	Constant rate of extension tensile testing machine	32
H.2.2	Jaws.....	32
H.3	Procedure.....	32
Annex I (normative) Test for strength of slider locking device		33
I.1	Principle.....	33
I.2	Apparatus	33
I.2.1	Constant rate of extension tensile testing machine	33
I.2.2	Jaws.....	33
I.3	Procedure.....	33
Annex J (normative) Test for open-end slide fastener single stringer slider retention		34
J.1	Principle.....	34
J.2	Apparatus	34

J.2.1	Constant rate of tension tensile testing machine	34
J.2.2	Jaws	34
J.3	Procedure.....	34
Annex K (normative) Torque test.....		35
K.1	Principle	35
K.2	Apparatus.....	35
K.3	Procedure.....	36
K.3.1	Preparation of the specimens.....	36
K.3.2	Method	36
K.4	Test to failure method for quality control	36
Annex L (informative) Sampling procedures for bulk quantities of slide fasteners.....		38
L.1	General.....	38
L.2	Guidance on interpretation of results for acceptance purposes	38
L.3	Guide to changing from normal to tightened test procedures.....	38
Annex M (informative) End-uses and recommended performance codes for labelling purposes		39
Bibliography.....		40

European foreword

This document (EN 16732:2015) has been prepared by Technical Committee CEN/TC 248 "Textiles and textile products", the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2016, and conflicting national standards shall be withdrawn at the latest by June 2016.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

According to the CEN/CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Introduction

The different types of slide fasteners are defined by the material of the elements (teeth), which form their slide fastener chains. They can be of metallic, moulded plastic or monofilament plastic construction.

Metallic elements can be produced from flat or profiled wire and are usually clamped around the edge of a beaded tape. An alternative approach is to cast metallic elements directly onto such a tape. Similarly, plastic elements can be moulded onto a beaded tape. Such cast or moulded elements might have projections on which the slider operates to reduce abrasion of the tape.

Plastic coil slide fasteners have polyamide or polyester monofilaments that are wound into coils to form engaging elements. The coils can be attached to the face of flat tapes by sewing. Alternatively, the coils can be woven or knitted into the tapes as they are constructed. Monofilament plastic elements can also be of the meander type, which straddle the tape edge.

Typical slide fastener chain types are shown in Figure 1.

1 Scope

This European Standard specifies performance levels and test methods for the following characteristics of slide fasteners made from interlocking components mounted on tapes: strengths of puller attachment, closed-end, top stop, open-end slide fastener box, reciprocating mechanism, closed slide fastener when extended laterally, open-end attachment when extended laterally, slider locking device, and open-end slide fastener single stringer slider retention and slider resistance to torque.

NOTE The tests specified in Annexes B to K have been specifically devised to permit their direct application to finished slide fasteners with a view to giving the user reasonable assurance that a slide fastener conforming to the requirements of this standard can satisfactorily fulfil its intended purpose. Annex L gives information about sampling procedures for bulk quantities of slide fasteners.

In addition, performance levels are also specified for colour fastness to washing, dry cleaning and water, and for dimensional stability to washing and dry cleaning.

This European Standard is applicable to slide fasteners for general use and is not applicable to slide fasteners for specialist purposes (for example: pressure sealed slide fasteners for diving suits).

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 20105-A02, *Textiles - Tests for colour fastness - Part A02: Grey scale for assessing change in colour (ISO 105-A02)*

EN 20105-A03, *Textiles - Tests for colour fastness - Part A03: Grey scale for assessing staining (ISO 105-A03)*

EN ISO 105-C06, *Textiles - Tests for colour fastness - Part C06: Colour fastness to domestic and commercial laundering (ISO 105-C06)*

EN ISO 105-D01, *Textiles - Tests for colour fastness - Part D01: Colour fastness to dry cleaning using perchloroethylene solvent (ISO 105-D01)*

EN ISO 105-E01, *Textiles - Tests for colour fastness - Part E01: Colour fastness to water (ISO 105-E01)*

EN ISO 139, *Textiles - Standard atmospheres for conditioning and testing (ISO 139)*

EN ISO 3175-2, *Textiles - Professional care, drycleaning and wetcleaning of fabrics and garments - Part 2: Procedure for testing performance when cleaning and finishing using tetrachloroethene (ISO 3175-2)*

EN ISO 5077, *Textiles - Determination of dimensional change in washing and drying (ISO 5077)*

EN ISO 6330, *Textiles - Domestic washing and drying procedures for textile testing (ISO 6330)*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 **slide fastener (zip)**

fastening device consisting of two flexible, interlocking stringers, with or without end stops, and one or more sliders so arranged that by moving the slider along the stringers in one direction an opening is formed, and by moving it in the other direction the opening is closed

3.2 **stringer**

tape with an attached row of elements designed to interlock with a row similarly attached to another tape

3.3 **tape**

narrow fabric to which elements are fitted

3.4 **element (tooth)**

engaging component fixed to the edge of the tape (see Figure 2)

3.5 **slider**

moving component consisting essentially of a slider body and, normally, a puller which opens or closes the slide fastener by separating or engaging the single elements of the stringer

Note 1 to entry: The slider might incorporate a locking device. Alternative slider types are available with a flip-over puller or double pullers, to facilitate operation from both front and back sides.

3.6 **slider body**

component that joins or separates the elements when sliding along the two stringers of slide fastener

3.7 **puller**

fitting attached to the slider body to facilitate manipulation

3.8 **locking device**

device incorporated in the slider unit restricting its free movement along the slide fastener length in an opening direction

Note 1 to entry: The locking device might operate either automatically on release of the puller or by manual pressure on the puller.

3.9 **slide fastener length**

distance from the top of the slider to the bottom of the bottom stop, or box in the case of an open-end slide fastener, measured with the slider in the top position and with the puller in the downward position (see Figure 2)

Note 1 to entry: Some suppliers measure the effective length of slide fasteners from the top of the slider to the bottom edge of the tape, especially in the case of two way open-end slide fasteners.

3.10

bottom stop

stop at the bottom end of the chain that checks the opening movement of the slider

Note 1 to entry: See Figure 2a), (Key n. 5).

3.11

top stop

stop(s) at the top end of the chain that check(s) the closing movement of the slider

3.12

chain

continuous closure formed by two interlocking compatible stringers

Note 1 to entry: See Figure 2a), (Key n.8).

3.13

chain width

width across the interlocked elements or shoulder on which the slider runs, whichever is the greater

Note 1 to entry: See Figure 2b), (Key n.6).

3.14

bottom end

end which is adjacent to the slider when the device is fully open

3.15

top end

end which is adjacent to the slider when the device is fully closed

3.16

open-end slide fastener

slide fastener having a special fitment at the bottom end of each stringer in place of the bottom stop, so as to permit the two stringers to be completely separated and re-assembled at will when the slider is in the fully open position

Note 1 to entry: The special fitment normally consists of a pin permanently fixed to the bottom end of one stringer, which fits into a box permanently fixed to the bottom end of the other stringer.

Note 2 to entry: See Figure 3c) and 4a).

3.17

closed-end slide fastener

slide fastener which does not permit the complete separation of the two stringers

Note 1 to entry: Normally the top end of the slide fastener separates as the slider is lowered, although there is one type whose top ends are permanently joined together by means of a bridge stop [see Figure 3a) and Figure 3b), 4b), 4c), 4d)].

3.18

concealed slide fastener

slide fastener with the tapes folded so that on closure neither the slider body nor the slide fastener are visible from the outside of the article

Note 1 to entry: See Figure 1g).

3.19

two-way slide fastener

slide fastener fitted with two sliders that operate with equal facility in either direction

Note 1 to entry: This type is available in a variety of forms, as illustrated in Figure 4.

3.20

batch

quantity of slide fasteners having a specific design, performance code and chain size

4 Requirements

When subjected to the tests specified in Clause 5 (as applicable to the features of the slide fastener design to be tested), other than the slide fastener length measurements (see 5.2), samples of new slide fasteners shall conform to Table 1 and to Table 2 if applicable (children items).

The overall performance for the slide fastener, as determined by the minimum test results, shall be that of the lowest performance grade achieved by any test specimen for any applicable test.

Attention shall be given to the use of the sampling procedures given in Annex L with regard to the interpretation of potential outlier results.

It is permissible to perform more than one test on the same slide fastener but care should be taken to ensure that damage sustained in testing does not compromise subsequent test results.

A minimum of 3 specimens shall be tested in respect of each applicable test. Failure of any part of a slide fastener before the specified force or number of cycles is reached in any of these tests shall be deemed a failure of the sample. For the acceptance criteria for larger batches the sampling scheme in Annex L shall be used and the number of specimens for each test increased accordingly.

Annex L gives information about an appropriate sampling procedure for bulk quantities of slide fasteners.

Annex M gives information about end-use and performance codes.

Table 1 — Performance requirements of slide fasteners according to end use

Annex	Test description	Units	Performance code ^a				
			A	B	C	D	E
B	Strength of puller attachment (min.)	N	70	80	200	250	300
C	Strength of closed-end (min.)	N	35	60	80	100	140
D	Strength of top stop (min.)	N	50	70	90	110	130
E	Strength of open-end slide fastener box (min.)	N	40	70	90	120	150
F	Resistance to reciprocation: Minimum cycles without failure	Cycles	500	500	500	500	500
G	Lateral strength of slide fastener (min.)	N	150	200	250	370	470
H	Lateral strength of open-end attachment (min.)	N	40	70	90	120	160
I	Strength of slider locking device (min.)	N	10	15	25	40	60

^a These performance codes correspond to the description of slide fastener type as follows: A (ultra-light), B (light), C (medium), D (medium-heavy) and E (heavy).

Table 2 — Additional performance requirements of slide fasteners for children's items

Annex	Test description	Units	Minimum requirement
J	Open-end slide fastener single stringer slider retention	N	70
K	Torque strength	N.m	0,34

In addition, to the requirements of Table 1 and Table 2, slide fasteners shall conform to the colour fastness and dimensional stability requirements of Table 3.

Table 3 — Colour fastness and dimensional stability requirements of slide fasteners

Property	Method of test	Performance level ^d
Colour fastness ^a minimum rating to:		
dry cleaning	EN ISO 105-D01	Change in colour and staining 3-4
washing	EN ISO 105-C06, Method A2S	Change in colour and staining 3-4
water	EN ISO 105-E01	Change in colour and staining 3-4
Maximum dimensional change on:		
washing	EN ISO 5077 ^{b, c}	-4 % of original length
dry cleaning	EN ISO 3175-2 ^c	-3 % of original length
^a Colour change and staining measured using the Grey scale according to EN 20105-A02 and EN 20105-A03. ^b Using washing procedure 4N and tumble drying procedure F at a temperature not exceeding 80 °C as described in EN ISO 6330. ^c Except that the change in slide fastener length only, as defined in 3.9, shall be determined. ^d In some cases performance levels can be lower due to technical reasons (e.g.: denim, pigment prints, fluorescent colours, etc.). In other cases they can be higher (e.g.: contrast colour) Variation of the performance levels shall be agreed between the parties		

NOTE Guidance on the factors to be considered when specifying slide fasteners is given in Annex A.

5 Conditioning and testing

5.1 Conditioning of test samples

Prior to being subjected to the tests specified in 5.2 to 5.11, sample slide fasteners shall first be conditioned for minimum of 16 h and then tested in the reference standard atmosphere for testing textiles as defined in EN ISO 139 [i.e. a temperature of (20 ± 2) °C and a relative humidity of (65 ± 4) %].

5.2 Slide fastener length measurement

The length tolerance for slide fasteners compared with the nominal length shall be $\pm 1,5$ % or ± 5 mm (whichever is the greater), unless otherwise specified between parties. The slide-fastener length shall be measured on a smooth flat surface using a one-millimetre graduated ruler.

5.3 Strength of puller attachment

When tested in accordance with Annex B, slide fasteners shall conform to the performance code specified in Table 1.

5.4 Strength of closed-end

When tested in accordance with Annex C, closed-end slide fasteners shall conform to the performance code specified in Table 1.

5.5 Strength of top stop

When tested in accordance with Annex D, slide fasteners shall conform to the performance code specified in Table 1.

5.6 Strength of open-end slide fastener box

When tested in accordance with Annex E, slide fasteners shall conform to the performance code as specified in Table 1. This method may also be applied to test the retention of the lower slider on two-way slide fasteners.

5.7 Resistance to reciprocation

When tested in accordance with Annex F, a slide fastener 200 mm or longer shall complete 500 cycles without failure.

If a slide fastener is less than 200 mm long then it is permissible to attach extension stringers by suitable means to the top and/or bottom of the existing stringers such that the slide fastener can be mounted on the apparatus described in Annex F and tested. The means of attachment of the extension stringers is not critical but shall be of sufficient strength as to withstand the forces applied during the test. Where the length of the interlocking elements of the slide fastener is insufficient to permit reciprocation to be performed, then it is permissible to test a nominally identical slide fastener with a longer length of interlocking elements.

5.8 Lateral strength of slide fastener

When tested in accordance with Annex G, slide fasteners shall conform to the performance code specified in Table 1.

5.9 Lateral strength of open-end attachment

When tested in accordance with Annex H, slide fasteners shall conform to the performance code specified in Table 1.

5.10 Strength of slider locking device

When tested in accordance with Annex I, a slider fitted with a locking device shall withstand the lateral force specified in Table 1 when the lock is engaged and the stringers are pulled at right angles to the length of the slide fastener.

5.11 Open-end slide fastener single stringer slider retention

When testing in accordance with Annex J, slide fasteners shall conform to the performance requirement specified in Table 2.

5.12 Torque strength

When testing in accordance with Annex K, slide fasteners shall conform to the minimum requirement as specified in Table 2.

6 Washing and dry cleaning test

If particular post-washing/dry cleaning performance levels are specified in the care information for the slide fasteners or for the article in which the slide fastener is intended to be used, the samples shall be tested in accordance with Clause 5 after subjecting samples to the specified cleansing procedures. If no cleansing procedures are specified but it is desired to determine the performance of the fastener after laundering then the samples shall be subjected to one or both of the default cleansing regimes detailed below. For fasteners which can be both washed and dry cleaned, separate sets of samples shall be tested after washing and after dry cleaning.

- a) One wash and dry in accordance with, respectively, procedure 4 N and tumble drying procedure F specified in EN ISO 6330.

b) One dry cleaning cycle in accordance with EN ISO 3175-2.

NOTE After dry cleaning the application of a suitable lubricant prior to reciprocation is acceptable.

7 Test report


The test report shall include the following information:

- a) a reference to this European Standard (i.e. EN 16732);
- b) identification of slide fasteners tested and declared performance code, if known;
- c) where known, information on the intended end-use;
- d) date of the tests;
- e) final performance code based on test results;
- f) a description of any deviation from the test methods specified in this standard;
- g) the numerical result obtained for each test; and
- h) a description of any washing or dry cleaning procedures performed and any observed effects of these procedures.



8 Marking

The following information shall be indicated on the package, the swing ticket or any associated commercial documents:


- a) the name of the manufacturer;
- b) number and date of this standard and the performance code of the slide fastener, as given in Table 1;
- c) details of slide fastener type, length, colour, chain and tape width, element material and,
- d) any special characteristics or manufacturer's identification which defines these details.

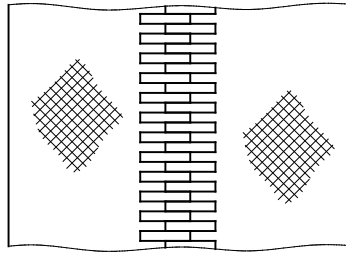


a) Metal elements

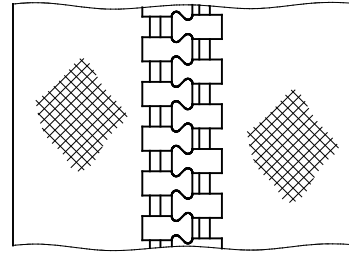


b) Diecast or plastics moulded elements

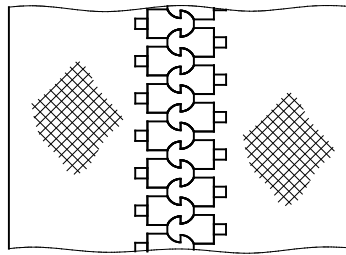


c) Diecast or moulded winged elements

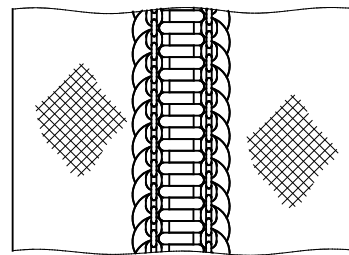


d) Offset coil elements

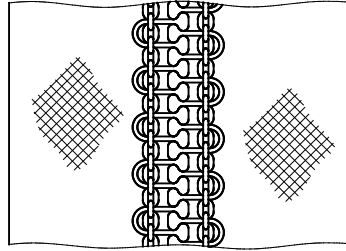

e) Meander or ladder elements

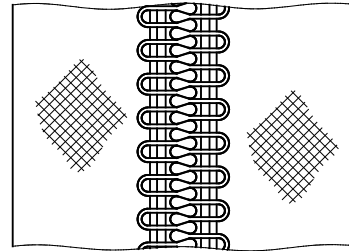


f) Woven-in coil elements

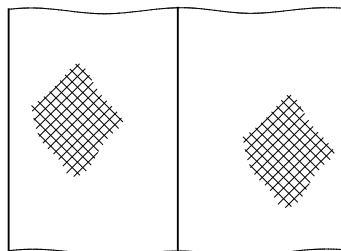

g) Concealed slide fastener

Figure 1 — Slide fastener chain types

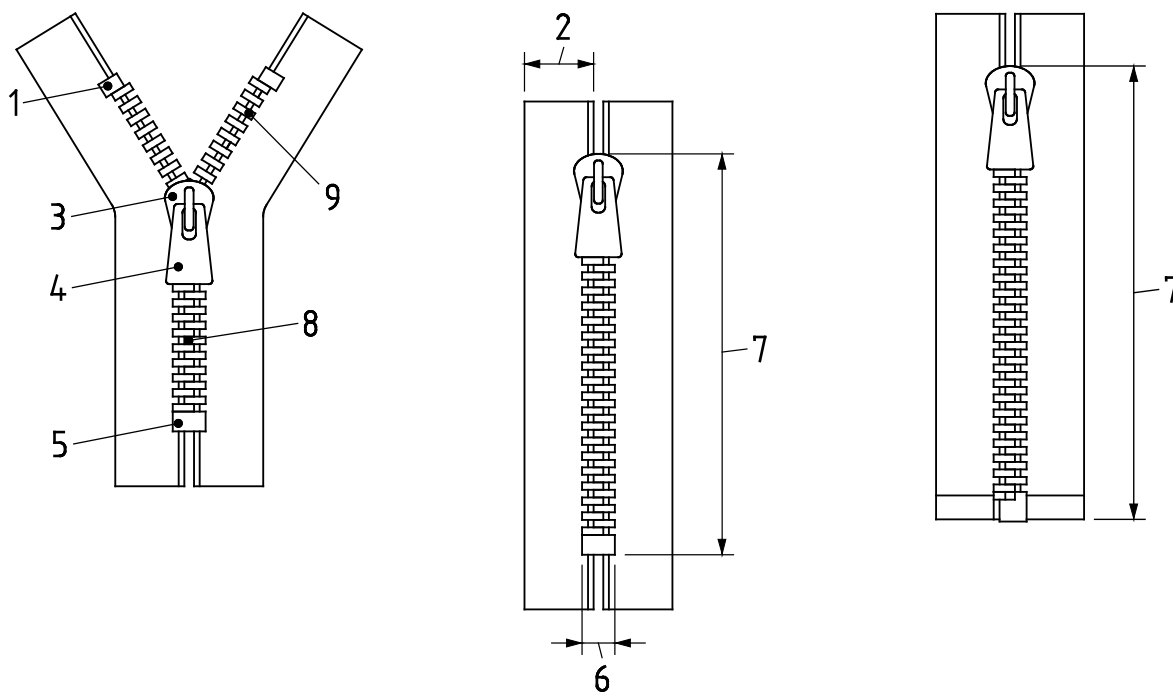

- Key**
- 1 top stop
 - 2 tape width
 - 3 slider
 - 4 puller
 - 5 bottom stop
 - 6 chain width
 - 7 length of slide fastener
 - 8 chain
 - 9 elements (teeth)
- a) Basic components dimensions b) Closed-end slide fastener dimensions c) open-end slide fastener dimensions

Figure 2 — Slide fasteners: basic components dimensions

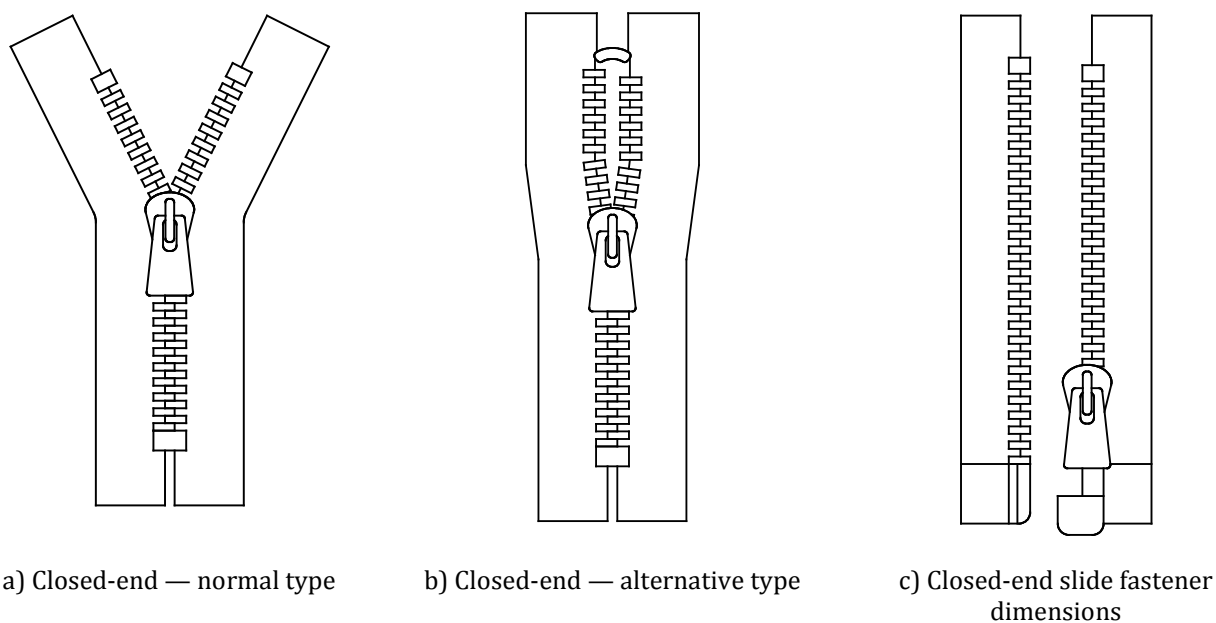


Figure 3 — One-way slide fasteners

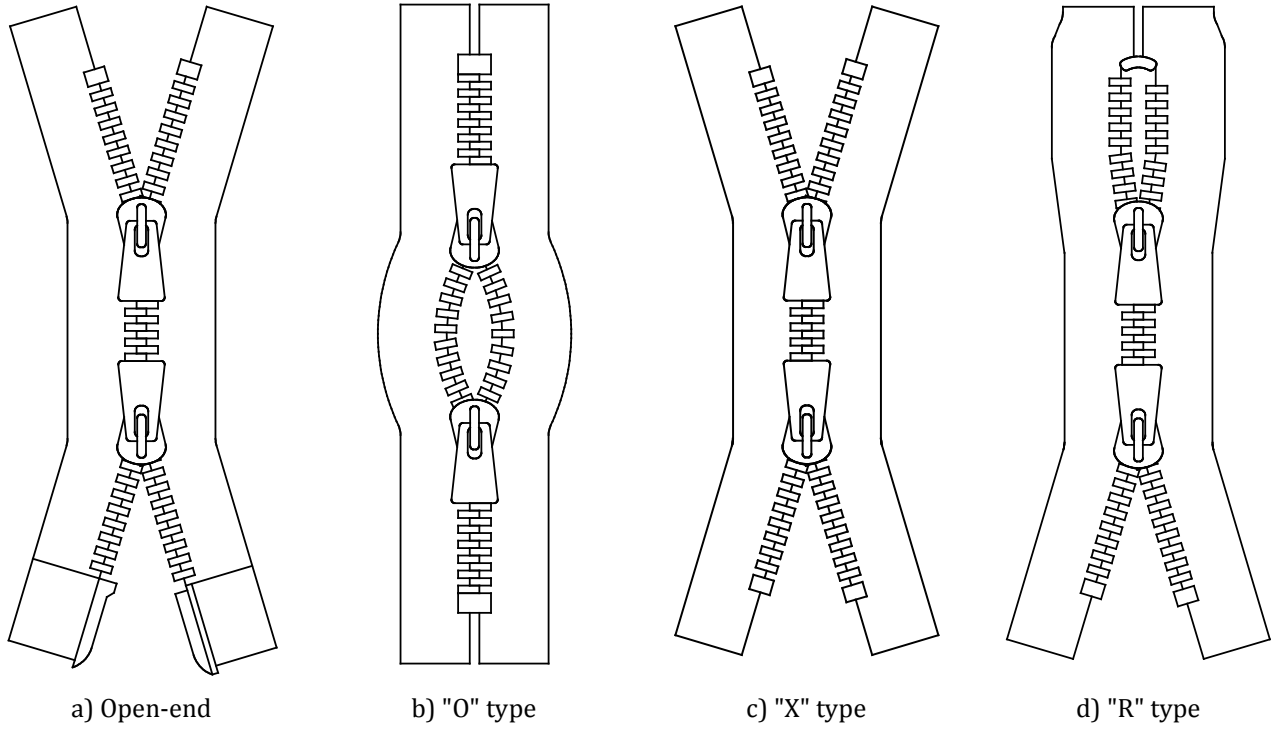


Figure 4 — Two-way slide fasteners

Annex A (informative)

Guidance on factors to be taken into consideration when specifying slide fasteners

The following information should be included in the slide fastener specifications:

- a) the type of slide fastener (e.g. closed end, open end, left-handed, right-handed, etc.);
- b) the fabric construction used in the tape;
- c) the type and material of the elements;
- d) the slide fastener length;
- e) the chain width;
- f) the tape width, as shown in Figure 2a) Key 2;
- g) the slider type;
- h) the performance code of the slide fastener;
- i) any other special features of the slide fastener;
- j) any end-product related characteristics which might affect the recommendation of minimum performance code.

Annex B (normative)

Test for strength of puller attachment

B.1 Principle

The puller is subjected to tension whilst the slider is rigidly supported.

B.2 Apparatus

B.2.1 Constant rate of extension tensile testing machine


Constant rate of extension tensile testing machine conforms to EN ISO 7500-1 and produces a rate of jaw separation of (100 ± 10) mm/min. The force range is such that the breaking strength of the test specimen falls between 10 % and 90 % of the maximum on the scale.

B.2.2 Fixture to retain the slider body rigidly

Fixture to retain the slider body rigidly, such as a face-plate or a blanking-off plate, to allow the tension to be applied to the puller and its attachment to the slider body (see example in Figure B.1).

B.3 Procedure

Mount the test specimen in one jaw of the tensile testing machine, with the puller passed through a hole in the fixture. Arrange the fixture so that the slider and the chain are rigidly clamped in place, with only the puller and its attachment to the slider being free. Secure the end of the puller to the other jaw so that tension is applied perpendicular to the face of the slider. Set the testing machine in operation until either the specified force is reached or the specimen fails.

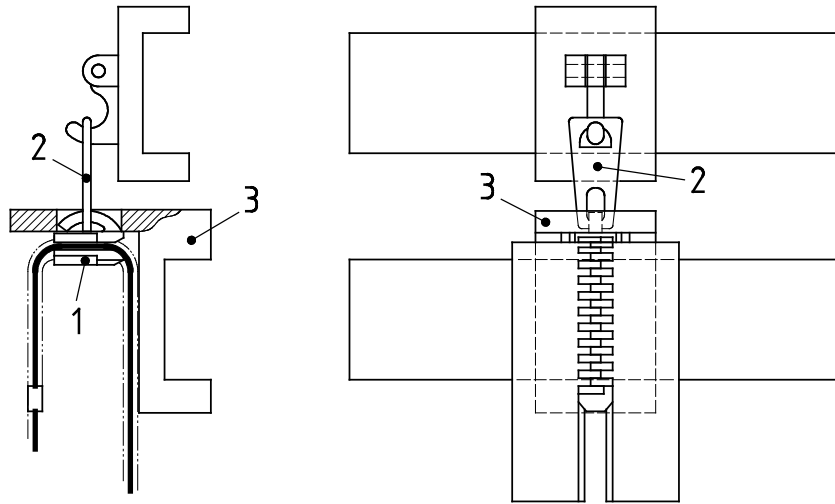

Key

- 1 slider body
- 2 puller
- 3 fixture

Figure B.1 — Example of puller attachment test

Annex C (normative)

Test for strength of closed-end

C.1 Principle

The bottom stop is subjected to a force via the slider by tension applied to the stringers.

C.2 Apparatus

C.2.1 Constant rate of extension tensile testing machine

See Annex B.


C.2.2 Clamping device

The clamping devices of the machine shall be positioned with the central point of the two jaws in the line of applied force, the front edges shall be at right angles to the line of applied force and their clamping faces shall be in the same plane.

The jaws shall be capable of holding the test specimen without allowing it to slip and designed so that they do not cut or otherwise weaken the test specimen.

The faces of the jaws shall be smooth and flat, except that when, even with packing, the test specimen cannot be held satisfactorily with flat-faced jaws, engraved or corrugated jaws can be used to prevent slippage.

The width of the jaws shall be (25 ± 1) mm (see Figure C.1).

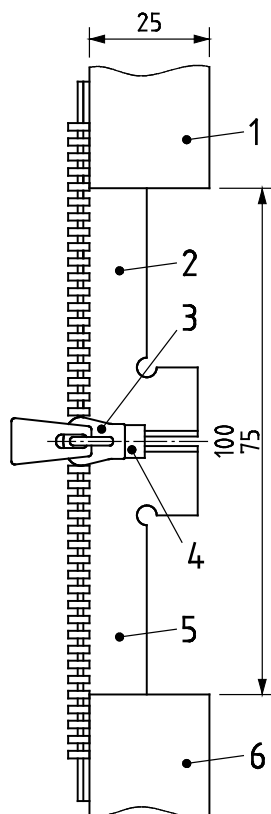

Key

- 1 upper clamp
- 2 stringer
- 3 slider body
- 4 bottom stop
- 5 stringer
- 6 lower clamp (jaw)

Figure C.1 — Closed-end test

C.3 Procedure

With the test specimen in its open position and the slider adjacent to the bottom stop, clamp one stringer in each of the two jaws approximately between 75 mm and 100 mm between the jaws. (This might be better achieved by cutting away the surplus stringer). Ensure that the locking mechanism is inoperative. Apply a longitudinal force to the stringers thus forcing the slider against the bottom stop. Set the machine in operation until either the specified force is reached or the specimen fails.

Instances of failure include slipping of the bottom stop and removal of adjacent elements.

Annex D (normative)

Test for strength of top stop


D.1 Principle

The top stop is subjected to a force via the slider applied through the puller.

D.2 Apparatus

Constant rate of extension tensile testing machine, as described in Annex B.

Dimensions in millimetres

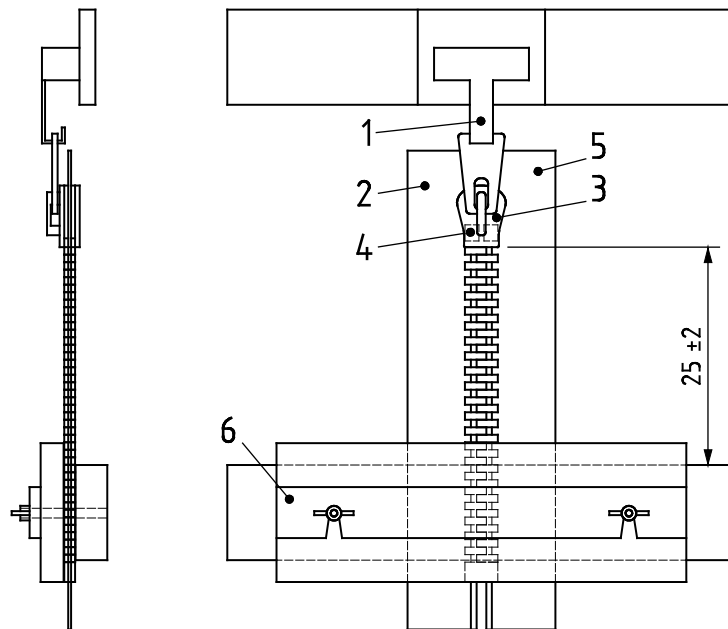

Key

- 1 puller
- 2 stringer
- 3 slider body
- 4 top stop
- 5 stringer
- 6 lower clamp (jaw)

Figure D.1 — Example of top stop test

D.3 Procedure

With the slide fastener in the closed position and the slider adjacent to the top stop, secure the puller in the moving jaw of the machine and secure the closed slide fastener stringers in the fixed clamp of the machine such that the length of closed slide fastener between the top of the fixed jaw and the bottom of the slider is set to (25 ± 2) mm (see Figure D.1). Set the machine in operation until the specified force is reached or until the specimen fails.

NOTE Instances of failure include slipping of the top stops, the slider riding over the top stops and the slider coming apart.

Annex E (normative)

Test for strength of open-end slide fastener box

E.1 Principle

The box (see note 3.16), is subjected to longitudinal force whilst the slide fastener chain is in the closed position.

E.2 Apparatus


E.2.1 Constant rate of extension tensile testing machine

See Annex B.

E.2.2 Slotted plate

Slotted plate, shaped to clear the tape, chain and pin and to bear against the whole of the top edges of the box. In the case of a non-grippable box the use of an alternative slotted plate shall be reported (see Figure E.1).

Dimensions in millimetres

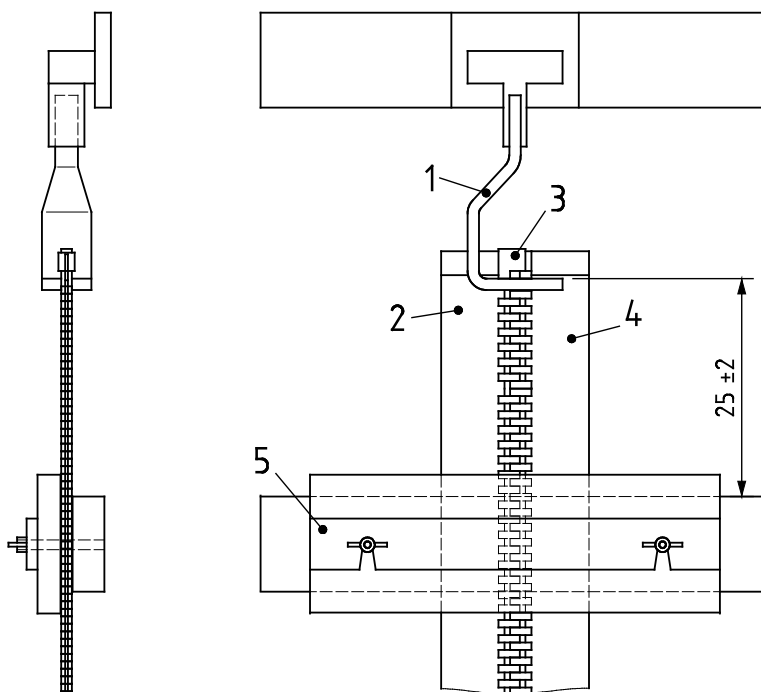

Key

- 1 upper clamp with slotted plate
- 2 stringer
- 3 open end box
- 4 stringer
- 5 lower clamp

Figure E.1 — Open-end slide fastener box test

E.3 Procedure

With the test specimen in the closed position, clamp the whole slotted plate into the moveable jaw of the apparatus and insert the slide fastener such that the open-end slide fastener box is gripped in the slotted plate. For two-way slide fasteners, clamp the puller of the lower slider into the upper jaw. Clamp the interlocked chain into the other jaw of the apparatus such that the distance between the top of the slotted plate and the top of the lower jaw is (25 ± 2) mm (see Figure E.1). Set the machine in operation until the specified force is reached or the test specimen fails.

Annex F (normative)

Test for resistance to reciprocation

F.1 Principle

The test specimen is subjected to a specified number of cyclic operations whilst under simultaneous lateral and longitudinal tension.


F.2 Apparatus

Vertically operated testing machine of the type shown in Figure F.1 and providing the following facilities.

- a) Means of holding the test specimen firmly at the bottom end, with the slide fastener in the closed position, without the chain being damaged.
- b) Means of separately gripping the two stringers at the other end so that the slide fastener beyond the slider is open. These gripping devices form the means of applying longitudinal spring balance forces to the slide fastener and are therefore connected together by a swivel-plate or other similar device, so that the slide fastener can be centred when the forces are applied. The gripping devices also swivel at the points of connection to the swivel-plate to facilitate the operation of the slider on the test specimen. The distance between the gripping devices is such that when the slider is at the lowest point in the cycle the two ends of the slide fastener subtend an angle of $60^{\circ} \pm 10^{\circ}$ (see Figure F.1).
- c) Means of gripping the tapes securely midway along the traversed length at opposite points of the testing zone so that the clamps can be subjected to force by means of spring balances. The clamps are mounted so that they are "floating", i.e. free to follow the natural direction of opening of the test specimen.

The clamps are attached at an angle of $10^{\circ} \pm 5^{\circ}$ and are capable of moving 5 mm in the direction of the pulleys. Setting pads are provided to hold the clamps in position until they are secured to the tapes. The spring balances are of the tubular type and are 100 N balances for the lateral tension and 50 N balances for the longitudinal force. In each case the scale is 44 mm in length. The 100 N balance has a spring rating of 2,25 N/mm and the 50 N balance one of 1,10 N/mm. They are graduated in 1 N steps and accurate to within 1 N on each reading.

- d) Means of applying a regular reciprocating action, at (30 ± 1) cycles per minute. through the medium of the puller, to the slider on the test specimen. The clamp or other gripping device may provide an indirect form of connection in which the clamp is in two parts, one of which is attached to the reciprocating device and the other to the puller on the specimen. This method of attachment can incorporate a spring mechanism or other feature to withdraw any automatic locking device fitted to the slider on the specimen.

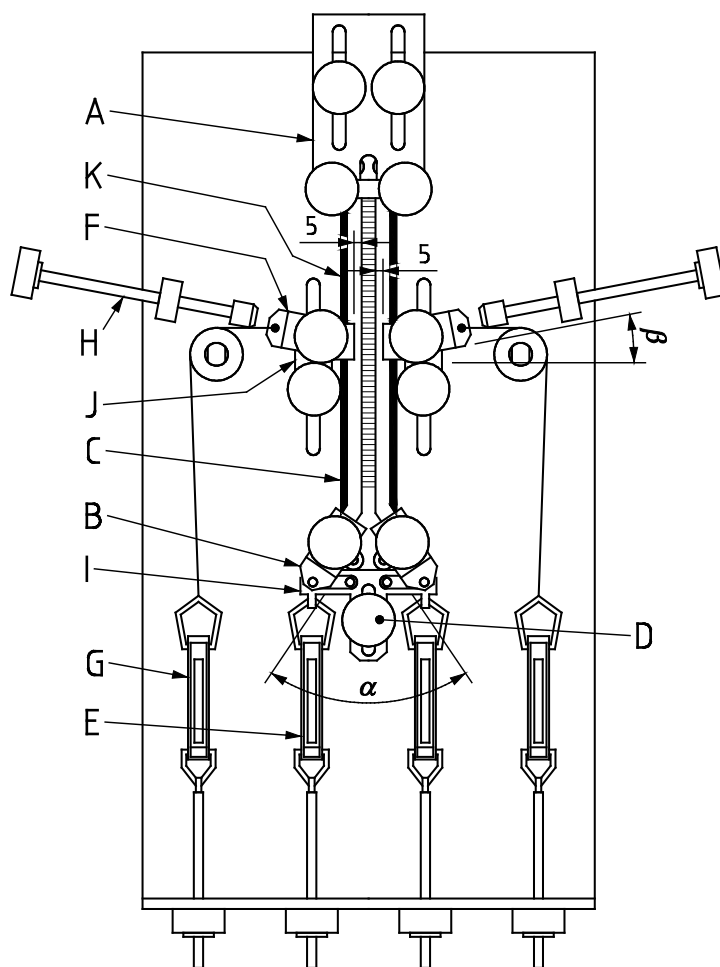

Key

- | | |
|--------------------------------|---------------------------|
| α 60° | |
| β 10° | F lateral clamps |
| A top clamp | G lateral spring balances |
| B longitudinal clamps | H adjusting screw |
| C test specimen | I swivel plate |
| D stop pin | J setting pads |
| E longitudinal spring balances | K test specimen |

Figure F.1 — Resistance to reciprocation test

F.3 Procedure

F.3.1 Preparation of the specimens

Mount the test specimen in the vertical plane so that the bottom end is away from the spring balance end of the testing machine. Leave the stringers separate at the other end so that they can be individually mounted in the testing machine (see Figure F.1). The lateral and longitudinal forces applied are as given in Table F.1.

Table F.1 — Lateral and longitudinal applied forces for reciprocating test

Performance code	Lateral force on each stringer N	Longitudinal force on each stringer N
A	7	5
B	10	7
C	16	14
D	24	18
E	30	23

F.3.2 Method

Arrange the machine so that the length of traverse of the slider is from 75 mm to 90 mm in each direction, a to-and-fro movement of 150 mm to 180 mm forming a cycle. The procedure then follows the steps indicated below.

- 1) Operate the testing machine by hand until the puller is in the lowest position, and place in position the setting pads.
- 2) Clamp the puller, ensuring that any locking device is withdrawn.
- 3) Place the slide fastener loosely in position in the top clamp, A.
- 4) Secure the slide fastener ends in the longitudinal clamps, B.
- 5) Take hold of the slide fastener C at the upper end and draw upwards until pin D prevents any further upward movement, without stretching the tape. Tighten clamp A. If the slide fastener is completely closed, then the tape ends that are attached by the bottom tape clamps are too long. To overcome this, release clamps B, F and A and cut off a length of each bottom tape end. To reassemble start at Step 3.
- 6) Apply the appropriate longitudinal forces given in Table F.1 by adjusting the spring balances E.
- 7) Secure lateral clamps F to the slide fastener tapes, leaving gaps of 5 mm between the lateral clamps and the chain at their nearest points. Ensure that the centre-lines of the clamps coincide with the strings that pass over the pulleys. Ensure that the clamps, F, are held firmly against the setting pads, J, whilst securing the clamps to the slide fastener tape. Withdraw the setting pads after fixing the clamps.
- 8) Apply the appropriate lateral forces given in Table F.1 by adjusting spring balances G.
- 9) Set the counter to zero. Set machine in motion for one cycle only to equalize the position of test specimen.
- 10) Check the forces of spring balances E and G and adjust if necessary. When the slider is in the lowest position set the adjusting screws, H, a minimum of 5 mm away from the lateral clamps, F.
- 11) Set the machine in motion.
- 12) Once the test has started, do not readjust the spring balances E and G.

- 13) Allow the machine to operate until 500 cycles have been completed. After 500 cycles, examine the slide fastener and record if the slide fastener has failed. Mechanisms of failure include slider breakage or detachment from chain, detachment of puller from slider, tape breakage, etc.

Annex G (normative)

Test for lateral strength of slide fastener

G.1 Principle

The test specimen is subjected to lateral force under controlled conditions whilst the slide fastener chain is in the closed position.

G.2 Apparatus

G.2.1 Constant rate of extension tensile testing machine

As described in Annex B, with jaws or other securing devices having a gripping surface 25 mm wide and constructed and finished such as not to damage the tape or allow the test specimen to slip (see Figure G.1).

G.2.2 Jaws

See Annex C.

Dimensions in millimetres

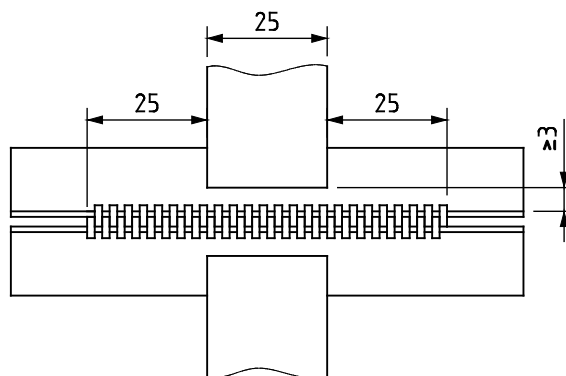


Figure G.1 — Lateral strength test

G.3 Procedure

Secure the test specimen in place with the jaws so arranged that at least half the width of each tape is gripped and there is at least 25 mm of closed chain on each side. Set the testing machine in operation until the specified force is reached or the test specimen fails.

Annex H (normative)

Test for lateral strength of open-end attachment

H.1 Principle

The test specimen is subjected to straight lateral force under controlled conditions whilst the slide fastener chain is in the closed position.

H.2 Apparatus

H.2.1 Constant rate of extension tensile testing machine

See Annex B.

H.2.2 Jaws

See Annex C.

Dimensions in millimetres

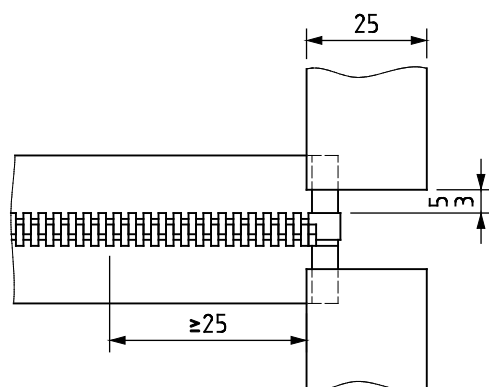


Figure H.1 — Lateral strength of open-end attachment test

H.3 Procedure

Secure the test specimen in place with the jaws set between 3 mm and 5 mm from the side edges of the box, and with one edge of each jaw aligned with the last element in the chain (as shown in Figure H.1) there is at least 25 mm of closed chain. Set the machine in operation until the specified force is reached or the test specimen fails.

Annex I (normative)

Test for strength of slider locking device

I.1 Principle

The slider is locked on the chain and the locking device subjected to tension via the chain stringers in such a way as to bring the locking device under pressure from the chain.

I.2 Apparatus

I.2.1 Constant rate of extension tensile testing machine

See Annex B.

I.2.2 Jaws


See Annex C.

I.3 Procedure

Mount the test specimen in the open position, with the locking device locked into the chain 25 mm from the top stops. Set the jaws 50 mm apart and secure the top of the stringer into the jaw adjacent to the top stop so that the top of the slider is 25 mm from the edge of each jaw, as shown in Figure I.1. Set the machine in motion and increase the force until the locking mechanism slips, the specified force is reached or the test specimen fails.

NOTE Instances of failure of the test specimen include slipping of the locking mechanism or damage to an element.

Dimensions in millimetres

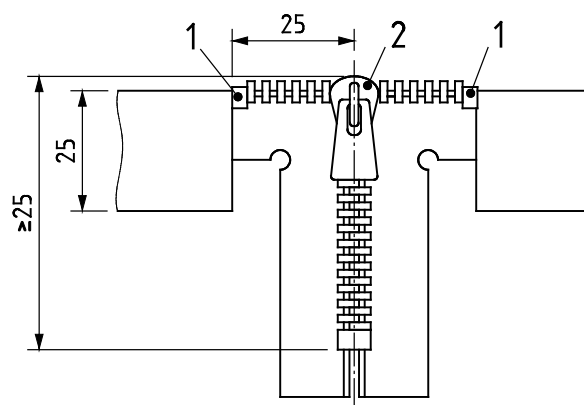

Key

- 1 top stops
- 2 slider

Figure I.1 — Slider locking device test

Annex J (normative)

Test for open-end slide fastener single stringer slider retention

J.1 Principle

The single top stop is subjected to a force via the slider applied through the puller.

J.2 Apparatus

J.2.1 Constant rate of tension tensile testing machine

See Annex B.

J.2.2 Jaws

See Annex C.

J.3 Procedure

Open the test specimen to provide a single stringer with the slider adjacent to the top stop. Secure the puller in the upper jaw of the testing machine and the other end of the specimen in the lower jaw such as the minimum distance between the jaws is 25mm, as shown in Figure J.1, steps being taken to avoid damaging the stringer. Set the machine in operation until the specified force is reached or the test specimen fails.

NOTE Instances of failure include the slider becoming detached from the top of the slide fastener and the removal of the puller from the slider body.

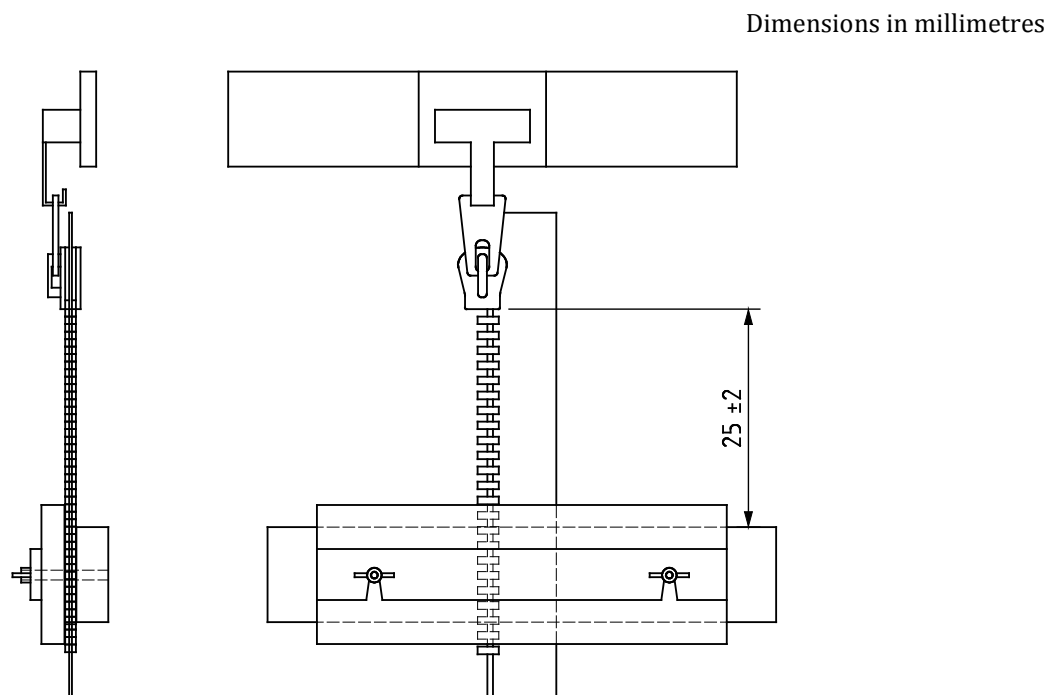


Figure J.1 — Open-end slide fastener single stringer slider retention test

Annex K (normative)

Torque test

K.1 Principle

This test method covers the determination of the resistance of a slider against a torque applied to the puller of a zipper in a plane perpendicular to its longitudinal axis.


This test method may be used to determine puller strength which measures the ability of a slider to resist deformation or rupture when a torque stress is applied on the puller during operation of the zipper in the end-product.

K.2 Apparatus

Consisting of a puller twist fixture having a means for positioning the slider body, and for clamping the puller perpendicularly to the slider body as shown in Figure K.1. The puller clamp shall be rotatable around its longitudinal axis and shall be equipped with a dial for measuring the angle of rotation. The jaws shall be capable of holding the test specimen without allowing it to slip

Provision shall be made to apply torsional forces to the clamp by means of torque wrenches of the adjustable slip type at a constant rate.

The wrench selected for each test shall be such that the torque exerted falls between 20 % and 80 % of its scale capacity (of at least 0,70 Nm).

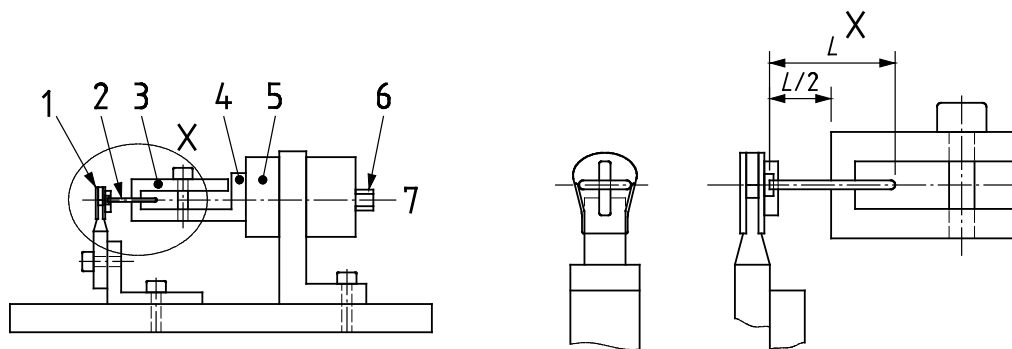

Key

- 1 slider
- 2 puller
- 3 pull tab clamp
- 4 testing drum
- 5 angular dial
- 6 for attaching of torque wrench
- 7 axis of rotation
- X detail of slider clamp

Figure K.1 — Pull tab twist test

K.3 Procedure

K.3.1 Preparation of the specimens

Remove the slider from the stringers of the fastener. Clamp the slider in one of the clamps and the puller in the other, so that the puller is perpendicular to the slider and the longitudinal centre line of the puller is aligned with the axis of rotation between the two clamps, and the puller is gripped in the middle of its total length as shown in Figure K1, Key X.

Depending on the construction of the puller and its attachment it may be necessary to adjust the gripping position, in this case the gripping position should be reported.

The amount of permanent twist imparted to the puller or other permanent damage or deformation or detachment is noted.

K.3.2 Method

Operate the testing device so that the two jaws rotate relative to each other in a clockwise direction, when looking from the puller side of the slider, at a constant speed in order to achieve 180° rotation in 5s until either:

- a) the specified torque is reached, or
- b) the puller breaks or twists off the slider, or
- c) the jaws have rotated through a total of 180°.

Maintain the maximum rotation or required torque for 10 s. Permit the test component to return to a relaxed condition. Repeat this procedure in an anticlockwise direction.

NOTE Applicable specification can be found in some standards dealing with safety requirements intended for children articles (e.g. clothing, sleep bags).

Repeat the same procedure for at least four additional specimens. Report the cases a),b),c) listed above.

If a puller slippage occurs in the jaws, the test shall be reported as not suitable.

K.4 Test to failure method for quality control

IMPORTANT — This method is intended for quality control and it is not to be used to comply with the requirement of Table 2.

Prepare the specimen as in K.3.1.

Operate the testing device (K.2) so that the two jaws rotate relative to each other in a clockwise direction, when looking from the puller side of the slider, at a constant speed of approximately 9°/s in order to achieve 180° rotation between 15s and 25s until either:

- the puller breaks or twists off the slider;
- the jaws have rotated through a total of 180°.

If a puller slippage occurs in the jaws, the test shall be reported as not suitable.

Record the maximum torque in N.m to the nearest 0,01 N.m and the type of failure such as:

- slider broke at the point of attachment to the puller.
- puller broke at the point of attachment to the slider.

- slider broke at a point away from the attachment to the puller.
- puller broke at a point away from the attachment to the slider.
- puller twisted but did not break.

If the puller is permanently twisted, estimate the amount of twist to the nearest 5°.

Repeat the procedure for two further test specimens.

Repeat the procedure for three further test specimens, this time rotating the jaws in an anticlockwise direction.

Calculate the arithmetic mean of the six maximum torques (clockwise and anticlockwise).

Annex L (informative)

Sampling procedures for bulk quantities of slide fasteners

L.1 General

Batch sizes and test rates should be in accordance with Table L.1 based on ISO 2859-1 (with AQL Acceptance Quality Limit 4,0 and at special inspection level S3), which should be consulted for information on sampling plans, including the switch from normal to tightened procedures.

L.2 Guidance on interpretation of results for acceptance purposes

Based on the sampling details given in Table L.1, the appropriate number of test samples shall be tested for each test applicable to the design of slide fastener. Any test specimen within any test carried out which does not achieve the required performance level shall be considered to be a 'defect' for the purposes of determining acceptability or rejection of the batch. The Acceptance and Rejection levels given in Table L.1 are applicable to all defects detected for all tests applicable to the specific design of slide fastener being inspected. If the total number of defects does not exceed the number given in the Acceptance column of Table L.1 then the batch shall be accepted. If the total number of defects is equal to or greater than the number given in the Rejection column of Table L.1 then the batch shall be rejected.

L.3 Guide to changing from normal to tightened test procedures

If two of five or fewer successive batches have been rejected at the normal test rate, then the tightened test rate should be introduced and remain in force until five successive batches have been accepted, after which the normal test rate can be restored.

Table L.1 — Batch sizes and test rates

Test rate	Batch size	No of samples	No of defects giving rise to	
			Acceptance	Rejection
Normal	2 to 150	3	0	1
	151 to 3 200	13	1	2
	3 201 to 35 000	20	2	3
	35 001 to 500 000	32	3	4
Tightened	2 to 150	5	0	1
	151 to 35 000	20	1	2
	35 001 to 500 000	32	2	3

Annex M
(informative)

End-uses and recommended performance codes for labelling purposes

Table M.1 — End-uses and recommended performance codes for labelling purposes

End uses	Performance code				
	A	B	C	D	E
Dresses	X	X			
Knitwear	X	X	X		
Light leather goods		X	X		
Skirts, jeans or trousers		X	X		
Upholstery		X	X		
Foundation garments			X		
Coats and jackets			X	X	
Overalls			X		
Luggage			X	X	X
Sleeping bags			X	X	
Lightweight and inner tents			X		
Footwear			X	X	
Leather garments			X	X	
Ski clothes			X	X	
Wet suits					X
Awnings and frame tents					X
Mattresses			X	X	
Pillows		X	X		
Children's sleep bags			X		
Children clothes			X		

NOTE Advice on the end use of slide fasteners may be indicated at the point of sale or earlier using the information given in Table M.1 and Annex A. For industrial users a technical advisory service is made available by most manufacturers. Some end-use categories given in Table M.1 overlap several performance codes; this is because certain items, e.g. knitwear, are manufactured in various weights and thus are designed for a variety of end uses. Users of this standard will therefore preferably use their judgement in selecting a performance code following the guidance given in Table M.1 especially considering extreme conditions of use.

Bibliography

- [1] BS 3084:2006, *Slide fasteners (zips) — Specification*
- [2] NF G 91-005:1984, *Slide fasteners — Methods of testing — Mechanical characteristics*
- [3] ASTM D2061-07, *Standard test methods for strength test for zippers*
- [4] EN ISO 7500-1, *Metallic materials - Verification of static uniaxial testing machines - Part 1: Tension/compression testing machines - Verification and calibration of the force-measuring system (ISO 7500-1)*
- [5] ISO 2859-1, *Sampling procedures for inspection by attributes — Part 1: Sampling schemes indexed by acceptance quality limit (AQL) for lot-by-lot inspection*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™