

BS EN 60544-2:2012



BSI Standards Publication

Electrical insulating materials — Determination of the effects of ionizing radiation on insulating materials

Part 2: Procedures for irradiation and test

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN 60544-2:2012. It is identical to IEC 60544-2:2012. It supersedes BS 7811-2:1995 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee GEL/112, Evaluation and qualification of electrical insulating materials and systems.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012

Published by BSI Standards Limited 2012

ISBN 978 0 580 75750 1

ICS 17.240; 29.035.01

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2012.

Amendments issued since publication

Date	Text affected
-------------	----------------------

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN 60544-2

October 2012

ICS 17.240; 29.035.01

English version

**Electrical insulating materials -
Determination of the effects of ionizing radiation on insulating materials -
Part 2: Procedures for irradiation and test
(IEC 60544-2:2012)**

Matériaux isolants électriques -
Détermination des effets des
rayonnements ionisants
sur les matériaux isolants -
Partie 2: Méthodes d'irradiation et d'essai
(CEI 60544-2:2012)

Elektroisolierstoffe -
Bestimmung der Auswirkungen
ionisierender Strahlung auf Isolierstoffe -
Teil 2: Verfahren zur Bestrahlung und
Prüfung
(IEC 60544-2:2012)

This European Standard was approved by CENELEC on 2012-08-13. CENELEC members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CENELEC member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CENELEC member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CENELEC members are the national electrotechnical committees of Austria, Belgium, Bulgaria, Croatia, Cyprus, the Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, the Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

CENELEC

European Committee for Electrotechnical Standardization
Comité Européen de Normalisation Electrotechnique
Europäisches Komitee für Elektrotechnische Normung

Management Centre: Avenue Marnix 17, B - 1000 Brussels

Foreword

The text of document 112/208/FDIS, future edition 3 of IEC 60544-2, prepared by IEC/TC 112 "Evaluation and qualification of electrical insulating materials and systems" was submitted to the IEC-CENELEC parallel vote and approved by CENELEC as EN 60544-2:2012.

The following dates are fixed:

- latest date by which the document has to be implemented at national level by publication of an identical national standard or by endorsement (dop) 2013-05-13
- latest date by which the national standards conflicting with the document have to be withdrawn (dow) 2015-08-13

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CENELEC [and/or CEN] shall not be held responsible for identifying any or all such patent rights.

Endorsement notice

The text of the International Standard IEC 60544-2:2012 was approved by CENELEC as a European Standard without any modification.

Annex ZA (normative)

Normative references to international publications with their corresponding European publications

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

NOTE When an international publication has been modified by common modifications, indicated by (mod), the relevant EN/HD applies.

<u>Publication</u>	<u>Year</u>	<u>Title</u>	<u>EN/HD</u>	<u>Year</u>
IEC 60093	-	Methods of test for volume resistivity and surface resistivity of solid electrical insulating materials	HD 429 S1	-
IEC 60167	-	Methods of test for the determination of the insulation resistance of solid insulating materials	HD 568 S1	-
IEC 60212	-	Standard conditions for use prior to and during the testing of solid electrical insulating materials	EN 60212	-
IEC 60243-1	-	Electrical strength of insulating materials - Test methods - Part 1: Tests at power frequencies	EN 60243-1	-
IEC 60544-1	-	Electrical insulating materials - Determination of the effects of ionizing radiation - Part 1: Radiation interaction and dosimetry	EN 60544-1	-
IEC 60544-4	-	Electrical insulating materials - Determination of the effects of ionizing radiation - Part 4: Classification system for service in radiation environments	EN 60544-4	-
ISO 37	-	Rubber, vulcanized or thermoplastic - Determination of tensile stress-strain properties	-	-
ISO 48	-	Rubber, vulcanized or thermoplastic - Determination of hardness (hardness between 10 IRHD and 100 IRHD)	-	-
ISO 178	-	Plastics - Determination of flexural properties	EN ISO 178	-
ISO 179	Series	Plastics - Determination of Charpy impact properties	EN ISO 179	Series
ISO 527	Series	Plastics - Determination of tensile properties	EN ISO 527	Series
ISO 815	Series	Rubber, vulcanized or thermoplastic - Determination of compression set	-	-
ISO 868	-	Plastics and ebonite - Determination of indentation hardness by means of a durometer (Shore hardness)	EN ISO 868	-

CONTENTS

INTRODUCTION.....	6
1 Scope.....	8
2 Normative references	8
3 Irradiation.....	9
3.1 Type of radiation and dosimetry	9
3.2 Irradiation conditions	10
3.3 Sample preparation	10
3.4 Irradiation procedures	10
3.4.1 Irradiation dose-rate control.....	10
3.4.2 Irradiation temperature control.....	10
3.4.3 Irradiation in air	11
3.4.4 Irradiation in a medium other than air	11
3.4.5 Irradiation in a vacuum	11
3.4.6 Irradiation at high pressure.....	12
3.4.7 Irradiation during mechanical stressing.....	12
3.4.8 Irradiation during electrical stressing	12
3.4.9 Combined irradiation procedures	12
3.5 Post-irradiation effects	12
3.6 Specified irradiation conditions.....	12
4 Test.....	12
4.1 General.....	12
4.2 Test procedures	13
4.3 Evaluation criteria	13
4.3.1 End-point criteria	13
4.3.2 Values of the absorbed dose	14
4.4 Evaluation	14
5 Report.....	15
5.1 General.....	15
5.2 Material.....	15
5.3 Irradiation.....	15
5.4 Test.....	15
5.5 Results.....	15
Annex A (informative) Examples of test reports.....	16
Bibliography.....	21
Figure A.1 – Change of mechanical properties as a function of absorbed dose for magnetic coil insulation.....	17
Figure A.2 – Breakdown voltage of insulating tape as a function of absorbed dose	20
Table 1 – Critical properties and end-point criteria to be considered in evaluating the classification of insulating materials in radiation environments	14
Table A.1 – Example 1 – Magnetic coil insulation	16
Table A.2 – Example 2 – Cable insulation	18

Table A.3 – Example 3 – Insulating tape 19

INTRODUCTION

When selecting insulating materials for applications in radiation environments, the component designers should have available reliable test data to compare candidate materials. To be meaningful, the performance data should be obtained on each material by standardized procedures, and the procedures should be designed to demonstrate the influence that variations of the service conditions have on the significant properties. This point is of particular concern where in normal service conditions low dose rates exist and where the insulation materials have been selected from radiation endurance data obtained from tests conducted at high dose rates.

Environmental conditions shall be well controlled and documented during the measurement of radiation effects. Important environmental parameters include temperature, reactive medium and mechanical and electrical stresses present during the irradiation. If air is present, radiation-induced species can enter into reactions with oxygen that would not occur in its absence. This is responsible for an observed influence of the absorbed dose rate for certain types of polymers if irradiated in air. As a result, the resistance may be several orders of magnitude lower than when the sample is irradiated under vacuum or in the presence of inert gas. This is generally called the "dose-rate effect", which is described and reviewed in references [1] to [14]¹.

NOTE For the user of this Part of IEC 60544 who wants to go into more detail, the cited references are listed in the Bibliography. Where these are not publications in internationally available journals, addresses where the cited scientific reports can be obtained are given at the end of the references.

The irradiation time can become relevant because of time-dependent complications caused by:

- a) physical effects such as diffusion-limited oxidation [8], [10]; and
- b) chemical phenomena such as rate-determining hydroperoxide breakdown reactions [10], [14].

Typical diffusion-limited effects are commonly observed in radiation studies of polymers in air. Their importance depends upon the interrelationship of the geometry of the polymer with the oxygen permeation and consumption rates, both of which depend upon temperature [10]. This means that the irradiation of thick samples in air may result in oxidation only near the air-exposed surfaces of the sample, resulting in material property changes similar to those obtained by irradiation in an oxygen-free environment. Therefore, when the material is to be used in air for a long period of time at a low dose rate, depositing the same total dose at a high dose rate in a short exposure period may not determine its durability. Previous experiments or considerations of sample thickness combined with estimates of oxygen permeation and consumption rates [8], [10] may eliminate such concerns. A technique that may be useful for eliminating oxygen diffusion effects by increasing the surrounding oxygen pressure is under investigation [8].

Radiation-induced reactions will be influenced by temperature. An increase in reaction rate with temperature can result in a synergistic effect of radiation and heat. In the case of the more commonly used thermal ageing prediction, the Arrhenius method is employed; this makes use of an equation based on fundamental chemical kinetics. Despite considerable ongoing investigations of radiation ageing methodologies, this field is much less developed [9]. General equations involving dose, time, Arrhenius activation energy, dose rate and temperature are being tested for modelling of ageing experiments [10-12]. It should be noted that sequential application of radiation and heat, as it is frequently practised, can give very different results depending on the order in which they are performed, and that synergistic effects may not be properly simulated [13], [14].

The electrical and mechanical properties required of insulating materials and the acceptable amount of radiation-induced changes are so varied that it is not possible to establish

¹ References in square brackets refer to the bibliography.

acceptable properties within the framework of a recommendation. The same holds for the irradiation conditions. Therefore, this standard recommends only a few properties and irradiation conditions which previous experience has shown to be appropriate. The properties recommended are those that are especially sensitive to radiation. For a specific application, other properties may have to be selected.

Part 1 of IEC 60544 constitutes an introduction dealing very broadly with the problems involved in evaluating radiation effects. It also provides a guide to dosimetry terminology, several methods of determining the exposure and absorbed dose, and methods of calculating the absorbed dose in any specific material from the dosimetry method applied. The present part describes procedures for irradiation and test. Part 4 of IEC 60544 defines a classification system to categorize the radiation endurance of insulating materials. It provides a set of parameters characterizing the suitability for radiation service. It is a guide for the selection, indexing and specification of insulating materials. The earlier Part 3 of IEC 60544 has been incorporated into the present Part 2.

ELECTRICAL INSULATING MATERIALS – DETERMINATION OF THE EFFECTS OF IONIZING RADIATION ON INSULATING MATERIALS –

Part 2: Procedures for irradiation and test

1 Scope

This Part of IEC 60544 specifies the controls maintained over the exposure conditions during and after the irradiation of insulating materials with ionizing radiation prior to the determination of radiation-induced changes in physical or chemical properties.

This standard specifies a number of potentially significant irradiation conditions as well as various parameters which can influence the radiation-induced reactions under these conditions.

The objective of this standard is to emphasize the importance of selecting suitable specimens, exposure conditions and test methods for determining the effect of radiation on appropriately chosen properties. Since many materials are used either in air or in inert environments, standard exposure conditions are recommended for both of these situations.

It should be noted that this standard does not consider measurements which are performed during the irradiation.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60093, *Methods of test for volume resistivity and surface resistivity of solid electrical insulating materials*

IEC 60167, *Methods of test for the determination of the insulation resistance of solid insulating materials*

IEC 60212, *Standard conditions for use prior to and during the testing of solid electrical insulating materials*

IEC 60243-1, *Electrical strength of insulating materials – Test methods – Part 1: Tests at power frequencies*

IEC 60544-1, *Electrical insulating materials – Determination of the effects of ionizing radiation – Part 1: Radiation interaction and dosimetry*

IEC 60544-4, *Electrical insulating materials – Determination of the effects of ionizing radiation – Part 4: Classification system for service in radiation environments*

ISO 37, *Rubber, vulcanized or thermoplastic – Determination of tensile stress-strain properties*

ISO 48, *Rubber, vulcanized or thermoplastic – Determination of hardness (hardness between 10 IRHD and 100 IRHD)*

ISO 178, *Plastics – Determination of flexural properties*

ISO 179 (all parts), *Plastics – Determination of Charpy impact properties*

ISO 527 (all parts), *Plastics – Determination of tensile properties*

ISO 815 (all parts), *Rubber, vulcanized or thermoplastic – Determination of compression set*

ISO 868, *Plastics and ebonite – Determination of indentation hardness by means of a durometer (Shore hardness)*

3 Irradiation

3.1 Type of radiation and dosimetry

The following types of radiation are covered by the standard:

- X- and γ -rays;
- electrons;
- protons;
- neutrons;
- combined γ -rays and neutrons ("reactor" radiation).

In general, the radiation effects may be different for different types of radiation. However, in many practical applications, it has been found that with analogous experimental conditions, equal absorbed dose and equal linear energy transfer, the changes in properties will be only slightly dependent on the type of radiation [15-17]. Thus, the preferred type of radiation should be one for which the absorbed dose measurement is simple and precise, for example ^{60}Co γ -rays or fast electrons. For a comparison of the effect of reactor radiation with γ -rays or fast electrons, specimens with the same chemical composition can be irradiated with these various types of radiation and the radiation-induced changes can be compared.

Radiation-induced changes are related to the absorbed radiation energy, expressed by the absorbed dose. Recommended methods of dosimetry are listed in IEC 60544-1. The definitions of absorbed dose, absorbed dose rate and the units are also given in IEC 60544-1 and repeated here for convenience.

The absorbed dose, D , is the quotient of $d\bar{\epsilon}$ by dm , where $d\bar{\epsilon}$ is the mean energy imparted by ionizing radiation to the matter in a volume element and dm is the mass of the matter in that volume element.

$$D = \frac{d\bar{\epsilon}}{dm}$$

The absorbed dose rate, \dot{D} , is the increment of the absorbed dose dD in the time interval dt .

$$\dot{D} = \frac{dD}{dt}$$

Units

The SI unit of absorbed dose is the gray (Gy);

1 Gy = 1 J/kg (= 10² rad).

Usual multiples for higher doses are the kilogray (kGy) or megagray (MGy).

The SI unit of absorbed dose rate is the gray per second;

1 Gy/s = 1 W/kg (=10² rad/s = 0,36 Mrad/h).

3.2 Irradiation conditions

The irradiation conditions which must be established are as follows:

- type and energy of the radiation;
- absorbed dose;
- absorbed dose rate;
- surrounding medium;
- temperature;
- mechanical, electrical and other stresses;
- sample thickness.

It is preferable to use γ -rays, X-rays or electrons for the irradiation (see 3.1). Their energy should be so chosen that the homogeneity of the absorbed dose in the sample is within $\pm 15\%$.

3.3 Sample preparation

The test specimens shall be carefully prepared in accordance with the appropriate IEC and ISO standards, because a variation in test results may be due to differences in the quality of test specimens.

Because the effect of radiation can depend on the dimensions of the specimens, these shall be uniform for all comparison studies. It is preferable to irradiate the test specimens in the geometry needed for subsequent tests. If, however, the test specimens have to be cut from a larger irradiated test piece, the position of the specimen in the test piece shall be reported.

Non-irradiated control specimens shall be produced in the same manner and subjected to the same conditioning and post-irradiation treatment as the irradiated specimens.

3.4 Irradiation procedures

3.4.1 Irradiation dose-rate control

The exposure rate is usually non-uniform in the radiation field. In addition, it is reduced by the energy absorption in the specimen itself. Therefore, the absorbed dose cannot be homogeneous. Improvements in homogeneity may be achieved by filtering methods, by irradiation of the specimens from several directions, by traversing the radiation field at a constant rate or by scanning the specimen with the radiation beam. The homogeneity of the absorbed dose rate should be improved rotating or moving the sample during the irradiation, for example, by means of suitable equipments. It is expected that variations in dose rate within $\pm 15\%$ will not appreciably affect the results (see 3.2); variations outside this recommended value shall be reported.

3.4.2 Irradiation temperature control

The specimens shall be conditioned at the irradiation temperature for 48 h, or until an approximate equilibrium with the irradiation temperature is ensured.

The temperatures shall be chosen from the standardized series given in IEC 60212.

The temperature of the specimens during irradiation shall be determined by the use of a supplementary specimen containing a temperature-measuring device, irradiated under the same conditions as the other specimens. The measuring device and its position in the specimen have to be carefully chosen so to avoid that the irradiation influences the temperature measurements.

The temperature variations are a function of the actual temperature of the experiment. Larger tolerances (e.g. ± 5 K) are allowed at ambient temperatures up to approximately 40 °C, smaller tolerances (e.g. ± 2 K) are reasonable at higher temperatures where temperature control is used. Deviations of more than ± 2 K shall be reported.

Irradiation at high dose rates may cause the temperature to rise. The temperature may be controlled in any way that does not affect the material properties or radiation conditions.

Irradiations in the region of a transition (e.g. melting, glass or secondary transition) shall be noted, since degradation behaviour can change significantly as a material passes through such a transition.

3.4.3 Irradiation in air

Specimens to be irradiated in air shall be arranged so that free access to air is ensured on all sides. The build-up of radiation-induced reaction products is to be prevented (e.g. by a flow of fresh air over the specimen), except in cases where it is desirable to determine whether the products (e.g. O₃ or HCl) affect the material properties.

If the nature of the radiation source requires that the specimens be enclosed in a container, package the specimens in the standard atmosphere. In general, the conditions in the container (e.g. pressure and chemical composition of atmosphere) will be changed by irradiation. This could seriously affect the results. Therefore, the air within the container should be changed frequently. It shall be stated in the report that irradiation was made in a closed container, the material of which the container was made, the ratio between the volumes of specimens and air, and how often the air was renewed. The possibility of a pressure rise by heating or by reaction products is to be considered in the design of the container so that this effect is minimized.

3.4.4 Irradiation in a medium other than air

Specimens to be irradiated in a gas other than air shall be conditioned in a container at a pressure of ≤ 1 Pa (10^{-5} bar) for at least 8 h, followed by three flushes with the gas. After flushing, the specimens shall remain in the container filled with gas at the temperature of the irradiation until an approximate equilibrium of the specimens with the gas is ensured. During irradiation it is best to maintain a continuous flow of gas through the specimen container. When necessary, a sealed container may be used if the gas is changed periodically. Sealing the container for the entire exposure is permitted only if it is unavoidable due to the nature of the source. The details of the method shall be reported.

Specimens to be irradiated in a liquid medium shall be immersed for a sufficient period of time to reach approximate equilibrium with the liquid before the irradiation. The radiation resistance may be influenced by swelling induced during the conditioning time. During the entire period of irradiation the specimens shall be completely immersed in the liquid. Stirring of the liquid, streaming or other methods used to supply new liquid to the specimen shall be reported.

3.4.5 Irradiation in a vacuum

Specimens to be irradiated in a vacuum shall be conditioned in a container at a pressure of ≤ 1 Pa (10^{-5} bar) for at least 24 h and that pressure shall not be exceeded throughout the irradiation.

3.4.6 Irradiation at high pressure

Specimens to be irradiated at high pressure shall be conditioned in a container at that pressure for sufficient lengths of time to reach approximate equilibrium, and the selected pressure shall be maintained throughout the irradiation. A possible technique for irradiation under oxygen pressure is described in [8]. Details of the exposure conditions shall be reported.

3.4.7 Irradiation during mechanical stressing

The specimens shall be arranged on a suitable fixture so that they will be subject to a mechanical stress during irradiation. A description of the method shall be reported.

3.4.8 Irradiation during electrical stressing

The specimens shall be arranged on a suitable fixture so that they will be subject to an electrical stress during irradiation. A description of the method shall be reported.

3.4.9 Combined irradiation procedures

When any combination of two or more of the variables listed in the above procedures is used, the combined procedure shall incorporate all the appropriate features of the separate procedures involved.

3.5 Post-irradiation effects

The irradiation of polymers results in the formation of free radicals or other reactive species. The rate at which some of these are formed may be much greater than their reaction rate; this leads to the accumulation of reactive species within the irradiated material and to the possibility of continuing reactions after the specimen has been removed from the radiation field. Because of this effect, specimens shall be tested as soon as possible (preferably within one week) after the end of irradiation.

3.6 Specified irradiation conditions

Problems related to assessing the effects at long-term service conditions by short-term laboratory tests are discussed in the Introduction. Two irradiation conditions are given below which are intended to provide a measure of the time-related oxygen effects:

- Short time exposure in non-oxidizing conditions, e.g. either in the absence of oxygen or for thick samples at high absorbed dose rates usually in excess of 1 Gy/s.
Since radiation heating can occur at high dose rates, the upper limit is governed by the specified test temperature.
- Long time exposure conditions in the presence of oxygen (ambient air) at low dose rates up to 3×10^{-2} Gy/s.

NOTE The recommended long time exposure employs a dose rate that was chosen as a compromise between long-term field service conditions and practical test durations. It can still be several orders of magnitude higher than the dose rate that occurs in many long-term applications of interest. Further significant dose rate effects may apply due to these differences, and the size will depend on the polymer type and sample thickness. At present, test procedures predicting life times at much lower dose rates than 3×10^{-2} Gy/s are subject to research [9 – 12].

For application in nuclear reactor service, it is preferable to irradiate the specimens at two temperatures: room temperature (23 ± 5) °C and 80 °C. Consideration should be given to 3.4.2.

4 Test

4.1 General

The radiation resistance can be characterized by:

- the absorbed dose required to produce a predetermined change in a property (see 4.3.1), or
- the amount of change in a property produced by a fixed value of absorbed dose (see 4.3.2).

To establish radiation resistance the following points shall be defined:

- irradiation conditions (see Clause 3);
- properties whose changes may be evaluated (see 4.2);
- end-point criteria of properties and/or values of absorbed dose (see 4.3).

The tests are intended to determine permanent changes in the properties of the material. Transient changes occurring during the irradiation are not dealt with in this standard.

4.2 Test procedures

Some properties which may be considered for monitoring radiation effects are listed in Table 1 together with the appropriate test procedures. Although electrical properties can change drastically when a material fails, they are much less sensitive than mechanical properties for monitoring damage built up before failure [18], [19]. Mechanical properties may be improved initially in plastics which crosslink, but with higher absorbed doses most plastics become brittle and technically unusable. This process of becoming brittle should be considered when the properties to be tested are chosen.

For normal application, experience has shown that the most appropriate mechanical properties are

- the flexural stress at maximum load for rigid plastics, and
- the percentage elongation at break for flexible plastics and elastomers.

Should the application warrant it, the user may specify an alternative property taken from Table 1 or any alternative procedure. Also, since the radiation source and container have a limited volume over which the radiation field is sufficiently uniform, this may imply restrictions in sample size.

4.3 Evaluation criteria

4.3.1 End-point criteria

The end-point criterion may be expressed as an absolute property value or a percentage of the initial value. Either method may be used to classify materials for radiation resistance. Table 1 provides examples of ranking materials using a percentage of the initial value. The assessment of a radiation index is given in IEC 60544-4.

For a specific application or service condition, a more appropriate end-point value may be selected that will reflect end-use requirements.

Table 1 – Critical properties and end-point criteria to be considered in evaluating the classification of insulating materials in radiation environments

Type of material	Properties to be tested	Test procedures	End-point criteria ^a
Rigid plastics	<ul style="list-style-type: none"> – Flexural strength – Tensile strength at yield – Tensile strength at break – Impact strength – Volume and surface resistivity – Insulation resistance – Electrical strength 	<ul style="list-style-type: none"> ISO 178 ISO 527 ISO 527 ISO 179 IEC 60093 IEC 60167 IEC 60243-1 	<ul style="list-style-type: none"> 50 % 50 % 50 % 50 % 10 % 10 % 50 %
Flexible plastics	<ul style="list-style-type: none"> – Elongation at break – Tensile strength at yield – Tensile strength at break – Impact strength – Volume and surface resistivity – Insulation resistance – Electrical strength 	<ul style="list-style-type: none"> ISO 527 ISO 527 ISO 527 ISO 179 IEC 60093 IEC 60167 IEC 60243-1 	<ul style="list-style-type: none"> 50 % 50 % 50 % 50 % 10 % 10 % 50 %
Elastomer	<ul style="list-style-type: none"> – Elongation at break – Tensile strength at break – Hardness/IRHD – Hardness/Shore A – Compression set – Volume and surface resistivity – Insulation resistance – Electrical strength 	<ul style="list-style-type: none"> ISO 37 ISO 37 ISO 48 ISO 868 ISO 815 IEC 60093 IEC 60167 IEC 60243-1 	<ul style="list-style-type: none"> 50 % 50 % <li rowspan="2">} Change of 10 units 50 % 10 % 10 % 50 %
^a The values given in per cent are expressed as a percentage of the initial value.			

4.3.2 Values of the absorbed dose

Radiation resistance may also be determined by exposing a material to a specified absorbed dose which has been agreed upon or has been established in a material standard. In such a case the end-point criteria may not be reached at the final dose.

The recommended absorbed dose values to use when following property changes are

$$10^3, 10^4, 10^5, 3 \times 10^5, 10^6, 3 \times 10^6, 10^7, 3 \times 10^7, 10^8 \text{ Gy.}$$

NOTE In many cases, it is expedient to use as a limit the absorbed dose of 10^7 Gy, or in special cases 10^8 Gy.

4.4 Evaluation

The properties of the irradiated and control specimens are determined according to the relevant standards, and the changes are reported as the difference in or ratio between the values of the property in the irradiated and in the control specimens.

To determine the absorbed dose which produces a given change in a property (end-point criterion, see 4.3), the values of the property or changes in the values are plotted against the absorbed dose. The absorbed dose corresponding to the end-point criterion for a property is then determined by interpolation (see Example 1 in Annex A).

NOTE Determination by extrapolation of an absorbed dose which produces a given change is possible only in a very limited way because the values of the properties do not change with increasing absorbed dose according to any simple mathematical expression.

5 Report

5.1 General

The report shall include a reference to this standard, report any deviations from the recommended procedures of this standard and list the following information:

5.2 Material

The description of the material under test shall include as much of the following information as is available:

- type of polymer and preparation method;
- supplier;
- formulation and compounding data, such as: fillers (including size and form), plasticizers, stabilizing agents, light absorbers, etc.;
- physical properties: density, melting point, glass transition temperature, crystallinity, orientation, solubility, etc.

5.3 Irradiation

- Description of the radiation source:
Type, activity or beam power, kind and energy spectrum of radiation. For reactor irradiation, the proportion of γ -rays, thermal, epithermal and fast neutrons.
- Specification of the absorbed dose:
Method of dosimetry, absorbed dose rates (with tolerances), period of irradiation and absorbed dose of the different specimens. For accelerators, list pulse repetition rate, pulse length and maximum flux density. Also list the traverse cycle of the specimen and "in-time" and "out-time".
For reactors and other neutron sources, make the calculation of absorbed dose rate on the basis of the flux density, determined separately for thermal, epithermal and fast neutrons, and for γ -rays.
- Conditioning and irradiation procedure, including pertinent details, for example temperature, atmosphere or medium, pressure, stress on specimen, container.
- Special post-irradiation treatment.
- Date of irradiation.

5.4 Test

Properties tested and relevant test standards and, as appropriate (see 4.3):

- end-point criteria;
- specified absorbed dose.

5.5 Results

As appropriate (see 4.4):

- absorbed dose required to reach the specified end-point criterion, or a graph;
- values of the properties in the irradiated specimens and control specimens, as well as the property changes.

Date of property test.

Examples of test reports are given in Annex A for (1) magnet coil insulation, (2) cable insulation, (3) insulating tape.

Annex A
(informative)

Examples of test reports

EXAMPLE 1 – Magnet coil insulation

Radiation test report according to the IEC 60544 series

1. Material: Epoxy – Phenol – Novolac – Bisphenol A resin
 Composition: Resin EPN 1138 + MY745 + CY221 (50:50:20),
 hardener: HY905 (120),
 accelerator: XB2687 (0,3)
 Curing: 24 h at 120 °C
 Application: Magnet coil insulation
 Supplier: NN

2. Irradiation
 Pool reactor, in water, 40 °C
 Fast neutron flux ($E > 1 \text{ MeV}$): $3 \times 10^{12} \text{ n/cm}^2 \text{ s}$
 Thermal neutron flux: $5 \times 10^{12} \text{ n/cm}^2 \text{ s}$
 Gamma dose rate: 400 Gy/s
 Absorbed doses: $5 \times 10^6, 1 \times 10^7, 2,5 \times 10^7, 5 \times 10^7 \text{ Gy}$
 Dosimetry method: Calorimeter and activation detectors
 Irradiation date: xy

3. Test
 Method: Flexural strength ISO 178
 Sample size: 80 mm × 10 mm × 4 mm
 Critical property: Flexural strength at maximum load
 End-point criterion: 50 % of initial value
 Test date: xy

4. Results: See Table A.1 and Figure A.1.

Table A.1 – Example 1 – Magnetic coil insulation

N°	Characteristics			Mechanical properties		
	Composition	Curing conditions	Absorbed dose Gy	Flexural strength S MPa	Deflection at break D mm	Tangent modulus of elasticity M GPa
297	EPN 1138/MY 745/CY 221/HY 905/XB 2687	24 h at 120 °C	0	127	12,4	3,8
			5×10^6	94	6,4	3,9
			1×10^7	70	4,5	4,1
			$2,5 \times 10^7$	14	1,2	4,3
			5×10^7	2	0,7	0,5

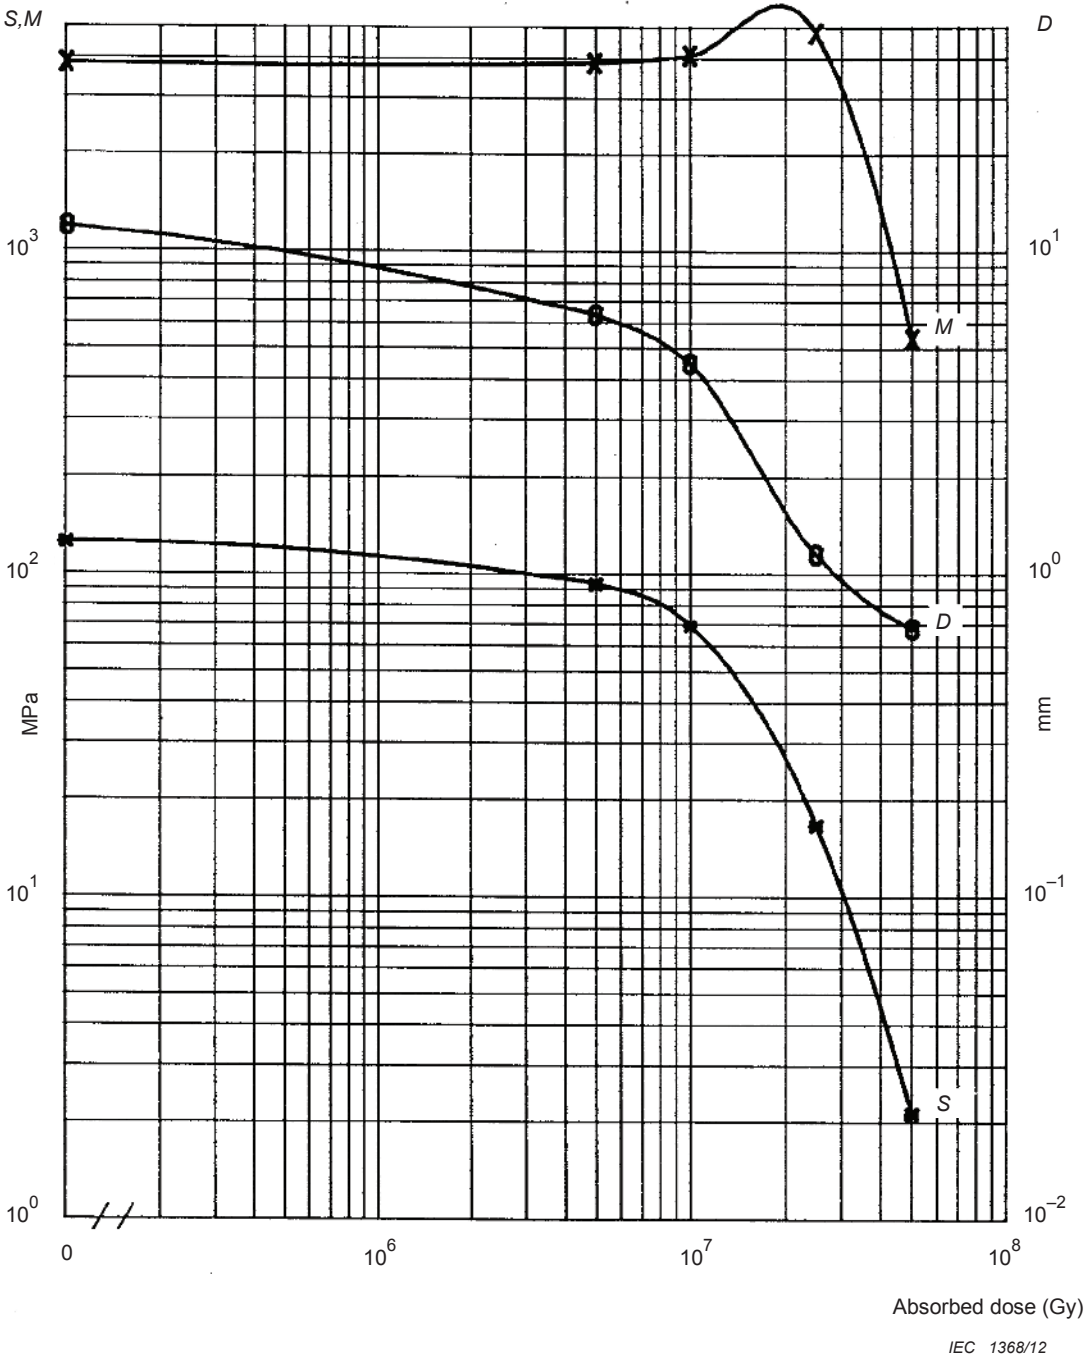


Figure A.1 – Change of mechanical properties as a function of absorbed dose for magnetic coil insulation

EXAMPLE 2 – Cable insulation

Radiation test report according to the IEC 60544 series

1. Material: Low-density polyethylene. Thermoplastic cable insulation, 0,08 % phenolic type stabilizer, density 0,936 g/cm³.

Supplier: NN
2. Irradiation

Series A, B, C, D: Pool-reactor, position E1, in air, 25 °C
Absorbed doses: 5 × 10⁵, 1 × 10⁶, 2 × 10⁶, 5 × 10⁶, Gy
Dose rate: 7 to 70 Gy/s
Irradiation date: xy

Series E, F: ⁶⁰Co source in air, 20 °C
Absorbed doses: 5 × 10⁵, 1 × 10⁶ Gy
Dose rate: 0,03 Gy/s
Irradiation date: xy
3. Test

Method: Tensile test, ISO 527, Hardness test ISO 868
Sample: Type S2 taken from moulded plates (2 mm thickness)
Critical property: Elongation at break
End-point criterion: 50 % of initial value
Test date: (Series A, B, C, D) xy
(Series E, F) xy
4. Results: See Table A.2.

Table A.2 – Example 2 – Cable insulation

No.	Material, Type,	Source, Series	Dose Gy	Dose rate Gy/s	Traction		Hardness Shore D
					Strength R MPa	Elongation E %	
524	PE-LD insulation thermoplastic Stabilized T/0,08	Reactor	0,0	0,0	13,7 ± 1,4	588 ± 36,0	44,0
		A	5,0 × 10 ⁵	70,0	18,1 ± 1,0	391,0 ± 4,5	45,0
		B	1,0 × 10 ⁶	56,0	10,1 ± 0,5	214,0 ± 6,0	47,5
		C	1,9 × 10 ⁶	7,8	11,8 ± 0,6	61,0 ± 2,0	52,0
		D	5,0 × 10 ⁶	56,0	9,6 ± 0,5	19,0 ± 2,2	47,0
	Idem	Cobalt 60	0,0	0,0	13,7 ± 1,4	588 ± 36,0	44,0
		E	5,0 × 10 ⁵	0,03	10,3 ± 0,5	80,1 ± 9,0	50,5
		F	1,0 × 10 ⁶	0,03	10,9 ± 0,5	55,0 ± 5,0	51,0

EXAMPLE 3 – Insulating tape

Radiation test report according to the IEC 60544 series

1. Material: Insulation tape for high-voltage machines
Silicone resin + samica + glass cloth

Supplier: NN

2. Irradiation

Spent-fuel element, in air, 45 °C

Dose rate: 2,7 Gy/s

Absorbed doses: 5×10^6 , $9,2 \times 10^6$, 5×10^7 Gy

Irradiation date: xy

3. Test

Method: Breakdown voltage at straight and 45° bent sample (IEC 60243-1)

Critical property: Breakdown voltage on straight sample


End-point criterion: 50 % of initial value

Test date: xy

4. Results: See Table A.3 and Figure A.2.

Table A.3 – Example 3 – Insulating tape

No.	Material Type Supplier Remarks	Dose Gy	Breakdown voltage kV		Radiation index at 10^5 Gy/h IEC 60544-4
			Straight	Bent 45°	
E 07	Silicone + Samica + glass cloth + PC film Insulating tape for Class F, HV machines	0,0	$5,10 \pm 0,30$	$4,50 \pm 0,54$	<6,0
		5×10^6	$1,80 \pm 0,10$	$0,90 \pm 0,07$	
		$9,2 \times 10^6$	$1,90 \pm 0,45$	$1,00 \pm 0,10$	
		5×10^7	$1,70 \pm 0,25$	$1,00 \pm 0,10$	

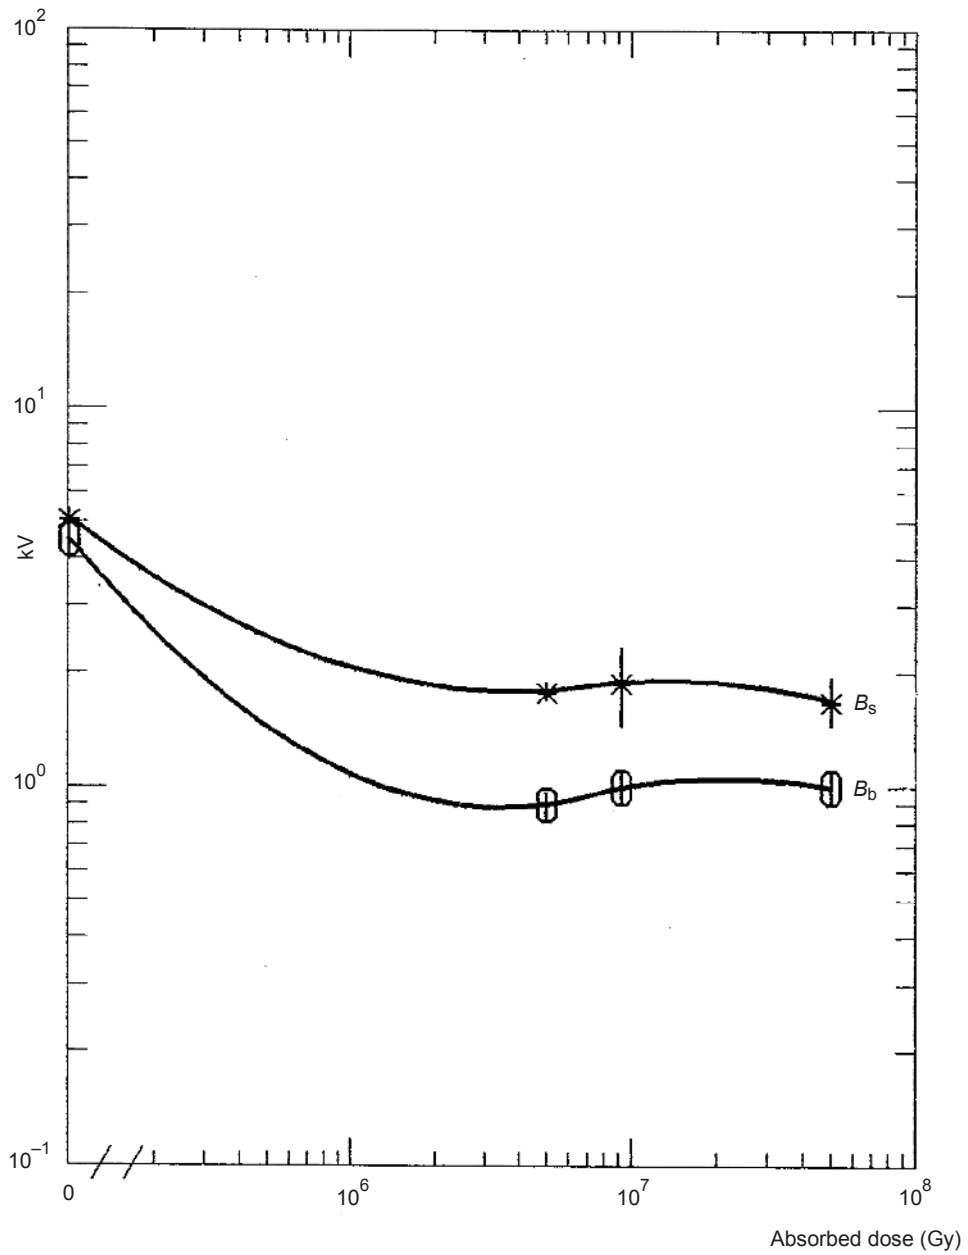

IEC 1369/12

Key

- B_s straight sample
- B_b bent sample

Figure A.2 – Breakdown voltage of insulating tape as a function of absorbed dose

Bibliography

- [1] WILSKI, H., "*Long-duration irradiation of plastics at low dose rate, Radiation Effects in Physics, Chemistry and Biology*", Proc. 2nd Int. Congr. on Radiation Research, Harrogate (1962), eds. M. Ebert and A. Howard (North-Holland Publ. Co., Amsterdam, 1963).
- [2] GILLEN, K.T. and CLOUGH, R.L., "*Occurrence and implications of radiation dose rate effects for material ageing studies*", Rad. Phys. Chem. 18 (3-4), 661-669 (1981).
- [3] ARAKAWA, K., SEGUCHI, T., WATANABE, Y., HAYAKAWA, N., KURIYAMA, I. and MACHI, S. "*Dose-rate effect on radiation-induced oxidization of polyethylene and ethylene-propylene copolymer*", J. Polym. Sci., Polym. Chem. Ed. 19, 2123 (1981).
- [4] MAIER, P. and STOLARZ, A., "*Long-term radiation effects on commercial cable insulating materials irradiated at CERN*", CERN Report 83-08 (1983).
- [5] WILSKI, H. "*Review: The radiation-induced degradation of polymers*", Rad. Phys. Chem. 29, No. 1, pp. 1-14 (1987).
- [6] WÜNDRICH, K., "*A review of radiation resistance for plastic and elastomeric materials*", Rad. Phys. Chem. 24, No. 5/6, pp. 503-510 (1985).
- [7] CLOUGH, R.L., "*Radiation resistant polymers*", in: Encyclopedia of Polymer Science and Engineering, Volume 13, Second Edition, Wiley, New York.
- [8] SEGUCHI, T. and ARAKAWA, K., "*Oxidation region in polymer materials irradiated in oxygen under pressure*", Report JAERI-M-9671, Japan Atomic Energy Research Institute (1981)(in Japanese).
- [9] CLOUGH, R.L., GILLEN, K.T., CAMPAN, J.L., GAUSSENS, G., SCHÖNBACHER, H., SEGUCHI, T., WILSKI, H. and MACHI, S. "*Accelerated aging tests for predicting radiation degradation of organic materials*", Nuclear Safety 25, 238-254 (1984).
- [10] GILLEN, K.T., and CLOUGH, R.L., "*A kinetic model for predicting oxidative degradation rates in combined radiation-thermal environments*", J. Polym. Sci., Polym. Chem. Ed. 23, 2683 (1985).
- [11] SEGUCHI, T., "*Analysis of dose rate dependence on radiation-thermal combined aging of polymer materials*", Proceedings Int. ANS/ENS Topical Meeting "Operability of Nuclear Power Systems in Normal and Adverse Environments", Albuquerque, NM, October 1986.
- [12] BURNAY, S.G. and HITCHON, J.W. "*Prediction of service lifetimes of elastomeric seals during radiation aging*", J. Nucl. Mater. 131, 197 (1985).
- [13] SEGUCHI, T., ARAKAWA, K., HAYAKAWA, N., MACHI, S., YAGYU, H., SORIMACHI, M., YAMAMOTO, Y. "*Radiation-thermal combined degradation of cable insulating materials*", The Institute of Electrical Engineers of Japan (IEEJ), paper presented at IEEJ technical meeting on electrical insulation, 1980, Tokyo, EIM-80-94, Tokyo(1980) (in Japanese) .
- [14] CLOUGH, R.L. and GILLEN, K.T. "*Combined environment aging effects*", Jour. Polym. Sci., Polym. Chem. Ed. 19 (8), 2041-2051 (1981).
- [15] SEGUCHI, T., HAYAKAWA, N., YOSHIDA, K., TAMURA, N., KATSUMURA, Y. and TABATA, Y. "*Fast neutron irradiation effects-II. Crosslinking of polyethylene, ethylen-*

propylene copolymer, and tetrafluoroethylene-propylene copolymer", Rad. Phys. Chem. 26, 221-225 (1985).

- [16] HANISCH, F., MAIER, P. , OKADA, S. and SCHÖNBACHER, H. "*The effects of radiation types and dose rates on selected cable insulating materials*", Radiat., Phys., Chem., Vol. 30, No. 1, pp 1-9 (1987).
- [17] WYANT, F., BUCKALEW, H.W., CHENION, J., CARLIN, F., GAUSSENS, G., LE TUTOUR, P. and LE MEUR, M. "*US/French Joint Research Program regarding the behaviour of polymer base materials subjected to beta radiation*", Sandia Report SAND 86-0366, NUREG/CR-4530 (1986).
- [18] STUETZER, O. "*Correlation of electric cable failure with mechanical degradation*", Sandia Report SAND 83-2622, NUREG/CR 3623 (1984).
- [19] LIPTAK, G., SCHULER, R., MAIER, P., Schönbacher, H., HABERTHÜR, B., MÜLLER, H. and ZEIER, W. "*Radiation tests on selected electrical insulating materials for high power and high voltage application*", CERN Report 85-02 (1985).
- [20] IEC 60544-3, *Guide for determining the effects of ionizing radiation on insulating materials – Part 3: Test procedures for permanent effects* (withdrawn 1991)

NOTE 1 CERN reports can be obtained from: Scientific Information Service CERN, CH-1211 Geneva 23, Switzerland.

NOTE 2 JAERI reports can be obtained from: Takasaki Radiation Chemistry Research Establishment JAEA, Takasaki, Watanuki-machi, Gunma-ken 370-1292 Japan

NOTE 3 SANDIA reports can be obtained from: National Technical Information Service Springfield, Virginia 22161, USA.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™