

BS EN 61951-2:2011



BSI Standards Publication

Secondary cells and batteries containing alkaline or other non-acid electrolytes — Portable sealed rechargeable single cells

Part 2: Nickel-metal hydride

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN 61951-2:2011. It is identical to IEC 61951-2:2011. It supersedes BS EN 61951-2:2003 which will be withdrawn on 29th June 2014.

The UK participation in its preparation was entrusted by Technical Committee PEL/21, Secondary cells and batteries, to Subcommittee PEL/21/1, Secondary cells and batteries containing alkaline and other non-acidic electrolytes.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 57918 9

ICS 29.220.30

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 August 2011.

Amendments issued since publication

Amd. No.	Date	Text affected
----------	------	---------------

English version

**Secondary cells and batteries containing alkaline or other non-acid electrolytes -
 Portable sealed rechargeable single cells -
 Part 2: Nickel-metal hydride
 (IEC 61951-2:2011)**

Accumulateurs alcalins et autres
 accumulateurs à électrolyte non acide -
 Accumulateurs individuels portables
 étanches -
 Partie 2: Nickel-métal hydrure
 (CEI 61951-2:2011)

Akkumulatoren und Batterien mit
 alkalischem oder anderen
 nichtsäurehaltigen Elektrolyten -
 Tragbare wiederaufladbare gasdichte
 Einzelzellen -
 Teil 2: Nickel-Metallhydrid
 (IEC 61951-2:2011)

This European Standard was approved by CENELEC on 2011-06-29. CENELEC members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CENELEC member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CENELEC member into its own language and notified to the Central Secretariat has the same status as the official versions.

CENELEC members are the national electrotechnical committees of Austria, Belgium, Bulgaria, Croatia, Cyprus, the Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, the Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

CENELEC

European Committee for Electrotechnical Standardization
 Comité Européen de Normalisation Electrotechnique
 Europäisches Komitee für Elektrotechnische Normung

Management Centre: Avenue Marnix 17, B - 1000 Brussels

Foreword

The text of document 21A/484/FDIS, future edition 3 of IEC 61951-2, prepared by SC 21A, Secondary cells and batteries containing alkaline or other non-acid electrolytes, of IEC TC 21, Secondary cells and batteries, was submitted to the IEC-CENELEC parallel vote and was approved by CENELEC as EN 61951-2 on 2011-06-29.

This European Standard supersedes EN 61951-2:2003.

EN 61951-2:2011 includes the following significant technical changes with respect to EN 61951-2:2003:

- Clause 4: addition of 2 parameters;
- Clause 5: addition of cells type “S” and cells type “T”;
- Subclause 6.1.2: addition of new cylindrical cells;
- Subclause 7.8: addition of a specific test for “S” cells.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN and CENELEC shall not be held responsible for identifying any or all such patent rights.

The following dates were fixed:

- latest date by which the EN has to be implemented
at national level by publication of an identical
national standard or by endorsement (dop) 2012-03-29
- latest date by which the national standards conflicting
with the EN have to be withdrawn (dow) 2014-06-29

Annex ZA has been added by CENELEC.

Endorsement notice

The text of the International Standard IEC 61951-2:2011 was approved by CENELEC as a European Standard without any modification.

In the official version, for Bibliography, the following notes have to be added for the standards indicated:

- | | | |
|------------------|------|--------------------------------|
| IEC 60051 series | NOTE | Harmonized in EN 60051 series. |
| IEC 61434 | NOTE | Harmonized as EN 61434. |
-

Annex ZA (normative)

Normative references to international publications with their corresponding European publications

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

NOTE When an international publication has been modified by common modifications, indicated by (mod), the relevant EN/HD applies.

<u>Publication</u>	<u>Year</u>	<u>Title</u>	<u>EN/HD</u>	<u>Year</u>
IEC 60050-482	-	International Electrotechnical Vocabulary - Part 482: Primary and secondary cells and batteries	-	-
IEC 60086	Series	Primary batteries	EN 60086	Series
IEC 60086-1	2006	Primary batteries - Part 1: General	EN 60086-1 ¹⁾	2007
IEC 60086-2	2006	Primary batteries - Part 2: Physical and electrical specifications	EN 60086-2 ²⁾	2007
IEC 60410	-	Sampling plans and procedures for inspection by attributes	-	-
IEC 61959	-	Secondary cells and batteries containing alkaline or other non-acid electrolytes - Mechanical tests for sealed portable secondary cells and batteries	EN 61959	-
IEC 62133	-	Secondary cells and batteries containing alkaline or other non-acid electrolytes - Safety requirements for portable sealed secondary cells, and for batteries made from them, for use in portable applications	EN 62133	-

¹⁾ EN 60086-1 is superseded by EN 60086-1:2011, which is based on IEC 60086-1:2011.

²⁾ EN 60086-2 is superseded by EN 60086-2:2011, which is based on IEC 60086-2:2011.

CONTENTS

1	Scope	6
2	Normative references	6
3	Terms and definitions	6
4	Parameter measurement tolerances	7
5	Cell designation and marking	8
5.1	Cell designation	8
5.1.1	Small prismatic cells and cylindrical cells	8
5.1.2	Button cells	9
5.2	Cell termination	9
5.3	Marking	9
5.3.1	Small prismatic cells and cylindrical cells	9
5.3.2	Button cells	10
6	Dimensions	10
6.1	Small prismatic cells and cylindrical cells	10
6.1.1	General	10
6.1.2	Small prismatic cells	11
6.1.3	Cylindrical cells	12
6.2	Button cells	14
7	Electrical tests	14
7.1	General	14
7.2	Charging procedure for test purposes	14
7.3	Discharge performance	15
7.3.1	General	15
7.3.2	Discharge performance at 20 °C	15
7.3.3	Discharge performance at 0 °C	15
7.3.4	Discharge performance for rapid charge cells (R cells)	16
7.4	Charge (capacity) retention	16
7.5	Endurance	17
7.5.1	Endurance in cycles	17
7.5.2	Permanent charge endurance	19
7.6	Charge acceptance at constant voltage	23
7.7	Overcharge	23
7.7.1	Small prismatic, L, M, H, X, LS or MS cylindrical, and button cells	23
7.7.2	LT/LU, MT/MU or HT/HU cylindrical cells	23
7.7.3	R cylindrical cells	23
7.8	Safety device operation	24
7.9	Surface temperature limitation device operation (for S cell only)	24
7.10	Storage	25
7.11	Charge acceptance at +55 °C for LT, MT or HT cylindrical cells	25
7.12	Internal resistance	26
7.12.1	General	26
7.12.2	Measurement of the internal a.c. resistance	26
7.12.3	Measurement of the internal d.c. resistance	27
8	Mechanical tests	27

9	Safety requirements	27
10	Type approval and batch acceptance.....	27
10.1	Type approval	27
10.1.1	Type approval for small prismatic cells and button cells.....	27
10.1.2	Type approval for cylindrical cells.....	28
10.2	Batch acceptance.....	29
	Bibliography.....	31
	Figure 1 – Jacketed cylindrical cells.....	11
	Figure 2 – Jacketed small prismatic cells.....	11
	Figure 3 – Jacketed cells dimensionally interchangeable with primary cells	12
	Figure 4 – Button cells	14
	Table 1 – Dimensions of jacketed small prismatic cells	11
	Table 2 – Jacketed cylindrical cells dimensionally interchangeable with primary cells	12
	Table 3 – Jacketed cylindrical cells not dimensionally interchangeable with primary cells.....	13
	Table 4 – Dimensions of button cells	14
	Table 5 – Discharge performance at 20 °C for small prismatic cells and cylindrical cells.....	15
	Table 6 – Discharge performance at 20 °C for button cells.....	15
	Table 7 – Discharge performance at 0 °C for small prismatic cells and cylindrical cells.....	16
	Table 8 – Discharge performance at 0 °C for button cells.....	16
	Table 9 – Endurance in cycles for small prismatic, button and cylindrical cells not dimensionally interchangeable with primary cells	17
	Table 10 – Endurance in cycles for H or X cells	18
	Table 11 – Endurance in cycles for X cells.....	18
	Table 12 – Endurance in cycles for HR or XR cells	19
	Table 13 – Permanent charge endurance for L, M, H or X cells.....	19
	Table 14 – Permanent charge endurance for LT, MT or HT cells.....	21
	Table 15 – Permanent charge endurance for LU, MU or HU cells.....	22
	Table 16 – Overcharge at 0 °C.....	23
	Table 17 – Charge and discharge at +55 °C.....	26
	Table 18 – Constant discharge currents used for measurement of d.c. resistance.....	27
	Table 19 – Sequence of tests for type approval for small prismatic and for button cells	28
	Table 20 – Sequence of tests for type approval for cylindrical cells.....	29
	Table 21 – Recommended test sequence for batch acceptance	30

SECONDARY CELLS AND BATTERIES CONTAINING ALKALINE OR OTHER NON-ACID ELECTROLYTES – PORTABLE SEALED RECHARGEABLE SINGLE CELLS –

Part 2: Nickel-metal hydride

1 Scope

This part of IEC 61951 specifies marking, designation, dimensions, tests and requirements for portable sealed nickel-metal hydride, small prismatic, cylindrical and button rechargeable single cells, suitable for use in any orientation.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

IEC 60050-482, *International Electrotechnical Vocabulary – Part 482: Primary and secondary cells and batteries*

IEC 60086 (all parts), *Primary batteries*

IEC 60086-1 (2006), *Primary batteries – Part 1: General*

IEC 60086-2 (2006), *Primary batteries – Part 2: Physical and electrical specifications*

IEC 60410, *Sampling plans and procedures for inspection by attributes*

IEC 61959, *Secondary cells and batteries containing alkaline or other non-acid electrolytes – Mechanical tests for sealed portable secondary cells and batteries*

IEC 62133, *Secondary cells and batteries containing alkaline or other non-acid electrolytes – Safety requirements for portable sealed secondary cells and for batteries made from them, for use in portable applications*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in the IEC 60050-482 and the following apply.

3.1

nominal voltage

suitable approximate value of voltage used to designate or identify the voltage of a cell or battery

NOTE 1 The nominal voltage of a sealed nickel-metal hydride rechargeable single cell is 1,2 V.

NOTE 2 The nominal voltage of a battery of *n* series connected cells is equal to *n* times the nominal voltage of a single cell.

3.2**rated capacity**

quantity of electricity C_5 Ah (ampere-hours) declared by the manufacturer which a single cell can deliver during a 5 h period when charging, storing and discharging under the conditions specified in 7.3.2

3.3**small prismatic cell**

cell in the form of a rectangular parallelepiped whose width and thickness dimensions are not more than 25 mm

3.4**cylindrical cell**

cell of circular cross-section in which the overall height is equal to, or greater than the overall diameter

3.5**button cell**

cell of circular cross-section in which the overall height is less than the overall diameter

3.6**nickel-metal hydride cell**

cell containing a nickel hydroxide compound for the positive electrode, a hydrogen absorbing alloy for the negative electrode, and potassium hydroxide or other alkaline solution as electrolyte. Positive electrodes are isolated from negative electrodes by a separator

3.7**sealed cell**

cell which remains closed and does not release either gas or liquid when operated within the limits of charge and temperature specified by the manufacturer. The cell is equipped with a safety device to prevent dangerously high internal pressure. The cell does not require addition to the electrolyte and is designed to operate during its life in its original sealed state

NOTE The nickel-metal hydride cell, however, may release gas towards the end of its life due to the accumulation of hydrogen in the cell.

3.8**portable cell**

cell designed mainly for use in an easily hand-carried battery

3.9**surface temperature limited cell**

cell which performs a function that prevents the temperature increase from a certain standard point even at the moment of anomaly occurrence such as short circuit of cell

4 Parameter measurement tolerances

The overall accuracy of controlled or measured values, relative to the specified or actual values, shall be within the following tolerances:

- a) $\pm 1 \%$ for voltage;
- b) $\pm 1 \%$ for current;
- c) $\pm 1 \%$ for capacity;
- d) $\pm 2 \text{ }^\circ\text{C}$ for temperature;
- e) $\pm 0,1 \%$ for time;
- f) $\pm 0,1 \text{ mm}$ for dimensions;

g) $\pm 2\%$ for humidity.

These tolerances comprise the combined accuracy of the measuring instruments, the measurement techniques used and all other sources of error in the test procedure.

The details of the instrumentation used shall be provided in each report of results.

5 Cell designation and marking

5.1 Cell designation

5.1.1 Small prismatic cells and cylindrical cells

5.1.1.1 General

Sealed nickel-metal hydride small prismatic rechargeable single cells and cylindrical rechargeable single cells shall be designated by a letter L, M, H or X which signifies:

- low rate of discharge (L);
- medium rate of discharge (M);
- high rate of discharge (H);
- very high rate of discharge (X).

NOTE These cells are typically but not exclusively used for the following discharge rates:

- L up to $0,5 I_t$ A;
- M up to $3,5 I_t$ A;
- H up to $7,0 I_t$ A;
- X up to and above $7,0 I_t$ A.

When a cell is intended for permanent charge at elevated temperatures, typically higher than $40\text{ }^\circ\text{C}$, a letter "T" is placed after the letter L, M, H or X.

When a cell is intended for permanent charge at elevated temperatures, typically higher than $50\text{ }^\circ\text{C}$, a letter "U" is placed after the letter L, M, H or X.

When a cell is intended for surface temperature limitation, a letter "S" is placed after the letter L or M.

When a cell is intended for rapid charge, typically at $1,0 I_t$ A, a letter "R" is placed after the letter L, M, H or X.

5.1.1.2 Small prismatic cells

Sealed nickel-metal hydride small prismatic rechargeable single cells shall be designated by the letters "HF" followed by a letter L, M, H or X followed by three groups of figures, each group being separated by a solidus, as follows:

- a) The two figures to the left of the first solidus shall indicate the maximum width specified for the cell, expressed in millimetres, rounded up to the next whole number.
- b) The two figures in the middle shall indicate the maximum thickness specified for the cell, expressed in millimetres, rounded up to the next whole number.
- c) The two figures to the right of the second solidus shall indicate the maximum height specified for the cell, expressed in millimetres, rounded up to the next whole number.

EXAMPLE HFL 18/07/49 designation identifies a small prismatic cell of low discharge rate capability, with a maximum width of 18 mm, a maximum thickness of 7 mm and a maximum height of 49 mm.

5.1.1.3 Cylindrical cells

Sealed nickel-metal hydride cylindrical rechargeable single cells shall be designated by the letters "HR" followed by a letter L, M, H or X followed by two groups of figures, each group being separated by a solidus, as follows:

- a) The two figures to the left of the solidus shall indicate the maximum diameter specified for the cell, expressed in millimetres, rounded up to the next whole number.
- b) The two figures to the right of the solidus shall indicate the maximum height specified for the cell, expressed in millimetres, rounded up to the next whole number.

When a manufacturer designs a cell with dimensions and tolerances which make it interchangeable with a primary cell, the designation of Table 2 shall also be marked on the cell.

EXAMPLE 1 HRL 33/62 designation identifies a cylindrical cell of low discharge rate capability, with a maximum diameter of 33 mm and a maximum height of 61,5 mm.

EXAMPLE 2 HRLT 33/62 designation identifies a cylindrical cell of low discharge rate capability, intended for permanent charge at elevated temperatures with a maximum diameter of 33 mm and a maximum height of 61,5 mm.

EXAMPLE 3 HRXR 23/43 designation identifies a cylindrical cell of very high discharge rate capability, intended for rapid charge, with a maximum diameter of 23 mm and a maximum height of 43 mm.

For cells dimensionally interchangeable with primary cells, the following single or double figures following the letter L, M, R or S may indicate:

- 20- Size D;
- 14- Size C;
- 6- Size AA;
- 03- Size AAA.

NOTE Cells dimensionally interchangeable with primary cells correspond to M type unless otherwise specified

For the purpose of this explanation, an example is given below.

EXAMPLE 4 HRMR03 designation identifies a sealed nickel-metal hydride cylindrical rechargeable single cell, of medium discharge rate capability, also intended for rapid charge, dimensionally interchangeable with primary cell and whose type designation is AAA.

5.1.2 Button cells

Sealed nickel-metal hydride button rechargeable single cells shall be designated by the letters "HB" followed by two groups of figures separated by a solidus, as follows:

- a) The three figures to the left of the solidus shall indicate the maximum diameter specified for the cell, expressed in tenths of millimetres, rounded up to the next whole number.
- b) The three figures to the right of the solidus shall indicate the maximum height specified for the cell, expressed in tenths of millimetres, rounded up to the next whole number.

EXAMPLE HB 116/054 designation identifies a button cell, with a maximum diameter of 11,6 mm and a maximum height of 5,4 mm.

5.2 Cell termination

This standard does not specify cell termination.

5.3 Marking

5.3.1 Small prismatic cells and cylindrical cells

Each jacketed cell supplied without connections shall carry durable markings giving the following minimum information:

- sealed rechargeable nickel-metal hydride or Ni-MH;
- designation as specified in 5.1 (in addition, it is permissible for a manufacturer to use his own type designation);
- rated capacity;
- nominal voltage;
- recommended charge rate and time or permanent charge current for "T" cells;
- polarity;
- date of manufacture (which may be in code);
- name or identification of manufacturer or supplier.

NOTE In general, sealed nickel-metal hydride rechargeable single cells with connection tabs need no labels if they form an integral part of a battery, in which case, the battery itself is marked with the above information.

5.3.2 Button cells

Each button cell supplied without connection shall carry durable markings giving the following minimum information:


- designation as specified in 5.1;
- polarity;
- date of manufacture (which may be in code);
- name or identification of manufacturer or supplier.

6 Dimensions


6.1 Small prismatic cells and cylindrical cells

6.1.1 General

Figures 1 and 2 show the shape of the cells.

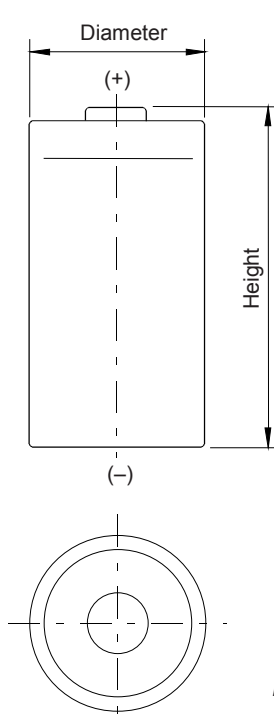

IEC 1140/03

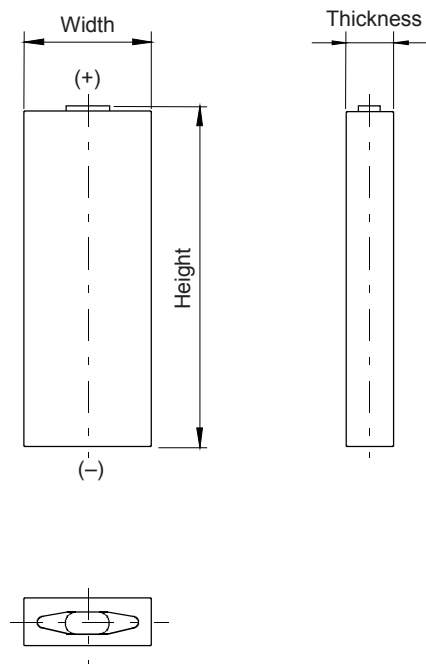

IEC 1141/03

Figure 1 – Jacketed cylindrical cells

Figure 2 – Jacketed small prismatic cells

6.1.2 Small prismatic cells

Table 1 shows the dimensions for jacketed small prismatic cells.

Table 1 – Dimensions of jacketed small prismatic cells

Cell designation	Width mm	Thickness mm	Height mm
HF 15/08/49	14,5	7,4	48,2
HF 15/09/49	14,5	8,3	48,2
HF 16/07/34 ^a	16,0	6,6	34,0
HF 18/07/36	17,3	6,1	35,7
HF 18/07/49	17,3	6,1	48,2
HF 18/09/49	17,3	8,3	48,2
HF 18/07/68	17,3	6,1	67,3
HF 18/11/68	17,3	10,7	67,3
HF 18/18/68	17,3	17,3	67,3
HF 23/11/68	22,7	10,7	67,3
HF 23/15/68	22,7	14,5	67,3

^a New cell.

6.1.3 Cylindrical cells

6.1.3.1 Cells dimensionally interchangeable with primary cells

Table 2 gives the requirements relative to the dimensions for jacketed cylindrical cells which are dimensionally interchangeable with primary cells.

Table 2 – Jacketed cylindrical cells dimensionally interchangeable with primary cells

Cell Designation a	Type designation (reference) b	Corresponding primary cell CEI 60086 c	Nominal voltage (V)	Dimensions (mm)										
				A	B	C	D _d	E	F		G	Φ		ΦP
				Max	Min	Min	-	Max	Max	Min	Min	Max	Min	Max
HR03	AAA	R03 LR03	1,2	44,5	(43,3)	4,3	-	0,5	3,8	(2,0)	0,8	10,5	9,5	0,4
HR6	AA	R6 LR6		50,5	(49,2)	7,0	-	0,5	5,5	(4,2)	1,0	14,5	13,5	0,5
HR14	C	R14 LR14		50,0	(48,6)	13,0	-	0,9	7,5	(5,5)	1,5	26,2	24,9	1,0
HR20	D	R20 LR20		61,5	(59,5)	18,0	-	1,0	9,5	(7,8)	1,5	34,2	32,3	1,0

NOTE Figures in parentheses are reference values.

^a Cell designations shall be in accordance with the nomenclature rules given in IEC 60086-1.

^b In some countries, these cell types are also known as AAA (R 03); AA (R 6); C (R 14); D (R 20).

^c Carbon zinc cells (R) and alkaline primary cells (LR) shall be compliant with the provisions of IEC 60086-2, respectively.

^d There is no specification for the value "D" for sealed nickel-metal hydride cylindrical rechargeable single cells interchangeable with primary cells.

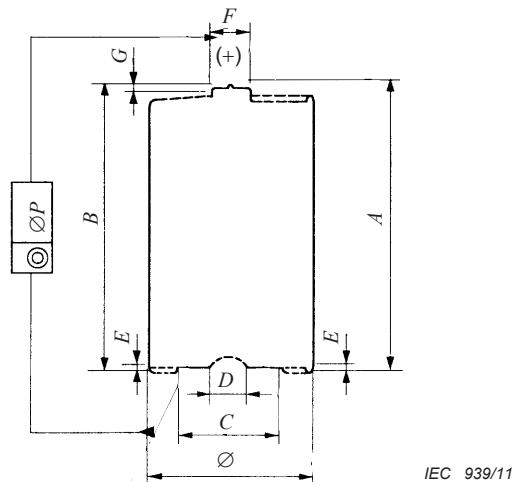


Figure 3 – Jacketed cells dimensionally interchangeable with primary cells

The cell dimensions of Figure 3 are given below:

- A : maximum overall height of the cell;
- B : minimum distance between the flats of the positive and the negative contacts;
- C : minimum outer diameter of the negative flat contact surface;
- D : maximum inner diameter of the negative flat contact surface;

- e) E : maximum recess of the negative flat contact surface;
 f) F : maximum diameter of the positive contact within the specified projection height;
 g) G : minimum projection of the flat positive contact;
 h) \varnothing : maximum and minimum diameters of the cell;
 i) $\varnothing P$: concentricity of the positive contact.

6.1.3.2 Cells not dimensionally interchangeable with primary cells

Table 3 shows the dimensions for jacketed cylindrical cells not dimensionally interchangeable with primary cells.

Table 3 – Jacketed cylindrical cells not dimensionally interchangeable with primary cells


Cell designation ^a	Diameter mm	Height mm
HR 11/45	10,5	44,5
HR 11/51	10,5	50,5
HR 11/67	10,5	67,0
HR 15/43	14,5	43,0
HR 15/49	14,5	49,0
HR 15/51	14,5	50,5
^b HR 15/67	15,0	67,0
HR 17/29	17,0	28,5
HR 17/43	17,0	43,0
HR 17/50	17,0	50,0
HR 17/67	17,0	67,0
^b HR 18/44	18,0	43,5
^b HR 18/67	18,0	67,0
^b HR 19/67	19,0	67,0
HR 23/34	23,0	34,0
HR 23/43	23,0	43,0
^b HR 23/44	23,0	43,5
^b HR 23/50	23,0	50,0
^b HR 23/60	23,0	61,0
HR 26/47	25,8	47,0
HR 26/50	25,8	50,0
HR 33/36	33,0	36,0
HR 33/62	33,0	61,5
HR 33/91	33,0	91,0
^b HR 34/60	33,5	59,5

^a The letters HR to be followed by L, M, H or X and T and/or R as appropriate (see 5.1).

^b 8 new cells.

6.2 Button cells

Cells shall be constructed as design I or II.

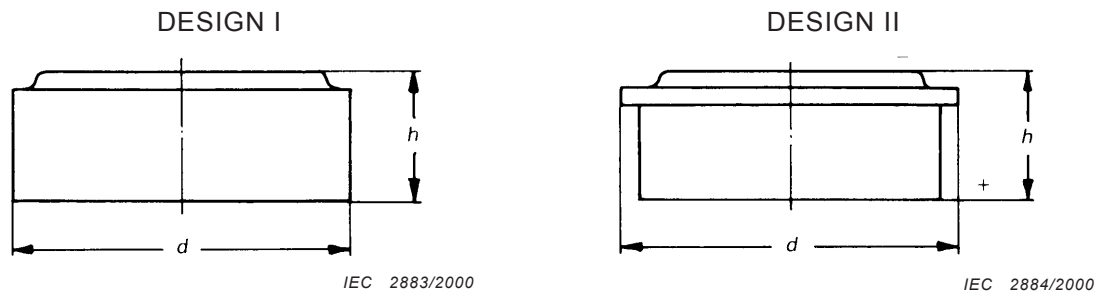

NOTE The polarity of design I is not standardized.

Figure 4 – Button cells

Table 4 shows the dimensions of sealed nickel-metal hydride button rechargeable single cells.

Table 4 – Dimensions of button cells

Cell designation	Overall diameter d mm	Overall height h mm
HB 079/054	7,9	5,4
HB 116/054	11,6	5,4
HB 156/064	15,6	6,4
HB 222/048	22,2	4,8
HB 252/061	25,2	6,1
HB 252/065	25,2	6,5
HB 252/078	25,2	7,8
HB 347/060	34,7	6,0

7 Electrical tests

7.1 General

Charge and discharge currents for the tests in accordance with this clause and with Clause 5 shall be based on the rated capacity, (C_5 Ah). These currents are expressed as multiples of I_t A, where I_t A = C_5 Ah/1 h.

In all tests, except where noted, no leakage of electrolyte in liquid form shall be observed.

7.2 Charging procedure for test purposes

Unless otherwise stated in this standard, the charging procedure for test purposes shall be carried out in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$ and a relative humidity of $65\% \pm 20\%$, at a constant current of $0,1 I_t$ A, for 16 h. The tests shall be performed within one month of the arrival date or the purchasing date.

Prior to charging, the cell shall be discharged in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2 I_t$ A, down to a final voltage of 1,0 V.

7.3 Discharge performance

7.3.1 General

The following discharge tests shall be carried out in the sequence given.

7.3.2 Discharge performance at 20 °C

The cell shall be charged in accordance with 7.2. After charging, the cell shall be stored in an ambient temperature of 20 °C ± 5 °C, for not less than 1 h and not more than 4 h.

The cell shall then be discharged in an ambient temperature of 20 °C ± 5 °C and as specified in Tables 5 or 6. The duration of discharge shall be not less than the values specified in Tables 5 or 6.

The 0,2 I_t A discharge test is performed in order to verify the declared rated capacity of the cell.

Table 5 – Discharge performance at 20 °C for small prismatic cells and cylindrical cells

Discharge conditions		Minimum discharge duration h/min			
Rate of constant current A	Final voltage V	Cell designation			
		L/LT/LU/LS	M/MT/MU/MS	H/HT/HU	X
0,2 I_t ^a	1,0	5 h	5 h	5 h	5 h
1,0 I_t	0,9	–	42 min	48 min	54 min
5,0 I_t ^b	0,8	–	–	6 min	9 min
10,0 I_t ^b	0,7	–	–	–	4 min

^a Five cycles are permitted for this test. The test shall be terminated at the end of the first cycle which meets the requirement.

^b Prior to the 5 I_t A and 10 I_t A tests, a conditioning cycle may be included if necessary. This cycle shall consist of charging at 0,1 I_t A in accordance with 7.2 and discharging at 0,2 I_t A in an ambient temperature of 20 °C ± 5 °C according to 7.3.2.

Table 6 – Discharge performance at 20 °C for button cells

Discharge conditions		Minimum discharge duration h/min
Rate of constant current A	Final voltage V	
0,2 I_t ^a	1,0	5 h
1,0 I_t	0,9	35 min

^a Five cycles are permitted for this test. The test shall be terminated at the end of the first cycle which meets the requirement.

7.3.3 Discharge performance at 0 °C

The cell shall be charged in accordance with 7.2. After charging, the cell shall be stored, in an ambient temperature of 0 °C ± 2 °C for not less than 16 h and not more than 24 h.

The cell shall then be discharged in an ambient temperature of 0 °C ± 2 °C and as specified in Tables 7 or 8. The duration of discharge shall be not less than the values specified in Tables 7 or 8.

Table 7 – Discharge performance at 0 °C for small prismatic cells and cylindrical cells

Discharge conditions		Minimum discharge duration h/min			
Rate of constant current A	Final voltage V	Cell designation			
		L/LT/LU/LS	M/MT/MU/MS	H/HT/HU	X
0,2 I_t	1,0	2 h	4 h	4 h	4 h 30 min
1,0 I_t	0,9	–	36 min	42 min	48 min
2,0 I_t ^a	0,8	–	–	15 min	21 min
3,0 I_t ^a	0,8	–	–	–	12 min

^a Prior to the 2,0 I_t A and 3,0 I_t A tests, a conditioning cycle may be included if necessary. This cycle shall consist of charging at 0,1 I_t A in accordance with 7.2 and discharging at 0,2 I_t A in an ambient temperature of 20 °C ± 5 °C according to 7.3.2.

Table 8 – Discharge performance at 0 °C for button cells

Discharge conditions		Minimum discharge duration h/min
Rate of constant current A	Final voltage V	
0,2 I_t	1,0	4 h
1,0 I_t	0,9	27 min

7.3.4 Discharge performance for rapid charge cells (R cells)

R cells shall be charged at a constant current of 1,0 I_t A for 1,2 h or other appropriate charge termination method as recommended by the cell manufacturer, followed by a charge at 0,1 I_t A for 2 h, in an ambient temperature of 20 °C ± 5 °C. After charging, the cell shall be stored and discharged as specified in 7.3.2 and 7.3.3.

The duration of discharge shall be not less than the values specified in Table 5 for discharge at 20 °C ± 5 °C and in Table 7 for discharge at 0 °C ± 2 °C.

7.4 Charge (capacity) retention

The charge (capacity) retention shall be determined by the following test. After charging in accordance with 7.2, the cell shall be stored on open circuit for 28 days. The average ambient temperature shall be 20 °C ± 2 °C. The temperature may be allowed to vary within the range of 20 °C ± 5 °C for short periods during the storage.

The cells shall be discharged under the conditions specified in 7.3.2 at a rate of 0,2 I_t A.

The duration of discharge after 28 days storage at 20 °C shall be not less than:

- 3 h for small prismatic cells and cylindrical cells;
- 3 h 45 min for button cells.

7.5 Endurance

7.5.1 Endurance in cycles

7.5.1.1 General

Prior to the endurance in cycles test, the cell shall be discharged at a constant current of $0,2 I_t$ A to a final voltage of 1,0 V.

The following endurance test shall then be carried out, irrespective of cell designation, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$. Charge and discharge shall be carried out at constant current throughout, in accordance with the conditions specified in Tables 9, 10, 11 and 12. Precautions shall be taken to prevent the cell-case temperature from rising above 35 °C during the test, by providing a forced air draught if necessary.

NOTE The actual cell temperature, not the ambient temperature, determines cell performance.

7.5.1.2 Small prismatic, button and cylindrical cells not dimensionally interchangeable with primary cells

Table 9 – Endurance in cycles for small prismatic, button and cylindrical cells not dimensionally interchangeable with primary cells

Cycle number	Charge	Stand in charged condition	Discharge
1	$0,10 I_t$ A for 16 h	None	$0,25 I_t$ A for 2 h 20 min ^a
2 to 48	$0,25 I_t$ A for 3 h 10 min	None	$0,25 I_t$ A for 2 h 20 min ^a
49	$0,25 I_t$ A for 3 h 10 min	None	$0,25 I_t$ A to 1,0 V
50	$0,10 I_t$ A for 16 h	1 h to 4 h	$0,20 I_t$ A to 1,0 V ^b

^a If the cell voltage drops below 1,0 V, discharge may be discontinued.

^b It is permissible to allow sufficient open-circuit rest time after the completion of discharge at cycle 50, so as to start cycle 51 at a convenient time. A similar procedure may be adopted at cycles 100, 150, 200, 250, 300, 350, 400 and 450.

Cycles 1 to 50 shall be repeated until the discharge duration on any 50th cycle becomes less than 3 h. At this stage, a repeat capacity measurement as specified for cycle 50 shall be carried out.

The endurance test is considered complete when two such successive capacity cycles give a discharge duration of less than 3 h. The total number of cycles obtained when the test is completed shall be not less than:

- 400 for small prismatic cells;
- 500 for L/LR, M/MR, H/HR or X/XR cells;
- 50 for LT/LU, MT/MU or HT/HU cells;
- 500 for button cells.

7.5.1.3 Cylindrical cells dimensionally interchangeable with primary cells

The cell shall be tested in accordance with 7.5.1.2. The total number of cycles obtained when the test is completed shall be not less than:

- 500 for AAA cells with a rated capacity less than 800 mAh;
- 300 for AAA cells with a rated capacity of 800 mAh or more;
- 500 for AA cells with a rated capacity less than 2 100 mAh;
- 300 for AA cells with a rated capacity of 2 100 mAh or more;
- 500 for D and C cells.

7.5.1.4 Cylindrical cells (accelerated test procedures)

7.5.1.4.1 General

In order to accelerate the test or to use cycling conditions approximating those in actual applications, one of the following alternative procedures, shown in Tables 10, 11 and 12, relevant to the cell may be carried out as an alternative to 7.5.1.2.

7.5.1.4.2 H or X cells

Table 10 – Endurance in cycles for H or X cells

Cycle number	Charge	Stand in charged condition	Discharge	Total duration including subsequent rest
1	0,1 I_t A for 16 h	30 min	1,0 I_t A to 1,0 V	90 min
2 to 48	0,3 I_t A for 4h ^a	30 min	1,0 I_t A to 1,0 V	90 min
49	0,3 I_t A for 4h ^a	24 h	1,0 I_t A to 1,0 V	90 min
50	0,1 I_t A for 16 h	1 h to 4h	0,2 I_t A to 1,0 V	^b

^a Or appropriate charge termination, as recommended by the manufacturer.

^b It is permissible to allow sufficient open-circuit rest time after the completion of discharge at cycle 50, so as to start cycle 51 at a convenient time. A similar procedure may be adopted at cycles 100, 150, 200, 250, 300, 350, 400, and 450.

Cycles 1 to 50 shall be repeated until the discharge duration to the final voltage of 1,0 V on any 49th cycle becomes less than 30 min or until the discharge duration to the final voltage of 1,0 V on any 50th cycle becomes less than 3 h. At this stage, a repeat capacity measurement as specified for cycle 50 shall be carried out and if the discharge time is less than 3 h again the test is terminated.

The total number of cycles obtained when the test is completed shall be not less than 500.

7.5.1.4.3 X cells

Table 11 – Endurance in cycles for X cells

Cycle number	Charge	Stand in charged condition	Discharge	
			Conditions	Total duration including subsequent rest
1	0,1 I_t A for 16 h	30 min	5,0 I_t A to 0,8 V	42 min
2 to 48	1,0 I_t A for 1h ^a	30 min	5,0 I_t A to 0,8 V	42 min
49	1,0 I_t A for 1h ^a	24 h	5,0 I_t A to 0,8 V	42 min
50	0,1 I_t A for 16 h	1 h to 4 h	0,2 I_t A to 1,0 V ^b	^b

^a Or appropriate charge termination, as recommended by the manufacturer.

^b It is permissible to allow sufficient open-circuit rest time after the completion of discharge at cycle 50, so as to start cycle 51 at a convenient time. A similar procedure may be adopted at cycles 100, 150, 200, 250, 300, 350, 400 and 450.

Cycles 1 to 50 shall be repeated until the discharge duration to the final voltage of 0,8 V on any 49th cycle becomes less than 5 min or until the discharge duration to the final voltage of 1,0 V on any 50th cycle becomes less than 3 h. At this stage, a repeat capacity measurement as specified for cycle 50 shall be carried out and if the discharge time is less than 3 h again the test is terminated.

The total number of cycles obtained when the test is completed shall be not less than 500.

7.5.1.4.4 HR or XR cells

Table 12 – Endurance in cycles for HR or XR cells

Cycle number	Charge	Stand in charged condition	Discharge	
			Conditions	Total duration including subsequent rest
1	0,1 I_t A for 16 h	30 min	1,0 I_t A to 1,0 V	90 min
2 to 48	1,0 I_t A for ^a	30 min	1,0 I_t A to 1,0 V	90 min
49	1,0 I_t A for ^a	24 h	1,0 I_t A to 1,0 V	90 min
50	1,0 I_t A for ^a plus 0,1 I_t A for 2 h	1 h to 4 h	0,2 I_t A to 1,0 V ^b	^b

^a With appropriate charge termination, as recommended by the manufacturer, for example use $-\Delta V$ or $\Delta T/\Delta t$ control method.

^b It is permissible to allow sufficient open-circuit rest time after the completion of discharge at cycle 50, so as to start cycle 51 at a convenient time. A similar procedure may be adopted at cycles 100, 150, 200, 250, 300, 350, 400 and 450.

Cycles 1 to 50 shall be repeated until the discharge duration to the final voltage of 1,0 V on any 49th cycle becomes less than 30 min or until the discharge duration to the final voltage of 1,0 V on any 50th cycle becomes less than 3 h. At this stage, a repeat capacity measurement as specified for cycle 50 shall be carried out and if the discharge time is less than 3 h again the test is terminated.

The total number of cycles obtained when the test is completed shall be not less than 500.

7.5.2 Permanent charge endurance

7.5.2.1 Small prismatic and button cells

There is no requirement for permanent charge endurance tests on small prismatic and button cells.

7.5.2.2 L, M, H or X cylindrical cells

Prior to this test, the cell shall be discharged at 0,2 I_t A to a final voltage of 1,0 V.

The following permanent charge endurance test shall be carried out in an ambient temperature of 20 °C \pm 5 °C. Charge and discharge shall be carried out at constant current throughout, using the conditions specified in Table 13.

Table 13 – Permanent charge endurance for L, M, H or X cells

Cycle number	Charge	Discharge ^a
1	0,05 I_t A for 91 days	0,2 I_t A to 1,0 V
2	0,05 I_t A for 91 days	0,2 I_t A to 1,0 V
3	0,05 I_t A for 91 days	0,2 I_t A to 1,0 V
4	0,05 I_t A for 91 days	0,2 I_t A to 1,0 V

^a The discharge is carried out immediately on completion of charging.

Precautions shall be taken to prevent cell-case temperature from rising above 25 °C during the test by providing a forced air draught if necessary.

The discharge duration at cycle 4 shall be not less than 3 h.

7.5.2.3 LT, MT or HT cylindrical cells

The permanent charge endurance test shall be performed in three steps according to the conditions specified in Table 14.

It consists of:

- a charge acceptance test at +40 °C;
- an ageing period of six months at +70 °C;
- a final charge acceptance test to check the cell's performance after ageing.

NOTE 1 The six months aging period and the temperature of +70 °C has been selected to simulate four years of permanent charge operation at +40 °C.

Prior to this test, the cell shall be discharged at $20\text{ °C} \pm 5\text{ °C}$, at $0,2 I_t$ A, to a final voltage of 1,0 V and stored, in an ambient temperature of $+40\text{ °C} \pm 2\text{ °C}$, for not less than 16 h and not more than 24 h.

The cell shall then be charged and discharged at constant current under the conditions specified in Table 14 while maintained in an ambient temperature of $+40\text{ °C} \pm 2\text{ °C}$ or $+70\text{ °C} \pm 2\text{ °C}$ as appropriate.

The discharge conditions A or B may be chosen to suit the user's requirements. The discharge is carried out immediately on completion of charging.

After performing the first charge acceptance test at +40 °C the cell is stored in an ambient temperature of $+70\text{ °C} \pm 2\text{ °C}$ for not less than 16 h and not more than 24 h.

During the ageing period of six months at +70 °C, precautions shall be taken to prevent the cell-case temperature from rising above +75 °C, by providing a forced air draught, if necessary.

NOTE 2 The actual cell case temperature, not the ambient temperature, determines cell performance.

The discharge duration of the three cycles at +70 °C shall be recorded. Leakage of electrolyte shall not occur during this test.

After completion of the ageing period, the cell shall be stored in an ambient temperature of $+40\text{ °C} \pm 2\text{ °C}$ for not less than 16 h and not more than 24 h. The three cycles at +40 °C of the initial charge acceptance test are then repeated using the conditions specified in Table 14. The duration of discharge shall be not less than the values specified in Table 14.

Table 14 – Permanent charge endurance for LT, MT or HT cells

Cycle number	Ambient temperature	Charge	Discharge A or B ^a	Minimum discharge duration
1	+40 °C ± 2 °C	0,05 I_t A for 48 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	No requirement
2		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	3 h 45 min
3		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	42 min
4	+70 °C ± 2 °C	0,05 I_t A for 60 days	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	No requirement
5		0,05 I_t A for 60 days	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	
6		0,05 I_t A for 60 days	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	
7	+40 °C ± 2 °C	0,05 I_t A for 48 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	No requirement
8		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	2 h 30 min
9		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	24 min
^a A: for LT, MT or HT cells. B: for MT or HT cells only.				

7.5.2.4 LU, MU or HU cylindrical cells

The permanent charge endurance test shall be performed in three steps according to the conditions specified in Table 15

It consists of:

- a charge acceptance test at +50 °C;
- an ageing period of twelve months at +70 °C;
- a final charge acceptance test to check the cell's performance after ageing.

NOTE 1 The twelve months ageing period and the temperature of +70 °C has been selected to simulate four years of permanent charge operation at +50 °C.

Prior to this test, the cell shall be discharged at 20 °C ± 5 °C, at 0,2 I_t A, to a final voltage of 1,0 V and stored, in an ambient temperature of +50 °C ± 2 °C, for not less than 16 h and not more than 24 h.

The cell shall then be charged and discharged at constant currents under the conditions specified in Table 15 while maintained in an ambient temperature of +50 °C ± 2 °C or +70 °C ± 2 °C as appropriate.

The discharge conditions A or B may be chosen to suit the user's requirements. The discharge is carried out immediately on completion of charging.

After performing the first charge acceptance test at +50 °C, the cell is stored in an ambient temperature of +70 °C ± 2 °C for not less than 16 h and not more than 24 h.

During the ageing period of twelve months at +70 °C, precautions shall be taken to prevent the cell-case temperature from rising above +75 °C, by providing a forced air draught, if necessary.

NOTE 2 The actual cell case temperature, not the ambient temperature, determines cell performance.

The discharge duration of the three cycles at +70 °C shall be recorded. Leakage of electrolyte shall not occur during this test.

After completion of the ageing period, the cell shall be stored in an ambient temperature of +50 °C ± 2 °C for not less than 16 h and not more than 24 h. The three cycles at +50 °C of the initial charge acceptance test are then repeated using the conditions specified in Table 15. The duration of discharge shall be not less than the values specified in Table 15.

Table 15 – Permanent charge endurance for LU, MU or HU cells

Cycle number	Ambient temperature	Charge	Discharge A or B ^a	Minimum discharge duration	
1	+50 °C ± 2 °C	0,05 I_t A for 48 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	No requirement	
2		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	3 h 45 min 42 min	
3		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	3 h 45 min 42 min	
4	+70 °C ± 2 °C	0,05 I_t A for 120 days	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	No requirement	
5		0,05 I_t A for 120 days	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V		
6		0,05 I_t A for 120 days	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V		
7	+50 °C ± 2 °C	0,05 I_t A for 48 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V	No requirement	
8		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V		2 h 30 min 24 min
9		0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V		2 h 30 min 24 min
^a A: for LU, MU or HU cells. B: for MU or HU cells only.					

7.6 Charge acceptance at constant voltage

This standard does not specify a charge acceptance test at constant voltage.

Charging at constant voltage is not recommended.

7.7 Overcharge

7.7.1 Small prismatic, L, M, H, X, LS or MS cylindrical, and button cells

The ability of the cell to withstand an overcharge shall be determined by the following test.

Prior to this test, the cell shall be discharged in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2 I_t$ A, down to a final voltage of 1,0 V.

The cell shall then be charged, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,1 I_t$ A for 48 h. After this charging operation, the cell shall be stored, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, for not less than 1 h and not more than 4 h.

The cell shall then be discharged at $20\text{ °C} \pm 5\text{ °C}$ at a constant current of $0,2 I_t$ A to a final voltage of 1,0 V.

The duration of discharge shall be not less than 5 h.

7.7.2 LT/LU, MT/MU or HT/HU cylindrical cells

The ability of the cell to withstand an overcharge shall be determined by the following test performed at $0\text{ °C} \pm 2\text{ °C}$ in circulating air.

Prior to this test, the cell shall be discharged in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$ at $0,2 I_t$ A to a final voltage of 1,0 V and stored, at $0\text{ °C} \pm 2\text{ °C}$, for not less than 16 h and not more than 24 h.

Charge and discharge shall be carried out at constant current, using the conditions specified in Table 16. The discharge condition A or B may be chosen to suit the user's requirements.

Table 16 – Overcharge at 0 °C

Charge	Discharge A ^a	Discharge B ^a
	LT/LU, MT/MU, HT/HU cells	MT/MU, HT/HU cells
$0,05 I_t$ A for 28 days	$0,2 I_t$ A to 1,0 V	$1,0 I_t$ A to 0,9 V

^a The discharge is carried out immediately on completion of charging.

The duration of discharge shall be not less than that specified in Table 7.

7.7.3 R cylindrical cells

The ability of the cell to withstand an overcharge shall be determined by the following test.

Prior to this test, the cell shall be discharged in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2 I_t$ A, to a final voltage of 1,0 V.

The cell shall be charged in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$ at a constant current of $1,0 I_t$ A for 1,2 h or other appropriate charge termination such as $-\Delta V$ or as recommended by the manufacturer. Then charging should be continued in the same ambient temperature at a

constant current of $0,1 I_t$ A for 48 h. After this charging operation, the cell shall be stored, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, for not less than 1 h and not more than 4 h.

The cell shall then be discharged at $20\text{ °C} \pm 5\text{ °C}$ at a constant current of $0,2 I_t$ A to a final voltage of 1,0 V.

The duration of discharge shall be not less than 5 h.

7.8 Safety device operation

Warning: EXTREME CAUTION SHALL BE EXERCISED WHEN CARRYING OUT THIS TEST ! CELLS SHALL BE TESTED INDIVIDUALLY, AND IT SHOULD BE NOTED THAT CELLS FAILING TO MEET THE REQUIREMENT COULD BURST WITH EXPLOSIVE FORCE EVEN AFTER THE CELL HAS BEEN DISCONNECTED FROM THE CHARGE CURRENT.
FOR THIS REASON, THE TEST SHALL BE CARRIED OUT IN A PROTECTIVE CHAMBER.

The following test shall be carried out in order to establish that the safety device of the cell will operate to allow the escape of gas when the internal pressure exceeds a critical value.

NOTE Some button cells do not have a safety vent. This test should not be performed on this type of cell.

The cell shall undergo a forced discharge in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2 I_t$ A, to a final voltage of 0 V.

The current shall then be increased to $1,0 I_t$ A and the forced discharge continued in the same ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, for 60 min.

During and at the end of this discharge, the cell shall not disrupt or burst. Leakage of electrolyte and deformation of the cell are acceptable.

7.9 Surface temperature limitation device operation (for S cell only)

Warning: EXTREME CAUTION SHALL BE EXERCISED WHEN CARRYING OUT THIS TEST! THE CELL COULD BURST WITH EXPLOSIVE FORCE OR ITS CONTENT COULD FLOW OUT. IN ADDITION, IT SHOULD BE NOTED THAT THE CELL WILL GENERATE HEAT.
FOR THIS REASON, THE TEST SHALL BE CARRIED OUT IN A PROTECTIVE CHAMBER.

The following test shall be carried out in order to establish that the surface temperature limitation device will operate to prevent the cell temperature from excessively rising when the surface temperature limited cell is misused.

After charging in accordance with 7.2, the test shall be carried out as follows:

Test method: Four cells shall be connected in series but one of the four cells shall be placed in a reverse position. In this state, the terminals of the series string are connected by a wire to cause a short circuit. Short-circuit resistance: 100 mΩ or less.

The test shall be terminated, when one of the following two cases occurs first:

- 24 hours have elapsed or
- the cell-case temperature has been reduced by 20 % from the maximum temperature increase.

Then, verify the followings:

- the cell has not exploded and not taken fire;

- the cell temperature increase is less than 45 °C;
- no leakage shall be found by visual inspection.

7.10 Storage

Storage should be carried out according to the recommendations of the manufacturer.

Prior to this test, the cell shall be discharged, in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2 I_t$ A, to a final voltage of 1,0 V. It shall then be charged in accordance with:

- 7.2 for button cells, small prismatic cells, L, M, H, X, LS, MS, LT/LU, MT/MU or HT/HU cylindrical cells;
- 7.3.4 for R cylindrical cells.

The cell shall then be stored on open circuit, at a mean temperature of $20\text{ °C} \pm 5\text{ °C}$ and a relative humidity of $65\% \pm 20\%$ for 12 months.

During the storage period, the ambient temperature shall not, at any time, fluctuate beyond the limits of $20\text{ °C} \pm 10\text{ °C}$.

After completion of the storage period, the cell shall be discharged in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$, at a constant current of $0,2 I_t$ A, to a final voltage of 1,0 V and then charged in accordance with:

- 7.2 for button cells, small prismatic cells, L, M, H, X, LS, MS, LT/LU, MT/MU or HT/HU cylindrical cells;
- 7.3.4 for R cylindrical cells.

The cell shall then be discharged at each rate of constant current appropriate to cell designation as specified in 7.3.2. Five cycles are permitted for this test. The test shall be terminated at the end of the first cycle which meets the requirement.

The minimum discharge duration for each rate of constant current shall be not less than 80 % of the values specified in Tables 5 or 6.

NOTE In the case of a quality acceptance procedure, provisional approval of cell performance may be agreed, pending satisfactory results on discharge after storage.

7.11 Charge acceptance at +55 °C for LT, MT or HT cylindrical cells

This test is not a requirement. It will be used as reference of performance and is applicable to LT, MT or HT cylindrical cells only.

The cell shall be discharged in an ambient temperature of $20\text{ °C} \pm 5\text{ °C}$ at a constant current of $0,2 I_t$ A to a final voltage of 1,0 V and stored in an ambient temperature of $+55\text{ °C} \pm 2\text{ °C}$ for not less than 16 h and not more than 24 h.

The charge acceptance test shall then be carried out in an ambient temperature of $+55\text{ °C} \pm 2\text{ °C}$. Charge and discharge shall be carried out at constant currents, using the conditions specified in Table 17. The discharge conditions A or B may be chosen to suit the users' requirements.

Table 17 – Charge and discharge at +55 °C

Cycle number	Charge	Discharge A or B ^a
1	0,05 I_t A for 48 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V
2 ^b	0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V
3 ^b	0,05 I_t A for 24 h	A: 0,2 I_t A to 1,0 V or B: 1,0 I_t A to 1,0 V
^a Discharge A is used with LT, MT or HT cells. Discharge B is used with MT or HT cells. ^b The duration of discharge of cycles 2 and 3 shall be recorded and provided in any report of results.		

7.12 Internal resistance

7.12.1 General

The internal resistance of sealed nickel-metal hydride small prismatic or cylindrical rechargeable single cells shall be checked either by the alternating current (a.c.) or by the direct current (d.c.) method.

Should the need arise for the internal resistance to be measured by both a.c. and d.c. methods on the same cell, then the a.c. method shall be used first, followed by the d.c. method. In this case, it is not necessary to discharge and charge the cell between conducting a.c. and d.c. methods.

Prior to the measurements, the cell shall be discharged at 0,2 I_t A to a final voltage of 1,0 V. The cell shall be charged in accordance with 7.2. After charging, the cell shall be stored, in an ambient temperature of 20 °C ± 5 °C, for not less than 1 h and not more than 4 h.

The measurement of internal resistance shall be carried out in an ambient temperature of 20 °C ± 5 °C.

7.12.2 Measurement of the internal a.c. resistance

The alternating r.m.s. voltage, U_a , shall be measured when applying to the cell an alternating r.m.s. current, I_a , at the frequency of 1,0 kHz ± 0,1 kHz for a period of 1 s to 5 s.

The internal a.c. resistance, R_{ac} , is given by

$$R_{ac} = \frac{U_a}{I_a} \Omega$$

where

U_a is the alternating r.m.s. voltage;

I_a is the alternating r.m.s. current.

NOTE 1 The alternating current should be selected so that the peak voltage stays below 20 mV.

NOTE 2 This method will measure the impedance which, in the range of frequency specified, is approximately equal to the resistance.

NOTE 3 Connections to the battery terminals should be made in such a way that voltage measurement contacts are separate from contacts used to carry current.

7.12.3 Measurement of the internal d.c. resistance

The cell shall be discharged at a constant current of value I_1 as specified in Table 18. At the end of a discharge period of 10 s, the voltage U_1 during discharge shall be measured and recorded. The discharge current shall then be immediately increased to a constant value of I_2 as specified in Table 18 and the corresponding voltage U_2 during discharge shall be measured and recorded again at the end of a discharge period of 3 s.

All voltage measurements shall be made at the terminals of the cell independently of contacts used to carry current.

The internal d.c. resistance, R_{dc} , of the cell shall be calculated using the following formula:

$$R_{dc} = \frac{U_1 - U_2}{I_2 - I_1} \quad \Omega$$

where

I_1, I_2 are the constant discharge currents;

U_1, U_2 are the appropriate voltages measured during discharge.

Table 18 – Constant discharge currents used for measurement of d.c. resistance

Current	Cell designation		
	HRL ^a	HRM ^a HRH ^a	HRX
I_1	0,2 I_t A	0,5 I_t A	1,0 I_t A
I_2	2,0 I_t A	5,0 I_t A	10,0 I_t A

^a And corresponding "T", "S" and "R" cells.

8 Mechanical tests

Mechanical tests shall be performed according to IEC 61959.

9 Safety requirements

Safety requirements shall be fulfilled according to IEC 62133.

10 Type approval and batch acceptance

10.1 Type approval

10.1.1 Type approval for small prismatic cells and button cells

For type approval, the sequence of tests and sample sizes given in Table 19 shall be used. Six groups of cells, denominated A, B, C, D, E and F respectively, shall be tested. The total number of cells required for type approval is 27. This total includes an extra cell, permitting a repeat test to cover any incident which may occur outside the supplier's responsibility.

Tests shall be carried out in sequence within each group of cells. All cells are subjected to the test in group A, after which they are divided into five groups at random according to the sample sizes shown in Table 19.

The number of defective cells tolerated per group, and in total, is given in Table 19. A cell is considered to be defective if it does not meet the requirements of all or part of the tests of a group.

**Table 19 – Sequence of tests for type approval
for small prismatic and for button cells**

Group	Sample size	Clause or subclause	Tests	Number of defective cells tolerated	
				Per group	In total
A	27	5.3 6 7.3.2 7.3.2	Marking Dimensions Discharge at 20 °C, at 0,2 I_t A Discharge at 20 °C, at 1,0 I_t A	0	3
B	5	7.3.3 7.3.3	Discharge at 0 °C, at 0,2 I_t A Discharge at 0 °C, at 1,0 I_t A	1	
C	5	7.7 7.8	Overcharge Safety device operation	0	
D	5	7.5	Endurance in cycles	1	
E	6	7.4	Charge (capacity) retention	1	
F	5	7.10	Storage	1	
		7.3.2	Discharge at 20 °C, at 0,2 I_t A		

10.1.2 Type approval for cylindrical cells

For type approval, the sequence of tests and sample sizes given in Table 20 shall be used. Seven groups of cells, denominated A, B, C, D, E, F and G respectively, shall be tested. The total number of cells required for type approval is 32. This total includes an extra cell, permitting a repeat test to cover any incident which may occur outside the supplier's responsibility.

Tests shall be carried out in sequence within each group of cells. All cells are subjected to the test in group A, after which they are divided into six groups at random according to the sample sizes shown in Table 20.

The number of defective cells tolerated per group, and in total, is given in Table 20. A cell is considered to be defective if it does not meet the requirements of all or part of the tests of a group.

**Table 20 – Sequence of tests for type approval
for cylindrical cells**

Group	Sample size	Clause or subclause	Tests	Number of defective cells tolerated	
				per group	in total
A	32	5.3 6.1 7.3.2 7.3.2	Marking Dimensions Discharge at 20 °C at 0,2 I_t A Discharge at 20 °C at 1,0 I_t A (M, H and X cells) ^a 5,0 I_t A (H and X cells) ^a 10,0 I_t A (X cells only)	0	3
B	5	7.3.3 7.3.3	Discharge at 0 °C at 0,2 I_t A Discharge at 0 °C at 1,0 I_t A (M, H and X cells) ^a 2,0 I_t A (H and X cells) ^a 3,0 I_t A (X cells only)	1	
C	5	7.7 7.8	Overcharge Safety device operation	0	
D	5	7.5.1	Endurance in cycles	1	
E	5	7.5.2 7.8	Permanent charge endurance Safety device operation	1 0	
F	6	7.4	Charge retention	1	
G	5	7.10 7.3.2 7.3.2	Storage Discharge at 20 °C at 0,2 I_t A Discharge at 20 °C at 1,0 I_t A (M, H and X cells) ^a 5,0 I_t A (H and X cells) ^a 10,0 I_t A (X cells only)	1	

^a And corresponding "T", "U" and "R" cells.

10.2 Batch acceptance

These tests are applicable to deliveries of individual cells.

The sampling procedure shall be established in accordance with IEC 60410. Unless otherwise agreed between supplier and purchaser, inspections and tests shall be performed using inspection levels and AQLs (acceptable quality level) recommended in Table 21.

Table 21 – Recommended test sequence for batch acceptance

Group	Clause or subclause	Inspection/tests	Recommendation	
			Inspection level	AQL %
A	As agreed	Visual inspection		
		– absence of mechanical damage	II	4
		– absence of corrosion on case and terminals	II	4
		– number, position and secure fittings of connection tabs	S3	1
		– absence of liquid electrolyte on case and terminals	II	0,65
B	6 As agreed 5.3	Physical inspection		
		– dimensions	S3	1
		– weight	S3	1
		– marking	S3	1
C	7.3.2 7.3.2	Electrical inspection		
		– open-circuit voltage and polarity	II	0,65
		– discharge at 20 °C at 0,2 I_t A	S3	1
		– discharge at 20 °C at 1,0 I_t A	S3	1

NOTE Two or more failures on a single cell are not cumulative. Only the failure corresponding to the lowest AQL is taken into consideration.

Bibliography

IEC 60051 (all parts), *Direct acting indicating analogue electrical measuring instruments and their accessories*

IEC 60485, *Digital electronic d.c. voltmeters and d.c. electronic analogue-to-digital convertors*¹

IEC 61434, *Secondary cells and batteries containing alkaline or other non-acid electrolytes – Guide to the designation of current in alkaline secondary cell and battery standards*

¹ This publication was withdrawn.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™