



BSI Standards Publication

**Rubber, vulcanized or thermoplastic —  
Determination of adhesion to textile fabrics**

---

## National foreword

This British Standard is the UK implementation of ISO 36:2017. It supersedes BS ISO 36:2011, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/22, Testing and analysis of rubber.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2017  
Published by BSI Standards Limited 2017

ISBN 978 0 580 97183 9

ICS 59.080.40; 83.060

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2017.

### Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

---

# INTERNATIONAL STANDARD

**ISO**  
**36**

Sixth edition  
2017-05

---

---

## **Rubber, vulcanized or thermoplastic — Determination of adhesion to textile fabrics**

*Caoutchouc vulcanisé ou thermoplastique — Détermination de  
l'adhérence aux textiles*



Reference number  
ISO 36:2017(E)

© ISO 2017



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

<b>Contents</b>		Page
<b>Foreword</b> .....		<b>iv</b>
<b>1 Scope</b> .....		<b>1</b>
<b>2 Normative references</b> .....		<b>1</b>
<b>3 Terms and definitions</b> .....		<b>1</b>
<b>4 Principle</b> .....		<b>2</b>
<b>5 Apparatus</b> .....		<b>2</b>
<b>6 Calibration</b> .....		<b>2</b>
<b>7 Test piece</b> .....		<b>2</b>
<b>8 Number of test pieces</b> .....		<b>3</b>
<b>9 Time-interval between vulcanization and testing</b> .....		<b>3</b>
<b>10 Conditioning of test pieces and temperature of test</b> .....		<b>3</b>
<b>11 Procedure</b> .....		<b>3</b>
<b>12 Expression of results</b> .....		<b>4</b>
<b>13 Test report</b> .....		<b>4</b>
<b>Annex A (normative) Calibration schedule</b> .....		<b>6</b>
<b>Bibliography</b> .....		<b>8</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html)

This document was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

This sixth edition cancels and replaces the fifth edition (ISO 36:2011), of which it constitutes a minor revision to update the normative references in [Clause 2](#).

# Rubber, vulcanized or thermoplastic — Determination of adhesion to textile fabrics

**WARNING** — Persons using this document should be familiar with normal laboratory practice. This document does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

## 1 Scope

This document specifies a method of test for measuring the force required to separate, by stripping, two plies of fabric bonded with rubber, or a rubber layer and a fabric ply bonded together.

The method is applicable when the ply surfaces are approximately plane or when they are in the form of a cylinder having an internal diameter greater than approximately 50 mm. The method is not applicable when the ply surfaces contain sharp bends, angles or other gross irregularities which cannot be excluded when cutting out test pieces.

This document does not apply to coated fabrics, which are tested in accordance with ISO 2411, or textile conveyor belts, which are tested in accordance with ISO 252.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5893:2002, *Rubber and plastics test equipment — Tensile, flexural and compression types (constant rate of traverse) — Specification*

ISO 6133:2015, *Rubber and plastics — Analysis of multi-peak traces obtained in determinations of tear strength and adhesion strength*

ISO 18899:2013, *Rubber — Guide to the calibration of test equipment*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

### 3.1

#### adhesion strength

force per unit width required to cause a separation at the interface between the assembled components

Note 1 to entry: Any separation occurring at any other point, for example inside either component under test, is a failure of the component material, and does not indicate an adhesion strength. In such cases, the adhesion strength is greater than the strength of the weakest component involved.

## 4 Principle

The stripping force required to separate two plies of fabric bonded with rubber, or a rubber layer and a fabric ply bonded together, is measured under specified conditions using test pieces of standard dimensions in the form of a flat strip.

## 5 Apparatus

**5.1 Test machine**, power-driven and equipped with a suitable dynamometer; it shall be capable of maintaining a substantially constant rate of traverse of the moving head during the test and shall be linked to an autographic recorder or a computer with graphic capabilities for data acquisition and processing. An inertialess dynamometer (of the electronic or optical type, for example) should preferably be used.

The machine shall comply with the requirements of ISO 5893, be capable of measuring force with an accuracy corresponding to class 1 as defined in ISO 5893:2002, and have a rate of traverse of the moving grip of  $50 \text{ mm/min} \pm 5 \text{ mm/min}$ .

The machine shall be fitted with grips capable of holding the test piece and the ply to be separated without slipping during the test.

**5.2 Autographic recorder**, with a scale sufficiently large to permit easy interpretation of the trace, or computer with graphic capabilities and software enabling it to comply with the procedure for data processing described in ISO 6133.

## 6 Calibration

The test apparatus shall be calibrated in accordance with the schedule given in [Annex A](#).

## 7 Test piece

The test piece shall have a width of  $25 \text{ mm} \pm 0,5 \text{ mm}$  and shall be of sufficient length to permit ply separation during measurement over a length of at least 100 mm. The minimum thickness of the constituent components, or of one of them, shall be such that the weakest component can transmit the force necessary for separation without breaking.

The test piece shall be cut in a plane parallel to the warp in the length direction and parallel to the weft in the width direction.


If required, also cut test pieces in a plane parallel to the weft in the length direction and parallel to the warp in the width direction.

If there is a danger of bits of fabric being removed from the test piece due to irregularity of fabric alignment, make the test pieces slightly wider, but at least the ply to be stripped shall be cut to the width of 25 mm.

The thickness shall be suitably reduced in accordance with ISO 23529, if necessary, in order to ensure that the line of separation of the plies during the test lies as close as possible to the plane of the strips of test piece held in the grips (see [Figure 1](#)). For tests intended to be comparable, the test pieces shall have the same dimensions.

Whenever possible, the standard test piece shall be cut from the article and prepared in accordance with the relevant product standard, if one exists.



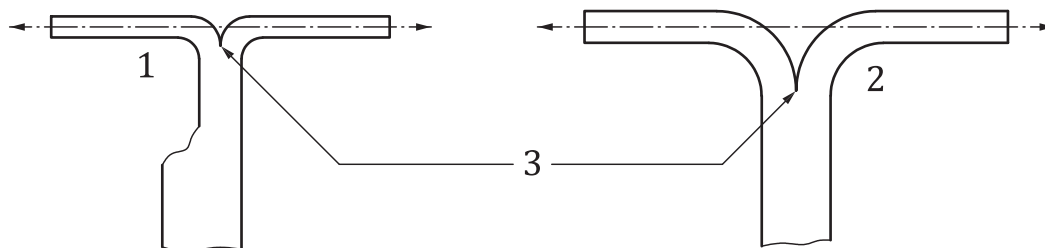

**Key**

- 1 ideal
- 2 undesirable
- 3 line of separation

**Figure 1 — Position of line of separation of plies**

## 8 Number of test pieces

Unless otherwise specified, three test pieces shall be tested for each direction of test.

## 9 Time-interval between vulcanization and testing

Unless otherwise specified for technical reasons, the following requirements for time-intervals shall be observed:

- a) For all test purposes, the minimum time between vulcanization and testing shall be 16 h.
- b) For non-product tests, the maximum time between vulcanization and test shall be four weeks, and for evaluations intended to be comparable the tests shall be carried out, as far as possible, after the same time-interval.
- c) For product tests, whenever possible, the time between vulcanization and testing shall not exceed three months. In other cases, tests shall be made within two months of the date of receipt of the product by the customer.

## 10 Conditioning of test pieces and temperature of test

Condition all test pieces in accordance with ISO 23529. If the preparation of test pieces involves buffing, the interval between buffing and testing shall be not less than 16 h and not greater than 72 h.

For tests at a standard laboratory temperature (see ISO 23529), test pieces that do not require further preparation may be tested immediately, if cut from conditioned test samples. Where additional preparation is involved, a minimum conditioning period of 3 h at a standard laboratory temperature shall be allowed.

For tests at temperatures other than a standard laboratory temperature, condition the test pieces at the temperature at which the test is to be conducted for a period sufficient to enable the test pieces to attain substantial equilibrium in accordance with ISO 23529.

## 11 Procedure

Take the test piece as described in [Clause 7](#) and separate a ply of fabric or a rubber layer by hand for a distance of approximately 50 mm. The use of a scalpel or similar implement might be necessary to initiate the separation.

Fix the separated ends of the test piece in the grips of the test machine (5.1) and adjust so that the tension is distributed uniformly and so that no twisting of the test piece will occur during the test. Place the body of the test piece in the non-driven grip and the ply to be separated in the power-driven grip so that the angle of separation is approximately 180°. It is important to ensure that the strips of test piece held in the grips lie in the same plane.

Start the machine and continue the ply separation while recording on the chart recorder or in the memory of the computer (see 5.2) the force values over a length separation of at least 100 mm. The rate of travel of the power-driven grip shall be 50 mm/min ± 5 mm/min.

Examine the separated pieces for separation or failure.

## 12 Expression of results

**12.1** Calculate the adhesion strength of the test piece by dividing the separation force, determined in accordance with ISO 6133:2015 using method A, B, C, D or E, as appropriate to the trace, by the width of the test piece. Report the result as the median of the individual values obtained for the three test pieces, expressed in newtons per millimetre.

**12.2** Describe the type of failure or separation using the following terminology:

- R indicates that the failure is in the rubber layer;
- RA indicates that the separation is between the rubber layer and the adhesive;
- AT indicates that the separation is between the adhesive and the fabric;
- RB indicates that the failure is in the rubber bond between two fabric plies;
- T indicates that the failure is in the fabric;
- RT indicates that the separation is between the rubber and the fabric when no adhesive is present.

## 13 Test report

The test report shall include the following information:

- a) sample details:
  - 1) a full description of the sample and its origin,
  - 2) the method of preparation of the test pieces from the sample, for example moulded or cut,
  - 3) whether the test pieces were cut with their length in a plane parallel or perpendicular to the warp direction;
- b) a reference to the test method used, i.e. the number of this document (ISO 36);
- c) test details:
  - 1) the standard laboratory temperature used,
  - 2) the time and temperature of conditioning prior to the test,
  - 3) the temperature of test, if other than a standard laboratory temperature, and the relative humidity, if necessary,
  - 4) the number of test pieces tested (if not three),

- 5) details of any procedures not specified in this document;
- d) test results:
  - 1) the individual test results,
  - 2) the median value of the individual results,
  - 3) the method of calculation used, i.e. A, B, C, D or E (see [12.1](#)),
  - 4) the type of failure or separation (see [12.2](#));
- e) the date of the test.

## Annex A (normative)

### Calibration schedule

#### A.1 Inspection

Before any calibration is undertaken, the condition of the items to be calibrated shall be ascertained by inspection and recorded in any calibration report or certificate. It shall be reported whether calibration is carried out in the “as-received” condition or after rectification of any abnormality or fault.

It shall be ascertained that the apparatus is generally fit for the intended purpose, including any parameters specified as approximate and for which the apparatus does not therefore need to be formally calibrated. If such parameters are liable to change, then the need for periodic checks shall be written into the detailed calibration procedures.

#### A.2 Schedule

Verification/calibration of the test apparatus is a mandatory part of this document. However, the frequency of calibration and the procedures used are, unless otherwise stated, at the discretion of the individual laboratory, using ISO 18899 for guidance.

The calibration schedule given in [Table A.1](#) has been compiled by listing all of the parameters specified in the test method, together with the specified requirement. A parameter and requirement can relate to the main test apparatus, to part of that apparatus or to an ancillary apparatus necessary for the test.

For each parameter, a calibration procedure is indicated by reference to ISO 18899, to another publication or to a procedure particular to the test method which is detailed (whenever a calibration procedure which is more specific or detailed than that in ISO 18899 is available, it shall be used in preference).

The verification frequency for each parameter is given by a code-letter. The code-letters used in the calibration schedule are:

- C requirement to be confirmed, but no measurement;
- S standard interval selected as described in ISO 18899;
- U in use.

**Table A.1 — Calibration frequency schedule**

Parameter	Requirement	Subclause in ISO 18899:2013	Verification frequency guide	Notes
Test machine	Complying with ISO 5893			
Force measurement accuracy	Class 1	21.1	S	
Rate of traverse of moving grip	(50 ± 5) mm/min	23.4	S	
Grips	No slippage	C	U	
Autographic recorder	With a sufficiently large scale (see <a href="#">5.2</a> )	C	S	To permit easy interpretation

In addition to the items listed in [Table A.1](#), use of the following is implied, all of which need calibrating in accordance with ISO 18899:

- a thermometer for monitoring the conditioning and test temperatures;
- instruments for determining dimensions of the test pieces.

## Bibliography

- [1] ISO 252, *Conveyor belts — Adhesion between constitutive elements — Test methods*
- [2] ISO 2411, *Rubber- or plastics-coated fabrics — Determination of coating adhesion*









## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

## Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

## Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com).

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Useful Contacts

### Customer Services

**Tel:** +44 345 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 345 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)

### BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK