

BS ISO 602:2015



BSI Standards Publication

Coal — Determination of mineral matter

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 602:2015.

The UK participation in its preparation was entrusted to Technical Committee PTI/16, Solid mineral fuels.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015.
Published by BSI Standards Limited 2015

ISBN 978 0 580 88406 1
ICS 73.040

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 April 2015.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

BS ISO 602:2015

ISO
602

Third edition
2015-04-15

**Coal — Determination of mineral
matter**

Charbon — Détermination du taux de matières minérales



Reference number
ISO 602:2015(E)

© ISO 2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Principle	1
4 Reagents	1
5 Apparatus	1
6 Preparation of sample	2
7 Procedure	2
8 Expression of results	3
9 Precision of the method	3
9.1 Repeatability.....	4
9.2 Reproducibility.....	4
10 Test report	4
Annex A (normative) Example of calculation	6
Bibliography	7

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT), see the following URL: [Foreword — Supplementary Information](#).

The committee responsible for this document is ISO/TC 27, *Solid mineral fuels*, Subcommittee SC 05, *Methods of analysis*.

This third edition cancels and replaces the second edition (ISO 602:1983), which constitutes a minor revision.

Coal — Determination of mineral matter

1 Scope

This International Standard specifies a method of determining the amount of mineral matter in all types of coal, including brown coals and lignites.

2 Normative references

There are no normative references cited in this document.

3 Principle

The following principle applies:

- a) partial demineralization of a sample of the coal by treatment with hydrochloric and hydrofluoric acids under such conditions that the coal substance remains unaffected;
- b) recording of the loss in mass of the coal due to the acid treatment and determination of the undissolved part of the mineral matter by ashing the partially demineralized coal;
- c) determination of the iron content of the ash so that the pyrites present in the extracted coal can be calculated; and
- d) determination of the amount of hydrochloric acid absorbed by the coal substance.

4 Reagents

During the analysis, use only reagents of recognized analytical grade and only distilled water or water of equivalent purity.

4.1 Hydrochloric acid, ρ 1,18 g/ml.

4.2 Hydrochloric acid, solution, $c(\text{HCl})$ 5 mol/l.

4.3 Hydrofluoric acid, ρ 1,13 g/ml.

WARNING — Very toxic by inhalation, in contact with skin, and if swallowed. Causes severe burns.

Keep container tightly closed in a well-ventilated place. In case of contact with eyes, rinse immediately with plenty of water and seek medical advice.

Wear suitable protective clothing and gloves. In case of accident or feeling unwell, seek medical advice immediately (show the label where possible).

5 Apparatus

All the apparatus listed below shall be resistant to acids, especially hydrofluoric acid. A suitable material is polyvinyl chloride (PVC).

5.1 Beaker, of capacity 200 ml, with a cover slip.

5.2 Thermometer pocket: a tube, sealed at one end, to carry a thermometer.

5.3 Stirrer.

5.4 Wash-bottle.

5.5 Filter, quantitative filter paper with 1 µm aperture and a sintered alumina filter plate, as shown in [Figure 1](#).

5.6 Filter flask.

5.7 Balance, accurate to 0,1 mg.

6 Preparation of sample

The coal used for determination of mineral matter is the analysis sample, ground to pass a sieve of 200 µm aperture. If necessary, expose the sample in a thin layer for the minimum time required for the moisture content to reach approximate equilibrium with the laboratory atmosphere (see ISO 11722 for moisture in the analysis sample).

Before starting the determination, mix the air-dried analysis sample of coal (see the note) thoroughly for at least 1 min, preferably by mechanical means.

NOTE Alternatively, the coal sample can be dried at 105 °C to 110 °C before carrying out the procedure.

7 Procedure

Weigh, to the nearest 0,1 mg, about 6 g of the sample into the beaker ([5.1](#)) and add 40 ml of the hydrochloric acid solution ([4.2](#)) (see Note [1](#)). Insert the stirrer ([5.3](#)) and the tube ([5.2](#)) carrying a thermometer and place the cover slip over the beaker. Place the beaker in a water-bath adjusted to maintain the temperature of the solution between 55 °C to 60 °C. Stir the contents at 5 min intervals, remove the beaker after 45 min and allow the coal suspension to settle for 10 min. Filter the solution through the filter ([5.5](#)) under suction.

Wash the coal retained on the filter with water, drain and transfer the coal back to the beaker with the aid of not more than 5 ml of water. Care is required to avoid loss of coal by splashing (see Note [2](#)).

Add 40 ml of the hydrofluoric acid ([4.3](#)) to the beaker and repeat the heat treatment and filtration as previously described. Rinse the coal retained on the filter into the beaker with not more than 5 ml of water. Add 50 ml of hydrochloric acid ([4.1](#)) to the beaker, replace it in the water-bath and repeat the heat treatment previously described. Filter and wash the coal three times, decanting each time. Transfer the coal entirely to the filter and wash 20 times with 25 ml portions of hot water each time. Recover any residual coal from the beaker by means of a rubber tipped rod and cold water. Drain the coal under suction for 5 min to 10 min.

Dismantle the filter, break up the wet coal, and dry the filter and coal in a vacuum oven at 50 °C and a pressure of 3,5 kPa¹⁾ absolute for about 1,5 h. Remove and allow to cool in air for about 1 h to attain equilibrium and then weigh. Recover the coal and transfer as much as possible to a glass stoppered bottle. Brush the filter top and filter paper free from coal and reweigh. Obtain the mass of extracted coal by difference.

Mix the extracted coal thoroughly and determine its moisture (see ISO 11722 for moisture in the analysis sample), ash (see ISO 1171 for determination of ash), and chlorine (see ISO 587 for determination of chlorine), as well as the total iron content of the ash (see ISO 157 for determination of forms of sulphur); determine also the moisture and ash content of the original sample, each determination being carried

1) 1 kPa = 10 mbar.

out according to the appropriate International Standards (see Bibliography). Calculate the hydrochloric acid equivalent to the chlorine content and the pyrites equivalent to the total iron content.

NOTE 1 For reactive coals, including brown coals and lignites, the acids can be placed in the beaker before adding the sample to avoid local overheating.

NOTE 2 The first hydrochloric acid extraction is unnecessary for coals having a carbon dioxide content of less than 0,5 % (m/m).

8 Expression of results

All results used in the calculation shall be on the dry basis. The mineral matter, *MM*, expressed as a percentage by mass, is given by Formula (1)²⁾.

$$\frac{m_1 - m_2 + m_3 + m_4 + 1,1 m_5}{m_1} \times 100 \quad (1)$$

where

*m*₁ is the mass, in grams, of the test portion taken;

*m*₂ is the mass, in grams, of the test portion after extraction;

*m*₃ is the mass, in grams, of pyrites in the extracted coal;

*m*₄ is the mass, in grams, of hydrochloric acid in the extracted coal;

*m*₅ is the mass, in grams, of ash, less iron oxide from the pyrites in the extracted coal

The mineral matter factor, *F*_{MM}, is given by Formula (2):

$$\frac{MM}{A} \quad (2)$$

where

A is the percentage of ash in the original coal.

An example of the calculation is given in [Annex A](#).

The result (preferably the mean of two determinations, see [Clause 9](#)) shall be reported to the nearest 0,1 %.

NOTE 1 If it is required to derive the mineral matter from the percentage of ash by the application of a formula, see ISO 1170.

NOTE 2 The factor 1,1 allows approximately for the water of hydration of the aluminium and silicon compounds in the demineralized coal. In most cases, the correction is small and can be ignored.

9 Precision of the method

Mineral matter	Maximum acceptable difference between results obtained	
	In the same laboratory (repeatability)	In different laboratories (reproducibility)
	0,4 % absolute	(see 9.2)

2) See the notes.

9.1 Repeatability

The result of duplicate determinations, carried out at different times in the same laboratory by the same operator with the same apparatus on the same analysis sample, should not differ by more than the above value.


9.2 Reproducibility

No value for reproducibility can be quoted for determinations carried out in different laboratories, since insufficient data are available.

10 Test report

The test report shall include the following information:

- a) an identification of the product tested;
- b) the reference of the method used;
- c) the results and the method of expression used;
- d) any unusual features noted during the determination;
- e) any operation not included in this International Standard, or regarded as optional.

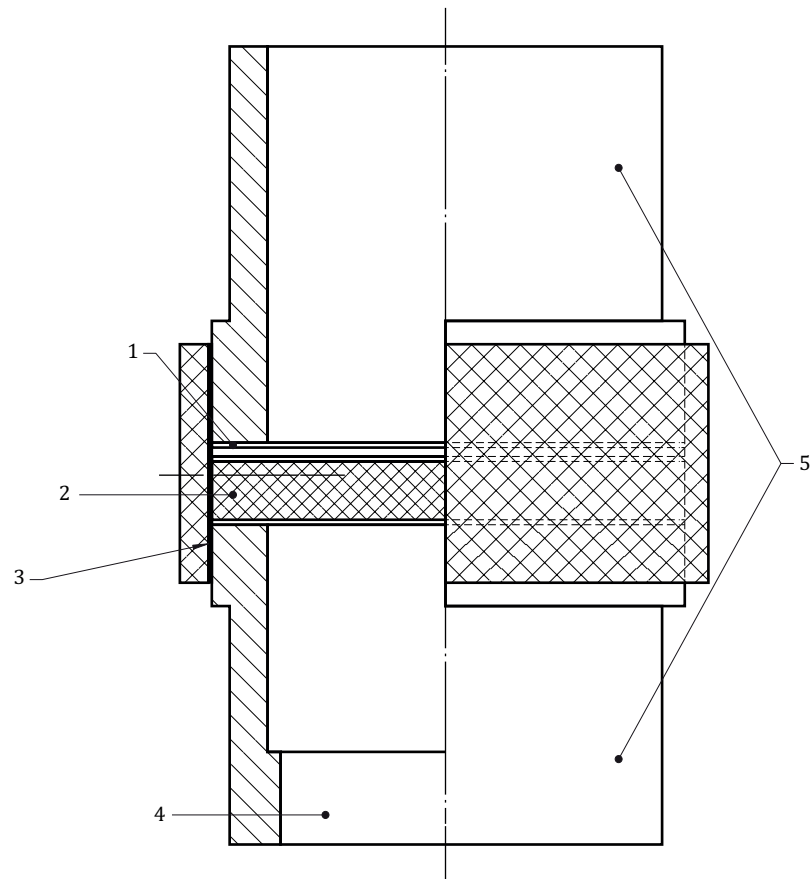

Key

- 1 paper filter, connected to the upper cylinder with an adhesive substance
- 2 plate of sintered alumina
- 3 rubber ring
- 4 cylinder of acid resistant material (for example, polyvinyl chloride)
- 5 cylinder of acid resistant material (for example, polyvinyl chloride)

Figure 1 — Filtering device (Left half shown in section)

Annex A (normative)

Example of calculation

The following example illustrates the method of calculation. All results are quoted on the dry basis.

		% (m/m)	g
1 Mass of original coal	=	6,836	(m_1)
2 Ash content of original coal	=	52,8	(A)
3 Mass of extracted coal	=	3,205	(m_2)
4 Ash content of extracted coal	=	6,03	(A_1)
5 Amount of hydrochloric acid absorbed by the extracted coal	=	1,06	(P_1)
6 Amount of iron oxide in the ash of the extracted coal	=	4,2	(P_2)
7 Loss in mass of the sample ($m_1 - m_2$)	=	3,631	
8 Mass of hydrochloric acid absorbed ($P_1 m_2 / 100$)	=	0,034	(m_4)
9 Mass of the pyrites in the extracted coal ($1,5 P_2 m_2 / 100$)	=	0,202	(m_3)
10 Mass of the residual ash [$1,1 m_2 (A_1 - P_2) / 100$]	=	0,065	($1,1 m_5$)
11 Total mass of mineral matter ($m_1 - m_2 + m_3 + m_4 + 1,1 m_5$)	=	3,932	(m_6)
12 Percentage of mineral matter ($100 m_6 / m_1$)	=	57,5	(MM)
13 Mineral matter factor (MM/A)	=	1,09	(F_{MM})

Bibliography

- [1] ISO 157, *Coal — Determination of forms of sulfur*
- [2] ISO 587, *Solid mineral fuels — Determination of chlorine using Eschka mixture*
- [3] ISO 1170, *Coal and coke — Calculation of analyses to different bases*
- [4] ISO 1171, *Solid mineral fuels — Determination of ash*
- [5] ISO 11722, *Solid mineral fuels — Hard coal — Determination of moisture in the general analysis test sample by drying in nitrogen*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™