

BS ISO 622:2016



BSI Standards Publication

**Solid mineral fuels —
Determination of phosphorus
content — Reduced
molybdophosphate
photometric method**

National foreword

This British Standard is the UK implementation of ISO 622:2016. It supersedes BS 1016-9:1977 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PTI/16, Solid mineral fuels.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.
Published by BSI Standards Limited 2016

ISBN 978 0 580 92525 2

ICS 75.160.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2016.

Amendments/Corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

BS ISO 622:2016

ISO
622

Second edition
2016-11-15

**Solid mineral fuels — Determination
of phosphorus content — Reduced
molybdophosphate photometric
method**

*Combustibles minéraux solides — Dosage du phosphore — Méthode
photométrique au molybdophosphate réduit*



Reference number
ISO 622:2016(E)

© ISO 2016



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
4.1 Extraction.....	1
4.2 Determination.....	1
5 Reagents	2
6 Apparatus	2
7 Sample preparation	3
8 Procedure	3
8.1 Dry oxidation method.....	3
8.2 Wet oxidation method.....	4
8.3 Determination.....	5
9 Expression of results	5
9.1 Method of calculation and formulae.....	5
10 Precision of the method	6
10.1 Repeatability.....	6
10.2 Reproducibility.....	6

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 27, *Solid minerals fuels*, Subcommittee SC 5, *Methods of analysis*.

This second edition cancels and replaces the first edition (ISO 622:1981), which has been technically revised. This document incorporates changes related to references and other minor items following its systematic review.

Solid mineral fuels — Determination of phosphorus content — Reduced molybdophosphate photometric method

1 Scope

This document specifies a reduced molybdophosphate photometric method for the determination of the total phosphorus content of hard coal, lignites and coke. Two methods for taking the phosphorus into solution are specified, namely extraction from the coal or coke ash with acid or by repeated oxidation of the coal or coke, by acid, to remove carbonaceous matter.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 383, *Laboratory glassware — Interchangeable conical ground joints*

ISO 565, *Test sieves — Metal wire cloth, perforated metal plate and electroformed sheet — Nominal sizes of openings*

ISO 1171, *Solid mineral fuels — Determination of ash*

ISO 18283, *Hard coal and coke — Manual sampling*

3 Terms and definitions

No terms and definitions are defined in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Principle

4.1 Extraction

Method 1: Removal of carbonaceous material by ashing in a muffle furnace under specified conditions, and extraction of phosphorus by treatment with hydrofluoric and sulphuric acids.

Method 2: Removal of carbonaceous material by repeated oxidation with nitric acid in the presence of sulphuric acid.

4.2 Determination

Addition of ammonium molybdate and ascorbic acid solution to the acid solution. Measurement of the absorbance of the resulting blue solution by a suitable optical instrument.

5 Reagents

During the analysis, use only reagents of recognized analytical grade and only distilled water or water of equivalent purity.

5.1 Hydrofluoric acid, approximately 400 g/l solution.

WARNING — Aqueous hydrofluoric acid is a highly corrosive liquid which attacks glass; the vapour is irritant and toxic. Its action on the skin and eyes is strongly corrosive, producing severe and painful burns which may not be immediately evident and which respond slowly to treatment. The solution should be handled only inside a well-ventilated fume cupboard. In the event of contact or suspected contact, flood with water and seek immediate medical attention. The manufacturer's literature should be consulted for further information.

5.2 Sulphuric acid, approximately 490 g/l solution.

5.3 Sulphuric acid, concentrated, ρ 1,84 g/ml, approximately 98 % (m/m) solution.

5.4 Nitric acid, concentrated, ρ 1,42 g/ml, approximately 70 % (m/m) solution.

5.5 Ammonium molybdate, 60 g/l solution.

5.6 Ascorbic acid, 50 g/l solution.

Prepare the solution fresh daily.

5.7 Antimony potassium tartrate ($\text{KSbO}\cdot\text{C}_4\text{H}_4\text{O}_6$), 1,36 g/l solution.

5.8 Reagent solution.

Mix 25 ml of the sulphuric acid solution (5.2), 10 ml of the ammonium molybdate solution (5.5), 10 ml of the ascorbic acid solution (5.6) and 5 ml of the antimony potassium tartrate solution (5.7). Prepare fresh immediately before use.

5.9 Phosphorus, standard stock solution corresponding to 0,100 g of P per litre.

Weigh, to the nearest 0,000 1 g, 0,439 2 g of potassium dihydrogen monophosphate (KH_2PO_4) (dried at 110 °C for 1 h) and dissolve in water. Transfer the solution quantitatively to a 1 000 ml one-mark volumetric flask, dilute to the mark and mix.

1 ml of this standard stock solution contains 0,100 mg of P.

5.10 Phosphorus, standard working solution corresponding to 1 mg of P per litre.

Transfer 10 ml of the standard phosphorus solution (5.9) to a 1 000 ml one-mark volumetric flask, dilute to the mark and mix. Prepare fresh immediately before use.

1 ml of this standard working solution contains 1 µg of P.

6 Apparatus

Ordinary laboratory apparatus and

6.1 Muffle furnace, as specified in ISO 1171.

6.2 Dish, of silica, porcelain or platinum, as specified in ISO 1171.

6.3 Insulating plate, of silica, 6 mm thick, or its equivalent, of such size as to be an easy sliding fit into the muffle furnace (6.1).

6.4 Platinum crucible, of capacity 25 ml to 30 ml, with lid.

6.5 Hot-air bath.

6.6 Digestion apparatus (see Figure 1), constructed of borosilicate glass, consisting of the following:

6.6.1 Flask, Kjeldahl flask, of capacity 300 ml, fitted with a 24/29 ground glass socket complying with ISO 383.

6.6.2 Fume duct, of outside diameter approximately 28 mm, fitted with a dropping funnel of capacity at least 15 ml and a 24/29 ground glass cone complying with ISO 383. The fume duct may be of one piece or assembled from spate units by means of ground glass joints.

6.6.3 Fume extractor, comprising a glass tube of diameter approximately 40 mm, sealed at one end and drawn out at the other end to form a connection to the water pump. The tube is fitted with a drain stopcock and a series of lipped holes to accommodate a number of fume ducts.

6.7 Spectrophotometer, or **photoelectric absorptiometer**, of the required sensitivity.

7 Sample preparation

The sample of coal or coke shall be the analysis sample, ground to pass a 212 μm test sieve complying with the requirements of ISO 565, taken and prepared in accordance with ISO 18283. The sample shall be thoroughly mixed, preferably by a mechanical means, immediately before the determination.

8 Procedure

8.1 Dry oxidation method

8.1.1 Determine the percentage of ash in the coal or coke as specified in ISO 1171. Grind the ash in an agate mortar to pass a 63 μm sieve complying with ISO 565.

8.1.2 Weigh, to an accuracy of 0,1 mg, about 0,05 g of the ash into the platinum crucible (6.4).

8.1.3 Add 2,0 ml of the sulphuric acid solution (5.2) and about 2,0 ml of the hydrofluoric acid solution (5.1). Place the lid on the crucible and digest on a boiling water bath for 30 min in a well-ventilated fume cupboard. Remove and rinse the lid, collecting the washings in the crucible. Allow the solution to evaporate on the water bath until most of the hydrofluoric acid and water have been removed.

8.1.4 Transfer the crucible to the hot-air bath (6.5), evaporate until dense white fumes from the sulphuric acid have evolved for a few minutes. Allow to cool, add 0,5 ml of the sulphuric acid solution (5.2), heat for a few minutes and allow to cool.

NOTE It is essential that the contents of the crucible are not evaporated completely to dryness at any stage.

8.1.5 Add about 20 ml of water to the crucible and digest on the water bath for 30 min, when all the extract should be in one solution. Allow to cool, transfer the solution to a 100 ml one-mark volumetric flask and dilute with water to the mark (solution A).

If the sample has a high arsenic content, this can interfere with the result and the solution should be reduced before the phosphorus determination.

8.1.6 Prepare a blank solution exactly as described above, but omitting the coal or coke ash.

8.2 Wet oxidation method

8.2.1 Weigh, to an accuracy of 1 mg, about 1 g of the coal or coke sample.

8.2.2 Transfer the test portion ([8.2.1](#)) to the clean, dry Kjeldahl flask ([6.6.1](#)). Assemble the apparatus ([6.6](#)) as shown in [Figure 1](#), in a well-ventilated fume cupboard. Add 7 ml of the sulphuric acid ([5.3](#)) and 3,5 ml of the nitric acid ([5.4](#)) by means of the dropping funnel, rotating the flask so as to wash down any sample remaining in the neck.

8.2.3 After the initial reaction has subsided, heat the flask carefully so that the reaction proceeds smoothly and without frothing. Continue heating the flask under the same conditions until only fumes of sulphuric acid are evolved. Add 0,2 ml to 0,4 ml of the nitric acid ([5.4](#)) to the dropping funnel and run the acid, drop by drop, into the flask.

NOTE If violent frothing occurs on addition of the mixed acid, apply a damp cloth to the neck of the flask and heat intermittently as the frothing subsides.

8.2.4 Heat for 2 min to 3 min until no more dense brown fumes are evolved. Repeat the addition of the nitric acid and the heating, rotating the flask periodically to wash down any carbonaceous matter adhering to the sides of the flask, until all visible carbonaceous matter has been oxidized and the solution is a pale greenish-yellow colour. This may take 1 1/2 h to 2 h, or even longer in exceptional cases with some coke samples.

NOTE For the first 15 min of heating a coal sample, the reaction mixture is a tarry mass; subsequently, it changes its colour from black to dark reddish-brown, to amber, and finally to a pale greenish-yellow. If a black liquid still remains after 45 min heating, either

- a) too low a temperature has been used and the nitric acid has not reacted with the sample; raise the temperature to distil off excess nitric acid, then continue the normal oxidation as described, or
- b) too high a temperature has been used, nitric acid being distilled off without reacting; cool, add more nitric acid and heat the mixture as described.

8.2.5 Heat the flask more strongly until white fumes appear and allow to fume for 5 min. Cool the flask to approximately room temperature, remove the dropping funnel and fume duct assembly and add a few glass beads to the contents of the flask.

NOTE If the colour reverts to amber or deep red, add a further 0,2 ml to 0,4 ml of the nitric acid, heat to fuming and allow to fume for 5 min.

8.2.6 Add cautiously 10 ml of water, heat until white fumes appear and then allow to fume gently for 10 min. Cool the flask until the evolution of the white fumes ceases, add 0,2 ml of the nitric acid, reheat the flask and allow to fume for a further 10 min.

8.2.7 To ensure complete oxidation, cool the flask to approximately room temperature and repeat the procedure described in [8.2.5](#).

8.2.8 Cool the flask to approximately room temperature, add 10 ml of water, heat to fuming and allow to fume for 20 min. Add a further 10 ml of water, heat to fuming, allow to fume for 10 min and cool.

8.2.9 Add a further 20 ml of water to the flask and digest on the boiling water bath for 30 min, when all the extract should be in solution. Filter the solution through a hardened, acid-washed filter paper; allow to cool, transfer the filtrate to a 100 ml one-mark volumetric flask and dilute with water to the mark (solution B) (see the note in [8.1.5](#)).

8.2.10 Prepare a blank solution exactly as described above, but omitting the coal or coke sample.

8.3 Determination

8.3.1 Pipette 10 ml of solution A or B as appropriate (see [8.1.5](#) or [8.2.9](#)) (the aliquot portion taken may be varied according to the phosphorus content of the sample), 10 ml of the blank solution (see [8.1.6](#) or [8.2.10](#) as appropriate) and 10 ml of the standard solution ([5.10](#)) into separate 50 ml one-mark volumetric flasks. A fourth 50 ml flask is required for the reagent blank.

Calibration is linear for aliquot portions containing up to 30 µg of phosphorus. With high phosphorus coals or cokes, it may be necessary to take a smaller aliquot portion.

8.3.2 Pipette 5 ml of the reagent solution ([5.8](#)) into each flask, swirling the contents during the addition, dilute with water to the mark, and mix thoroughly. Allow to stand for 20 min.

8.3.3 Measure the absorbance of the solutions against water, in the spectrophotometer ([6.7](#)) using 40 mm cells at a wavelength of 710 nm or in the photoelectric absorptiometer fitted with an appropriate filter.

9 Expression of results

9.1 Method of calculation and formulae

Calculate the percentage of phosphorus (P) in the analysis sample, using [Formulae \(1\)](#) and [\(2\)](#).

a) Dry oxidation method (see [8.1](#)):

$$\frac{A (D_1 - D_2)}{1\ 000 Vm (D_3 - D_4)} \quad (1)$$

where

A is the percentage of ash in the analysis sample;

m is the mass, in grams, of ash taken;

V is the volume, in millilitres, of sample solution taken for colour development;

*D*₁ is the absorbance of the sample solution;

*D*₂ is the absorbance of the sample blank solution;

*D*₃ is the absorbance of the standard phosphorus solution ([5.10](#));

*D*₄ is the absorbance of the reagent blank solution.

b) Wet oxidation method (see 8.2):

$$\frac{(D_1 - D_2)}{10 Vm (D_3 - D_4)} \quad (2)$$

where

m is the mass, in grams, of the test portion;

V, D_1, D_2, D_3 and D_4 have the same meaning as in a) above.

Report the result, preferably the mean of duplicate determinations, to the nearest 0,001 %.

10 Precision of the method

10.1 Repeatability


The results of duplicate determinations, carried out at different times in the same laboratory by the same operator with the same apparatus on two representative portions taken from the same sample (see Clause 7), should not differ by more than the values given in Table 1.

10.2 Reproducibility

The means of the results of duplicate determinations, carried out in two different laboratories on representative portions taken from the same sample (see Clause 7), should not differ by more than the values given in Table 1.

Table 1

Phosphorus content of coal or coke % (m/m)	Repeatability	Reproducibility
Less than 0,02	0,002 absolute	0,005 absolute
Equal to or more than 0,02	10 % of the mean of the results	25 % of the mean of the results

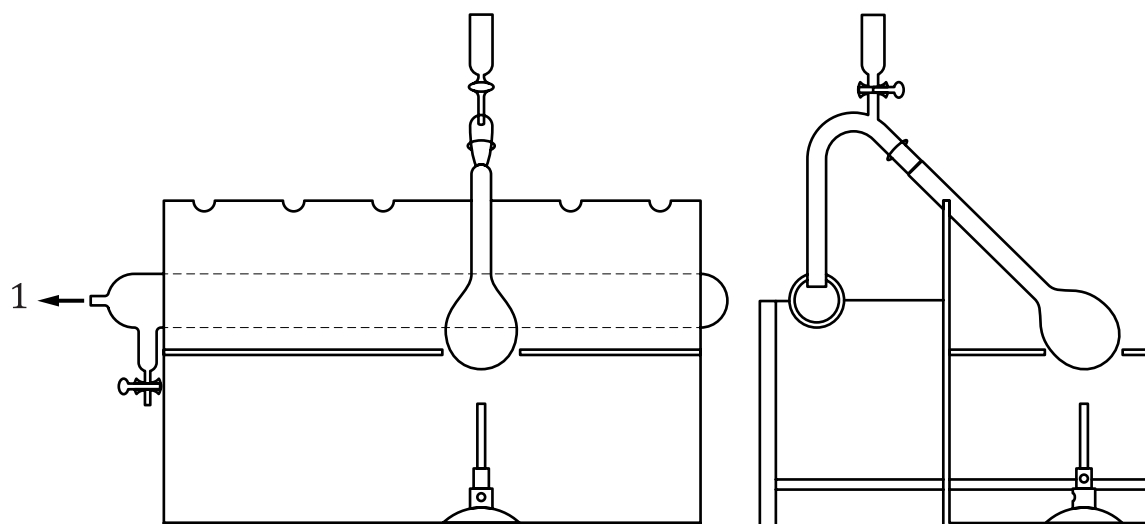

Key

1 to pump

Figure 1 — Apparatus for wet oxidation of the sample

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK