

BS ISO 1656:2014



BSI Standards Publication

Rubber, raw natural, and rubber latex, natural — Determination of nitrogen content

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 1656:2014. It supersedes BS 7164-21:1996 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/23, Test methods for rubber and non-black compounding ingredients.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 82378 7

ICS 83.040.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2014.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

BS ISO 1656:2014

ISO
1656

Fourth edition
2014-10-15

**Rubber, raw natural, and rubber latex,
natural — Determination of nitrogen
content**

*Caoutchouc brut naturel et latex de caoutchouc naturel — Dosage de
l'azote*



Reference number
ISO 1656:2014(E)

© ISO 2014



COPYRIGHT PROTECTED DOCUMENT

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Principle	1
4 Macro-method	1
4.1 Reagents.....	1
4.2 Apparatus.....	2
4.3 Sampling and preparation of test portion.....	2
4.4 Procedure.....	3
4.5 Blank test.....	3
4.6 Expression of results.....	3
5 Semi-micro method	4
5.1 Reagents.....	4
5.2 Apparatus.....	5
5.3 Sampling and preparation of test portion.....	5
5.4 Procedure.....	5
5.5 Blank test.....	6
5.6 Expression of results.....	6
6 Precision	7
7 Test report	7
Annex A (informative) Guidance for using precision results	17
Annex B (informative) Precision	18

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

This fourth edition cancels and replaces the third edition (ISO 1656:1996), which has been technically revised.

Rubber, raw natural, and rubber latex, natural — Determination of nitrogen content

WARNING — Persons using this International Standard should be familiar with normal laboratory practice. This International Standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

1 Scope

This International Standard specifies a macro-method and a semi-micro method for the determination of nitrogen in raw natural rubber and in natural rubber latex using variants of the Kjeldahl process.

NOTE The determination of nitrogen in natural rubber is usually carried out in order to arrive at an estimate of the protein content. Minor amounts of non-proteinous nitrogen containing constituents are also present. However, in the dry solids prepared from natural rubber latex, these materials can make a substantial contribution to the total nitrogen content.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 123, *Rubber latex — Sampling*

ISO 124, *Latex, rubber — Determination of total solids content*

ISO 1795, *Rubber, raw natural and raw synthetic — Sampling and further preparative procedures*

ISO/TR 9272, *Rubber and rubber products — Determination of precision for test method standards*

3 Principle

A known mass of the sample is digested with a mixture of sulfuric acid, potassium sulfate, and catalytic amounts of copper sulfate and selenium or sodium selenate, thereby converting nitrogen compounds into ammonium hydrogen sulfate from which the ammonia is distilled after making the mixture alkaline.

The distilled ammonia is absorbed either in standard volumetric sulfuric acid solution followed by titration of the excess acid with a standard volumetric base solution or in boric acid solution followed by titration with standard volumetric acid solution (as boric acid is a weak acid, it does not affect the indicator used for this titration).

4 Macro-method

4.1 Reagents

During the analysis, unless otherwise stated, use only reagents of recognized analytical grade and only distilled water or water of equivalent purity.

4.1.1 Catalyst mixture or catalyst solution

CAUTION — When working with selenium, avoid breathing vapours and/or contact with skin or clothing. Work only with adequate ventilation.

4.1.1.1 Catalyst mixture

Prepare a finely divided intimate mixture of the following:

- 30 parts by mass of anhydrous potassium sulfate (K_2SO_4);
- four parts by mass of copper sulfate pentahydrate ($CuSO_4 \cdot 5H_2O$);
- one part by mass of selenium powder or two parts by mass of sodium selenate decahydrate ($Na_2SeO_4 \cdot 10H_2O$).

4.1.1.2 Catalyst solution

Dissolve, with heating, the following:

- 110 g of anhydrous potassium sulfate;
- 14,7 g of copper sulfate pentahydrate;
- 3,7 g of selenium or 7,49 g of sodium selenate, in 600 cm³ of sulfuric acid (4.1.2).

4.1.2 Sulfuric acid, $\rho = 1,84$ g/cm³.

4.1.3 Sulfuric acid standard volumetric solution, $c(H_2SO_4) = 0,05$ mol/dm³.

4.1.4 Sodium hydroxide standard volumetric solution, $c(NaOH) = 0,1$ mol/dm³.

4.1.5 Sodium hydroxide solution, $c(NaOH)$ approximately 10 mol/dm³.

Dissolve 400 g of solid sodium hydroxide in 600 cm³ of water and dilute to 1 000 cm³.

4.1.6 Boric acid solution, $c(H_3BO_3)$ approximately 0,17 mol/dm³.

Dissolve 10,5 g of solid boric acid in water, warming if necessary, and dilute to 1 000 cm³ then cool the solution to room temperature.

4.1.7 Mixed indicator solution.

Dissolve 0,1 g of methyl red and 0,05 g of methylene blue in 100 cm³ of at least 95 % (V/V) ethanol.

This indicator might deteriorate during storage and shall therefore be freshly prepared.

4.2 Apparatus

Ordinary laboratory apparatus and Kjeldahl apparatus, with a digestion flask of capacity 800 cm³.

4.3 Sampling and preparation of test portion

For the determination of nitrogen in raw solid rubber, a test portion shall be taken from the homogenized piece, sampled and prepared in accordance with ISO 1795.

For the determination of nitrogen in latex, a representative portion (as specified in ISO 123) of thoroughly mixed latex containing about 2 g of total solids shall be dried to constant mass, as specified in ISO 124.

4.4 Procedure

4.4.1 Cut about 2 g of the rubber or dried latex, weighed to the nearest 0,5 mg, into small pieces and place in the digestion flask (see 4.2). Add about 13 g of the catalyst mixture (4.1.1.1) and 60 cm³ of the sulfuric acid (4.1.2) or, alternatively, 65 cm³ of the catalyst solution (4.1.1.2). Mix the contents of the flask by swirling and then boil gently until the solution is clear. Continue boiling for 1 h.

NOTE Acidic fumes evolved during digestion will be trapped in an alkaline solution and will be neutralized before being discharged.

Allow the digestion flask and its contents to cool to room temperature then cautiously add 200 cm³ of water and mix by swirling.

Place the receiving flask containing the absorbing solution in position, connect the distillation unit, and then slowly add 150 cm³ of the sodium hydroxide solution (4.1.5) to the digestion flask from a dropping funnel.

4.4.2 Carry out the absorption and titration of the liberated ammonia by the procedure described in 4.4.2.1 or 4.4.2.2. The temperature of the receiving flask shall be maintained below 30 °C to prevent any loss of ammonia.

NOTE Ensure proper disposal of the selenium-containing waste in the distillation flask.

4.4.2.1 Place 75 cm³ of water and, by means of a pipette, 25 cm³ of the standard volumetric sulfuric acid solution (4.1.3) in the receiving flask of the distillation unit together with two drops of mixed indicator solution (4.1.7). Position the receiving flask so that the end of the delivery tube from the condenser dips below the surface of the absorbing solution. While holding the stopper of the digestion flask in place, thoroughly mix the contents by swirling. Immediately commence distillation and continue at a steady rate until 200 cm³ of distillate have been collected. If the colour of the indicator changes, it indicates alkalinity of the absorbing solution. Discontinue the determination and repeat the procedure using more sulfuric acid or a smaller test portion.

When the distillation is complete (normally, when the volume in the flask reaches about 300 cm³), titrate the contents with the sodium hydroxide solution (4.1.4), reading the burette to the nearest 0,02 cm³.

4.4.2.2 Place 100 cm³ of the boric acid solution (4.1.6) in the receiving flask of the distillation unit with two drops of the mixed indicator solution (4.1.7). Carry out the distillation as described in 4.4.2.1 and titrate the distillate with the sulfuric acid solution (4.1.3), reading the burette to the nearest 0,02 cm³.

NOTE If the concentrations of the standard volumetric solution used are not exactly as specified in the list of reagents, appropriate corrections are to be made.

4.5 Blank test

In parallel with the determination, carry out a blank test using the same quantities of reagents under the same operating conditions but omitting the test portion.

4.6 Expression of results

4.6.1 When sulfuric acid is used as the absorbing solution as specified in 4.4.2.1, the nitrogen content of the rubber, expressed as a percentage by mass, is given by Formula (1):

$$\frac{(V_1 - V_2) \times c \times 0,014}{m} \times 100 \quad (1)$$

where

V_1 is the volume, in cubic centimetres, of sodium hydroxide solution (4.1.4) required for the titration;

V_2 is the volume, in cubic centimetres, of sodium hydroxide solution (4.1.4) required for the titration in the blank test;

c is the concentration of sodium hydroxide;

m is the mass, in grams, of the test portion.

Express the results to the nearest 0,01 %.

4.6.2 When boric acid is used as the absorbing solution as specified in 4.4.2.2, the nitrogen content of the rubber, expressed as a percentage by mass, is given by Formula (2):

$$\frac{(V_3 - V_4) \times c \times 0,028}{m} \times 100 \quad (2)$$

where

V_3 is the volume, in cubic centimetres, of sulfuric acid solution (4.1.3) required for the titration;

V_4 is the volume, in cubic centimetres, of sulfuric acid solution (4.1.3) required for the titration in the blank test;

c is the concentration of sulfuric acid;

m is the mass, in grams, of the test portion.

Express the results to the nearest 0,01 %.

5 Semi-micro method

5.1 Reagents

During the analysis, unless otherwise stated, use only reagents of recognized analytical grade and only distilled water or water of equivalent purity.

5.1.1 Catalyst mixture

CAUTION — When working with selenium, avoid breathing vapours and/or contact with skin or clothing. Work only with adequate ventilation.

Prepare a finely divided intimate mixture of the following:

- 30 parts by mass of anhydrous potassium sulfate (K_2SO_4);
- four parts by mass of copper sulfate pentahydrate ($CuSO_4 \cdot 5H_2O$);
- one part by mass of selenium powder or two parts by mass of sodium selenate decahydrate ($Na_2SeO_4 \cdot 10H_2O$).

5.1.2 Sulfuric acid, $\rho = 1,84 \text{ g/cm}^3$.

5.1.3 Sulfuric acid standard volumetric solution, $c(\text{H}_2\text{SO}_4)$ 0,01 mol/dm³.

5.1.4 Sodium hydroxide solution, $c(\text{NaOH})$ approximately 10 mol/dm³.

Dissolve 400 g of solid sodium hydroxide in 600 cm³ of water and dilute to 1 000 cm³.

5.1.5 Sodium hydroxide, standard volumetric solution, $c(\text{NaOH}) = 0,02$ mol/dm³, carbonate-free.

5.1.6 Boric acid solution, $c(\text{H}_3\text{BO}_3)$ approximately 0,17 mol/dm³.

Dissolve 10,5 g of solid boric acid in 200 cm³ of water, warming if necessary, and dilute to 1 000 cm³, then cool the solution to room temperature.

5.1.7 Mixed indicator solution.

Dissolve 0,1 g of methyl red and 0,05 g of methylene blue in 100 cm³ of at least 95 % (V/V) ethanol.

This indicator might deteriorate during storage and shall therefore be freshly prepared.

5.2 Apparatus

Ordinary laboratory apparatus and the following are to be used.

5.2.1 Semi-micro Kjeldahl digestion apparatus.

5.2.1.1 Digestion flasks of capacity 30 cm³ and 10 cm³ (for an example of a typical apparatus, see [Figure 1](#), [Figure 2](#), and [Figure 3](#)).

5.2.1.2 Automated digestion block (for an example of a typical apparatus, see [Figure 10](#)).

5.2.2 Semi-micro Kjeldahl distillation unit, with a condenser tube of silver, borosilicate glass, or tin (for an example, see [Figure 4](#) to [Figure 9](#)).

5.2.3 Semi-micro burette of capacity 5 cm³ or 10 cm³, graduated in 0,02 cm³ divisions.

5.3 Sampling and preparation of test portion

For the determination of nitrogen in raw solid rubber, a test portion shall be taken from the homogenized piece, sampled and prepared in accordance with ISO 1795.

For the determination of nitrogen in latex, a representative portion (as specified in ISO 123) of thoroughly mixed latex containing about 0,1 g of total solids shall be dried to constant mass, as specified in ISO 124.

5.4 Procedure

5.4.1 Weigh to the nearest 0,1 mg, 0,1 g to 0,2 g of the rubber or dried latex and place in a digestion flask ([5.2.1.1](#)). Add about 0,65 g of the catalyst mixture ([5.1.1](#)) and 3,0 cm³ of the sulfuric acid ([5.1.2](#)) and heat the contents carefully to the boiling point. Continue boiling for a further 30 min after the digest has become clear and green with no yellow tint.

NOTE Acidic fumes evolved during digestion will be trapped in an alkaline solution and will be neutralized before being discharged.

Avoid excess boiling, as indicated by a tendency for the digest to solidify on cooling, since this can lead to loss of nitrogen.

Bring the water in the steam generator of the distillation unit to boil and pass steam through the semi-micro Kjeldahl distillation unit (5.2.2), including the receiving flask, for at least 2 min. The water jacket of the condenser shall be empty of water during the steaming-out operation. Meanwhile, cool the digestion flask to room temperature or below, add 10 cm³ of water, and immediately transfer the contents to the distillation flask at the conclusion of the steaming-out process. Complete the transfer by rinsing three times with 3 cm³ portions of water and draining the flask thoroughly after each transfer.

5.4.2 Discard any condensate which has been collected in the receiver and complete the distillation and titration of ammonia by the procedure described in 5.4.2.1 or 5.4.2.2. The temperature of the receiving flask shall be maintained below 30 °C to prevent loss of ammonia.

NOTE Ensure proper disposal of the selenium-containing waste in the distillation flask.

5.4.2.1 Add from the semi-micro burette (5.2.3) to the steamed-out receiver of the distillation apparatus a measured volume of sulfuric acid solution (5.1.3), using at least 5 cm³ (the exact volume depending on the amount of nitrogen expected), together with two drops of the mixed indicator solution (5.1.7) and about 5 cm³ of water. Position the receiver so that the end of the delivery tube from the condenser dips below the surface of the acid. It is an advantage to tilt the receiver slightly to gain a greater depth of liquid.

Add approximately 15 cm³ of the sodium hydroxide solution (5.1.4) to the distillation flask by means of a measuring cylinder and pass steam from the generator through the distillation flask for 10 min to 12 min at such a rate that the final volume of liquid in the receiver is about 70 cm³. If the colour of the indicator changes, indicating alkalinity of the absorbing solution, discontinue the determination and repeat the procedure using more sulfuric acid or a smaller test portion.

When the distillation is complete, lower the receiving flask until the tip of the condenser is above the level of the acid, continue the distillation for another 1 min and then rinse the tip of the condenser tube with a few cubic centimetres of water which shall be collected in the distillate. Immediately titrate the contents of the receiving flask with the sodium hydroxide solution (5.1.5), reading the burette to the nearest 0,02 cm³.

5.4.2.2 Place about 10 cm³ of the boric acid solution (5.1.6) in the steamed-out receiving flask with two drops of the mixed indicator solution (5.1.7). Carry out the distillation as described in 5.4.2.1, but note that, in the presence of boric acid, the indicator colour should change immediately distillation of ammonia commences. Titrate the distillate with sulfuric acid solution (5.1.3), reading the burette to the nearest 0,02 cm³.

5.5 Blank test

In parallel with the determination, carry out a blank test using the same quantities of reagents under the same operating conditions but omitting the test portion.

5.6 Expression of results

5.6.1 When sulfuric acid is used as the absorbing solution as specified in 5.4.2.1, the nitrogen content of the rubber, expressed as a percentage by mass, is given by Formula (3):

$$\frac{(V_1 - V_2) \times c \times 0,014}{m} \times 100 \quad (3)$$

where

V_1 is the volume, in cubic centimetres, of sodium hydroxide solution (5.1.5) required for the titration;

V_2 is the volume, in cubic centimetres, of sodium hydroxide solution (5.1.5) required for the titration in the blank test;

c is the concentration of sodium hydroxide;

m is the mass, in grams, of the test portion.

Express the results to the nearest 0,01 %.

5.6.2 When boric acid is used as the absorbing solution as specified in 5.4.2.2, the nitrogen content of the rubber, expressed as a percentage by mass, is given by Formula (4):

$$\frac{(V_3 - V_4) \times c \times 0,028}{m} \times 100 \quad (4)$$

where

V_3 is the volume, in cubic centimetres, of sulfuric acid solution (5.1.3) required for the titration;

V_4 is the volume, in cubic centimetres, of sulfuric acid solution (5.1.3) required for the titration in the blank test;

c is the concentration of sulfuric acid;

m is the mass, in grams, of the test portion.

Express the results to the nearest 0,01 %.

6 Precision


See [Annex B](#).

7 Test report

The test report shall include the following information:

- a) reference to this International Standard (i.e. ISO 1656) and the method used;
- b) all details necessary for the identification of the material tested;
- c) results and the units in which they are expressed;
- d) any unusual features noted during the determination;
- e) any operation not included in this International Standard or in the International Standards to which reference is made and any operation regarded as optional;
- f) date of the test.

NOTE If the concentrations of the standard volumetric solutions used are not exactly as specified in the list of reagents, appropriate corrections are to be made.

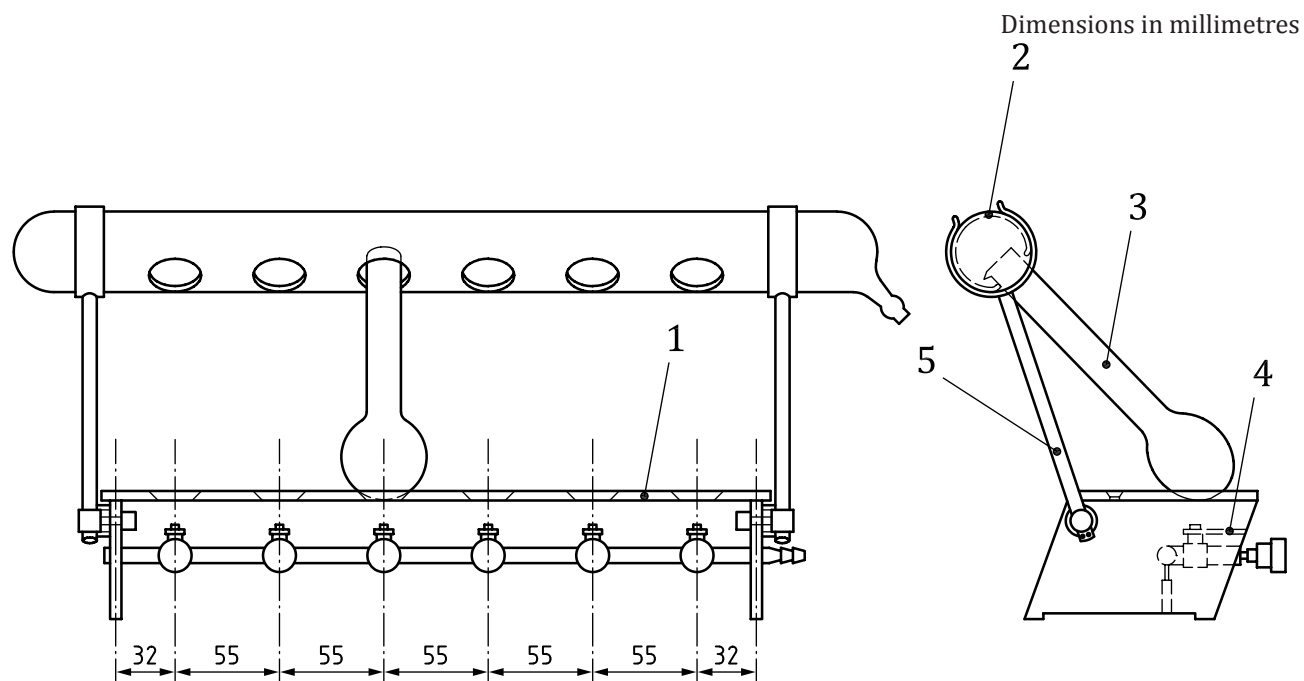


Key

- 1 shelf made of heat-resistant, thermally insulating material
- 2 exhaust tube
- 3 digestion flask
- 4 micro-burner
- 5 support rod with adjustment for angle and length

NOTE Where no tolerances are shown, normal working tolerances are allowed.

Figure 1 — Assembly of digestion apparatus for the semi-micro method

Dimensions in millimetres

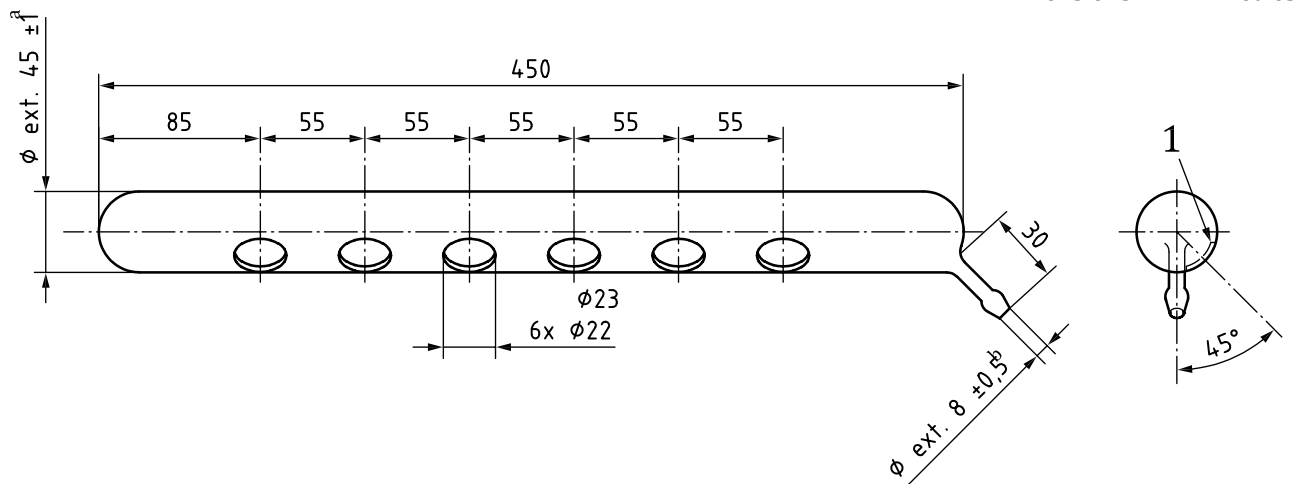


Key

- 1 internal flange
- a Wall 1,5 mm to 2,25 mm.
- b Wall 1,25 mm to 1,75 mm.


NOTE Where no tolerances are shown, normal working tolerances are allowed.

Figure 2 — Exhaust tube for the semi-micro method

Dimensions in millimetres

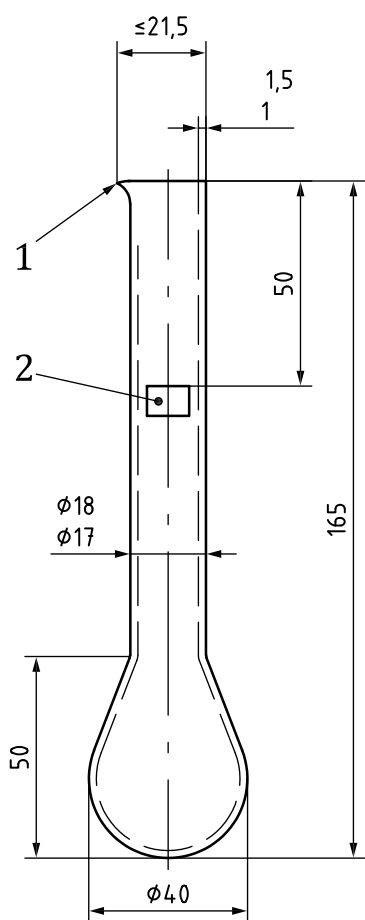

a) 30 cm³ flask

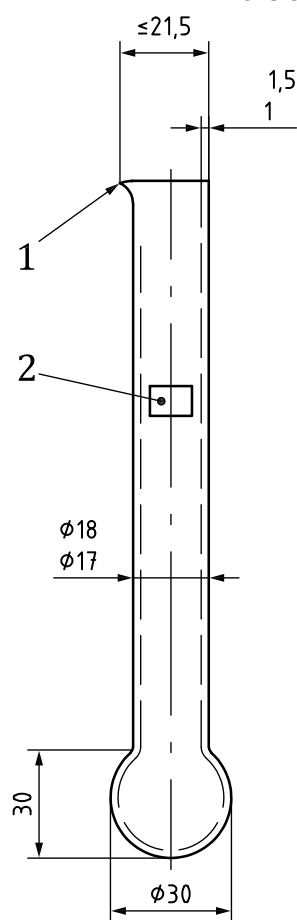


b) 10 cm³ flask

Key

- 1 spout
- 2 labelling badges


NOTE Where no tolerances are shown, normal working tolerances are allowed.

Figure 3 — Digestion flasks for the semi-micro method

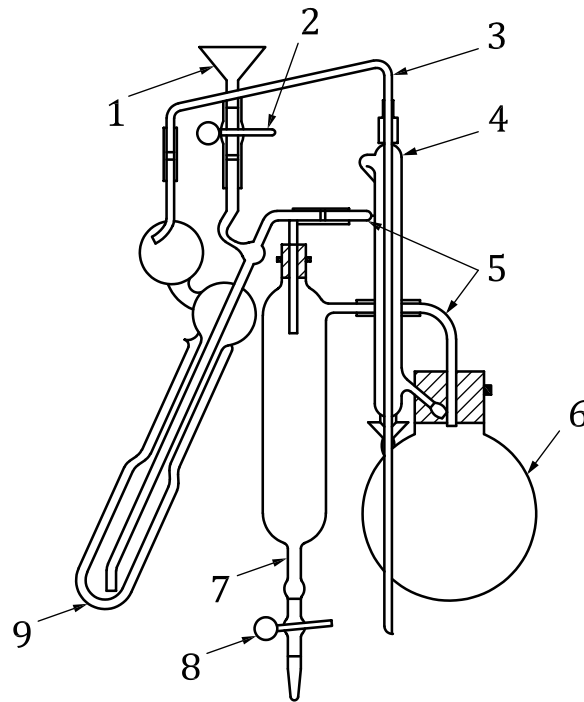

Elevation

(Three-quarter view as indicated by plan below)

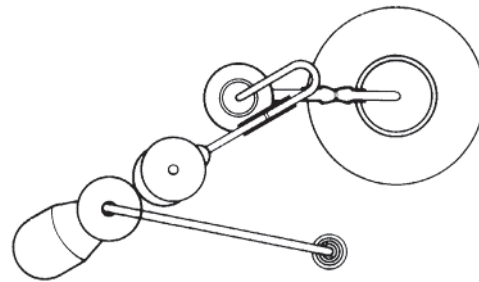


Plan

Key

- 1 funnel, \varnothing 50mm
- 2 spring clip
- 3 condenser tube
- 4 condenser
- 5 connecting tubes bent to fit after flasks are in position
- 6 steam-generating flask (1 dm³ flask with bolthead)
- 7 trap
- 8 spring clip
- 9 distillation flask

Figure 4 — Assembly of distillation apparatus for the semi-micro method

Dimensions in millimetres

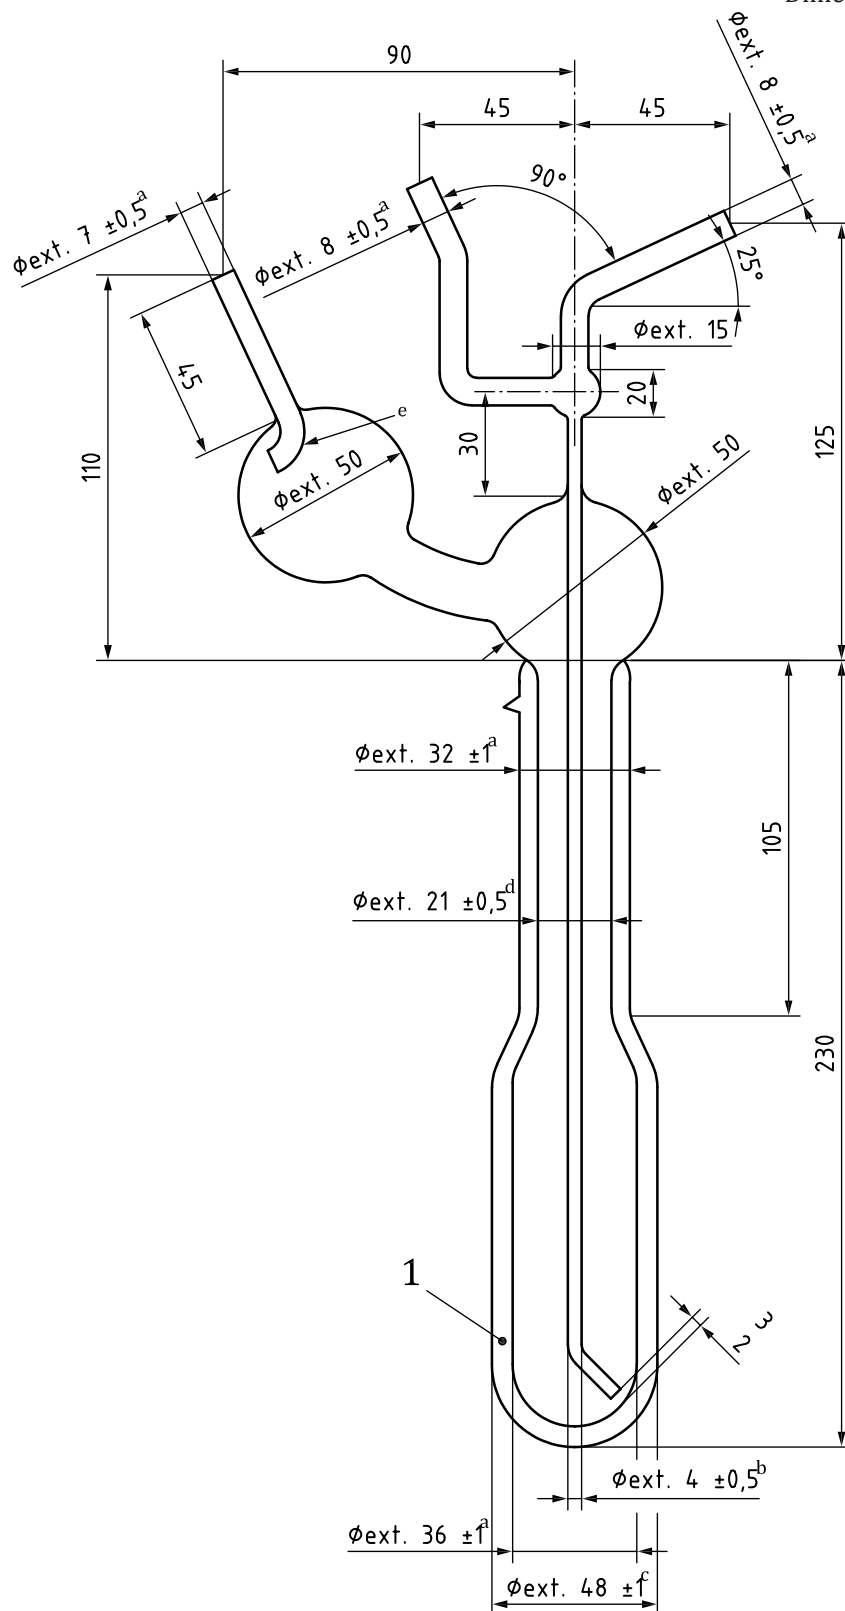


Key

- 1 jacket highly evacuated
- a Wall 1,25 mm to 1,75 mm.
- b Wall 0,5 mm to 1 mm.
- c Wall 1,5 mm to 2,25 mm.
- d Wall 1 mm to 1,5 mm.
- e Hole \varnothing 3 mm to \varnothing 4 mm.

NOTE Where no tolerances are shown, normal working tolerances are allowed.

Figure 5 — Distillation flask for the semi-micro method

Dimensions in millimetres

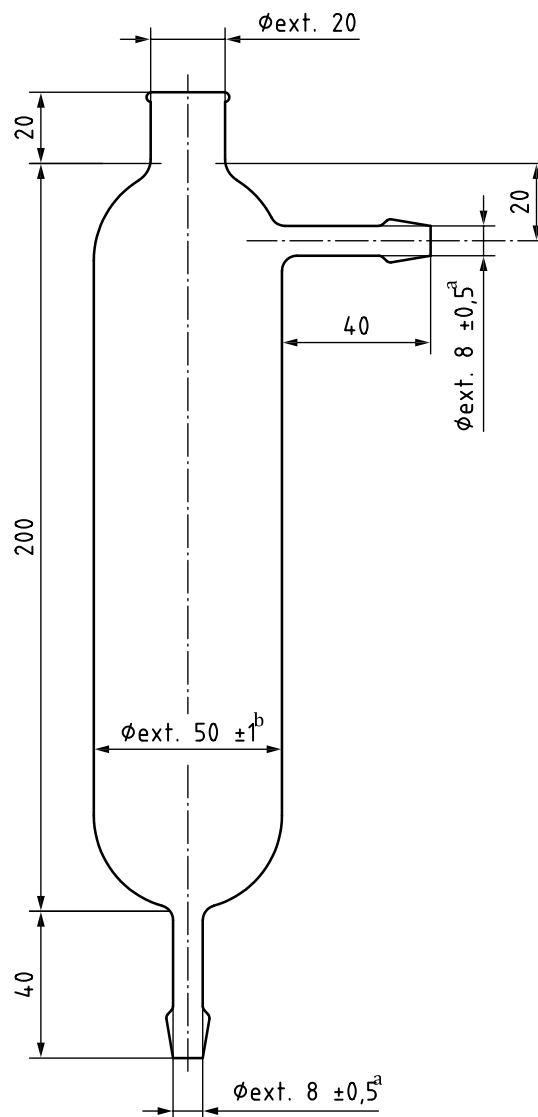

Key

- a Wall 1,25 mm to 1,75 mm.
- b Wall 1,25 mm to 2,25 mm.

NOTE Where no tolerances are shown, normal working tolerances are allowed.

Figure 6 — Trap for the semi-micro method

Dimensions in millimetres



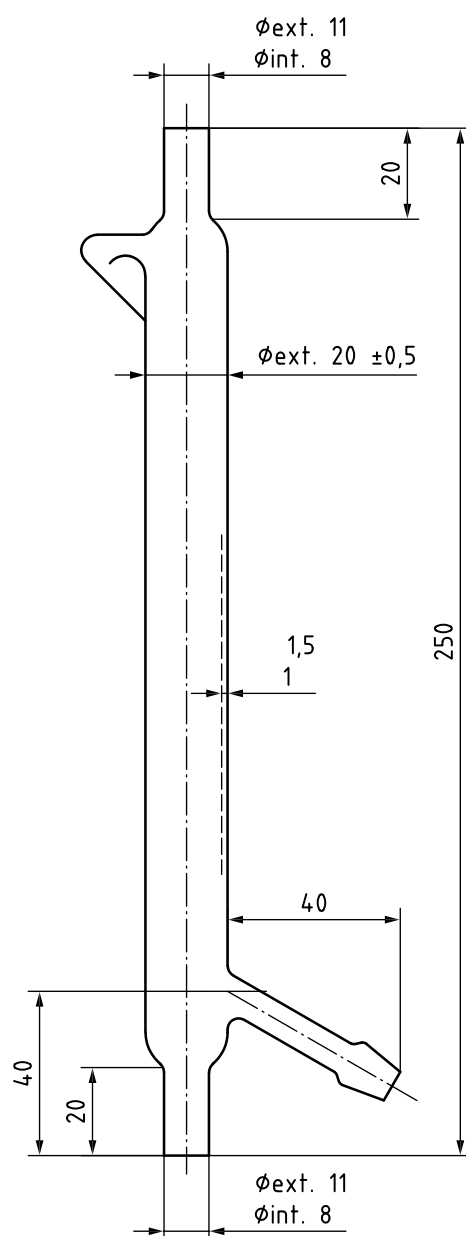


Figure 7 — Condenser jacket for the semi-micro method

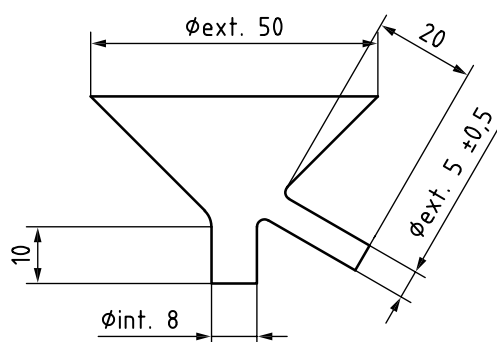

NOTE Where no tolerances are shown, normal working tolerances are allowed.


Figure 8 — Drip funnel for the semi-micro method

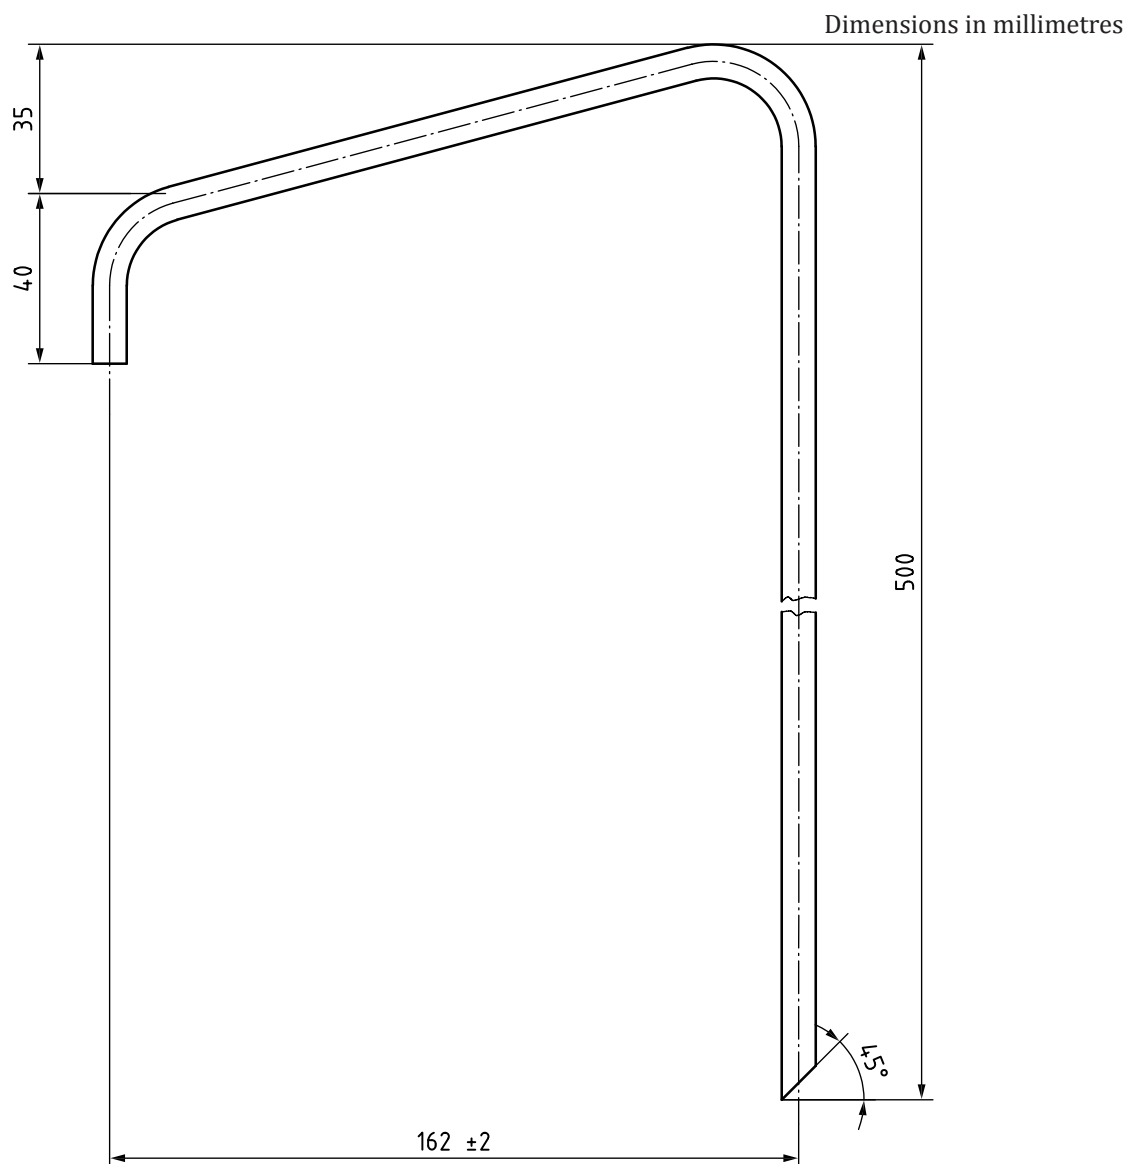

NOTE Where no tolerances are shown, normal working tolerances are allowed.

Figure 9 — Condenser tube for the semi-micro method

Dimensions in millimetres

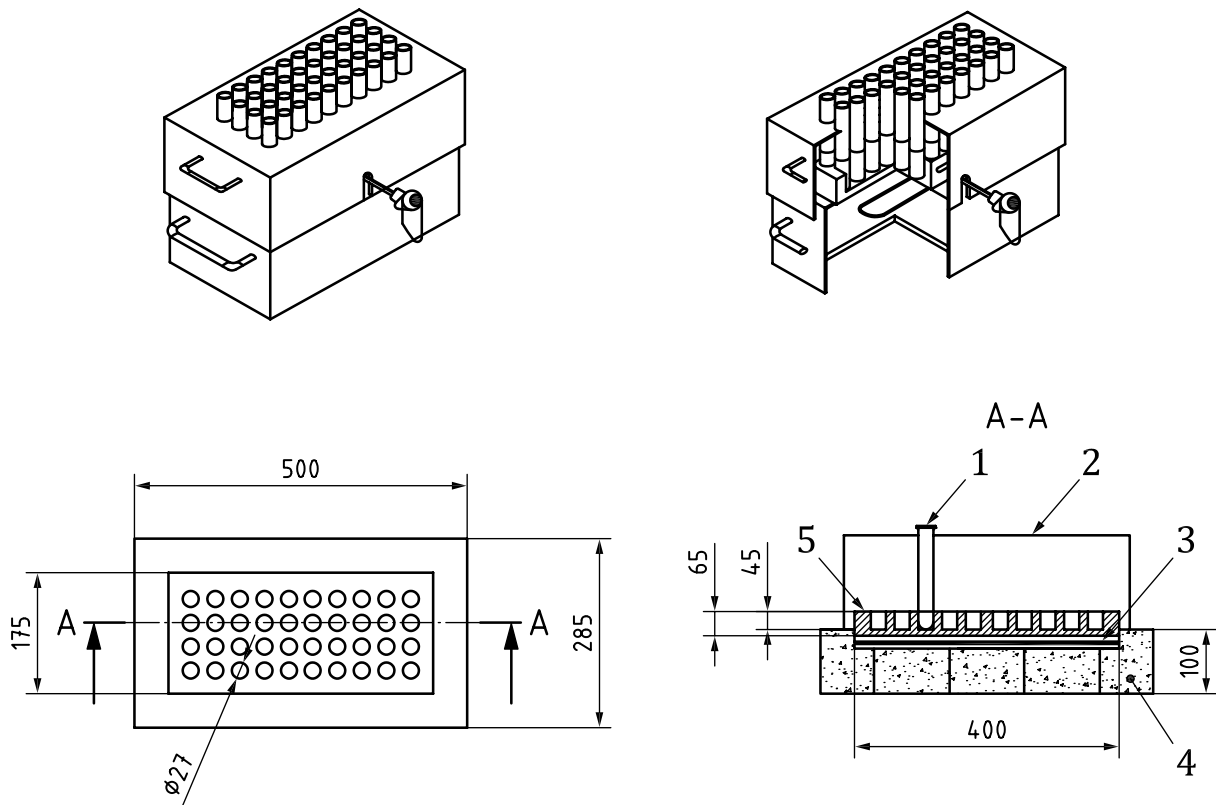

Key

- 1 tube
- 2 tube support
- 3 heater
- 4 insulator
- 5 aluminium block

NOTE Where no tolerances are shown, normal working tolerances are allowed.

Figure 10 — Digestion block

Annex A (informative)

Guidance for using precision results

A.1 The general procedure for using precision results is as follows, with the symbol $|x_1 - x_2|$ designating a positive difference in any two measurement values (i.e. without regard to sign).

A.2 Enter the appropriate precision table (for whatever test parameter is being considered) at an average value (of the measured parameter) nearest to the “test” data average under consideration. This line will give the applicable r , (r), R , or (R) for use in the decision process.

A.3 With these r and (r) values, the following general repeatability statements may be used to make decisions.

A.3.1 For an absolute difference: the difference $|x_1 - x_2|$ between two test (value) averages, found on nominally identical material samples under normal and correct operation of the test procedure, will exceed the tabulated repeatability r on average not more than once in 20 cases.

A.3.2 For a percentage difference between two test (value) averages: The percentage difference between two test values, found on nominally identical material samples under normal and correct operation of the test procedure, will exceed the tabulated repeatability (r) on average not more than once in 20 cases.

$$\left[|x_1 - x_2| / \left((x_1 + x_2) / 2 \right) \right] \times 100$$

A.4 With these R and (R) values, the following general reproducibility statements may be used to make decisions.

A.4.1 For an absolute difference: The absolute difference $|x_1 - x_2|$ between two independently measured test (value) averages, found in two laboratories using normal and correct test procedures on nominally identical material samples, will exceed the tabulated reproducibility R not more than once in 20 cases.

A.4.2 For a percentage difference between two test (value) averages: The percentage difference between two independently measured test (value) averages, found in two laboratories using normal and correct test procedures on nominally identical material samples, will exceed the tabulated reproducibility (R) not more than once in 20 cases.

$$\left[|x_1 - x_2| / \left((x_1 + x_2) / 2 \right) \right] \times 100$$

Annex B (informative)

Precision

B.1 General

The precision calculations to express repeatability and reproducibility were performed in accordance with ISO/TR 9272. Consult this Technical Report for precision concepts and nomenclature. [Annex A](#) gives guidance on the use of repeatability and reproducibility.

B.2 Precision details

An interlaboratory test programme was organized in 2012 by the Malaysian Rubber Board using semi-micro Kjeldahl digestion apparatus. Two separate programmes were conducted, one in March and one in September. The following two types of materials were sent to each laboratory:

- a) blended samples of two rubbers “A” and “B”;
- b) unblended (normal) samples of two rubbers “A” and “B”.

NOTE 1 Blended samples are samples that are blended before they are given to participants while the unblended samples are samples that are not blended before they are given to the participants.

NOTE 2 Materials A and B are two different samples that are coming from two different sources.

A special interlaboratory test programme was also organized by the Malaysian Rubber Board in 2013 to compare the automated digestion block apparatus and semi-micro Kjeldahl digestion apparatus.

For all samples, a test result was taken as the mean of three separate determinations.

A “type 1” precision was measured in the interlaboratory test programme. The time period for repeatability and reproducibility was on a scale of days. A total of 12 laboratories participated in the programme for blended samples and a total of 12 laboratories in the programme for unblended samples. For the special interlaboratory test programme to compare the automated digestion block apparatus and semi-micro Kjeldahl digestion apparatus; a total of five laboratories participated.

B.3 Precision results

The precision results for the blended-sample programme are given in [Table B.1](#) and the results for the unblended-sample programme are given in [Table B.2](#).

The precision results for the automated digestion block programme are given in [Table B.3](#) and the results for the semi-micro Kjeldahl digestion apparatus programme are given in [Table B.4](#).

Table B.1 — Type 1 precision — Blended-sample testing

Rubber sample	Average nitrogen content % (m/m)	Within-laboratory repeatability		Interlaboratory reproducibility	
		<i>r</i>	(<i>r</i>)	<i>R</i>	(<i>R</i>)
A	0,347 9	0,022 7	6,52	0,065 6	18,86
B	0,633 0	0,022 9	3,62	0,107 4	16,97

r = repeatability, in percent by mass
(*r*) = repeatability, in percent (relative) of the average
R = reproducibility, in percent by mass
(*R*) = reproducibility, in percent (relative) of the average

Table B.2 — Type 1 precision — Unblended-sample testing

Rubber sample	Average nitrogen content (% m/m)	Within-laboratory repeatability		Interlaboratory reproducibility	
		<i>r</i>	(<i>r</i>)	<i>R</i>	(<i>R</i>)
A	0,246 5	0,026 9	10,91	0,083 3	33,79
B	0,256 4	0,0255	9,95	0,082 0	31,98

See Table B.1 for symbol definitions.

Table B.3 — Type 1 precision — Automated digestion block

Rubber sample	Average nitrogen content (% m/m)	Within-lab repeatability		Interlaboratory reproducibility	
		<i>r</i>	(<i>r</i>)	<i>R</i>	(<i>R</i>)
SMR CV60	0,380 6	0,031 3	8,22	0,067 3	17,68
SMR 20	0,227 5	0,025 2	11,08	0,042 2	18,55
SMR L	0,373 1	0,025 8	6,92	0,062 8	16,83

See Table B.1 for symbol definitions.

Table B.4 — Type 1 precision — Semi-micro Kjeldahl digestion apparatus

Rubber sample	Average nitrogen content (% m/m)	Within-lab repeatability		Interlaboratory reproducibility	
		<i>r</i>	(<i>r</i>)	<i>R</i>	(<i>R</i>)
SMR CV60	0,381 7	0,016 5	4,32	0,079 4	20,80
SMR 20	0,232 5	0,027 6	11,87	0,058	24,95
SMR L	0,373 3	0,023 2	6,21	0,074 2	19,88

See Table B.1 for symbol definitions.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™