



BSI Standards Publication

**Rubber, vulcanized or thermoplastic — Determination of tension set under constant elongation, and of tension set, elongation and creep under constant tensile load**

**National foreword**

This British Standard is the UK implementation of ISO 2285:2013. It supersedes BS ISO 2285:2007 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/22, Physical testing of rubber.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013. Published by BSI Standards Limited 2013

ISBN 978 0 580 74851 6

ICS 83.060

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 June 2013.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

INTERNATIONAL  
STANDARD

**ISO**  
**2285**

Seventh edition  
2013-01-15

---

---

**Rubber, vulcanized or  
thermoplastic — Determination of  
tension set under constant elongation,  
and of tension set, elongation and  
creep under constant tensile load**

*Caoutchouc vulcanisé ou thermoplastique — Détermination de  
la déformation rémanente sous allongement constant et de la  
déformation rémanente, de l'allongement et du fluage sous charge  
constante de traction*



Reference number  
ISO 2285:2013(E)

© ISO 2013



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2013

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>2</b>
<b>4 Apparatus</b> .....	<b>2</b>
4.1 Constant-elongation measurements.....	2
4.2 Constant-load measurements.....	3
<b>5 Calibration</b> .....	<b>4</b>
<b>6 Test pieces</b> .....	<b>4</b>
6.1 Preparation.....	4
6.2 Test pieces for testing under constant elongation.....	4
6.3 Test pieces for testing under constant load.....	5
6.4 Marking.....	5
6.5 Number of test pieces.....	5
6.6 Time interval between forming and testing.....	5
6.7 Conditioning.....	6
<b>7 Procedure</b> .....	<b>6</b>
7.1 Testing under constant elongation.....	6
7.2 Testing under constant load.....	8
<b>8 Expression of results</b> .....	<b>8</b>
8.1 General.....	8
8.2 Constant elongation.....	8
8.3 Constant load.....	9
<b>9 Test report</b> .....	<b>9</b>
<b>Annex A (normative) Calibration schedule</b> .....	<b>11</b>
<b>Bibliography</b> .....	<b>13</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2285 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

This seventh edition cancels and replaces the sixth edition (ISO 2285:2007), which has been aligned with ISO 815-1 and an annex containing a calibration schedule has been added.

# Rubber, vulcanized or thermoplastic — Determination of tension set under constant elongation, and of tension set, elongation and creep under constant tensile load

**WARNING** — Persons using this International Standard should be familiar with normal laboratory practice. This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.

**CAUTION** — Certain procedures specified in this International Standard might involve the use or generation of substances, or the generation of waste, that could constitute a local environmental hazard. Reference should be made to appropriate documentation on safe handling and disposal after use.

## 1 Scope

This International Standard specifies a number of methods of determining the dimensional changes in test pieces of vulcanized or thermoplastic rubber during and after tensile loading for relatively short periods under constant elongation or constant loading.

The constant-elongation test is intended to measure the ability of rubbers to retain their elastic properties after extension, at a standard laboratory temperature, to a specified strain which is maintained for a specified time at the same or at a specified higher temperature and then released at the test temperature or at the standard laboratory temperature.

The constant-load test specifies a method for the determination of elongation, creep and tension set of rubbers subjected to a constant load at standard laboratory temperature.

The test methods are intended to measure the elastic properties of rubber in the hardness range 20 IRHD to 94 IRHD.

The creep measurement is not recommended for product design or the evaluation of low-creep materials. For these, reference should be made to ISO 8013. No agreement between the results of this test and those of ISO 8013 should be inferred.

**NOTE** The constant-load test is primarily intended for the measurement of state of cure and the quality control of thin-walled products. An increase in the state of cure or degree of crosslinking is usually reflected in a decrease in set, creep or elongation.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 188, *Rubber, vulcanized or thermoplastic — Accelerated ageing and heat resistance tests*

ISO 8013, *Rubber, vulcanized — Determination of creep in compression or shear*

ISO 18899:2004, *Rubber — Guide to the calibration of test equipment*

ISO 23529:2010, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

### 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply (see also the definitions of creep functions given in ISO 8013).

#### 3.1

##### **tension set at constant load**

elongation remaining in a test piece in the unloaded condition after it has been subjected to a constant load during a specified time, expressed as a percentage of the original length in the unloaded condition

#### 3.2

##### **tension set at constant elongation**

elongation remaining in a test piece in the relaxed condition after it has been subjected to a constant elongation during a specified time, expressed as a percentage of the elongation

#### 3.3

##### **creep**

increase in elongation of a test piece at constant load during a specified time, expressed as a percentage of the elongation at the beginning of that time

### 4 Apparatus

#### 4.1 Constant-elongation measurements

**4.1.1 Straining device**, consisting of a metal rod or other suitable guide fitted with pairs of holders, one fixed and one moveable, for the ends of the test piece. The holders shall be in the form of self-tightening clamps for strip test pieces, in the form of jaws to hold tab (enlarged) ends, and in the form of flat pulleys of about 5 mm width and 10 mm diameter for ring test pieces.

If so desired, a means of operating the moving holder other than by hand may be provided, for example a threaded rod. Suitable stops or graduations may also be provided to avoid over-extension in the initial straining of the test piece.

The straining device shall be so designed that, when used at high temperatures in an oven, it can be placed with the reference length of the test piece perpendicular to the direction of the air flow. It shall also be of minimum mass in order to avoid excessive lag in the attainment of temperature equilibrium after its introduction into the oven.

A multiple-unit straining device may be used, provided that the foregoing requirements are met.

**4.1.2 Oven**, conforming to the requirements of ISO 188 (if the test is to be carried out at a temperature above the standard laboratory temperature). For short heating times, controlled air flow is not necessary.

**4.1.3 Length-measuring device**, capable of measuring the reference length of the test piece to the nearest 0,1 mm.


For strip test pieces, a marker shall be provided to mark the length used as the reference length.

For ring test pieces, the reference length may be the inner diameter of the ring, in which case a graduated cone allowing measurements to be made to the nearest 0,1 mm shall be used. Alternatively, if measurements are to be made on a straight reference length, a rigid channel, 3,5 mm deep and 20 mm wide for large ring test pieces and 1,75 mm deep and 10 mm wide for small ring test pieces, shall be provided for straightening portions of such test pieces during marking and measuring of the reference length.



## 4.2 Constant-load measurements

**4.2.1 Straining device**, comprising clamps and weights, or equivalent, for loading the test pieces (see [Figure 1](#)).

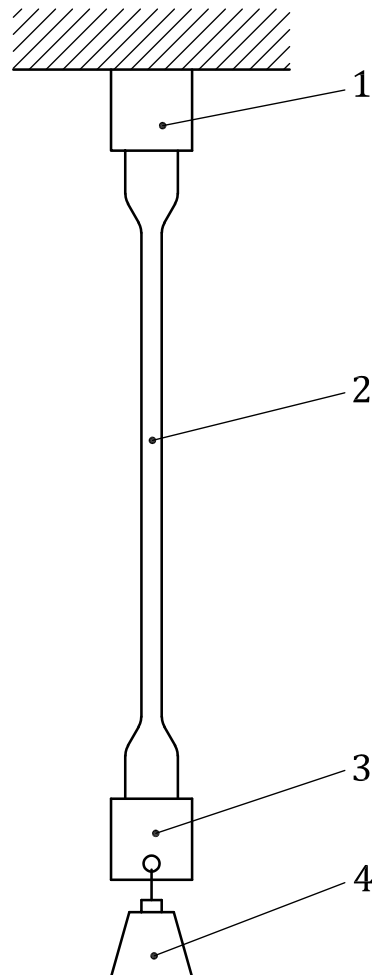

### Key

- 1 fixed clamp
- 2 test piece
- 3 clamp for holding weight
- 4 weight

**Figure 1 — Straining device**

**4.2.2 Thickness- and width-measuring device**, comprising a gauge for measuring the thickness and, where appropriate, the width of the test piece in accordance with ISO 23529:2010, method A.

The width of die-cut test pieces shall be taken as the distance between the cutting edges of the die in the narrow part, in which case a device capable of measuring the width to the nearest 0,05 mm in accordance with ISO 23529 shall be provided.

**4.2.3 Length-measuring device**, capable of measuring the reference length to the nearest 0,1 mm.

## 5 Calibration

The test apparatus shall be calibrated in accordance with the schedule given in [Annex A](#).

## 6 Test pieces

### 6.1 Preparation

Test pieces shall be prepared in accordance with ISO 23529. They shall be cut from flat sheet  $2 \text{ mm} \pm 0,2 \text{ mm}$  thick (except large ring test pieces, which shall be cut from sheet  $4 \text{ mm} \pm 0,2 \text{ mm}$  thick) prepared by moulding or slitting and buffing in accordance with ISO 23529.

Strip test pieces and strip test pieces with enlarged ends shall be cut using a sharp die with a cutter as specified in ISO 23529.

Ring test pieces shall be cut from sheet by means of a pair of concentric circular dies or rotating cutters. The separation of the two cutting edges shall not differ from the average value by more than  $0,05 \text{ mm}$ .

### 6.2 Test pieces for testing under constant elongation


#### 6.2.1 Strip test pieces

Strip test pieces shall be between  $2 \text{ mm}$  and  $10 \text{ mm}$  wide. A width of  $6 \text{ mm}$  is preferred.

The length of any given strip depends on the selected reference length and the type of straining device.

#### 6.2.2 Strip test pieces with enlarged ends

Test pieces with enlarged ends shall be as shown in [Figure 2](#), with a narrow section of length between  $25 \text{ mm}$  and  $50 \text{ mm}$  which shall be used as the reference length.

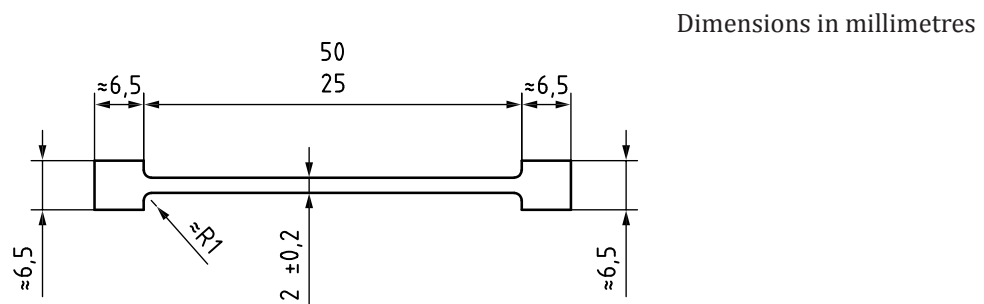

Thickness  $2 \text{ mm} \pm 0,2 \text{ mm}$

**Figure 2 — Test piece with enlarged ends**

#### 6.2.3 Ring test pieces

Ring test pieces shall be of one of the following sizes:

Large ring test piece:


- thickness:  $4 \text{ mm} \pm 0,2 \text{ mm}$ ;
- outer diameter:  $52,6 \text{ mm} \pm 0,2 \text{ mm}$ ;
- inner diameter:  $44,6 \text{ mm} \pm 0,2 \text{ mm}$ .

Small ring test piece:

- thickness:  $2 \text{ mm} \pm 0,2 \text{ mm}$ ;
- outer diameter:  $33,5 \text{ mm} \pm 0,2 \text{ mm}$ ;
- inner diameter:  $29,5 \text{ mm} \pm 0,2 \text{ mm}$ .

### 6.3 Test pieces for testing under constant load

Test pieces shall have the shape and dimensions shown in [Figure 3](#).

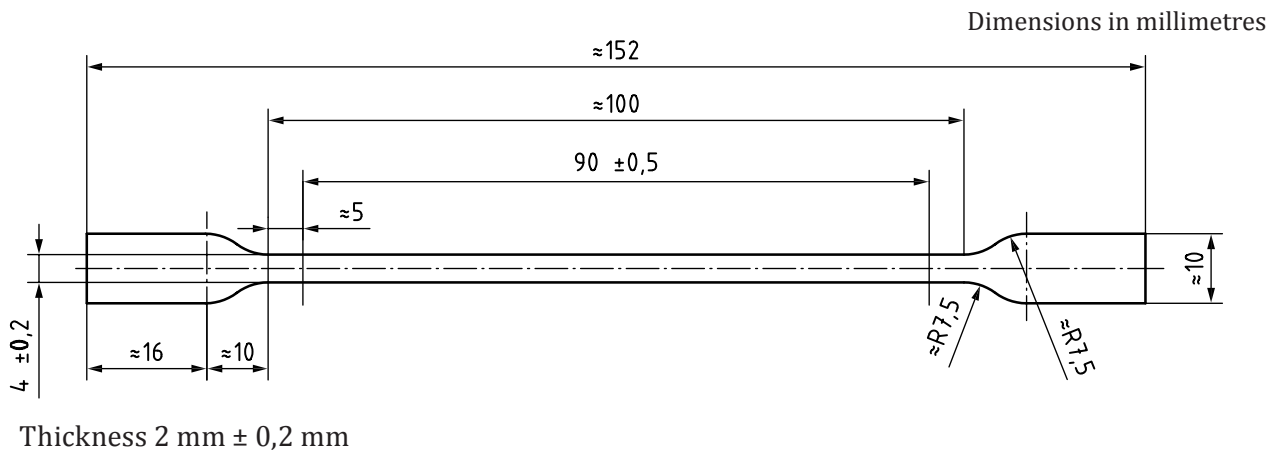

**Figure 3 — Test piece for constant loading**

## 6.4 Marking

### 6.4.1 General

Reference marks shall be marked on the test pieces, using a suitable marker and an ink which does not affect the material and withstands the temperature of test.

### 6.4.2 Tests at constant elongation

The reference length shall be between 25 mm and 50 mm, measured between the inner sides of the marks. For strip test pieces, the preferred length is 50 mm. Ring test pieces shall be straightened by means of a rigid channel (see [4.1.3](#)) and the reference length, preferably 40 mm for large ring test pieces and 25 mm for small ring test pieces, shall be marked on one of the straightened sides.

### 6.4.3 Tests at constant load

Two reference marks shall be marked on the central part of the test piece at a distance of  $90 \text{ mm} \pm 0,5 \text{ mm}$  from each other.

## 6.5 Number of test pieces

For each test, a minimum of three test pieces shall be used. (For material with a calendering grain, three test pieces shall be taken in each of two directions at right angles to each other.)

## 6.6 Time interval between forming and testing

The time interval between forming and testing shall be in accordance with ISO 23529.

Samples and test pieces shall be protected from light as completely as possible during the interval between forming and testing.

## 6.7 Conditioning

Prepared test pieces shall be conditioned immediately before testing for a minimum period of 3 h at one of the standard laboratory temperatures defined in ISO 23529, the same temperature being used throughout any one test or series of tests intended to be comparable.

## 7 Procedure

### 7.1 Testing under constant elongation

#### 7.1.1 Measurement of the test pieces

Measure the unstrained reference length ( $L_1$ ) of each test piece to the nearest 0,1 mm at standard laboratory temperature. Insert the test pieces in the straining device in the appropriate way.

#### 7.1.2 Stretching the test pieces

Extend the test pieces to the required strain. When testing ring test pieces, rotate the pulleys slightly by hand to equalize the strain in the two halves of the ring. Ensure that the reference length remains centralized between the two pulleys.

Between 10 min and 20 min after the specified strain has been reached, measure the strained reference length ( $L_2$ ) to the nearest 0,1 mm. When the inner diameter of ring test pieces is used as the reference length, it can be calculated from the diameter of the pulleys and the distance between them, measured to the nearest 0,1 mm. If the strain, calculated as specified in 7.1.4.1, does not conform to the appropriate standard value, taking into account tolerances, discard the test piece and prepare and test a replacement test piece with a modified applied strain.

#### 7.1.3 Exposure at the test temperature

##### 7.1.3.1 Tests at standard laboratory temperature

Maintain the strained test pieces at the standard laboratory temperature.

Immediately following the end of the test period, release the strain, remove the test pieces from the clamps or pulleys and lay them free on a flat non-sticky wooden surface. After  $(30^{+3}_0)$  min, measure the reference length to the nearest 0,1 mm ( $L_5$ ).

##### 7.1.3.2 Tests at temperatures other than standard laboratory temperature

Between 20 min and 30 min after the specified strain has been reached, place the strained test pieces in an oven operating at the test temperature and leave them there for the specified period.

There are three methods of cooling the test pieces and releasing the strain, of which method A is preferred.

#### Method A

At the end of the test period, remove the straining device from the oven, immediately release the strain, remove the test pieces from the clamps or pulleys and lay them on a flat non-sticky wooden surface. After  $(30^{+3}_0)$  min, measure the reference length to the nearest 0,1 mm.

#### Method B

At the end of the test period, remove the straining device from the oven but leave the test pieces in the strained condition. After  $(30^{+3}_0)$  min, release the strain, remove the test pieces from the clamps or pulleys and lay them on a flat non-sticky wooden surface. After a further  $(30^{+3}_0)$  min, measure the reference length to the nearest 0,1 mm.

### Method C

At the end of the test period, release the strain with the test pieces still in the oven held at the test temperature. After  $(30^{+3}_0)$  min, remove the straining device from the oven, remove the test pieces from the clamps or pulleys and lay them on a flat non-sticky wooden surface. After a further  $(30^{+3}_0)$  min, measure the reference length to the nearest 0,1 mm.

#### 7.1.4 Test conditions

##### 7.1.4.1 Strain

Calculate the strain  $\lambda$ , in %, using the equation:

$$\lambda = (L_2 - L_1) \times \frac{100}{L_1}$$

where

$L_1$  is the original, unstrained, reference length;

$L_2$  is the strained reference length.

The strain shall be one of the following values:

15 %  $\pm$  1,5 %

20 %  $\pm$  2 %

25 %  $\pm$  2,5 %

50 %  $\pm$  5 %

75 %  $\pm$  7,5 %

100 %  $\pm$  10 %

200 %  $\pm$  10 %

300 %  $\pm$  10 %

The strain values should be selected in accordance with the type of rubber (vulcanized or thermoplastic) and with the final application. For vulcanized rubbers, it is recommended that elongations greater than one third of the elongation at break at the test temperature should not be used. The strain value of 100 % is the preferred one, unless the above considerations dictate otherwise. For thermoplastic rubbers which give a yield point, only results calculated at strain values below the yield point are valid. When possible, the value 20 %  $\pm$  2 % is preferred for thermoplastic rubbers.

##### 7.1.4.2 Test period

The test pieces shall normally be strained for a period of  $(24_{-2}^0)$ h,  $(72_{-2}^0)$ h or  $(168_{-2}^0)$ h, the period commencing 30 min after the strain has been applied. If a longer test period is required, it shall be selected from those given in ISO 23529.

### 7.1.4.3 Temperature of test

The temperature of test shall be selected from those given in ISO 23529.

If no temperature is specified in the relevant product specification,  $70\text{ °C} \pm 1\text{ °C}$  is recommended.

## 7.2 Testing under constant load

### 7.2.1 General

Measure the length of the test piece between the reference marks ( $L_1$ ), the thickness and the width at standard laboratory temperature.

Clamp the test pieces into the straining device and load them to a stress of  $2,5\text{ MPa} \pm 0,1\text{ MPa}$ , based on the original cross-sectional area of the test piece. The load shall be applied without shock.

If, during testing, a stress of  $2,5\text{ MPa}$  proves to be too large, a stress of  $1,0\text{ MPa}$  may be used.

### 7.2.2 Elongation

$30\text{ s} \pm 2\text{ s}$  after loading the test piece, measure the distance between the reference marks ( $L_2$ ).

### 7.2.3 Creep

$60\text{ min} \pm 1\text{ min}$  after loading the test piece, measure the distance between the reference marks ( $L_3$ ).

### 7.2.4 Tension set

After the creep measurement, unload the test piece, remove it from the straining device and allow it to rest on a flat non-sticky wooden surface for  $10\text{ min} \pm 1\text{ min}$ . Measure the distance between the reference marks again ( $L_4$ ).

## 8 Expression of results

### 8.1 General

Calculate the individual test results as shown in [8.2](#) or [8.3](#). In each case, calculate the mean value of the results for the three test pieces. The individual values for the three test pieces shall be within 10 % of the mean value. If they are not, repeat the test using three further test pieces and report the median of all six results in the test report.

### 8.2 Constant elongation

The tension set  $E_4$  is given, in %, by the equation:

$$E_4 = 100(L_5 - L_1)/(L_2 - L_1)$$

where

$L_1$  is the original, unstrained, reference length;

$L_2$  is the strained reference length;

$L_5$  is the reference length after recovery.

### 8.3 Constant load

The elongation  $E_1$  is given, in %, by the equation:

$$E_1 = 100(L_2 - L_1) / L_1$$

The creep  $E_2$  is given, in %, by the equation:

$$E_2 = 100(L_3 - L_2) / (L_2 - L_1)$$

The tension set  $E_3$  is given, in %, by the equation:

$$E_3 = 100(L_4 - L_1) / L_1$$

where

- $L_1$  is the reference length, in mm, before loading;
- $L_2$  is the reference length, in mm, 30 s after loading;
- $L_3$  is the reference length, in mm, 60 min after loading;
- $L_4$  is the reference length, in mm, after 10 min rest following the measurement of length  $L_3$ .

## 9 Test report

The test report shall include the following information:

- a) details of sample and test pieces, i.e.
  - 1) a full description of the sample and its origin,
  - 2) details of the compound and the curing conditions, if known,
  - 3) the direction, relative to the grain, in which the test pieces were cut,
  - 4) the type of test piece used and its dimensions,
  - 5) the method of preparation of the test pieces, for example whether moulded, cut or extruded,
  - 6) details of any test piece preparation, for example buffing, and
  - 7) the number of test pieces tested;
- b) a reference to this International Standard, i.e. ISO 2285;
- c) test details, i.e.
  - 1) the duration and temperature of conditioning,
  - 2) the stress or elongation applied,
  - 3) the duration and temperature of the test,
  - 4) the method of cooling/strain release used (method A, B or C) (applies to constant-elongation method only), and

- 5) details of any deviation from the standard procedure;
- d) test results, i.e.
  - 1) the mean or median values of the individual test results, and
  - 2) the individual results, if required;
- e) the date of the test.



## Annex A (normative)

### Calibration schedule

#### A.1 Inspection

Before any calibration is undertaken, the condition of the items to be calibrated shall be ascertained by inspection and recorded on any calibration report or certificate. It shall be reported whether calibration is carried out in the “as-received” condition or after rectification of any abnormality or fault.

It shall be ascertained that the apparatus is generally fit for the intended purpose, including any parameters specified as approximate and for which the apparatus does not therefore need to be formally calibrated. If such parameters are liable to change, then the need for periodic checks shall be written into the detailed calibration procedures.

#### A.2 Schedule

Verification/calibration of the test apparatus is a mandatory part of this International Standard. However, the frequency of calibration and the procedures used are, unless otherwise stated, at the discretion of the individual laboratory, using ISO 18899 for guidance.

The calibration schedule given in [Table A.1](#) has been compiled by listing all of the parameters specified in the test method, together with the specified requirement. A parameter and requirement can relate to the main test apparatus, to part of that apparatus or to an ancillary apparatus necessary for the test.

For each parameter, a calibration procedure is indicated by reference to ISO 18899, to another publication or to a procedure particular to the test method which is detailed (whenever a calibration procedure which is more specific or detailed than that in ISO 18899 is available, it shall be used in preference).

The verification frequency for each parameter is given by a code-letter. The code-letters used in the calibration schedule are:

- C requirement to be confirmed but no measurement;
- N initial verification only;
- S standard interval as given in ISO 18899;
- U in use.

**Table A.1 — Calibration frequency schedule**

Parameter	Requirement	Subclause in ISO 18899:2004	Verification frequency guide	Notes
Straining device	Of minimum mass  One fixed test piece holder and one movable holder	C	U	

**Table A.1** (continued)

Parameter	Requirement	Subclause in ISO 18899:2004	Verification frequency guide	Notes
Test piece holders	For strip test pieces, self-tightening clamps	C	U	
	For rings, flat pulleys about 5 mm wide and 10 mm in diameter	C	U	
Oven	As specified in ISO 188			
Length measurement	Device used capable of measuring to the nearest 0,1 mm	15.1	S	
Width measurement	Device used capable of measuring to the nearest 0,1 mm	15.1	S	
Thickness measurement	Device used capable of measuring to the nearest 0,1 mm	15.1	S	
Graduated cone	Capable of measuring inner diameter of ring to nearest 0,1 mm	15.2	S	For ring test pieces
Rigid channel	3,5 mm deep × 20 mm wide	C	U	For large ring test pieces
	1,75 mm deep × 10 mm wide			For small ring test pieces

In addition to the items listed in [Table A.1](#), use of the following is implied, all of which need calibration in accordance with ISO 18899:

- a) a timer;
- b) a thermometer to monitor the test temperatures.

## Bibliography

- [1] ISO 815-1, *Rubber, vulcanized or thermoplastic — Determination of compression set — Part 1: At ambient or elevated temperatures*





# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™