



BSI Standards Publication

Iron ores — Determination of total iron content

Part 2: Titrimetric methods after titanium(III) chloride reduction

National foreword

This British Standard is the UK implementation of ISO 2597-2:2015. It supersedes BS ISO 2597-2:2008 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/58, Iron ores.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015.
Published by BSI Standards Limited 2015

ISBN 978 0 580 79561 9

ICS 73.060.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2015.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

ISO
2597-2

Second edition
2015-11-01

**Iron ores — Determination of total
iron content —**

Part 2:
**Titrimetric methods after
titanium(III) chloride reduction**

Minerais de fer — Dosage du fer total —

*Partie 2: Méthodes titrimétriques après réduction au chlorure de
titane(III)*



Reference number
ISO 2597-2:2015(E)

© ISO 2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Principle	1
3.1 Decomposition of the test portion	1
3.1.1 Acid decomposition	1
3.1.2 Fusion-filtration	2
3.2 Titration of iron	2
4 Reagents	2
5 Apparatus	3
6 Sampling and samples	4
6.1 Laboratory sample	4
6.2 Preparation of test samples	4
6.2.1 General	4
6.2.2 Ores having significant contents of combined water or oxidizable compounds	4
6.2.3 Ores outside the scope of 6.2.2	4
7 Procedure	5
7.1 Number of determinations	5
7.2 Blank test and check test	5
7.3 Determination of hygroscopic moisture content	5
7.4 Test portion	5
7.5 Determination	5
7.5.1 Decomposition of the test portion	5
7.5.2 Reduction	7
8 Expression of results	8
8.1 Calculation of total iron content	8
8.2 General treatment of results	8
8.2.1 Repeatability and permissible tolerance	8
8.2.2 Determination of analytical result	9
8.2.3 Between-laboratories precision	9
8.2.4 Check for trueness	9
8.2.5 Calculation of final result	10
8.3 Oxide factors	10
9 Test report	10
Annex A (normative) Flowsheet of the procedure for the acceptance of analytical values for test samples	12
Annex B (normative) Procedure of Japanese weighing method	13
Bibliography	14

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 102, *Iron ore and direct reduced iron*, Subcommittee SC 2, *Chemical analysis*.

This second edition cancels and replaces the first edition (ISO 2597-2:2008), which has been technically revised.

ISO 2597 consists of the following parts, under the general title *Iron ores — Determination of total iron content*:

- *Part 1: Titrimetric method after tin(II) chloride reduction*
- *Part 2: Titrimetric methods after titanium(III) chloride reduction*

Iron ores — Determination of total iron content —

Part 2:

Titrimetric methods after titanium(III) chloride reduction

WARNING — This part of ISO 2597 may involve hazardous materials, operations and equipment. This part of ISO 2597 does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this part of ISO 2597 to establish appropriate health and safety practices and determine the applicability of regulatory limitations prior to use.

1 Scope

This part of ISO 2597 specifies a titrimetric method, free from mercury pollution, for the determination of total iron content in iron ores, using potassium dichromate as titrant after reduction of the iron(III) by tin(II) chloride and titanium(III) chloride. The excess reductant is then oxidized by either dilute potassium dichromate.

This method is applicable to a concentration range of 30 % mass fraction to 72 % mass fraction of iron in natural iron ores, iron ore concentrates and agglomerates, including sinter products.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 80000-1:2009, *Quantities and unit — Part 1: General*

ISO 385, *Laboratory glassware — Burettes*

ISO 648, *Laboratory glassware — Single-volume pipettes*

ISO 1042, *Laboratory glassware — One-mark volumetric flasks*

ISO 2596, *Iron ores — Determination of hygroscopic moisture in analytical samples — Gravimetric, Karl Fischer and mass-loss methods*

ISO 3082, *Iron ores — Sampling and sample preparation procedures*

3 Principle

3.1 Decomposition of the test portion

3.1.1 Acid decomposition

For samples containing not more than 0,05 % mass fraction of vanadium, the test portion is treated with hydrochloric acid in the presence of tin chloride.

The residue is filtered, ignited and treated with hydrofluoric and sulfuric acids. The mixture is fused with potassium disulfate and the cold melt is dissolved in water more hydrochloric acid and combined with the main iron solution, which is treated with potassium permanganate and evaporated.

3.1.2 Fusion-filtration

For samples containing more than 0,05 % mass fraction of vanadium, the test portion is fused with a mixture of fluxes, the cold melt is leached with water and the precipitate is filtered, washed in sodium hydroxide solution, dissolved in hydrochloric acid and evaporated.

3.2 Titration of iron

The major portion of the iron(III) is reduced by tin(II) chloride and the remainder of the iron(III) is reduced by titanium(III) chloride. The excess reductant is oxidized with either dilute potassium dichromate solution. The reduced iron is titrated with potassium dichromate solution using the sodium diphenylaminesulfonate indicator.

4 Reagents

During the analysis, use only reagents of recognized analytical reagent grade, and only distilled water or water of equivalent purity.

4.1 Hydrochloric acid, ρ 1,16 g/ml to 1,19 g/ml. (Methods 1 and 2).

4.2 Hydrochloric acid, ρ 1,16 g/ml to 1,19 g/ml, diluted 1 + 1. (Methods 1 and 2).

4.3 Hydrochloric acid, ρ 1,16 g/ml to 1,19 g/ml, diluted 1 + 12. (Methods 1 and 2).

4.4 Hydrochloric acid, ρ 1,16 g/ml to 1,19 g/ml, diluted 2 + 100. (Methods 1 and 2).

4.5 Hydrofluoric acid, 40 % mass fraction (ρ 1,13 g/ml) or 48 % mass fraction (ρ 1,19 g/ml). (Methods 1 and 2).

4.6 Sulfuric acid, ρ 1,84 g/ml. (Methods 1 and 2).

4.7 Sulfuric acid, ρ 1,84 g/ml, diluted 1 + 1, carefully pour 1 volume of reagent [4.6](#) into one volume of cold water. (Methods 1 and 2).

4.8 Orthophosphoric acid, ρ 1,7 g/ml. (Methods 1 and 2).

4.9 Perchloric acid, 72 % mass fraction (ρ 1,7 g/ml), diluted 1 + 1. (Method 2).

4.10 Sulfuric acid–orthophosphoric acid mixture, pour 150 ml of orthophosphoric acid ([4.8](#)) into about 400 ml of water while stirring, add 150 ml of sulfuric acid ([4.6](#)), cool in a water bath, dilute with water to 1 l and mix well. (Methods 1 and 2).

4.11 Sodium hydroxide (NaOH), solution, 20 g/l. (Methods 1 and 2).

4.12 Hydrogen peroxide (H₂O₂), 30 % by volume solution. (Methods 1 and 2).

4.13 Hydrogen peroxide (H₂O₂), 30 % by volume solution, diluted 1 + 9. (Method 1).

4.14 Tin(II) chloride solution, 100 g/l, dissolve 100 g of crystalline tin(II) chloride (SnCl₂·2H₂O) in 200 ml of hydrochloric acid ([4.1](#)) by heating the solution in a water bath. Cool the solution and dilute with water to 1 l. This solution should be stored in a brown glass bottle with a small quantity of granular tin metal. (Methods 1 and 2).

4.15 Potassium permanganate (KMnO₄) solution, 25 g/l. (Methods 1 and 2).

4.16 Potassium dichromate (K₂Cr₂O₇) solution, 1 g/l. (Method 1).

4.17 Titanium(III) chloride (TiCl₃) solution, 20 g/l, dilute one volume of titanium(III) chloride solution (about 20 % TiCl₃) with nine volumes of hydrochloric acid (4.2). (Methods 1 and 2).

Alternatively, dissolve 1,3 g of titanium sponge in about 40 ml of hydrochloric acid (4.1) in a covered beaker by heating in a water bath. Cool the solution and dilute with water to 200 ml. Prepare fresh solution as needed.

4.18 Flux mixture, mix one portion of anhydrous sodium carbonate (Na₂CO₃) and two portions of sodium peroxide (Na₂O₂). (Methods 1 and 2).

4.19 Iron standard solution, 0,1 mol/l, transfer 5,58 g of iron(III) oxide (purity greater than 99,9 % mass fraction) to a 500 ml beaker flask and place a small filter funnel in the neck. Add 75 ml of hydrochloric acid (4.2) in small increments and heat until dissolved. (Methods 1 and 2).

Cool and oxidize with 5 ml of hydrogen peroxide (4.13) added in small portions. Heat to boiling and boil to decompose the excess hydrogen peroxide and to expel chlorine. Cool, transfer to a 1 000 ml volumetric flask and mix well.

1,00 ml of this solution is equivalent to 1,00 ml of the standard potassium dichromate solution (4.20).

4.20 Potassium dichromate (99,9 % minimum purity), standard solution, 0,016 67 mol/l, pulverize about 6 g of potassium dichromate reagent in an agate mortar, dry at 140 °C to 150 °C for 2 h, and cool to room temperature in a desiccator. (Methods 1 and 2).

Transfer 4,903 g of this material to a 300 ml beaker, dissolve in about 100 ml of water, transfer quantitatively to a 1 000 ml volumetric flask, make up to volume with water after cooling to 20 °C and mix well. Record the temperature at which this dilution was made (20 °C) on the stock bottle. Measure the temperature at each use to correct the volume of titrant used.

The volumetric flask should previously be calibrated by weighing the mass of water contained at 20 °C and converting to volume.

Water used for preparation should previously be equilibrated at room temperature.

A calibrated mercury thermometer, graduated in 0,1 °C divisions and having a marked dipping line, should be used. Take a sufficient volume of standard solution for dipping the thermometer and transfer to a suitable beaker. Measure the temperature of the solution to the nearest 0,1 °C, after dipping for more than 60 s.

4.21 Indigo carmine [5,5'-disulfonic acid disodium salt (C₁₆H₈O₈N₂S₂Na₂)] solution, 0,1 g/100 ml, dissolve 0,1 g of indigo carmine in a cold mixture of 50 ml sulfuric acid (4.7) and 50 ml of water. (Method 1).

4.22 Sodium diphenylaminesulfonate indicator solution, 0,2 g/100 ml, dissolve 0,2 g of sodium diphenylaminesulfonate (C₆H₅NHC₆H₄SO₃Na) in a small volume of water and dilute to 100 ml. (Method 1 and Method 2).

Store the solution in a brown glass bottle.

5 Apparatus

The pipette and volumetric flask specified are complying with ISO 648 and ISO 1042 respectively.

Ordinary laboratory apparatus, and the following.

5.1 Alumina, zirconium or vitreous carbon crucible, capacity 25 ml to 30 ml, crucibles should be cleaned before use to avoid contamination with iron.

5.2 Burette, class A, complying with ISO 385.

5.3 Weighing bottle, of approximate volume 10 ml and approximate mass 6 g.

5.4 Platinum crucible, capacity 25 ml to 30 ml and having a lid.

5.5 Weighing spatula, of a non-magnetic material or demagnetized stainless steel.

5.6 Muffle furnace, suitable for operation in the range 500 °C to 800 °C.

6 Sampling and samples

6.1 Laboratory sample

For analysis, use a laboratory sample of minus 100 μm particle size which has been taken and prepared in accordance with ISO 3082. In the case of ores having significant contents of combined water or oxidizable compounds, use a particle size of less than 160 μm .

NOTE 1 A guideline on significant contents of combined water and oxidizable compounds is incorporated in ISO 7764.

NOTE 2 If the determination of total iron relates to a reducibility test, prepare the laboratory sample by crushing and pulverizing, to less than 100 μm particle size, the whole of one of the reducibility test portions which has been reserved for chemical analysis. In the case of ores having significant contents of combined water or oxidizable compounds, use a particle size of less than 160 μm .

6.2 Preparation of test samples

6.2.1 General

Depending on the ore type, proceed in accordance with either [6.2.2](#) or [6.2.3](#).

6.2.2 Ores having significant contents of combined water or oxidizable compounds

Prepare an air-equilibrated test sample in accordance with ISO 2596 with the following types of ore:

- a) processed ores containing metallic iron;
- b) natural or processed ores in which the sulfur content is higher than 0,2 % mass fraction;
- c) natural or processed ores in which the content of combined water is higher than 2,5 % mass fraction.

6.2.3 Ores outside the scope of [6.2.2](#)

Prepare a predried test sample as follows. Thoroughly mix the laboratory sample and, taking multiple increments, extract a test sample in such a manner that it is representative of the whole contents of the container. Prepare test portions in accordance with the Japanese weighing method (see [Annex B](#)).

7 Procedure

7.1 Number of determinations

Carry out the analysis, at least in duplicate, in accordance with [Annex A](#), independently, on one test sample (see [6.2](#)).

NOTE The expression “independently” means that the second and any subsequent result(s) is (are) not affected by the previous result(s). For this particular analytical method, this condition implies that the repetition of the procedure is to be carried out either by the same operator at a different time, or by a different operator, including appropriate recalibration in either case.

7.2 Blank test and check test

In each run, one blank test and one analysis of a certified reference material of the same type of ore shall be carried out in parallel with the analysis of the ore sample(s) under the same conditions. A test sample of the certified reference material shall be prepared in the manner appropriate to the type of ore involved (see [6.2](#) and NOTE 1 below).

Where the analysis is carried out on several samples at the same time, the blank value may be represented by one test, provided that the procedure is the same and the reagents used are from the same reagent bottles.

Where the analysis is carried out on several samples of the same type of ore at the same time, the analytical value of one certified reference material may be used.

NOTE 1 The certified reference material is of the same type as the sample to be analysed and the properties of the two materials are sufficiently similar to ensure that in either case no significant changes in the analytical procedure will be necessary.

NOTE 2 The certified reference material is used only to validate the performance of the analytical procedure and expressly not to standardize the potassium dichromate solution.

7.3 Determination of hygroscopic moisture content

Where the ore type conforms to the specifications of [6.2.2](#), determine the hygroscopic moisture content in accordance with ISO 2596, simultaneously with the taking of the test portion (see [7.4](#)) for the determination of the iron content.

7.4 Test portion

Taking several increments, weigh to the nearest 0,000 2 g, approximately 0,4 g of the test sample (see [6.2](#)), using a non-magnetic spatula ([5.3](#)).

NOTE For samples having an iron content higher than 68 % mass fraction, weigh approximately 0,38 g.

Where the ore type is outside the scope of [6.2.2](#), transfer the portion to a weighing bottle and determine the mass of the test portion to the nearest 0,000 2 g in accordance with the Japanese weighing method (see [Annex B](#)).

7.5 Determination

7.5.1 Decomposition of the test portion

7.5.1.1 Acid decomposition (for samples containing $\leq 0,05$ % mass fraction vanadium)

Place the test portion (see [7.4](#)) in a dried 300 ml or 400 ml beaker, project some water on the inside wall of the beaker and suspend the test portion in water while swirling.

Add 20 ml of hydrochloric acid (4.1) and 10 to 20 drops tin(II) chloride solution (4.14), cover the beaker with a watch glass, heat the solution gently at about 80 °C for 1 h and continue heating without boiling at a higher temperature for about 10 min to decompose the portion

Normally, the test portion is completely decomposed after 50 min. In case of difficulty in decomposing the test portion, add some new drops of tin(II) chloride solution (4.14) and keep the test portion in a hotplate. The total decomposition time cannot exceed 90 min.

NOTE Avoid boiling to prevent volatilization loss of iron(III) chloride.

Remove the beaker from the source of heat, wash the watch glass in a jet of water, and dilute to 50 ml with warm water. Filter the insoluble residue on a filter paper. Scrub the remainder of the residue on the beaker wall by using a policeman, and transfer the remainder on to the filter paper with a small volume of warm hydrochloric acid (4.4). Wash the residue with warm hydrochloric acid (4.4) until the yellow colour of iron(III) chloride is no longer observed, and then wash in warm water six to eight times. Collect the filtrate and washings in a 500 ml or 600 ml beaker. Evaporate this main solution without boiling to about 70 ml (see NOTE above).

Place the filter paper and residue in a platinum crucible (5.4), dry then char the paper and finally ignite at 750 °C to 800 °C for 1 h. Allow the crucible to cool, moisten the residue with several drops of sulfuric acid (4.7), add about 5 ml of hydrofluoric acid (4.5), and heat gently to remove silica and sulfuric acid (until white fumes are no longer observed).

After cooling, add 3 g of potassium disulfate (4.20) to the crucible, cover the crucible with a lid, heat gently at first then strongly (dull red) until a clear melt is obtained. Cool, place the crucible and lid in a 250 ml or 300 ml beaker, add about 30 ml of warm water and 5 ml of hydrochloric acid (4.1) and warm to dissolve the melt. Remove the crucible and lid, wash with a small volume of warm water. Combine this solution with the main solution.

Add 5 drops of potassium permanganate solution (4.17), heat the solution to just below the boiling point and maintain at this temperature for 5 min to oxidize any arsenic and organic matter. Evaporate without boiling to about 70 ml, and follow the procedure specified in 7.5.2 (see NOTE above).

7.5.1.2 Fusion — filtration (for samples containing more than 0,05 % mass fraction of vanadium and/or samples not being decomposed by the acid-decomposition)

Place the test portion in an alumina, zirconium or vitreous carbon crucible (5.1), add about 4 g of flux mixture (4.18) and mix thoroughly. Place in a muffle furnace (5.6) at 500 °C ± 10 °C for 30 min (see NOTE 1). Remove from the furnace, heat over a burner to melt the sinter within 30 s and, swirling gently, continue heating allowing a total heating time of 2 min.

NOTE 1 Alternatively, a burner can be used instead of the furnace. In this case, fusion of the test portion is carried out as follows: heat the crucible over a burner, first at low temperature until the contents in the crucible begin to melt, then at high temperature (dull red) while swirling until a clear melt is obtained.

Cool, place the crucible in a 300 ml or 400 ml beaker, add about 100 ml of warm water and heat for a few minutes to dissolve the melt. Remove the crucible, wash and add the washings to the solution. Reserve the crucible. Cool the solution and filter through a close-textured filter paper. Wash the filter twice in sodium hydroxide solution (4.11) and discard the filtrate and washings.

NOTE 2 A filter paper, which is used for a fine precipitate such as barium sulfate, is more suitable than a close-textured filter paper.

Transfer the precipitate on the filter to the original beaker by washing in a jet of water, add 10 ml of hydrochloric acid (4.1), and warm to dissolve the precipitate. Place a 500 ml or 600 ml beaker under the funnel, pour the solution through the original filter paper to dissolve the remaining precipitate. Wash the filter three times in warm hydrochloric acid (4.3), and several times in warm hydrochloric acid (4.4). Finally wash with warm water until the washings are no longer acid. Combine the solution and washings in the 500 ml or 600 ml beaker. Place the reserved crucible in the beaker to dissolve any retained iron, remove the crucible, wash and add the washings to the solution. Evaporate this solution without boiling (see NOTE in 7.5.1.1) to about 70 ml and follow the procedure specified in 7.5.2.

7.5.2 Reduction

7.5.2.1 Method 1: Oxidation of excess titanium(III) chloride with dilute dichromate solution using indigo carmine indicator solution

Maintain the solution obtained in 7.5.1 at 90 °C to 95 °C and wash the cover and inside wall of the beaker in a small amount of hot water. Immediately add tin(II) chloride solution (4.14) dropwise to reduce iron(III), while swirling the solution in the beaker until only a faint yellow tint of the iron(III) chloride solution remains.

It is essential that some iron(III) remain unreduced. If the solution is made colourless by the excessive addition of tin(II) chloride solution, add hydrogen peroxide (4.13) or potassium permanganate solution (4.15) dropwise until the solution changes to a faint yellow tint.

NOTE It is convenient to use dilute potassium dichromate solution as a reference solution for establishing the desired slight yellow tint of the iron solution. The solution is prepared by diluting 5 ml of potassium dichromate standard solution (4.20) to 100 ml with water.

Wash the inside wall of the beaker using a small amount of hot water. Add 3 to 4 drops of indigo carmine solution (4.21) as indicator, then titanium(III) chloride solution (4.17) drop by drop, while swirling the solution, until it turns blue then colourless. Add 2 to 3 drops in excess. Immediately add dilute potassium dichromate solution (4.16) drop by drop, to oxidize the excess of titanium(III) chloride, until the solution changes to a persistent blue colour which lasts for 5 s.

Place in a cooling bath for several minutes, then dilute the solution to about 300 ml using cold water. Follow the procedure specified in 7.5.2.3.

7.5.2.2 Method 2: Oxidation of excess titanium(III) chloride solution with perchloric acid

Maintain the solution obtained in 7.5.1 at 90 °C to 95 °C and wash the cover and inside wall of the beaker with a small amount of hot water. Immediately add tin(II) chloride solution (4.14) dropwise to reduce iron(III), while swirling the solution in the beaker until only a light yellow colour remains (see NOTE in 7.5.2.1).

Reduce the remaining iron(III) by adding titanium(III) chloride solution (4.17), drop by drop, until the yellow colour has disappeared, then add an additional 3 to 5 drops. Wash the inside wall of the beaker with a small amount of water and reheat rapidly to an incipient boil. Remove from the source of heat and immediately add, all at once, 5 ml of perchloric acid (4.9). Mix well by swirling for about 5 s. Dilute immediately with cold (<10 °C) water to 300 ml. Cool rapidly to <15 °C and follow the procedure specified in 7.5.2.3.

7.5.2.3 Titration

Titrate the cold solution obtained in accordance with 7.5.2.1 or 7.5.2.2 with the potassium dichromate standard solution (4.20), while swirling, until the amount of the titrate reaches 10 ml. Add 30 ml of sulfuric acid-orthophosphoric acid mixture (4.10) and continue to titrate with the potassium dichromate standard solution (4.20) using 0,5 ml of the sodium diphenylaminesulfonate solution (4.22) as an indicator. The end point is reached when the green colour of the solution changes to a bluish green and a final drop of the titrant imparts a violet colour.

NOTE Barium diphenylaminesulfonate can be used as an indicator.

The ambient temperature of the potassium dichromate solution should be noted. If this differs by more than 1 °C from the temperature at which it was prepared (20 °C), make the appropriate volumetric correction: 0,02 % relative for each 1 °C of difference (for example, the titre should be decreased when the ambient temperature during the titration is higher than the temperature during preparation of the standard volumetric solution). A correction for the temperature difference, if any, is essential.

7.5.2.4 Blank test

Determine the blank test value (7.2) using the same amounts of all reagents and following all the steps of the procedure. Immediately before reduction (7.5.2) with tin(II) chloride solution (4.14) add, by means of a one-mark pipette, 1,00 ml of iron standard solution (4.19) and titrate the solution as described in 7.5.2.2. Record the volume of this titration as V_0 . The blank test value of this titration, V_2 , is calculated in Formula (1):

$$V_2 = V_0 - 1,00 \quad (1)$$

NOTE 1 In the absence of iron, the sodium diphenylaminesulfonate indicator does not react with the dichromate solution. The addition of the iron solution is therefore necessary to promote indicator response in the blank solution and thus allow a suitable correction for the blank in terms of its equivalent in millilitres of the potassium dichromate standard solution.

NOTE 2 The 1 ml one-mark pipette is previously calibrated by weighing the mass of water delivered and converting to volume.

8 Expression of results

8.1 Calculation of total iron content

The total iron content, w_{Fe} , as a percentage mass fraction, is calculated from Formula (2):

$$w_{\text{Fe}} = \frac{V_1 - V_2}{m} \times 0,005\,584\,7 \times 100 \times K \quad (2)$$

where

V_1 is the volume, in millilitres, of potassium dichromate standard solution (4.13) used for the titration of the test sample;

V_2 is the volume, in millilitres, of potassium dichromate standard solution used for the titration in the blank test, corrected for the iron added in 7.5.2.4;

m is the mass, in grams, of the test portion;

0,005 584 7 is a multiple of the atomic mass of iron;

K is 1,00 for predried test samples (6.2.3), and for air-equilibrated test samples (6.2.2) is the conversion factor found from Formula (3):

$$K = \frac{100}{100 - A} \quad (3)$$

where A is the hygroscopic moisture content, as a percentage mass fraction, determined in accordance with ISO 2596.

8.2 General treatment of results

8.2.1 Repeatability and permissible tolerance

The precision of this analytical method is expressed by the following regression Formulae:

$$R_d = 0,181 \quad (4)$$

$$P = 0,399 \quad (5)$$

$$\sigma_d = 0,064 \quad (6)$$

$$\sigma_L = 0,130 \quad (7)$$

where

R_d is the independent duplicate limit;

P is the permissible tolerance between laboratories;

σ_d is the independent duplicate standard deviation;

σ_L is the between laboratories standard deviation.

8.2.2 Determination of analytical result

Having computed the independent duplicate results according to Formula (1), compare them with the independent duplicate limit, R_d , using the procedure given in [Annex A](#), and obtain the final laboratory result μ (see [8.2.5](#)).

8.2.3 Between-laboratories precision

Between-laboratories precision is used to determine the agreement between the final results reported by two laboratories. The assumption is that both laboratories followed the procedure described in [8.2.2](#). Compute the following quantity:

$$\mu_{12} = \frac{\mu_1 - \mu_2}{2}$$

where

μ_1 is the final result reported by laboratory 1;

μ_2 is the final result reported by laboratory 2;

$\mu_{1,2}$ is the mean of the final results.

If $|\mu_1 - \mu_2| \leq P$, the final results are in agreement.

8.2.4 Check for trueness

The trueness of the analytical method shall be checked by applying it to a certified reference material (CRM) or a reference material (RM) (see NOTE 1 of [7.2](#)). Calculate the analytical result, μ , for the CRM/RM using the procedures in [8.1](#) and [8.2](#), and compare it with the reference or certified value A_c . There are two possibilities:

- a) $|\mu_c - A_c| \leq C$ in which case the difference between the reported result and the certified/reference value is statistically insignificant.
- b) $|\mu_c - A_c| > C$ in which case the difference between the reported result and the certified/reference value is statistically significant.

where

μ_c is the final result for the certified reference material;

A_c is the certified/reference value for the CRM/RM;

C is a value dependent on the type of CRM/RM used, see Formula (8) below.

NOTE ISO Guide 35 can be used to prepare and certify reference materials used for this purpose.

For a CRM certified by an inter-laboratory test programme:

$$C = 2 \sqrt{\sigma_L^2 + \frac{\sigma_d^2}{n} + V(A_c)} \quad (8)$$

where

$V(A_c)$ is the variance of the certified value A_c ($= 0$ for a CRM certified by only one laboratory);

n is the number of replicate determinations carried out on the CRM/RM.

A CRM certified by only one laboratory should be avoided unless it is known to have an unbiased certified value.

8.2.5 Calculation of final result

The final result is the arithmetic mean of the acceptable analytical values for the test sample, or as otherwise determined by the operations specified in [Annex A](#), calculated to four decimal places and rounded off to the second decimal place as follows:

- a) where the figure in the third decimal place is less than 5, it is discarded and the figure in the second decimal place according to ISO 80000-1:2009, B.3, Rule A. is kept unchanged;
- b) where the figure in the third decimal place is 5 and there is a figure other than 0 in the fourth decimal place, or where the figure in the third decimal place is greater than 5, the figure in the second decimal place is increased by one;
- c) where the figure in the third decimal place is 5 and there is a figure 0 in the fourth decimal place, the 5 is discarded and the figure in the second decimal place is kept unchanged if it is 0, 2, 4, 6 or 8 and is increased by one if it is 1, 3, 5, 7 or 9.

8.3 Oxide factors

$$w_{\text{Fe}_2\text{O}_3} = 1,430 w_{\text{Fe}}$$

$$w_{\text{FeO}} = 1,286 w_{\text{Fe}}$$

$$w_{\text{Fe}_3\text{O}_4} = 1,382 w_{\text{Fe}}$$

9 Test report


The test report shall include the following information:

- a) name and address of the testing laboratory;
- b) date of issue of the test report;
- c) reference to this part of ISO 2597, i.e. ISO 2597-2:2015;
- d) details necessary for the identification of the sample;
- e) result of the analysis;

- f) reference number of the result;
- g) any characteristics noticed during the determination and any operations not specified in this part of ISO 2597 which may have had an influence on the results, either for the test sample or the certified reference material(s).

Annex A (normative)

Flowsheet of the procedure for the acceptance of analytical values for test samples

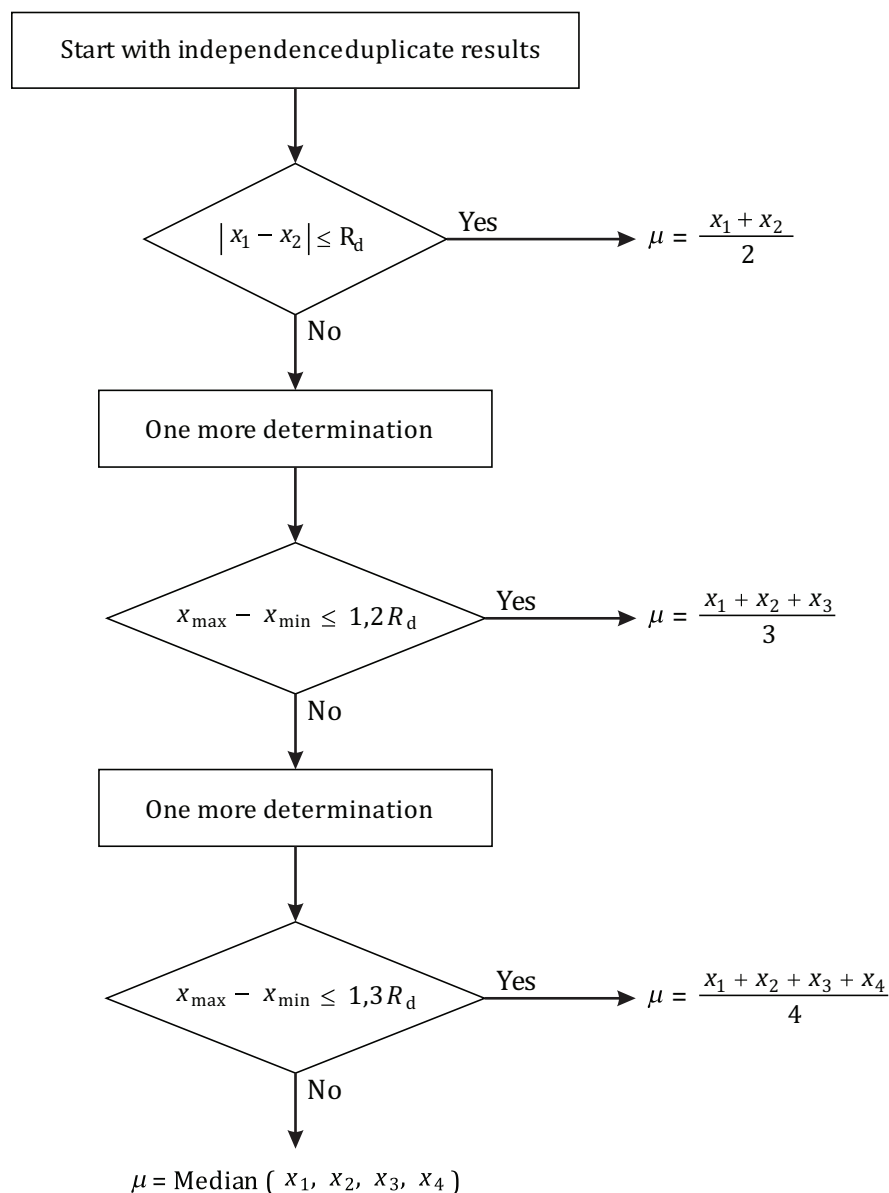

Key

R_d permissible tolerance within a laboratory (repeatability)

Figure A.1 — Flowsheet of the procedure for the acceptance of analytical values for test samples

Annex B (normative)

Procedure of Japanese weighing method

Dry a weighing bottle ([5.3](#)) and a well-fitting lid at a temperature of $105\text{ °C} \pm 2\text{ °C}$ and cool in desiccator. Take from the sample a test portion of 0,4 g and transfer to the dried weighing bottle. Spread the test sample evenly in the weighing bottle.

NOTE Take the test sample in multiple increments in such a way that it is representative of the entire contents of the container.

Dry the open weighing bottle with the test portion and the lid in a laboratory oven for 2 h at $105\text{ °C} \pm 2\text{ °C}$.

Close the weighing bottle with the lid, transfer to a desiccator and cool to room temperature (20 min to 30 min).

Slightly remove the lid and quickly replace it again, then weigh the bottle with the lid on to the nearest 0,000 1 g (m_1).

Quickly transfer the test portion to a beaker or a crucible, described in [7.5.1](#), and then weigh the weighing bottle with the lid on (m_2).

The mass of the test portion, m , is the difference between the two weighings, m_1 and m_2 .

Bibliography

- [1] ISO 7764, *Iron ores — Preparation of predried test samples for chemical analysis*
- [2] ISO Guide 35, *Reference materials — General and statistical principles for certification*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™