

BS ISO 3310-2:2013



BSI Standards Publication

Test sieves — Technical requirements and testing

Part 2: Test sieves of perforated metal plate

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 3310-2:2013. It supersedes BS 410-2:2000 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee LBI/37, Particle characterization including sieving.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013.
Published by BSI Standards Limited 2013

ISBN 978 0 580 82112 7
ICS 19.120

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 August 2013.

Amendments/corrigenda issued since publication

Date	Text affected
-------------	----------------------

INTERNATIONAL
STANDARD

ISO
3310-2

Fifth edition
2013-09-01

**Test sieves — Technical requirements
and testing —**

Part 2:
Test sieves of perforated metal plate

Tamis de contrôle — Exigences techniques et vérifications —

Partie 2: Tamis de contrôle en tôles métalliques perforées



Reference number
ISO 3310-2:2013(E)

© ISO 2013



COPYRIGHT PROTECTED DOCUMENT

© ISO 2013

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Designation	1
5 Perforated metal plate	1
5.1 Requirements.....	1
5.2 Test methods.....	5
5.3 Documentation for sieve conformity.....	6
6 Test sieve frames	6
7 Marking of test sieves	7
Annex A (informative) Test sieve record card	8
Bibliography	9

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2. www.iso.org/directives.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received. www.iso.org/patents.

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 24, *Particle characterization including sieving*, Subcommittee SC 8, *Test sieves, sieving and industrial screens*.

This fifth edition cancels and replaces the fourth edition (ISO 3310-2:1999), which has been technically revised.

ISO 3310 consists of the following parts, under the general title *Test sieves — Technical requirements and testing*:

- *Part 1: Test sieves of metal wire cloth*
- *Part 2: Test sieves of perforated metal plate*
- *Part 3: Test sieves of electroformed sheets*

Introduction

As the accuracy of test sieving depends on the dimensional accuracy of the test sieve openings, it is considered necessary in this part of ISO 3310 to keep tolerances on the holes in perforated metal plate as close as possible as the manufacturing process allows.

Requirements other than tolerances on the holes, such as requirements for the pitch of holes, any corner radii, and plate thickness, have not been limited more closely than necessary, since the influence of these criteria on test sieving is of minor importance, and excessively strict requirements may make manufacturing unnecessarily difficult.

Test sieves — Technical requirements and testing —

Part 2:

Test sieves of perforated metal plate

1 Scope

This part of ISO 3310 specifies the technical requirements and corresponding test methods for test sieves of perforated metal plate.

It applies to test sieves having

- round holes, with sizes from 125 mm down to 1 mm, or
- square holes, with sizes from 125 mm down to 4 mm,

in accordance with ISO 565.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 565, *Test sieves — Metal wire cloth, perforated metal plate and electroformed sheet — Nominal sizes of openings*

ISO 2395, *Test sieves and test sieving — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 2395 apply.

4 Designation

Test sieves of perforated metal plate shall be designated by the nominal size of the holes, expressed in millimetres, and by the shape of the holes.

5 Perforated metal plate

5.1 Requirements

The tolerances on the individual size of holes and the selection of pitches shall be as specified in [Table 1](#).

5.1.1 Tolerances on individual size of holes

The tolerances on the individual size of holes as given in [Table 1](#), Column 4, apply to the widths of the mid-sections of square holes and to the diameters of round holes.

5.1.2 Pitch, p

5.1.2.1 The pitches given in [Table 1](#) apply to both round and square holes.

5.1.2.2 The nominal pitches given in [Table 1](#), Column 5, are preferred.

The nominal pitches should be within the limits of p_{\max} and p_{\min} as given in [Table 1](#), Columns 6 and 7. These are defined by a permissible range of choice of approximately $\pm 15\%$ of the value calculated from the nominal size of holes and the preferred pitch.

Table 1 — Tolerances on individual size of holes and selection of pitches

Dimensions in millimetres

Nominal sizes of holes, w^a			Tolerances on individual size of hole \pm	Pitch, p		
Principal sizes	Supplementary sizes			Preferred sizes	Permissible range of choice	
R 20/3	R 20	R 40/3		p_{nom}	p_{max}	p_{min}
(1)	(2)	(3)	(4)	(5)	(6)	(7)
125	125	125	1	160	184	143
	112		0,95	140	161	126
		106	0,9	132	152	119
	100		0,85	125	144	113
90	90	90	0,8	112	129	101
	80		0,7	100	115	90
		75	0,7	95	109	85
	71		0,65	90	103	81
63	63	63	0,6	80	92	72
	56		0,55	71	82	63,5
		53	0,55	67	77	60
	50		0,55	63	72,5	56,5
45	45	45	0,5	56	64,5	50,5
	40		0,45	50	57,5	45
		37,5	0,45	47,5	54,6	42,5
	35,5		0,4	45	51,7	40,5
31,5	31,5	31,5	0,4	40	46	36
	28		0,35	35,5	40,8	31,8
		26,5	0,35	33,5	38,5	30
	25		0,35	31,5	36	28,5
22,4	22,4	22,4	0,3	28	32,2	25,5
	20		0,3	25	29	22,5
		19	0,29	23,6	27,1	21,3
	18		0,28	22,4	25,8	20,2
16	16	16	0,27	20	23	18
	14		0,26	18	20,7	16
		13,2	0,25	17	19,5	15,1
	12,5		0,24	16	18,4	14,3

^a In accordance with ISO 565, the lower limit of the nominal size of square holes is 4 mm.

Table 1 (continued)

Nominal sizes of holes, w^a			Tolerances on individual size of hole \pm	Pitch, p		
Principal sizes	Supplementary sizes			Preferred sizes	Permissible range of choice	
R 20/3	R 20	R 40/3		p_{nom}	p_{max}	p_{min}
(1)	(2)	(3)	(4)	(5)	(6)	(7)
11,2	11,2	11,2	0,23	14	16,1	12,6
	10		0,21	12,6	14,5	11,3
		9,5	0,21	12,1	13,8	10,2
	9		0,2	11,6	13,3	9,8
8	8	8	0,19	10,4	12	9,2
	7,1		0,18	9,4	10,8	8
		6,7	0,17	8,9	10,2	7,5
	6,3		0,17	8,5	9,8	7,2
5,6	5,6	5,6	0,15	7,7	8,9	6,6
	5		0,14	6,9	7,9	5,9
		4,75	0,14	6,6	7,6	5,6
	4,5		0,14	6,3	7,2	5,3
4	4	4	0,13	5,8	6,7	4,9
	3,55		0,12	5,2	6	4,4
		3,35	0,11	5	5,7	4,2
	3,15		0,11	4,7	5,3	3,9
2,8	2,8	2,8	0,11	4,35	5	3,6
	2,5		0,11	3,9	4,5	3,3
		2,36	0,11	3,75	4,3	3,2
	2,24		0,1	3,6	4,1	3,1
2	2	2	0,09	3,3	3,8	2,8
	1,8		0,08	3,1	3,6	2,7
		1,7	0,08	3	3,4	2,5
	1,6		0,08	2,75	3,2	2,3
1,4	1,4	1,4	0,08	2,6	3	2,2
	1,25		0,08	2,45	2,9	2,1
		1,18	0,07	2,4	2,7	2
	1,12		0,07	2,22	2,5	1,8
1	1	1	0,07	2	2,3	1,7

^a In accordance with ISO 565, the lower limit of the nominal size of square holes is 4 mm.

5.1.3 Plate thickness

The nominal thicknesses given in [Table 2](#), Column 2, are preferred. The nominal thickness may, however, depart from these values within the permissible range of choice given in [Table 2](#), Columns 3 and 4.

Table 2 — Plate thicknesses

Dimensions in millimetres

Nominal sizes of holes <i>w</i>	Plate thickness		
	Preferred thickness	Permissible range of choice	
		max.	min.
(1)	(2)	(3)	(4)
125 to 50	3	3,5	2
45 to 16	2	2,5	1,5
14 to 8	1,5	2	1
7,1 to 1,7	1	1,5	0,8
1,6 to 1,0	0,6	1	0,5

5.1.4 Arrangement of holes

Round and square holes in perforated metal plates in test sieves (see [Figure 1](#)) shall be arranged in straight or staggered rows.

Sieves with hole sizes 4 mm and above shall have an unperforated margin. Partial holes are not permitted (see [Figure 2](#)). The unperforated margin is influenced by the hole size, pitch, and manufacturing method, resulting in different margin widths.

The corners of square holes may be rounded with a maximum permissible radius of rounding given by the formula

$$r_{\max} = 0,15w \tag{1}$$

where

r_{\max} is the maximum radius of rounding, in millimetres;

w is the nominal size of the hole, in millimetres.

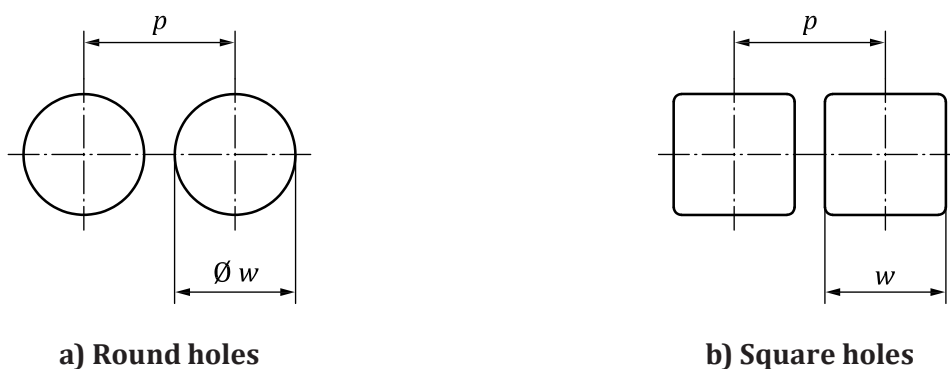


Figure 1 — Arrangement of square and round holes in test sieves

5.1.5 Material of plate

Plated steel is usually supplied. At the lower end of the aperture range, brass may be used. The purchaser should state specific requirements in the enquiry, such as stainless steel.

5.2 Test methods

Every hole in the perforated metal plate in a test sieve shall have the same probability of being inspected for compliance with the requirements listed in 5.1, Table 1, Column 4.

Measure the hole sizes using appropriate equipment with a precision of reading of 20 µm or 1/4 of the tolerance concerned (Table 1, Column 4), whichever is greater.

Test 1 — Visual examination of general condition

View the perforated metal plate against a uniformly illuminated background. If obvious deviations from uniformity of appearance are found, for example partial holes (4 mm and larger), the sieve is unacceptable.

Test 2 — Measurement of size of hole and pitch

Measure the hole size on the centre lines of square holes and on the diameter of round holes according to Table 3.

Table 3 — Minimum number of holes to be measured in a 200 mm diameter test sieve

Nominal sizes of holes <i>w</i> mm	Process for compliance and inspection	Process for calibration
(1)	(2)	(3)
125 to 22,4	All (max. 25 in larger sieves with diameter more than 200 mm)	All (max. 50 in larger sieves with diameter more than 200 mm)
20 to 4	2 × 15	2 × 30
3,55 to 2,24	2 × 20	2 × 40
2 to 1,6	2 × 25	2 × 50
1,4 to 1	2 × 40	2 × 80

Measure the dimensions of the holes and the pitches, *p*, over any selected area of the plate, along two straight lines and different directions, each line being at least 150 mm in length and including at least eight holes in each direction.

If the dimension of any hole exceeds the tolerance, the sieve is unacceptable.

If the minimum number of holes prescribed for examination is not available in the plate, check all the holes in the sieve.

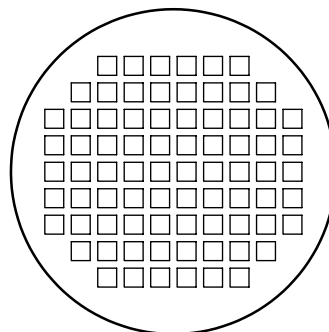


Figure 2 — Example of hole configuration for measurement of up to 20 holes

5.3 Documentation for sieve conformity

5.3.1 Test sieve record card

The manufacturer may provide a record card (see [Annex A](#)) with each new sieve, confirming that it has been inspected by the procedures described in [5.2](#). This card can be used subsequently to record the results of periodic tests and performance checks.

5.3.2 Certificates

All certificates shall mention the manufacturer's sieve serial number, date, and name or signature.

5.3.2.1 Compliance certificate

If no specific request has been made, the manufacturer shall provide a certificate of compliance stating that the test sieve has been inspected in accordance with [5.2](#) and found to be in compliance with this part of ISO 3310. This certificate may be combined with the test sieve record card (see [5.3.1](#) and [Annex A](#)).

5.3.2.2 Inspection certificate

The manufacturer may provide, at the specific request of the purchaser, a test sieve inspection certificate stating the test results for the average hole size. See [Table 3](#), Column 2.

5.3.2.3 Calibration certificate

The manufacturer may provide, at the specific request of the purchaser, a test sieve calibration certificate stating the results of their assessment. Results shall be stated for the number of holes measured, the average hole size, the plate thickness, and pitch. See [Table 3](#), Column 3.

6 Test sieve frames

It is recommended that the 200 mm round metal frame be used as far as possible.


Larger frames may be appropriate for larger quantities of material to be sieved and for hole sizes larger than 25 mm.

The shape and size of the test sieve frame have little effect on the results of the sieving operation (see ISO 2591-1). Sieves complete with a lid and receiver in a set shall be assembled so that escape of sample during a test sieving operation is prevented.

The frames shall be smoothly finished and they shall nest easily with other sieves, lids, and receivers of the same nominal frame size.

The seal of the perforated metal plate with the frame shall be so constructed as to prevent lodging of material to be sieved (see [Figure 3](#)).

The tolerances on test sieves of diameter 200 mm shall comply with [Table 4](#).

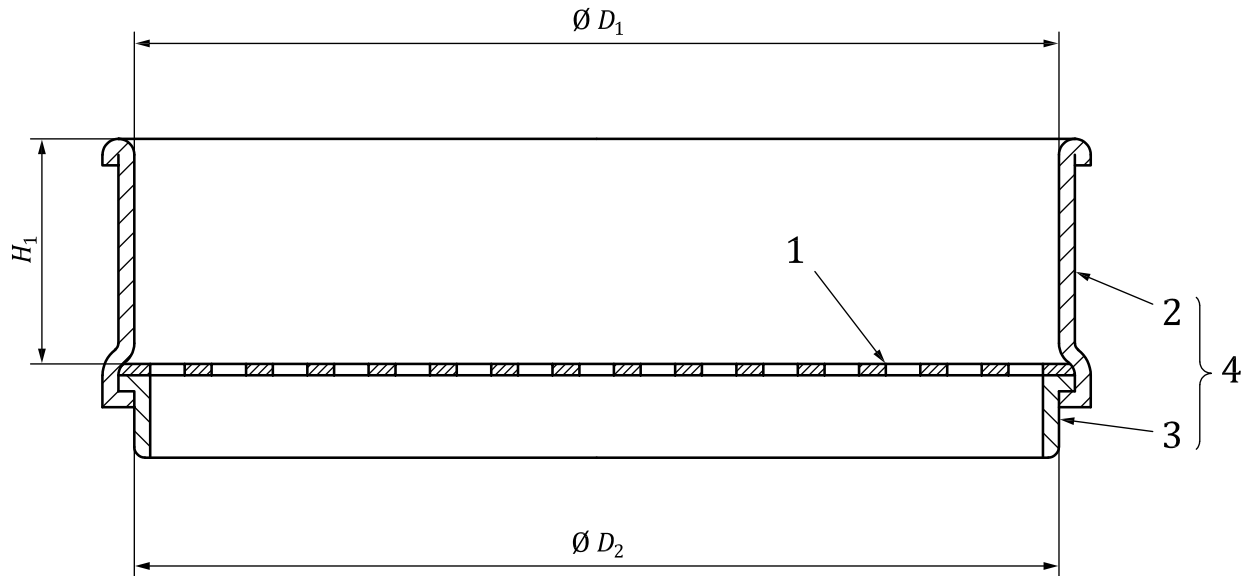

Key

- 1 perforated metal plate
- 2 main part
- 3 base
- 4 frame

Figure 3 — Cross section of test sieve (diagrammatic)

Table 4 — Tolerances on 200 mm diameter test sieves

Dimensions in millimetres

Test sieve nominal frame size		Diameter or length of effective sieving surface		Approximate depth
D_1	D_2	min.	max.	H_1
$200^{0}_{+0,6}$	$200^{-0,1}_{-0,7}$	185	200	50

NOTE The tolerances on D_1 and D_2 should also apply to other nominal frame sizes, such as 100 mm, 300 mm, and 400 mm.

7 Marking of test sieves

A metal label permanently attached to the frame shall give the following information:

- a) the nominal size and shape of holes;
- b) a reference to the standard(s) with which the test sieve is claimed to comply;
- c) the material of the perforated metal plate and of the frame;
- d) the name of the party (manufacturer or vendor) that is responsible for the sieve;
- e) the manufacturer's test sieve serial number.

Annex A (informative)

Test sieve record card

Table A.1 — Example of a test sieve record card for a perforated metal plate sieve

Standard: ISO 3310-2			TEST SIEVE RECORD CARD		Date: 1999-05-05 Signed:	
Sieve serial No.: 987654			Nominal size of holes		Certificate 5.3.2	
Certificate No.:			mm 100	Round	0	Compliance 1
				Square	<input checked="" type="checkbox"/>	<input checked="" type="checkbox"/>
			Tolerance on individual size of holes		Inspection 2	<input type="checkbox"/>
Date	Times used	Visual survey			Calibration 3 (Mark 1, 2, or 3)	
1998-05-05	New	Yes	Within tolerance		Yes	
<small>NOTE It is the user's responsibility to ensure that a used sieve is re-examined according to the circumstances and with a frequency appropriate to the degree of use that the sieve has undergone.</small>						

The sizes and tolerances in this part of ISO 3310 apply to new test sieves. With continued use, however, sieves will wear and it is necessary that all sieves should be examined visually for damage or blinding before each use. Sieves should also be checked periodically, depending on the frequency of use.

One method for checking consists of remeasuring the sieve apertures using the procedures described in 5.2. If the user is not prepared to make such periodic reinspections, recourse may be made by the sieve manufacturer/vendor or by specialists in testing.

Alternatively, sieves can be checked for performance by sieving a known material and comparing the amount of residue on the sieve with that expected.

Known material can be either

- a) reference material with an agreed particle size distribution, or
- b) material that has also been sieved on a set of master test sieves reserved solely for this checking operation.

Further guidance on checking procedures is provided in ISO 2591-1:1988, [\[1\]](#) 6.2.

Bibliography

- [1] ISO 2591-1:1988, *Test sieving — Part 1: Methods using test sieves of woven wire cloth and perforated metal plate.*
- [2] EN 10204:2004, *Metallic materials — Types of inspection documents*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™