

BS ISO 3324-2:2013



BSI Standards Publication

Aircraft tyres and rims

Part 2: Test methods for tyres

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 3324-2:2013. It supersedes BS 3M 45-2:1998 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ACE/1, International and European Aerospace Policy and Processes.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013. Published by BSI Standards Limited 2013

ISBN 978 0 580 70874 9

ICS 49.035; 83.160.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2013.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

BS ISO 3324-2:2013

ISO
3324-2

Third edition
2013-07-01

Aircraft tyres and rims —
Part 2:
Test methods for tyres

Pneumatiques et jantes pour aéronefs —
Partie 2: Méthodes d'essai des pneumatiques



Reference number
ISO 3324-2:2013(E)

© ISO 2013



COPYRIGHT PROTECTED DOCUMENT

© ISO 2013

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols	1
5 Tyre preparation/break-in	2
5.1 Tyre conditioning.....	2
5.2 Tyre inflation and ambient temperature.....	2
5.3 Break-in procedure: static.....	2
5.4 Break-in procedure: dynamic or alternate static testing.....	2
6 Static tests	2
6.1 Burst pressure (pressure proof test).....	2
6.2 Bead seating pressure.....	2
6.3 Air retention: tubeless tyres.....	3
6.4 Tyre dimensions.....	3
6.5 Load-deflection curves.....	4
7 Dynamometer tests	6
7.1 General.....	6
7.2 Pressure correction.....	6
7.3 Dynamometer test procedure: low-speed tyres for which no load/speed/time/distance data are specified.....	7
7.4 Dynamometer test procedure: low- and high-speed tyres.....	7
7.5 Dynamometer test speeds.....	12
7.6 Dynamometer test procedure: high-speed tyres with sortie load/speed/time/ distance data.....	13
Bibliography	15

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2. www.iso.org/directives

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received. www.iso.org/patents

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

The committee responsible for this document is ISO/TC 31, *Tyres, rims and valves*, Subcommittee SC 8, *Aircraft tyres and rims*.

This third edition cancels and replaces the second edition (ISO 3324-2:1998), which has been technically revised.

ISO 3324 consists of the following parts, under the general title *Aircraft tyres and rims*:

- *Part 1: Specifications*
- *Part 2: Test methods for tyres*

Aircraft tyres and rims —

Part 2: Test methods for tyres

1 Scope

This part of ISO 3324 specifies test methods for new and retreaded aircraft tyres in the following categories:

- a) low-speed tyres: for ground speeds up to and including 104 kn (120 mile/h);
- b) high-speed tyres: for ground speeds above 104 kn (120 mile/h).

NOTE 1 kn = 1,852 km/h = 1,1508 mile/h.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4223-1, *Definitions of some terms used in the tyre industry — Part 1: Pneumatic tyres*

3 Terms and definitions

For the purposes of this document, the definitions given in ISO 4223-1 apply.

4 Symbols

L_0	tyre load at start of take-off (greater than or equal to the rated load), in pounds
L'_0	tyre load at start of take-off for the operational load curve, in pounds
L_1	test tyre load at rotation, in pounds
L'_1	operational tyre load at rotation, in pounds
L_2	tyre load at lift-off, in pounds
S_0	speed at start of take-off, in miles per hour
S_1	speed at rotation, in miles per hour
S_2	tyre speed at lift-off, in miles per hour (greater than or equal to the rated speed)
T_0	time at start of take-off, in seconds
T_1	time at constant test load, in seconds
T_2	time to rotation, in seconds
T_3	time to lift-off, in seconds

5 Tyre preparation/break-in

5.1 Tyre conditioning

Before break-in of the tyre, it shall be conditioned by mounting on its design rim and inflating it to the rated inflation pressure. It shall be allowed to remain in this condition for 12 h at an ambient temperature between 16 °C and 37,8 °C.

5.2 Tyre inflation and ambient temperature

After the tyre has been stretched for 12 h on the design rim as indicated in 5.1, the tyre pressure shall be adjusted to the rated pneumatic inflation pressure and checked with a gauge which has been calibrated to within one percent. All tests shall be carried out at ambient temperatures between 16 °C and 37,8 °C.

5.3 Break-in procedure: static

This method of tyre break-in is to prepare the test tyre by inflating it to rated inflation pressure and loading the tyre under direct vertical load against a hard flat unyielding surface until the tyre deflection measures 50 % of the section height. The load is then removed. This break-in is to be carried out at two locations equally spaced around the tyre, with the centreline of the contact patch being located at 180° intervals around the circumference of the tyre.

5.4 Break-in procedure: dynamic or alternate static testing

This method of tyre break-in is to prepare the test tyre by inflating it to rated inflation pressure corrected for flywheel curvature, then performing five rated load take-off cycles with a load-speed-time curve representative of the applicable aircraft.

6 Static tests

6.1 Burst pressure (pressure proof test)

Mount the tyre on a test wheel of adequate strength, and inflate it hydraulically at a slow rate to the minimum specified burst pressure.

Maintain the tyre at this pressure for 3 s without failure.

Continue inflating the tyre at a slow rate until burst.

Burst pressure tests of tubeless tyres may be conducted with an inner tube fitted.

6.2 Bead seating pressure

Determine the bead seating pressure by the following method:

The contact area of the wheel is cleaned to expose the metal surface.


Three pieces of shim copper or steel, 120° from each other, are fixed to one tyre bead. The shims are held in place with light gauge non-conducting adhesive tape (see [Figure 1](#)). The tape insulates the shims from the top of the rim flange.

This procedure calls for the use of a battery, fitted with two leads, one of which is a fixed lead containing a lamp or ohmmeter; the other lead is used as the probe lead to make contact with the three shims in turn.

The tyre is inflated in increments, and after each increment, the probe lead is placed on the shims in turn. When the lamp lights or the ohmmeter reading is zero, at all three shim locations, the bead is considered to be fully seated on the wheel at the recorded inflation pressure, and that pressure is considered to be the bead seating pressure.

Other procedures may be used if these are recognized and approved by the certification or airworthiness authority.

In all procedures, the test shall be conducted without the use of lubricant on the tyre bead or rim.

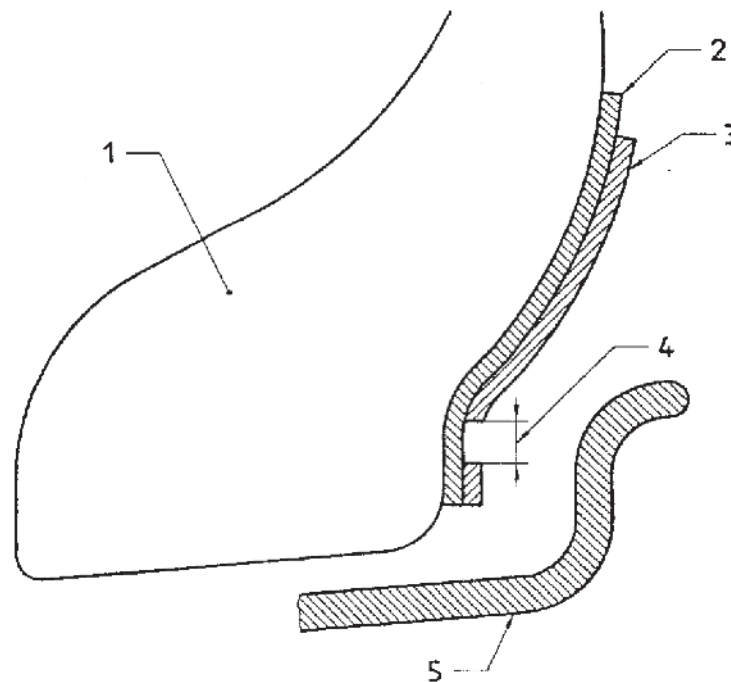

Key

- 1 tyre bead
- 2 steel or copper shims 0,05 mm (0,002 in)
- 3 non-conducting adhesive tape, thin gauge
- 4 gap in tape
- 5 wheel

Figure 1 — Bead seating pressure: electrical method

6.3 Air retention: tubeless tyres

After an initial 12 h minimum stabilization period at rated inflation pressure, the tyre shall be capable of retaining pressure with a loss of pressure not exceeding 5 % in 24 h. Ambient temperature shall be measured at the start and finish of the test to ensure that the pressure change was not caused by an ambient temperature change.

6.4 Tyre dimensions

Mount the tyre on the specified rim, inflate it to its maximum rated inflation pressure and allow it to stand for a minimum of 12 h at normal room temperature. After this lapse of time, readjust the inflation to the original value.

Following the pressure adjustment, measure and record the following tyre dimensions:

- overall diameter;
- overall width;
- shoulder diameter;

— shoulder width.

When a tyre does not have a readily identifiable shoulder point, measure the shoulder width at the maximum specified shoulder diameter and measure the shoulder diameter at the maximum specified shoulder width.

6.5 Load-deflection curves

6.5.1 Tyre mounting

Mount the tyre and inflate as specified in [6.4](#)

Install the tyre and wheel in the testing machine. Make every attempt to remove all the looseness (freeplay) between the wheel, axle, bushings, etc., so that an accurate zero point can be determined.

6.5.2 Vertical load deflection curves

6.5.2.1 To obtain the zero load and deflection point, move the tyre until it barely touches the flat plate. Do not pre-load.

Vertical load deflection curves shall be obtained on the inflated tyre by applying a vertical load and measuring the corresponding deflection between the wheel flange and the unyielding flat surface against which the tyre acts. The load shall be applied beginning from the point of contact of the tyre with the flat surface until the tyre bottoms, with continuous recording of load and corresponding deflection. The load shall then be reduced until its value reaches zero once more, again continuously monitoring load and corresponding deflection. The total load deflection loop or curve shall be presented as indicative of the vertical load deflection characteristics of the tyre. The tyre pressure should be recorded throughout the test.

This test shall be carried out at two locations around the tyre, each separated by 180°. Each vertical load deflection test shall be performed at the location which is opposite from the location of the last loading, in order to minimize the effect of a flat spot.

The time rate of the tyre deflection shall be not more than 50,8 mm/min.

6.5.2.2 Method for determining bottoming point

6.5.2.2.1 The tyre bottoming point is when the tyre has fully deflected its sidewall and is beginning to compress the lower sidewall structure. This is recognized by a noticeable change in the slope of the load deflection curve occurring at a high load and deflection. The bottoming point is the load and deflection at that point.

6.5.2.2.2 For the purposes of approximating the bottoming load for a given tyre with a given inflation pressure, the bottoming load shall be considered as that load at which the rate of loading (kg/25 mm) is 2,2 times the average rate of loading between 28 % and 48 % radial deflection.

6.5.2.2.3 The bottoming load is determined as follows (see [Figure 2](#)):

- a) Conduct the load deflection test in the usual manner, obtaining sufficient data to plot a representative curve for the inflation pressure required. (This should be carried slightly beyond the slope change described in [6.5.2.2.2](#).)
- b) Plot the load deflection curve.
- c) Calculate the inverse slope (kg/25 mm) between 28 % and 48 % deflection.

EXAMPLE 9 000 kg/36 mm = 6 250 kg/25 mm.

- d) Construct a straight line (A-A) having a slope (kg/25 mm) equal to 2,2 times that calculated in c).

EXAMPLE 2,2 × 6 250 = 13 750 kg/25 mm.

6.5.3.6 These lateral load deflection curves shall be obtained at two points around the periphery of the tyre, separated by 180°, and representing the centreline of the contact patch under loaded conditions. All curves shall be performed as indicative of the tyre lateral force deflection characteristics.

6.5.4 Fore-aft load deflection curves

6.5.4.1 Fore-aft deflection is defined as the deflection between the wheel flange at the point immediately above the centre of the contact patch, and the motion of the flat loading surface.

6.5.4.2 The surface of the plate in contact with the tyre shall be covered with a material designed to prevent tyre slippage. The tyre should be inflated to rated pressure with vertical loading equal to the rated load. The wheel should be restrained from rotating and marked in relationship to the tyre to indicate any tyre/wheel slippage. The fore-aft displacement may be obtained either by displacement of the yoke, or of the loading plate or both.

During the loading processes the wheel must be securely locked to prevent rotation so that no flat spots occur on the force vs. deflecting curve. Any wheel slippages should be noted.

6.5.4.3 Fore-aft load deflection curves shall be obtained by increasing the fore-aft load from zero to 15 % of the rated vertical load, then by decreasing this fore-aft force to zero and increasing it in the opposite direction to 15 % of the rated vertical load and finally returning to 15 % of the rated vertical load, completing the loop. The load, pressure, and fore-aft deflection shall be continuously recorded. The total fore and aft hysteresis loop shall represent the fore-aft deflection characteristics of the tyre. Two such loops will be obtained, one each at two positions located 180° apart around the circumference of the tyre. The rate of loading during the fore-aft process shall not be more than 50,8 mm/min.

6.5.4.4 During the process of fore-aft loading, vertical loads also tend to change somewhat. These shall be monitored and adjusted to a constant value equal to the rated load during the conduct of the test.

6.5.4.5 The vertical sinkage of the tyre accompanying this vertical load adjustment shall be measured and recorded using the same vertical deflection measuring techniques as in [6.5.2](#). It shall be presented as a plot of vertical sinkage vs. fore-aft force with the accompanying vertical load and inflation pressure clearly stated.

7 Dynamometer tests

7.1 General

7.1.1 Test procedure

Tyres shall be tested by means of one of the following test procedures:

- low speed tyres shall be tested either in accordance with [7.3](#) or in accordance with [7.4](#);
- high-speed tyres shall be tested in accordance with [7.4](#) or in accordance with [7.6](#).

7.1.2 Test temperature and cycle interval

The temperature of the gas contained in the tyre or of the casing measured at the hottest point of the tyre shall not be lower than 41 °C at the start of 90 % of the cycles. For the remaining cycles, the contained gas or casing temperature shall not be lower than 27 °C at the start of each cycle. Rolling the tyre on the dynamometer is acceptable to obtain the minimum starting temperature.

7.2 Pressure correction

The test inflation pressure shall be the pressure needed to provide the same loaded radius on the flywheel as was obtained on a flat surface at the rated tire load and inflation pressure.

7.3 Dynamometer test procedure: low-speed tyres for which no load/speed/time/distance data are specified

7.3.1 Dynamometer characteristics

The tyres shall be tested on a dynamometer having a stored kinetic energy, E_k , in joules, at a flywheel peripheral speed of 104 kn (120 mile/h) computed as follows:

$$E_k = 485LR$$

where LR is the rated tyre load for the ply rating, in kilograms.

7.3.2 Tyre load

Throughout all test cycles, the tyre shall be loaded against the flywheel at a load equal to or greater than its rated tyre load (LR).

7.3.3 Test speeds

The tyre shall satisfactorily withstand 200 landing cycles on a variable mass dynamometer flywheel, without any detectable signs of deterioration, other than normal tread/surface abrasion. If the exact number of flywheel plates cannot be used to obtain the calculated kinetic energy value, a greater number of plates shall be selected and the dynamometer speed adjusted to obtain the required kinetic energy. The total number of dynamometer landings shall be divided into two equal parts having the speed ranges described below.

- a) In the first series of 100 cycles, the tyre shall be loaded (“landed”) against the flywheel at 78 kn (90 mile/h) and the tyre unloaded (“unlanded”) at zero speed. The speed at “landing” shall be decreased as necessary (see [7.3.4](#)) to ensure that 56 % of the calculated kinetic energy is absorbed by the tyre during each cycle.
- b) In the second series of 100 cycles, the tyre shall be loaded (“landed”) against the flywheel at 104 kn (120 mile/h) and the tyre unloaded (“unlanded”) at 78 kn (90 mile/h). The speed of “unlanding” shall be increased as necessary (see [7.3.4](#)) to ensure that 44 % of the calculated kinetic energy is absorbed by the tyre during each cycle.

All speeds shall be expressed in knots.

7.3.4 Flywheel kinetic energy

If the correct number of flywheel plates cannot be used to obtain the computed kinetic energy value (see [7.3.1](#)), a greater number of plates shall be selected and the dynamometer test cycle speed adjusted to obtain the required kinetic energy for each series of test cycles. If this results in landing speeds of less than 70 kn (80 mile/h), the following shall apply:

- landing speed shall be determined by adding 28 % of the test E_k to the flywheel E_k at 55,6 kn (64 mile/h);
- unlanding speed shall then be determined by subtracting 28 % of the test E_k from the flywheel E_k at 55,6 kn (64 mile/h).

7.4 Dynamometer test procedure: low- and high-speed tyres

7.4.1 Test specimen

A single test specimen shall be used for a qualification test. The tyre shall withstand the following cycles without detectable signs of deterioration, other than normal expected tread surface abrasion, except when the overload take-off condition is run last (see [7.4.9](#)).

7.4.2 Dynamometer cycle requirements

All aircraft tyres shall satisfactorily withstand 61 dynamometer cycles. The dynamometer cycles shall consist of 50 take-off cycles and eight taxi cycles, two taxi cycles at 1,2 times the rated load, and one overload take-off cycle starting at 1,5 times the rated load. The sequence of running the dynamometer cycles is optional. If the overload take-off is not run last, the tyre shall not show detectable signs of deterioration, other than normal tread/surface abrasion, after this test.

7.4.3 Take-off cycles


The 50 take-off cycles shall realistically simulate tyre performance during runway operations for the most critical combination of take-off weight and speed, and aircraft centre-of-gravity position. Consideration shall be given to increased speeds resulting from elevated airport operations and high ambient temperatures. The load-speed-time (LST) data shall be compiled by the airframe manufacturer in compliance with the applicable airworthiness authority requirements. Refer to [Figures 3, 4](#) and [5](#) for graphic representations of the test.

Starting at zero speed, the tyre shall be loaded against the dynamometer flywheel. The test cycles shall simulate one of the curves in [Figures 3, 4](#) and [5](#).

- [Figure 3](#) defines a test cycle that is applicable to any aircraft tyre with a speed rating of 104 kn (120 mile/h) to 139 kn (160 mile/h).
- [Figure 4](#) defines a test cycle that is applicable to any aircraft tyre with a speed rating greater than 139 kn (160 mile/h).
- [Figure 5](#) defines a test cycle that is applicable for any speed rating.

7.4.4 Test load

The load at the start of the test shall be no less than the rated load of the tyre. The test loads shall conform to [Figures 3, 4](#) or [5](#). [Figures 3](#) and [4](#) define a test cycle that is generally applicable to any aircraft. If [Figure 5](#) is used to define the test cycle, the loads shall be selected based on the most critical take-off conditions established by the applicant based on the data obtained from the airframe manufacturer. At any speed throughout the test cycle, the ratio of the test load to the airframe manufacturer's LST curve shall be the same as or greater than at the start of the test.

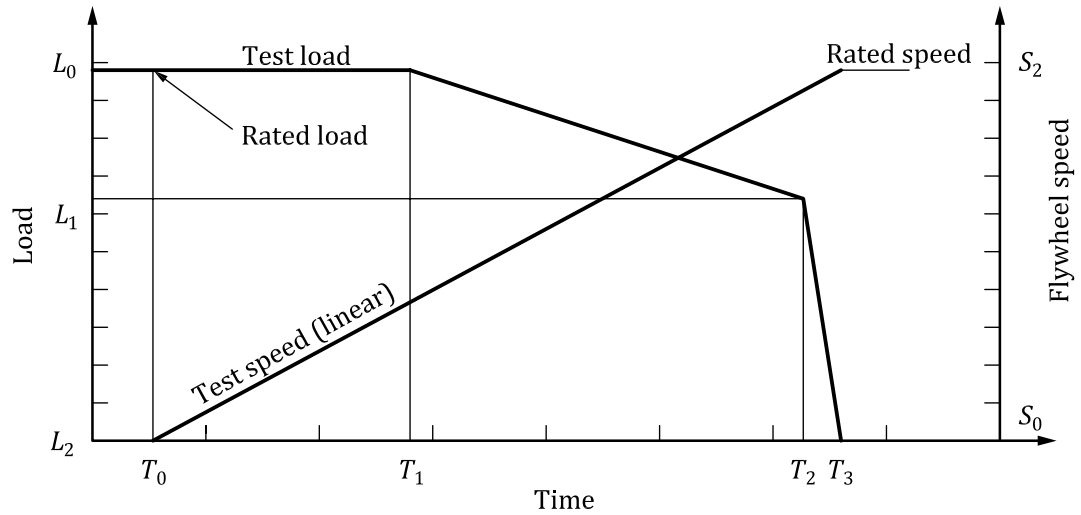


Key

L_1	$0,65 L_0$	S_0	zero speed
L_2	zero load	Roll distance	1 981 m
T_0	start time	$T_3 - T_2$	3 s max
T_1	20 s		

NOTE Test load at L_0 shall be equal to or greater than rated load of tyre. Test speed at S_2 shall be equal to or greater than rated speed of tyre.

Figure 3 — Graphic representation of a universal load-speed-time test cycle — 104 kn (120 mile/h) to 139 kn (160 mile/h)

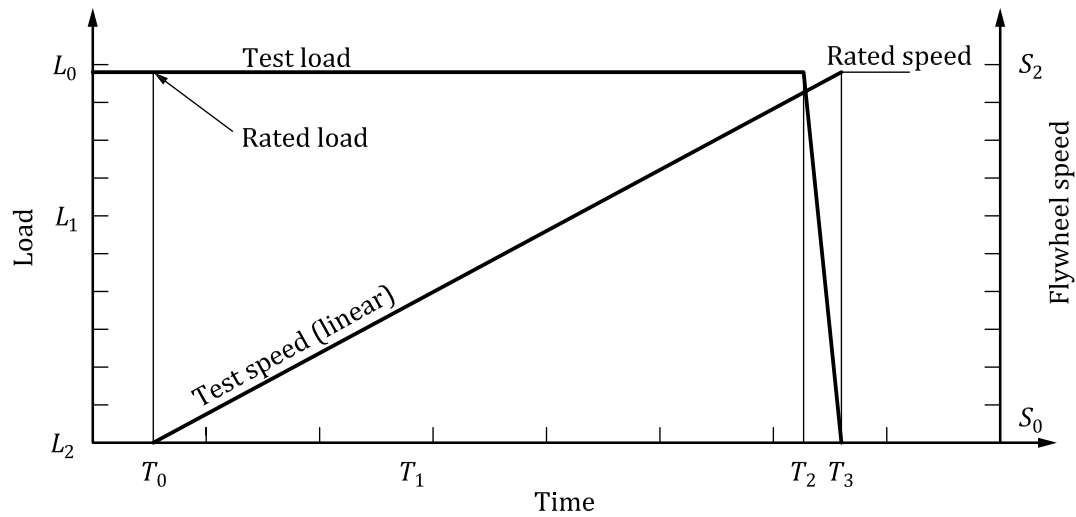


Key

- T_0 start time
- L_2 zero load
- S_0 zero speed
- Roll distance 3 505 m
- $T_3 - T_2$ 3 s max

NOTE Test load at L_0 shall be equal to or greater than rated load of tyre. Test speed at S_2 shall be equal to or greater than rated speed of tyre.

Figure 4 — Graphic representation of a universal load-speed-time test cycle — above 139 kn (160 mile/h)

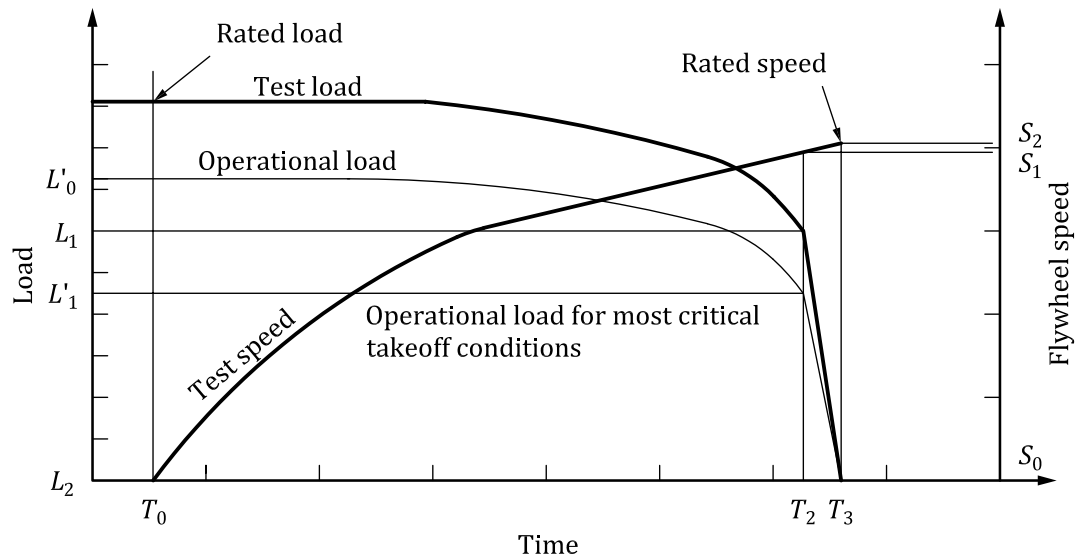

Key

T_0 start time	S_0 zero speed
L_1 tyre load at rotation	S_1 speed at rotation
L_2 zero load	L'_1 tyre load
T_2 time at rotation	L'_0 tyre load at start of take-off for operational load curve
T_3 time at end of cycle	

NOTE 1 Test load at L_0 shall be equal to or greater than rated load of tyre. Test speed at S_2 shall be equal to or greater than rated speed of tyre.

NOTE 2 Test load at any speed shall be equal to or greater than operational load. Test Load $\geq L'_1 \times (L_0 / L'_0)$. Roll distance is determined for each application.

Figure 5 — Graphic representation of a rational load-speed-time test cycle

7.4.5 Test inflation pressure

The test inflation pressure shall be that which is necessary to provide the same loaded radius on the flywheel as was obtained on a flat surface at the rated load and inflation pressure of the tyre. Both determinations shall be made at the same ambient temperature. An adjustment in test inflation pressure may not be made to compensate for changes created by temperature variations during the test.

7.4.6 Test temperatures and cycle interval

The temperature of the gas contained in the tyre or of the casing measured at the hottest point of the tyre shall not be lower than 41°C at the start of the overload take-off and at the start of at least 45 of the 50 take-off cycles, and 49°C at the start of at least nine of the ten taxi cycles. For the remaining cycles, the contained gas or casing temperature shall not be lower than 27°C at the start of each cycle. Rolling the tyre on the dynamometer flywheel is acceptable to obtain the minimum starting temperature.

7.4.7 Dynamometer take-off cycle speeds

The dynamometer test speeds for corresponding maximum aircraft take-off speeds are those given in [Table 2](#).

7.4.8 Taxi cycles

The tyre shall withstand 10 taxi cycles on a dynamometer under the test conditions given in [Table 1](#).

Table 1 — Taxi cycle test conditions

Number of taxis	Minimum tyre load	Minimum speed	Minimum roll distance	
			m	
	kg	kn	Tyre speed rating	
			104 kn (120 mile/h) to 139 kn (160 mile/h)	> 139 kn (160 mile/h)
8	rated load	35	7 620	10 668
2	1,2 × rated load	35	7 620	10 668

7.4.9 Overload take-off cycle

The overload take-off cycle shall duplicate the test described in [7.4.3](#) except that the test load shall be increased by a factor of 1,5 throughout. The tyre tread is not required to be in good condition after completion of this test cycle if it is run last. If the overload take-off cycle is not run last, it shall withstand the cycle without detectable signs of deterioration, other than normal tread/surface abrasion.

7.4.10 Diffusion test

Upon completion of the 61 test cycles, the tyre shall be capable of retaining inflation pressure for 24 h with the loss of pressure not exceeding 10 % of the initial test pressure. Ambient temperature should be measured at the start and finish of this test to ensure that the pressure change was not caused by an ambient temperature change.

7.4.11 Tyre/wheel slippage

No slippage of the tyre on the rim is allowed in the first five cycles. Slippage of the tyre on the rim during the subsequent cycles shall not damage the tube valve of tube type tyres, or the gas seal of the tyre bead of tubeless tyres.

7.5 Dynamometer test speeds

The applicable dynamometer test speeds for corresponding maximum operational ground speeds shall be as given in [Table 2](#).

Table 2 — Dynamometer test speeds

Maximum operational ground speed of aircraft kn (mile/h)		Dynamometer test speed kn (mile/h)
above	to	
0	104 (120)	104 (120)
104 (120)	139 (160)	139 (160)
139 (160)	165 (190)	165 (190)
165 (190)	182 (210)	182 (210)
182 (210)	195 (225)	195 (225)
195 (225)	204 (235)	204 (235)
204 (235)	213 (245)	213 (245)
213 (245)		Consult the aircraft manufacturer

7.6 Dynamometer test procedure: high-speed tyres with sortie load/speed/time/distance data

NOTE This procedure is applicable when the data are specified by the aircraft manufacturer in the form of total sortie test cycles.

7.6.1 Tyre performance

The test shall realistically simulate tyre performance for the most critical combination of aircraft mass and centre of gravity position for the sortie cycle from taxi-out to taxi-in.

Provision shall be made in determining the total test sequence for the following exceptional conditions:

- a) increased speeds and distances resulting from operation at high-altitude airports;
- b) increased speeds and distances resulting from operation at high ambient temperature;
- c) in-flight heating or cooling;
- d) increased distances resulting from reduced acceleration and deceleration required for operation of the aircraft.

7.6.2 Representative load/speed/time/distance data

Representative load/speed/time/distance data compiled by the aircraft manufacturer shall be the basis for establishing the applicable dynamometer test conditions, including data concerning:

- a) the probable incidence of the exceptional conditions stated in [7.6.1](#) in order to determine the percentage of the test cycles which shall include these conditions;
- b) tyre temperature cycle and time data relevant to [7.6.1](#) c).

7.6.3 Typical total test cycle sequence

A typical total test cycle sequence is shown schematically in [Figure 6](#). The curves and the sequence shall be adjusted, for the purpose of establishing the full and precise test cycle, according to the data supplied by the aircraft manufacturer.

In the interest of efficient utilization of testing equipment, it is permissible to remove the tyre assembly from the dynamometer in order to carry out the tyre in-flight heating or cooling phase, provided that the heating or cooling conditions are respected and there is no interruption to the continuity of the test cycle results.

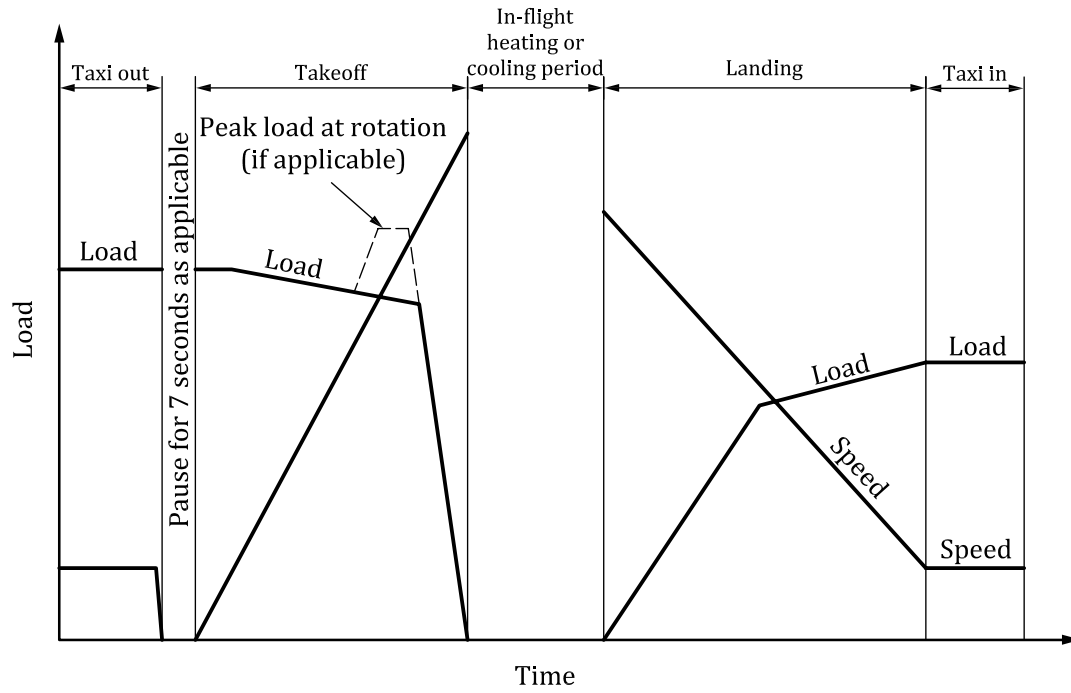


Figure 6 — Test cycle sequence — Total sortie

Bibliography

- [1] SAE ARP 4955A, *Recommended Practice for Measurement of Static and Dynamic Properties of Aircraft Tires*
- [2] SAE AS 4833, *Aircraft New Tire Standard — Bias and Radial*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™