

BS ISO 4386-1:2012



BSI Standards Publication

Plain bearings — Metallic multilayer plain bearings

Part 1: Non-destructive ultrasonic
testing of bond of thickness
greater than or equal to 0,5 mm

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 4386-1:2012. It supersedes BS 7585-1:1992, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee MCE/12, Plain bearings.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012.
Published by BSI Standards Limited 2012.

ISBN 978 0 580 73561 5

ICS 21.100.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2012.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

ISO
4386-1

Third edition
2012-10-15

**Plain bearings — Metallic multilayer
plain bearings —**

Part 1:

**Non-destructive ultrasonic testing
of bond of thickness greater than or
equal to 0,5 mm**

Paliers lisses — Paliers lisses métalliques multicouches —

*Partie 1: Contrôle non destructif aux ultrasons des défauts
d'adhérence d'épaisseur supérieure ou égale à 0,5 mm*



Reference number
ISO 4386-1:2012(E)

© ISO 2012



COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Symbols	1
4 Test equipment	1
4.1 Ultrasonic instrument.....	1
4.2 Probe.....	2
4.3 Reference block.....	2
5 Preparation of test surface	2
6 Testing	2
6.1 General.....	2
6.2 Testing with a back-wall echo.....	2
6.3 Testing without a back-wall echo.....	3
7 Test classes	6
8 Defect groups	6
9 Evaluation	7
9.1 General.....	7
9.2 Marking of defective areas.....	8
9.3 Designation.....	8
Bibliography	9

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 4386-1 was prepared by Technical Committee ISO/TC 123, *Plain bearings*, Subcommittee SC 2, *Materials and lubricants, their properties, characteristics, test methods and testing conditions*.

This third edition cancels and replaces the second edition (ISO 4386-1:1992), which has been technically revised.

ISO 4386 consists of the following parts, under the general title *Plain bearings — Metallic multilayer plain bearings*:

- *Part 1: Non-destructive ultrasonic testing of bond of thickness greater than or equal to 0,5 mm*
- *Part 2: Destructive testing of bond for bearing metal layer thicknesses greater than or equal to 2 mm*
- *Part 3: Non-destructive penetrant testing*

Plain bearings — Metallic multilayer plain bearings —

Part 1:

Non-destructive ultrasonic testing of bond of thickness greater than or equal to 0,5 mm

1 Scope

This part of ISO 4386 specifies an ultrasonic testing method for determining bond defects between the bearing metal and the backing. The test can be performed on metallic multilayer plain bearings consisting of steel- or copper-based material backings lined with bearing metal based on lead and tin, with layer thicknesses greater than or equal to 0,5 mm. For cast iron backings, this part of ISO 4386 is applicable with restrictions.

The ultrasonic signal reflected by the bond interface between the bearing metal and the backing is used to determine bonding defects.

Ultrasonic testing is not possible on edge zones of sliding surface, flange sides, joint areas, oil holes, grooves, etc. in a range of less than half the diameter of the ultrasonic probe because of undefined reflections. The same applies to bearings with dovetail keying grooves at the bond. Ultrasonic testing of bond does not apply along the edges of the dovetails.

Evaluation of the bond on the visible transition from the backing to the bearing metal (on end faces or joint faces) is only practicable by the penetrant testing method specified in ISO 4386-3.

This part of ISO 4386 only describes in detail the pulse-echo method. Within the meaning of this part of ISO 4386, the ultrasonic method only permits a qualitative evaluation of the bonding and not a quantitative determination of the bond strength. The ultrasonic bond test differs only between bond and bond defect.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4386-3, *Plain bearings — Metallic multilayer plain bearings — Part 3: Non-destructive penetrant testing*

3 Symbols

The following symbol is used in this part of ISO 4386.

Ra Surface roughness

4 Test equipment

4.1 Ultrasonic instrument

Pulse-echo ultrasonic instrument using rectified A-scope presentation shall be used for the test. The instrument shall be fitted with a calibrated attenuator, reading in decibels, and adjustable time base ranges.

4.2 Probe

For the standard procedure, normal beam probes shall be chosen with size and frequency in relation to the thickness of the bearing layer, backing thickness and backing material. The typical range of diameters is from 24 mm for 2 MHz to 6 mm for 10 MHz probes. For layer thickness < 1 mm, testing with dual-element probes may be favourable.

4.3 Reference block

The time base range shall be adjusted, using a reference block corresponding to the thicknesses of the bearing to be inspected.

5 Preparation of test surface

The test surface shall have a surface roughness of $Ra \leq 5 \mu\text{m}$. After machining, remove dirt and oil using suitable cleaning agents.

6 Testing

6.1 General

Test plain bearings using either contact scanning, with light machine oil as a couplant, or using immersion scanning. Suppression and swept-gain functions shall be switched off. The preferred test is performed from the bearing metal side under consideration of the back-wall echo. Bearings with smaller diameters can be difficult to inspect by contact scanning from the bearing metal side because of limited access of the ultrasonic probe. In such a case, contact scanning from the back surface may be used.



6.2 Testing with a back-wall echo

General preconditions are:



- a) free access with the probe to the contact surface;
- b) back-wall is always parallel to the bearing metal surface;
- c) no hollow spaces within the backing material (drilled holes, channels, etc.).

The time base range and sensitivity shall be adjusted so that at least the first back-wall echo is visible on the right-hand side of the screen at approximately 80 % of full screen height. In Figure 1, the bond echo (BE) is on the left-hand side of the screen near the input signal (IS). If in doubt about having the first back-wall echo (WE1) on the screen, use a reference block for adjustment.

Bond defect is given when the back-wall echo breaks down and at the same time, the bond echo on the left-hand side of the screen increases and repeats multiple times (see Figure 1). The border of the detected defect area is on the middle of the probe diameter when the back-wall echo is reduced to its half height under the above-mentioned conditions.

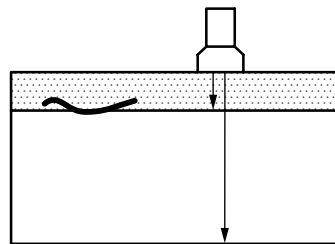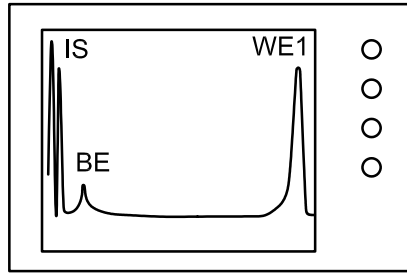

a) Bond

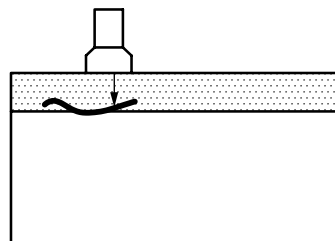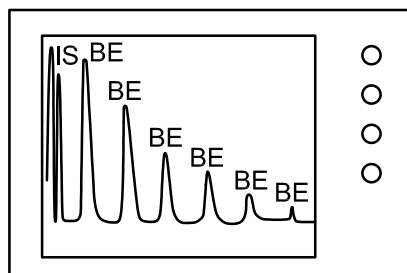

b) Defective bond

Key

- BE bond echo
- IS input signal
- WE₁ first back-wall echo

Figure 1 — Testing with a back-wall echo


6.3 Testing without a back-wall echo

If the preconditions of 6.2 are not fulfilled, testing without back-wall echo becomes necessary.

Use a reference piece with good bond between similar backing material and similar bearing metal lining as the tested bearing. Adjust the reference bond echo to 20 % of full screen height; see Figure 2.

Bond is given when the echo signal of the tested plain bearing is similar to the adjusted reference bond echo; see Figure 3.


Defective bond is given when the bond echo on the plain bearing is significant above the reference bond height; see Figure 4.

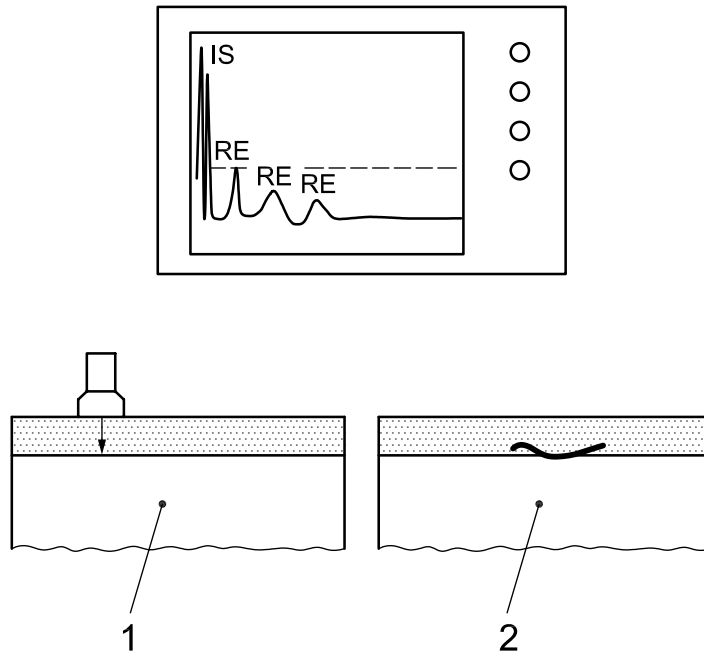

Key

- 1 reference block
- 2 test object
- IS input signal
- RE reference echo


**Figure 2 — Testing without a back-wall echo
Display and adjustment of reference echo**

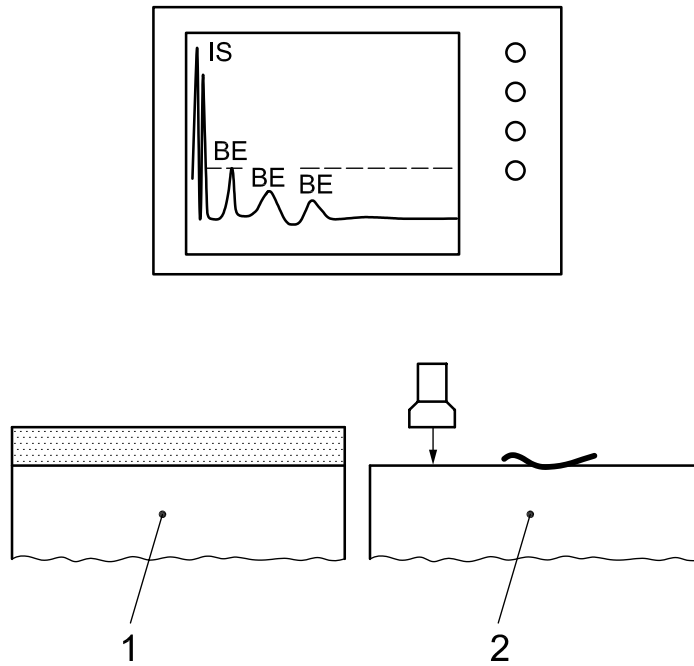

Key

- 1 reference block
- 2 test object
- IS input signal
- BE bond echo

**Figure 3 — Testing without a back-wall echo
Display of bond**

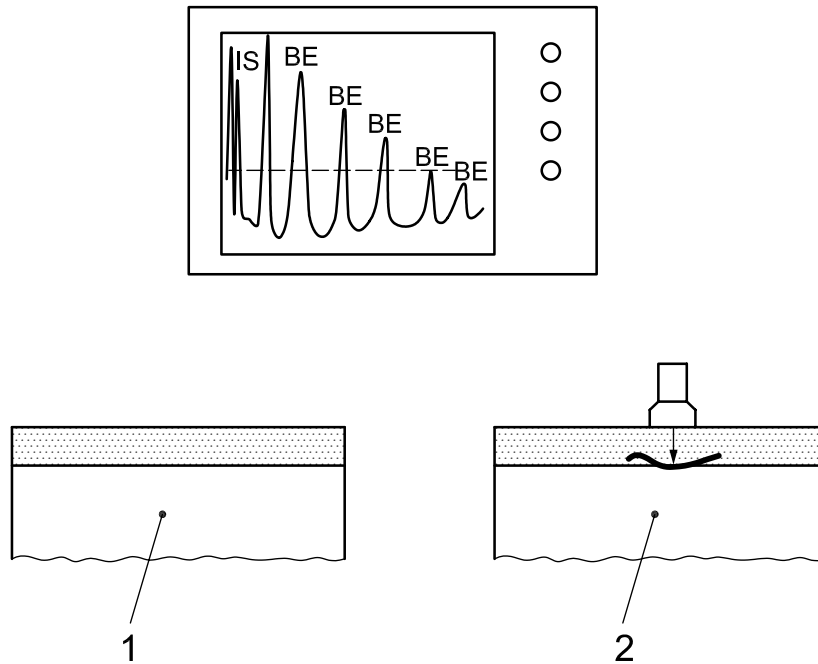

Key

- 1 reference block
- 2 test object
- IS input signal
- BE bond echo

**Figure 4 — Testing without a back-wall echo —
 Display of bond defect**

7 Test classes

The test shall be carried out in accordance with one of the following three classes, which are of increasing severity.

- Class 1: complete coverage of the testable area of the edge zones of the sliding surface at flange sides and joint areas; point-type coverage of the sliding surface.
- Class 2: complete coverage of the testable area of the edge zones of the sliding surface at flange sides and joint areas. In addition, complete coverage of the area of maximum loading (for example, in the case of a radial bearing with a bearing force acting vertically downwards, this would be in the range from 60° to 120° with respect to the sliding surface).
- Class 3: complete coverage of the testable area of the flange areas and sliding surface line-by-line. In order to cover all points, testing is carried out with an overlap of the lines of 20 % of the probe diameter.

8 Defect groups

As a guideline, Table 1 shows five different defect groups. The applicable defect groups shall be agreed between the customer and supplier in advance. It is recommended to define different defect groups for different regions of a bearing, depending on the kind, size and direction of the load (for example, defect group A for the high-loaded region and defect group B1 for the remaining regions of a journal bearing). Generally, defect group A should be reserved for high-loaded bearings and therefore the area of maximal loading.

Table 1 — Defect groups

Defect group	Max. dimension of single defects	Max. total defect
	mm ²	Percentage of bonding area ^a , %
A	0	0
B1	0,75 b^b	1
B2	2 b^b	1
C	2 b^b	2
D	4 b^b	5

^a The bonding area is the lined area of a journal bearing or a thrust plain bearing element.
^b The width, b , in millimetres, represents in case of journal bearing, the functional cylindrical length and in the case of thrust segments or rings, the distance between the inner and outer diameter. The summary of single defects may not exceed the maximum total defect size.

9 Evaluation

9.1 General

The tests should be carried out by operators educated for ultrasonic testing.

When evaluating the test results in accordance with this part of ISO 4386, bond defects equal to or larger than half the probe diameter are normally estimated.

In case of any irregularities on bond surface of a bearing backing, the relevant area shall be collected and documented in the drawing before lining with bearing metal. This avoids misinterpretation during ultrasonic testing as a bond defect.

If the bond echo signal becomes diffuse and missing scanning contact can be excluded, this indicates porosities within the bearing metal. Such areas of porosity shall be regarded as defects due to the uncertainty of evaluation of the bond.

For inspection of the bearing, the following steps shall be considered.

- a) After local repair work by a soldering procedure, the bond test shall be repeated in the respective area.

On edge zones, the visible transition from the backing to the bearing metal shall be checked in accordance with non-destructive penetrant testing specified in ISO 4386-3.

- b) Evaluation of defect distribution:

detected bond defects on new lined bearings give additional information depending on its location and distribution:

- 1) single bond defects in the flange side edge zone or in the corner between flange side - joint side: these defects are typically based on local temperature losses during the casting procedure. Usually these defects can be repaired by soldering procedure without any quality reduction;
- 2) single bond defects on sliding surface: if repair work by soldering can be carried out, successful sufficient bond strength is given and no quality reduction is given;
- 3) many bond defects distributed on sliding surface: many detected bond defects distributed on the total sliding surface and growing defects during the soldering procedure are indicators for low bond strength at all. Complete renewal of bearing metal lining is recommended.

9.2 Marking of defective areas

If possible, defective areas should be indicated by straight boundary lines. The location of the centre of the probe is decisive for determining the transition line between bond and no bond.

Isolated point-type defects shall be marked with a value equal to half the probe diameter.

If the distance between two or more defects is less than one tenth of the bearing width, b , these defects shall be regarded as one continuous defect.

9.3 Designation

With reference to this part of ISO 4386, the test class and the defect group shall be indicated as follows.

EXAMPLE Test Class 2, defect group B1 is designated as follows: **Test ISO 4386-1- 2 B1**

Bibliography

- [1] ISO 6280, *Plain bearings — Requirements on backings for thick-walled multilayer bearings*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™