



BSI Standards Publication

Plain bearings — Metallic multilayer plain bearings

Part 2: Destructive testing of bond
for bearing metal layer thicknesses
greater than or equal to 2 mm

National foreword

This British Standard is the UK implementation of ISO 4386-2:2012. It supersedes BS 7585-2:1992, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee MCE/12, Plain bearings.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012.
Published by BSI Standards Limited 2012.

ISBN 978 0 580 73562 2

ICS 21.100.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2012.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

ISO
4386-2

Second edition
2012-10-15

**Plain bearings — Metallic multilayer
plain bearings —**

Part 2:

**Destructive testing of bond for bearing
metal layer thicknesses greater than
or equal to 2 mm**

Paliers lisses — Paliers lisses métalliques multicouches —

*Partie 2: Détermination, par essai destructif, de l'adhérence du
matériau antifriction d'épaisseur supérieure ou égale à 2 mm*



Reference number
ISO 4386-2:2012(E)

© ISO 2012



COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Principle	1
4 Test equipment	1
4.1 General.....	1
4.2 Testing apparatus.....	2
5 Specimen	2
5.1 General.....	2
5.2 Specimen machining sequence.....	4
6 Procedure	5
7 Evaluation	5
7.1 General.....	5
7.2 Designation.....	6
7.3 Test report.....	6
8 Application for quality control and process qualification	7
8.1 General.....	7
8.2 Quality control.....	7
8.3 Process qualification.....	7

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 4386-2 was prepared by Technical Committee ISO/TC 123, *Plain bearings*, Subcommittee SC 2, *Materials and lubricants, their properties, characteristics, test methods and testing conditions*.

This second edition cancels and replaces the first edition (ISO 4386-2:1982), which has been technically revised.

ISO 4386 consists of the following parts, under the general title *Plain bearings — Metallic multilayer plain bearings*:

- *Part 1: Non-destructive ultrasonic testing of bond of thickness greater than or equal to 0,5 mm*
- *Part 2: Destructive testing of bond for bearing metal layer thicknesses greater than or equal to 2 mm*
- *Part 3: Non-destructive penetrant testing*

Introduction

Long years of experience with bond tests led to an adaptation of this part of ISO 4386. The test apparatus has been modified, to reduce the negative local bending stress influence on the specimen. The geometry of the test specimen has been modified to avoid negative influence due to tolerances. A description of the specimen machining sequence has been added to get a more uniform specimen. A subclause on the application for quality control has been added.

Plain bearings — Metallic multilayer plain bearings —

Part 2:

Destructive testing of bond for bearing metal layer thicknesses greater than or equal to 2 mm

1 Scope

This part of ISO 4386 specifies a tensile test method for determination of the bond strength between the bearing metal and the backing. The test can be applied to multilayer plain bearings with bearing metals based on lead, tin, copper or aluminium. For tested layer thicknesses of ≥ 2 mm, a raw lining thickness of a minimum additional 1 mm is necessary.

The backings are from steel, cast steel or copper alloys. The bond strength test does not apply to bearings with cast iron backing.

The test applies to all thrust bearings and to journal bearings with an inner diameter of backing ≥ 90 mm.

The test can be used for comparative investigations into the influence on the bond strength of various processes and types of material. In addition, the test is suitable for production control and for process qualification of bearing production.

For non-destructive ultrasonic testing of the bond between bearing metal and backing for bearing metal layer thicknesses ≥ 2 mm, see ISO 4386-1.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4381, *Plain bearings — Tin casting alloys for multilayer plain bearings*

3 Principle

During the tensile testing carried out vertically to the bond surface, the bond strength R_{Ch} , in newtons per square millimetre, is the quotient of the maximum force, F_{max} , in newtons and the bond surface, A , in square millimetres, of the specimen (see Table 2).

NOTE The subscript “Ch” refers to the test method proposed by Chalmers.

$$R_{Ch} = \frac{F_{max}}{A} \quad (1)$$


4 Test equipment

4.1 General

A calibrated tensile testing machine shall be used with apparatus in accordance with Table 1.

By means of careful adjustment of the apparatus, it shall be ensured that the force is acting vertically to the bond surface in order to avoid incorrect measurements.

4.2 Testing apparatus

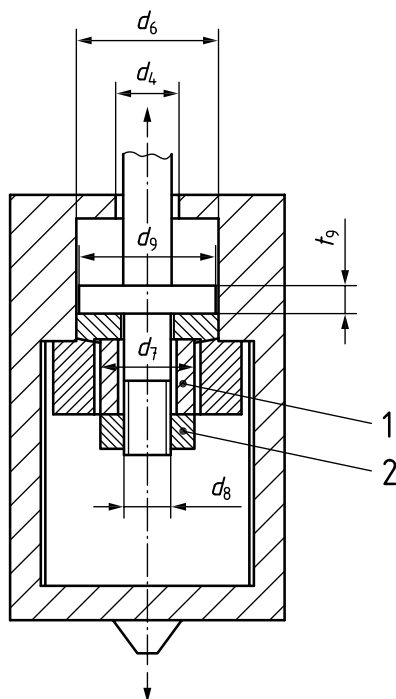

Key

- 1 distance tube
- 2 nut

Figure 1 — Main dimensions of apparatus

NOTE Details not indicated in this part of ISO 4386 are expected to be chosen accordingly.

Table 1 — Dimensions and tolerances for test apparatus

Dimensions in millimetres

Type of specimen	Apparatus geometry data					
	d_4	d_6	d_7	d_8	d_9	t_9
	$\begin{matrix} +0,1 \\ 0 \end{matrix}$	$\begin{matrix} +0,1 \\ 0 \end{matrix}$	$\begin{matrix} 0 \\ -0,1 \end{matrix}$	n.a.	n.a.	n.a.
T 100	8,1	19,8	15,9	M 8	19	4
T 200	12,1	29,1	23,9	M 12	28	4

5 Specimen

5.1 General

Tin casting alloys for multilayer plain bearings are specified in ISO 4381.

For selection of the type of specimen in the case of journal bearings, the inner diameter, d_1 , of the bearing has to be considered.

Specimen T 100 is valid from the minimum diameter $d_1 = 90$ mm up to $d_1 = 200$ mm.

Specimen T 200 is valid for all diameters $d_1 > 200$ mm.

For the thrust bearings specimen, T 100 and T 200 may be used. Whenever possible, T 200 should be preferred.


Both bearing metal faces shall be machined as a precondition for fixing the bearing metal layer on the test apparatus to avoid bending deformation of the bearing metal during test procedure. Use test apparatus in accordance with Table 1.

Specimens shall be manufactured in accordance with Table 2, Figure 2 and 5.1.

Table 2 — Dimensions and tolerances for specimens (see Figure 2)

Dimensions in millimetres

Type of specimen	Bond surface A mm^2	Inner diameter of the backing of journal bearing d_1	Specimen geometry data			
			d_2	d_3	d_4	d_5
T 100	100	90 - 200	19,60	16	$8,1$ 0	29
T 200	200	> 200	28,85	24	12,1	38

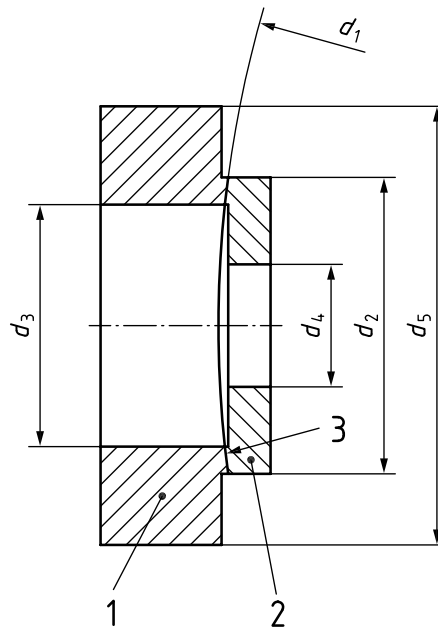



Key

- 1 backing
- 2 bearing metal
- 3 bond surface equal to test surface


Figure 2 — Specimen (from a journal bearing) for bond testing

5.2 Specimen machining sequence

Specimen machining sequence
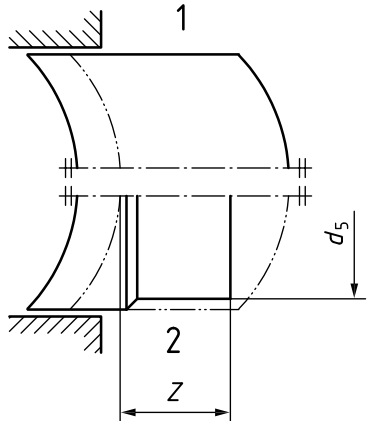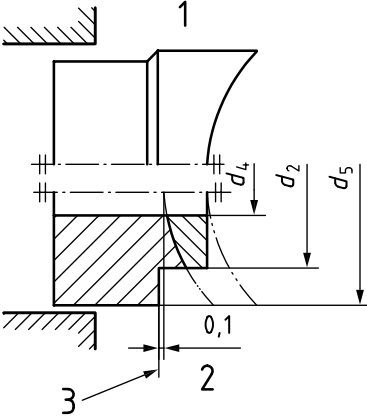
<p>Step 1: a) tighten raw specimen with bearing metal towards chuck b) machine d_5 c) machine backing front plane to thickness Z</p>		<p>T 100</p>	<p>T 200</p>
<p>Key 1 before machining 2 after machining Figure 3 — Step 1</p>		<p>$d_5 = 29$ $Z = 8 - 10$</p>	<p>$d_5 = 38$ $Z = 10 - 12$</p>
<p>Step 2: a) reverse specimen and tighten with backing towards chuck b) drill d_4 c) machine d_5 machine d_2 Machine the reference plane 0,1 mm deep into the steel, referred to the deepest point of bond surface d) machine bearing metal front face plane The raw lining thickness shall be min. 3 mm</p>			
<p>Key 1 before machining 2 after machining 3 reference plane Figure 4 — Step 2</p>		<p>$d_4 = 8,1^{+0,1}_0$ $d_5 = 29$ $d_2 = 19,60 \text{ h}8$</p>	<p>$d_4 = 12,1^{+0,1}_0$ $d_5 = 38$ $d_2 = 28,85 \text{ h}8$</p>

Specimen machining sequence
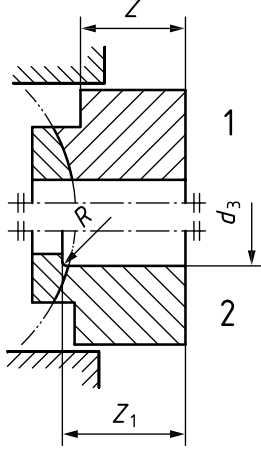
<p>Step 3: a) reverse specimen and tighten with bearing metal towards chuck b) machine d_3 with depth Z_1 Radius $R = 0,1$ mm</p>			
<p>Key 1 before machining 2 after machining</p>	<p>Figure 5 — Step 3</p>	<p>$d_3 = 16,0$ H8 $Z_1^{+0,1}_0 = Z + 0,9$</p>	<p>$d_3 = 24,0$ H8 $Z_1^{+0,1}_0 = Z + 0,9$</p>

6 Procedure

The apparatus, as shown in Figure 1, is mounted on the calibrated tensile testing machine. Subsequently, the specimen is locked into the apparatus, whereas the bearing metal surfaces are fixed to avoid local bending. For that purpose, hand tighten the nut (see Figure 1).

The force is steadily increased until the specimen fractures.

The increase in stress should be at about $10 \text{ N/mm}^2 \cdot \text{s}$.

The force of the specimen fracture is read from the testing machine.

7 Evaluation

7.1 General

With the aid of the force of failure, F_{\max} , found necessary to tear the bearing metal away from the backing in the region of the bond surface, the bond strength, R_{Ch} , is to be determined according to Formula (1). Previous existing local bond defects on the surface of failure shall be noted.

The characteristic limiting value of layer thickness for the absolute bond strength is a property of the bearing metal. It is 6 mm for Pb and Sn alloys. For other than Pb and Sn alloys, the value shall be determined in a series of tests with different thicknesses of the bearing material layers. Above the limit, the results are independent of the layer thickness.

Absolute bond strength is given when the layer thickness is greater than or equal to the characteristic limiting value of thickness. The result is independent of the layer thickness of the bearing metal.


Relative bond strength is given when the layer thickness is less than the characteristic limiting value of thickness. For layer thicknesses below the limiting value of thickness, it has been established experimentally that the relative bond strength drops linearly to the value zero (see Figure 2).

The evaluation procedure is as follows:

- layer thickness greater than or equal to characteristic limiting value of thickness: the value found is the absolute bond strength value;

- b) layer thickness less than characteristic limiting value of thickness: the value found is the relative bond strength value and has to be converted into the value of the absolute bond strength as shown in Figure 2 (as an example).

All results of absolute bond strength shall be limited to the tensile strength, R_m , of the tested bearing metal.

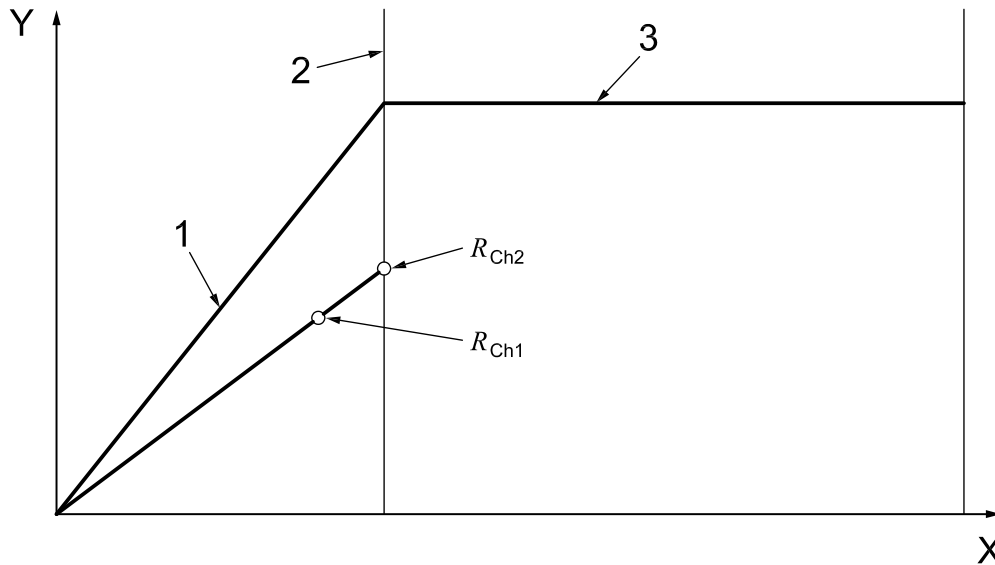

Key	
X	thickness of bearing metal layer
Y	bond strength
1	relative bond strength
2	limiting value
3	absolute bond strength
R_{Ch1}	measured value in the range of the relative bond strength
R_{Ch2}	value of the absolute bond strength determined graphically

Figure 6 — Principle curve of the bond strength as a function of the thickness of the bearing metal layer

7.2 Designation

With reference to this part of ISO 4386, the tensile test (represented by T) shall be indicated in the following order, for example a test surface of 200 mm² is designated as follows: **Test ISO 4386-2, 2009- T 200**

7.3 Test report

A test report on the result of the test shall be drawn up (by agreement) .

In the test report, the following shall be indicated:

- a) reference to this part of ISO 4386, i.e. ISO 4386-2;
- b) reference to the tested plain bearing;
- c) dimensions, layer thickness and materials of the plain bearing;
- d) type of specimen, for example T 200;
- e) number of specimens;

- f) for each specimen:
 - maximum force applied until fracture of the specimen;
 - relative and absolute bond strength determined;
 - description of the condition of the fractured surface inclusive of detected local bond defects or porosities;
- g) summary of a test series:
 - mean value of absolute bond strength;
 - maximum absolute bond strength;
 - minimum absolute bond strength;
- h) test personnel and date of test.

8 Application for quality control and process qualification

8.1 General

The bond strength depends on many influences, such as backing material quality, heat treatment of backing material, preparation of bond surface, bearing metal composition, casting temperature, backing temperature, backing geometry, cooling conditions, specimen machining tolerances and the test procedure itself.

Because of all these influences, in practice, bond strength results may vary. Less variation of results of a tested series is an indication for high uniformity in processing.

A sufficient number of specimens shall be taken from the test bearing. Specimens should be taken from the centre area of the bearing as well as from the area near the border and should be marked accordingly.

A test with a single specimen gives no quality indication. For a quality indication, the mean value of a series of tests shall be taken.

8.2 Quality control

Through this test procedure, usually the bearing will be destroyed. Therefore, this test procedure is not applicable to continuous quality control. In mass production, a single bearing can be immolated each time.

In single-part production, a separate bearing of the same materials and same geometry shall be produced in sequence with the original bearing, and specimens are to be taken from this separate bearing. Only this approach ensures comparable bond conditions on both bearings.

A mean value of absolute bond $\geq 0,6 R_m$ (tensile strength) of the bearing metal is a sufficient bond for plain bearings.

8.3 Process qualification

A process qualification can be carried out on a typical bearing of the production range.

The mean value of an absolute bond $\geq 0,8 R_m$ (tensile strength) of the bearing metal is a desirable bond for process qualification.

The associated processing data shall be documented and shall be used in the future for the tested bearing type. When dimensions, geometry or materials are to be modified, the process qualification shall be repeated under the new conditions.

NOTE 1 A frequent reason for low bond is a processing temperature that is too low due to local temperature losses.

If the recommended bond cannot be achieved, the heating and cooling conditions of the lining process shall be improved or a different lining process shall be chosen.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™