

BS ISO 4700:2015



BSI Standards Publication

Iron ore pellets for blast furnace and direct reduction feedstocks — Determination of the crushing strength

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 4700:2015. It supersedes BS ISO 4700:2007 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/58, Iron ores.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015. Published by BSI Standards Limited 2015

ISBN 978 0 580 79294 6

ICS 73.060.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 August 2015.

Amendments issued since publication

| Date | Text affected |
|------|---------------|
|------|---------------|

INTERNATIONAL
STANDARD

BS ISO 4700:2015

ISO
4700

Fourth edition
2015-08-01

**Iron ore pellets for blast furnace
and direct reduction feedstocks —
Determination of the crushing strength**

*Boulettes de minerais de fer pour charges de hauts fourneaux et
réduction directe — Détermination de la résistance à l'écrasement*



Reference number
ISO 4700:2015(E)

© ISO 2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

| | Page |
|--|-----------|
| Foreword | iv |
| Introduction | v |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 1 |
| 4 Principle | 1 |
| 5 Sampling, sample preparation and preparation of test portions | 1 |
| 5.1 Sampling and sample preparation..... | 1 |
| 5.2 Preparation of test portions..... | 2 |
| 6 Apparatus | 2 |
| 7 Procedure | 2 |
| 7.1 Number of determinations for the test..... | 2 |
| 7.2 Load application..... | 3 |
| 8 Expression of results | 4 |
| 9 Test report | 4 |
| 10 Verification | 5 |

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 102, *Iron ore and direct reduced iron*, Subcommittee SC 3, *Physical testing*.

This fourth edition cancels and replaces the third edition (ISO 4700:2007) which has been technically revised to provide clarification in [7.2](#) when using automatic equipment.

Introduction

This International Standard concerns one of a number of physical test methods that have been developed to measure various physical parameters and characteristics and to evaluate the behaviour of iron ores, including reducibility, disintegration, crushing strength, apparent density, etc. This method was developed to provide a uniform procedure, validated by collaborative testing, to facilitate comparisons of tests made in different laboratories.

The results of this test have to be considered in conjunction with other tests used to evaluate the quality of iron ores as feedstocks for blast furnace and direct reduction processes.

This International Standard can be used to provide test results as part of a production quality-control system, as a basis of a contract, or as part of a research project.

Iron ore pellets for blast furnace and direct reduction feedstocks — Determination of the crushing strength

CAUTION — This International Standard may involve hazardous operations and equipment. This International Standard does not purport to address all of the safety issues associated with its use. It is the responsibility of the user of this International Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to its use.

1 Scope

This International Standard specifies a method to provide a measure of the compressive load attained to cause breakage of pellets.

This International Standard is applicable to hot bonded pellets.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3082, *Iron ores — Sampling and sample preparation procedures*

ISO 11323, *Iron ore and direct reduced iron — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11323 apply.

4 Principle

A single pellet of a specific size range is compressed at a specific speed. The procedure is repeated on all pellets in the test portion. The crushing strength is calculated as the arithmetic mean of all the measurements obtained.

5 Sampling, sample preparation and preparation of test portions

5.1 Sampling and sample preparation

Sampling of a lot and preparation of a test sample shall be in accordance with ISO 3082.

The size range for pellets shall be $-12,5 \text{ mm} +10,0 \text{ mm}$.

A test sample of at least 1 kg, on a dry basis, of sized pellets shall be obtained.

Oven-dry the test sample to constant mass at $105 \text{ °C} \pm 5 \text{ °C}$ and cool it to room temperature before testing.

NOTE Constant mass is achieved when the difference in mass between two subsequent measurements becomes less than 0,05 % of the initial mass of the test sample.

5.2 Preparation of test portions

One test portion comprising at least 60 pellets, as agreed upon at the time of order, shall be taken from the test sample by random selection.

NOTE A method of determining the exact number of pellets to obtain a specific precision in the test results is to use the following equation:

$$n = \left(\frac{2\sigma}{\beta} \right)^2$$

where

- n is the number of pellets;
- σ is the standard deviation, in newtons, derived from several experiments;
- β is the required precision, in newtons, for 95 % confidence levels.

6 Apparatus

6.1 General

The test apparatus shall comprise the following:

- a) ordinary laboratory equipment, such as an oven, hand tools and safety equipment;
- b) loading unit;
- c) load transmission system;
- d) load indicator or recorder.

6.2 Loading unit, formed by two compressive flat platens made of steel, installed in mutual parallel planes. The surface of the platens that will be in contact with the sample shall be made of surface-hardened steel. A device capable of setting the speed of the compressive platen between 10 mm/min and 20 mm/min over the entire test period shall be used.

NOTE If the platen speed is not constant during the test cycle, results may differ depending upon the test machine used. More uniform results may be obtained using a test machine that applies a constant load increase.

6.3 Load transmission system, which shall be either a load cell or a lever. The capacity of the load cell for transmission of the applied load to the indicating unit shall be at least 10 kN.

6.4 Load indicator or recorder, which shall be either an electric indicator (digital read-out device, recording chart, meter with needle rider or other suitable device) for the load-cell type, or a mechanical indicator (gauge equipped with a needle rider or other suitable device) for the lever type. When using a load cell, the chart-recorder pen-response time shall be 1,0 s or less for a full-scale deflection. The minimum graduation shall be 1/100 of the full scale. The compression device shall be calibrated regularly.

7 Procedure

7.1 Number of determinations for the test

Carry out the test on 60 or more single pellets (see the Note in [5.2](#)).

7.2 Load application


Place a test piece (single pellet) at the approximate centre of the surface-hardened portion of the lower platen. Apply the load at a constant platen speed between 10 mm/min and 20 mm/min throughout the test period.

The test is complete when

- either the load falls to a value of 50 % or more of the maximum load recorded (see [Figure 1](#)),
- or the platen gap has reduced to 50 % of the initial mean test-piece diameter (see [Figure 2](#)).

In either case, the crushing strength is the maximum load attained in the test.


For automatic equipment, individual pellet strength values lower than 10 daN shall be excluded from the calculation of results.

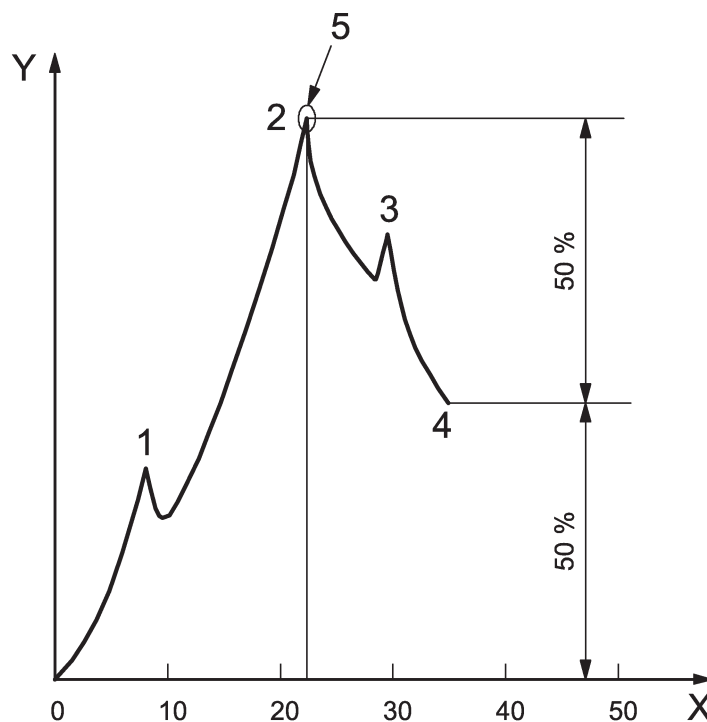

Key

- X contraction, %
- Y load
- 1 1st peak
- 2 2nd peak
- 3 3rd peak
- 4 stop
- 5 strength

Figure 1 — Measurement of crushing strength as explained in Example 1 in the procedure

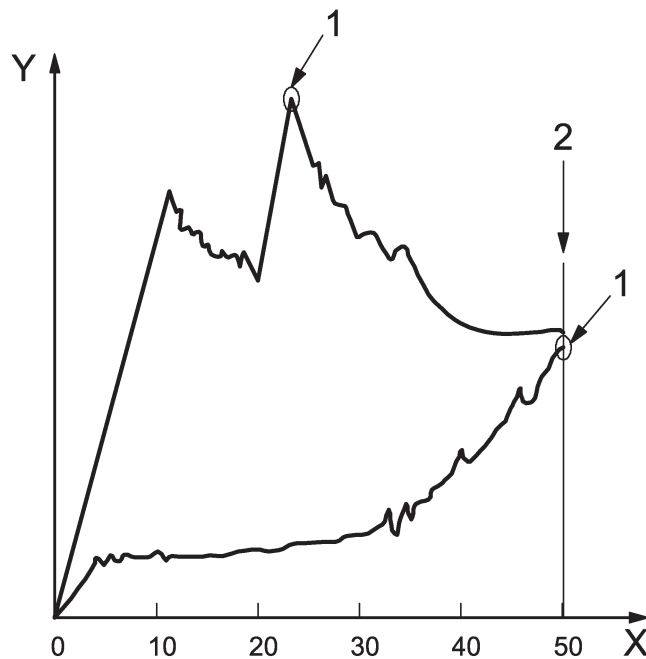

Key

- X contraction, %
- Y load
- 1 1st peak
- 2 2nd peak

Figure 2 — Measurement of crushing strength as explained in Example 2 in the procedure

8 Expression of results

The crushing strength, CS, is the arithmetic mean of all the measurements obtained.

Express the result, in decanewtons per pellet, to one decimal place.

9 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 4700;
- b) all details necessary for the identification of the sample;
- c) the name and address of the test laboratory;
- d) the date of the test;
- e) the date of the test report;
- f) the signature of the person responsible for the test;
- g) the details of any operation and any test conditions not specified in this International Standard or regarded as optional, as well as any incident which may have had an influence on the results;
- h) the crushing strength, CS;
- i) the standard deviation of the measurements;

- j) the size distribution of the sample for physical testing and the size range(s) of the pellets;
- k) a table of the relative frequency, in percent, or the measurements, classified at 50 daN intervals;
- l) the number of pellets in each specified size range tested;
- m) the platen speed used, expressed in mm/min.

10 Verification

Regular checking of the apparatus is essential to ensure test result reliability. The frequency of checking is a matter for each laboratory to determine.

The conditions of the following items shall be checked:

- compressive plates;
- compressive device;
- load cell or lever;
- load indicator;
- recording system;

It is recommended that internal reference material be prepared and used periodically to check test repeatability.

Appropriate records of verification activities shall be maintained.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK



...making excellence a habit.™