

Brown coals and lignites — Determination of moisture content —

**Part 2: Indirect gravimetric method for
moisture in the analysis sample**

ICS 73.040

National foreword

This British Standard was published by BSI. It is the UK implementation of ISO 5068-2:2007.

The UK participation in its preparation was entrusted to Technical Committee PTI/16, Solid mineral fuels.

A list of organizations represented on PTI/16 can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 28 February 2007

© BSI 2007

ISBN 978 0 580 50195 1

Amendments issued since publication

Amd. No.	Date	Comments

INTERNATIONAL
STANDARD

ISO
5068-2

First edition
2007-02-01

**Brown coals and lignites —
Determination of moisture content —**

**Part 2:
Indirect gravimetric method for moisture
in the analysis sample**

Charbons bruns et lignites — Détermination de l'humidité —

*Partie 2: Méthode gravimétrique indirecte pour l'humidité de l'échantillon
d'analyse*



Reference number
ISO 5068-2:2007(E)

Contents

Page

Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Definitions	1
4 Principle	1
5 Reagent.....	1
6 Apparatus	2
7 Sample	4
8 Procedure	4
9 Expression of results	4
10 Precision of method	5
11 Test report	5
Annex A (informative) Nitrogen-purification train.....	6

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 5068-2 was prepared by Technical Committee ISO/TC 27, *Solid mineral fuels*, Subcommittee SC 5, *Methods of analysis*.

This first edition of ISO 5068-2, together with ISO 5068-1, cancels and replaces ISO 5068:1983, which has been technically revised.

ISO 5068 consists of the following parts, under the general title *Brown coals and lignites — Determination of moisture content*:

- *Part 1: Indirect gravimetric method for total moisture*
- *Part 2: Indirect gravimetric method for moisture in the analysis sample*

Brown coals and lignites — Determination of moisture content —

Part 2: Indirect gravimetric method for moisture in the analysis sample

1 Scope

This International Standard specifies a method for the determination of the moisture content in the analysis sample of brown coals and lignites using an indirect gravimetric method.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1213-2, *Solid mineral fuels — Vocabulary — Part 2: Terms relating to sampling, testing and analysis*

ISO 5069-2, *Brown coals and lignites — Principles of sampling — Part 2: Sample preparation for determination of moisture content and for general analysis*

3 Definitions

For the purpose of this document, the definitions given in ISO 1213-2 apply.

4 Principle

A test portion of the general analysis test sample is dried to constant mass at a temperature of 105 °C to 110 °C in an atmosphere of nitrogen. The moisture content of the analysis sample is calculated from the loss in mass of the test portion.

NOTE Brown coals and lignites are hygroscopic and therefore their moisture content varies with change of humidity of the atmosphere. Hence, the moisture content of the analysis sample is determined whenever test portions are weighed out for other analyses sample, for example volatile matter, calorific value, carbon and hydrogen, etc.

5 Reagent

5.1 Desiccant, fresh or freshly regenerated and preferably self-indicating.

Suitable desiccants are magnesium perchlorate and silica gel.

WARNING — Magnesium perchlorate is a strong oxidizing agent. Do not attempt to regenerate the absorbent. Do not permit contact with organic materials or a reducing agent.

5.2 Nitrogen, high-purity, dry, with a maximum oxygen content of 30 $\mu\text{l/l}$.

NOTE Commercial nitrogen of this purity is available. See Annex A for details.


6 Apparatus

6.1 Oven, capable of being controlled at a temperature of 105 °C to 110°C and with the provision for the nitrogen to pass through it at a flow rate of approximately 15 times the oven volume per hour and of lowest practical volume, i.e. minimum free space.

Before using a new oven, carry out a temperature profile through the interior and take care to insert samples only where the temperature is known to be 105° to 110°C.

A suitable oven is illustrated in Figure 1.

Dimensions in millimetres

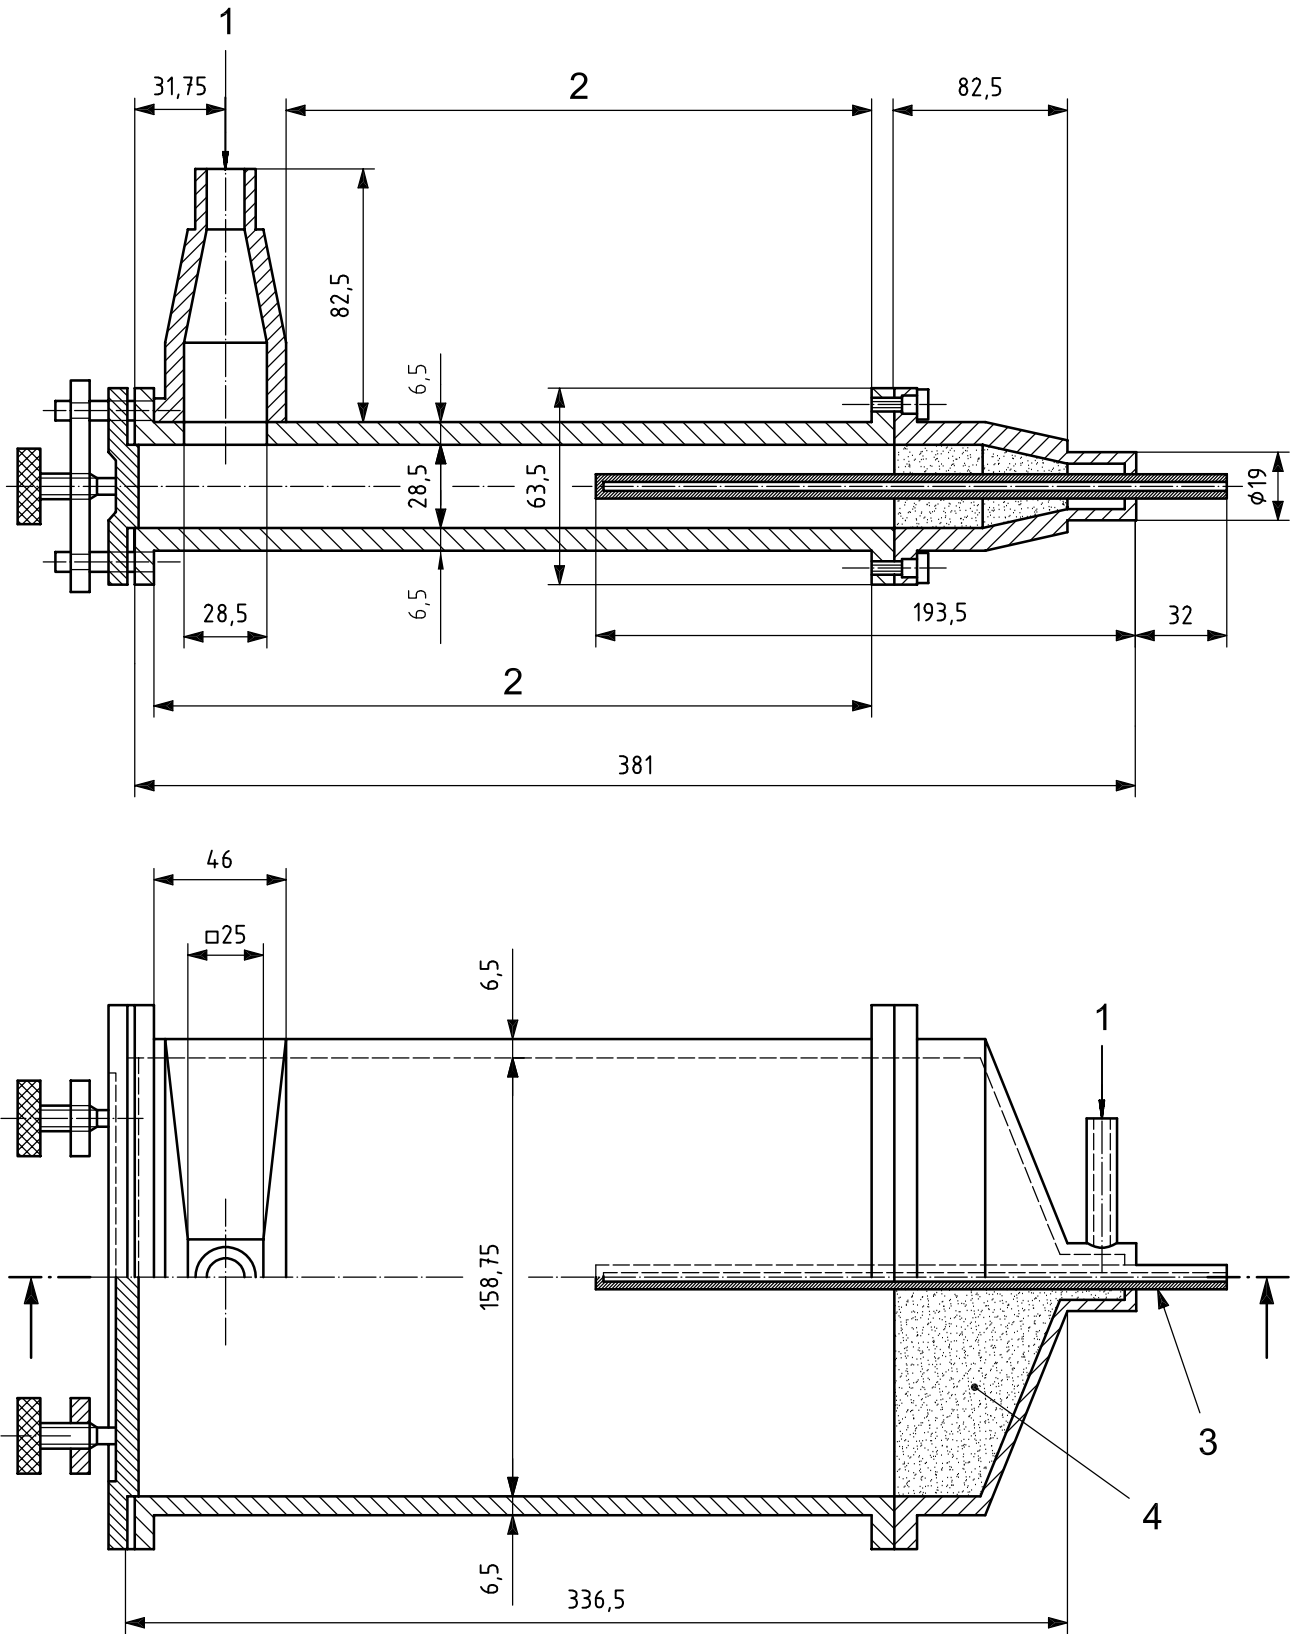

Key

- | | |
|-----------------------------|---|
| 1 nitrogen outlet | 3 thermometer tube |
| 2 space for heating element | 4 copper gauze, having apertures of nominal size 0,25 |

Figure 1 — Typical nitrogen oven

6.2 Weighing dish, a shallow dish, of silica or glass, with ground edges and fitted with a ground-glass cover, or a non-corrodible, heat-resistant material with a well-fitting lid.

The diameter of the dish shall be such that the mass of coal layer does not exceed 0,15 g/cm² for 1 g to 2 g of the analysis sample.

6.3 Balance, sensitive to 0,001 g.

6.4 Flow meter, capable of measuring the rate of flow nitrogen through the oven.

6.5 Drying tower, 250 ml capacity, packed with magnesium perchlorate or silica gel for drying the nitrogen.

6.6 Cooling vessel, for example a desiccator without desiccant, containing a metal plate, preferably of aluminium or copper.

The vessel may be provided with a means to pass dry nitrogen through it during the cooling period.

7 Sample

The analysis sample is prepared in accordance with ISO 5069-2 and generally ground to pass a 0,212 mm sieve.

8 Procedure

Raise the temperature of the oven to between 105 °C and 110 °C while passing nitrogen through it at a rate to provide 15 oven-volume changes per hour.

Weigh a clean, dry, empty weighing dish with its lid to the nearest 0,001 g. Spread into it an even layer of 1 g to 2 g of the analysis sample (Clause 7). Cover and reweigh to the nearest 0,001 g.

Place the uncovered vessel and its lid in the oven for 3 h or until constant mass is obtained.

NOTE The time required to achieve constant mass can be assessed by individual laboratories for each coal rank.

Remove the dish with the dried sample from the oven and replace the cover immediately. If the size of the oven allows this, replace the cover while the dish is still in the oven. Allow the covered dish to cool on a thick metal plate for no longer than 5 min. Transfer the dish to a cooling vessel and allow it to cool to room temperature (approximately 20 min). As soon as the sample reaches room temperature, reweigh to the nearest 0,001 g.

9 Expression of results

9.1 The moisture content, M_{ad} , of the analysis sample, expressed as a mass, is calculated using Equation (1):

$$M_{\text{ad}} = \frac{m_2 - m_3}{m_2 - m_1} \times 100 \quad (1)$$

where

m_1 is the mass of weighing dish and its lid, expressed in grams;

m_2 is the mass of weighing dish, lid and sample before heating, expressed in grams;

m_3 is the mass of weighing dish, lid and sample after heating, expressed in grams.

9.2 Take as the final result of the test the arithmetic mean of the results of duplicate determinations. Report the result to the nearest 0,1 %.

10 Precision of method

10.1 Repeatability limit

The results of duplicate determinations, carried out in the same laboratory by the same operator using the same apparatus on the same sample within short intervals of time, shall not differ by more than 0,3 %.

11 Test report

The test report shall contain the following information:

- a) identification of the sample tested;
- b) reference of the standard used;
- c) result and the method of expression used;
- d) date of the test.

Annex A (informative)

Nitrogen-purification train

It is essential that the nitrogen used for ventilating the minimum-free-space oven should be comparatively pure, since even the small residual amount of oxygen that is found in commercial nitrogen can cause oxidation and hence produce a low result in the moisture figure determined by the loss in mass on drying. A good purification train for nitrogen is, therefore, required. A suitable one is described here, which is capable of dealing with at least 600 ml per minute at a pressure of a few millimetres mercury gauge. A convenient source of the gas is a cylinder of compressed nitrogen. The purification train consists of a quartz tube 500 mm long and with an internal diameter of 37 mm, containing 1,2 kg of reduced copper in wire form. The purification tube is heated by a suitable furnace, which encloses the tube to a length of 380 mm and allows the part of the tube containing the copper wire filing to protrude approximately 80 mm at exit end in order to produce a temperature drop in the gas stream. The reduced copper is heated to approximately 500 °C. The last traces of oxygen are removed by the very large surface area of copper.

If it is necessary to reduce any copper oxide formed during the purification of the nitrogen, this can be done by passing hydrogen through the tube containing the copper, which is heated to 450 °C to 500 °C. During the reduction process, the water formed is expelled to atmosphere. The tube should be purged with nitrogen before use, the reduced copper emptied from the tube and any agglomerated material broken down, and the tube refilled.

Alternatively, a commercial source of nitrogen may be employed in the absence of a purification train, provided that the gas in the cylinder contains not more than 30 µl of oxygen per litre of nitrogen.

In either case, the purified nitrogen shall be passed through a column of magnesium perchlorate (or silica gel) to remove traces of moisture that can be present.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.
Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.