

BS ISO 6621-4:2015



BSI Standards Publication

Internal combustion engines — Piston rings

Part 4: General specifications

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 6621-4:2015. It supersedes BS ISO 6621-4:2003 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee MCE/14/-/10, RIC engines - Cylinders, pistons and rings.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015.
Published by BSI Standards Limited 2015

ISBN 978 0 580 74522 5

ICS 43.060.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2015.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

BS ISO 6621-4:2015

ISO
6621-4

Third edition
2015-03-15

**Internal combustion engines — Piston
rings —**

Part 4:
General specifications

*Moteurs à combustion interne — Segments de piston —
Partie 4: Spécifications générales*



Reference number
ISO 6621-4:2015(E)

© ISO 2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Piston ring codes	1
5 Designation of piston rings	4
5.1 Designation elements and order	4
5.2 Designation examples	5
6 Marking of piston rings	6
6.1 General	6
6.2 Mandatory topside identification marking	6
6.3 Additional marking	7
7 General characteristics	7
7.1 Ring shape	7
7.2 Light tightness	8
7.3 Closed gap	8
7.4 Tangential force, F_t , and diametral force, F_d , of single piece piston rings	8
7.5 Tangential force F_t of multipiece oil control rings as specified in ISO 6626-1, ISO 6626-2, and ISO 6626-3	12
7.6 Tangential force F_t of expander/segment oil control rings as specified in ISO 6627	13
8 Notches for preventing ring rotation	13
8.1 Ring joint with internal notch (only for compression rings as specified in ISO 6622 and ISO 6624)	13
8.2 Ring joint with side notch (only for compression rings as specified in ISO 6622)	15
9 Machining of surfaces	16
9.1 Peripheral surfaces	16
9.2 Side faces	16
9.3 Other surfaces	16
10 Plated, coated, and treated surfaces	17
10.1 Chromium plating on peripheral surfaces	17
10.2 Spray coated peripheral surfaces	20
10.3 Nitrided surfaces	24
10.4 Treated surfaces	25
10.5 Physical vapour deposition coating (PVD)	26
11 Miscellaneous	27
11.1 Cleanliness	27
11.2 Corrosion protection	27
11.3 Packaging	27
12 Traceability (optional)	27
Bibliography	28

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT), see the following URL: Foreword — Supplementary information.

The committee responsible for this document is ISO/TC 22, *Road vehicles*.

This third edition cancels and replaces the second edition (ISO 6621-4:2003), which has been technically revised.

ISO 6621 consists of the following parts, under the general title *Internal combustion engines — Piston rings*:

- *Part 1: Vocabulary*
- *Part 2: Inspection measuring principles*
- *Part 3: Material specifications*
- *Part 4: General specifications*
- *Part 5: Quality requirements*

Introduction

ISO 6621 is one of a series of International Standards dealing with piston rings for reciprocating internal combustion engines. Others are ISO 6622-1, ISO 6622-2, ISO 6623, ISO 6624-1, ISO 6624-2, ISO 6624-3, ISO 6624-4, ISO 6625, ISO 6626-1, ISO 6626-2, ISO 6626-3, and ISO 6627.

Internal combustion engines — Piston rings —

Part 4: General specifications

1 Scope

This part of ISO 6621 specifies the general characteristics of piston rings for reciprocating internal combustion engines for road vehicles and other applications (the individual dimensional criteria for these rings are given in the relevant International Standards). It also provides a system for ring coding, designation, and marking. It is applicable to all such rings of a nominal diameter from 30 mm up to and including 200 mm.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6507-3, *Metallic materials — Vickers hardness test — Part 3: Calibration of reference blocks*

ISO 6621-1, *Internal combustion engines — Piston rings — Part 1: Vocabulary*

ISO 6621-2, *Internal combustion engines — Piston rings — Part 2: Inspection measuring principles*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 6621-1 apply.

4 Piston ring codes

Codes used for piston rings shall be as given in [Table 1](#), corresponding to their explanatory descriptions.

Table 1 — Codes and descriptions in alphabetical order

Code	Description	Relevant International Standard
B	Barrel-faced rectangular ring	ISO 6622-1, ISO 6622-2
BA	Asymmetrical barrel-faced rectangular ring	ISO 6622-1, ISO 6622-2
CR1E ... CR2E	Peripheral surface chromium plated semi-inlaid design	ISO 6621-4
CR1F ... CR2F	Peripheral surface chromium plated inlaid design	ISO 6621-4
CRF ... CR4	Peripheral surface chromium plated fully faced design	ISO 6621-4
CSN, CSG, CSE	Type of coil spring	ISO 6626-1, ISO 6626-2
D	Bevelled edge oil control ring	ISO 6625
D22	Radial wall thickness for “d1/22”	ISO 6622-1, ISO 6623
<p>^a Material mark (for alternative materials) at the discretion of the manufacturer.</p> <p>^b Any other additional marking on customer's request, which shall be quoted clearly in the order, shall be agreed upon between manufacturer and customer.</p>		

Table 1 (continued)

Code	Description	Relevant International Standard
DSF	Coil spring loaded bevelled edge oil control ring	ISO 6626-1, ISO 6626-2
DSF-C	Coil spring loaded bevelled edge oil control ring, chromium plated, and profile ground	ISO 6626-1, ISO 6626-2
DSF-CNP	Coil spring loaded bevelled edge oil control ring, chromium plated, not profile ground	ISO 6626-1
DSF-NG	Coil spring loaded bevelled edge oil control ring (face geometry similar type DSF-C or DSF-CNP)	ISO 6626-1
DV	Bevelled edge V-groove oil control ring	ISO 6625
E	Scraper ring (stepped)	ISO 6623
EM1 ... EM4	Scraper ring (stepped), taper-faced	ISO 6623
ES-1 ... ES-4	Expander/segment oil control rings	ISO 6627
FE	Ferro oxidized on all sides	ISO 6621-4
G	Double bevelled oil control ring	ISO 6625
GSF	Coil spring loaded double bevelled oil control ring	ISO 6626-1, ISO 6626-2
HK	Straight faced half keystone ring 7°	ISO 6624-2, ISO 6624-4
HKB	Barrel faced half keystone ring 7°	ISO 6624-2, ISO 6624-4
HKBA	Asymmetrical barrel-faced half keystone ring	ISO 6624-2, ISO 6624-4
HOL	Openings in oil rings in form of holes	ISO 6626-2
IF	Internal bevel (top side)	ISO 6622, ISO 6624-1, ISO 6624-3
IFU	Internal bevel (bottom side)	ISO 6622
IFV	Variable internal bevel (top side) for defined twist	ISO 6622-1
IFVU	Variable internal bevel (bottom side) for defined twist	ISO 6622-1
IW	Internal step (top side)	ISO 6622-1, ISO 6624-1
IWU	Internal step (bottom side)	ISO 6622-1
K	Straight-faced keystone ring 15°	ISO 6624-1, ISO 6624-3
KA	Peripheral edges chamfered	ISO 6622
KB	Barrel-faced keystone ring 15°	ISO 6624-1, ISO 6624-3
KBA	Asymmetrical barrel-faced keystone ring 15°	ISO 6624-1, ISO 6624-3
KG	Reduced size of peripheral edges at the gap of chromium plated/spray coated/nitrided/PVD coated rings	ISO 6621-4
KI	Inside edges chamfered	ISO 6622
KM1 ... KM5	Taper-faced keystone ring 15°	ISO 6624-1, ISO 6624-3
KU	Reduced peripheral bottom edge chromium plated fully faced design	ISO 6621-4
LF	Uncoated ring peripheral surface or uncoated land peripheral surface, fully lapped	ISO 6621-4
LM	Taper-faced piston ring with partly cylindrical machined peripheral surface	ISO 6621-4

^a Material mark (for alternative materials) at the discretion of the manufacturer.

^b Any other additional marking on customer's request, which shall be quoted clearly in the order, shall be agreed upon between manufacturer and customer.

Table 1 (continued)

Code	Description	Relevant International Standard
LP	Taper-faced piston ring with lapped land over the whole circumference but not over the whole width of the peripheral surface	ISO 6621-4
M1 ...M5	Taper-faced rectangular ring	ISO 6622-1, ISO 6622-2
MC11 ... MC68	Material subclasses	ISO 6621-3
MM	Manufacturer's mark	ISO 6621-4
MR	Reduced ratio $m/(d_1 - a_1)$ for reduced load	ISO 6621-4
MU	Any other additional mark ^b	ISO 6621-4
MX	Material mark ^a	ISO 6621-4
MY	Mark for required ring shape "negative ovality"	ISO 6621-4
MZ	Mark for required ring shape "round"	ISO 6621-4
N	Napier ring (undercut step)	ISO 6623
NB030 ... NB130	Nitrided surface, case depth specified on peripheral surface and bottom side	ISO 6621-4
NE1 ... NE3	Ring joint with lateral stop	ISO 6621-4
NH1 ... NH3	Ring joint with internal stop	ISO 6621-4
NM1 ... NM4	Napier ring (undercut step), taper-faced	ISO 6623
NP030 ... NP130	Nitrided surface, case depth specified on peripheral surface only	ISO 6621-4
NS 010 ... NS 050	Nitrided surface, case depth on segments	ISO 6627
NT030 ... NT130	Nitrided surface, case depth specified on peripheral surface and side faces	ISO 6621-4
NX	Nitrided surface of expanders/spacers	ISO 6627
PC001...PC040	Physical vapour deposition coating (PVD) thickness	ISO 6621-4
PN 10...PN 25	Nominal contact pressure classes	ISO 6626-3
PNE, PNL, PNR, PNM, PNH, PNV	Contact pressure class	ISO 6626-1, ISO 6626-2, ISO 6627
PO	Phosphated on all sides	ISO 6621-4
PR	Phosphated on all sides (for rust protection purposes)	ISO 6621-4
R	Straight-faced rectangular ring	ISO 6622-1, ISO 6622-2
RU	Napier ring with reduced undercut or step	ISO 6623
S	Slotted oil control ring	ISO 6625
S005 ... S100	Closed gap (minimum values)	ISO 6621-4
SC1 ... SC4	Peripheral surface spray coated fully faced design	ISO 6621-4
SC1E ... SC4E	Peripheral surface spray coated semi-inlaid design	ISO 6621-4
SC1F ... SC4F	Peripheral surface spray coated inlaid design	ISO 6621-4
SSF	Coil spring loaded slotted oil control ring	ISO 6626-1, ISO 6626-2
SSF-L	Coil spring loaded slotted oil control ring with 0,6 mm nominal land width	ISO 6626-1, ISO 6626-2

^a Material mark (for alternative materials) at the discretion of the manufacturer.

^b Any other additional marking on customer's request, which shall be quoted clearly in the order, shall be agreed upon between manufacturer and customer.

Table 1 (continued)

Code	Description	Relevant International Standard
T	Straight-faced keystone ring 6°	ISO 6624-1, ISO 6624-3
TB	Barrel-faced keystone ring 6°	ISO 6624-1, ISO 6624-3
TBA	Asymmetrical barrel-faced keystone ring 6°	ISO 6624-1, ISO 6624-3
TM1 ... TM5	Taper-faced keystone ring 6°	ISO 6624-1, ISO 6624-3
TT	Seating tab angle θ	ISO 6627
WF	Reduced heat set	ISO 6621-5, ISO 6626-1, ISO 6626-2
WK	Reduced slot length	ISO 6626-1, ISO 6626-2
WTL	Radial wall thickness (large)	ISO 6626-3
WTS	Radial wall thickness (small)	ISO 6626-3
Y	Ring shape negative ovality	ISO 6621-4
Z	Ring shape round	ISO 6621-4
^a Material mark (for alternative materials) at the discretion of the manufacturer. ^b Any other additional marking on customer's request, which shall be quoted clearly in the order, shall be agreed upon between manufacturer and customer.		

5 Designation of piston rings

5.1 Designation elements and order

5.1.1 General

When designating piston rings complying with the relevant International Standards, the following details shall be provided in the order given, using the codes according to [Table 1](#).

5.1.2 Mandatory elements

The following mandatory elements shall constitute the designation of a piston ring:

- designation (i.e. piston ring);
- number of International Standard;
- type of piston ring (e.g. R);
- hyphen;
- size of piston ring, $d_1 \times h_1$;
- radial wall thickness “regular” without code;
- Code D22 if the selected wall thickness, in accordance with ISO 6622-1 and ISO 6623, is $d_1/22$;
- hyphen;
- material code (e.g. MC11).

5.1.3 Additional elements

The following optional elements may be added to the designation of a piston ring and, if so added, shall be positioned on a second line beneath or separated by a slash (/) from the mandatory elements given in [5.1.2](#):

- reduced ratio $m/(d_1 - a_1)$, MR;
- ring shape (e.g. Z);
- selected nominal closed gap if it differs from the closed gap specified in the dimension tables (e.g. S05);
- the selected coating (e.g. CR3);
- uncoated rings with fully lapped peripheral surface [e.g. for LF taper faced rings with partly cylindrical peripheral surface, LM (machined), or LP (lapped)];
- selected surface treatment (e.g. PO);
- selected inside edge feature (e.g. KA);
- inside step of bevel (e.g. IWU);
- selected notch to prevent ring rotation (e.g. NH1);
- reduced slot length, if required (e.g. WK);
- coil spring with reduced heat set, if required, (e.g. WF);
- selected type of coil spring, (e.g. CSG);
- selected pressure class (e.g. PNM).

5.1.4 Elements for additional marking

Any additional marking shall be the following with the additional elements of [5.1.3](#):

- manufacturer's mark, if required (e.g. MM);
- marking of required ring shape (e.g. MZ);
- material, MX (see [Table 1](#), Footnote a);
- code for any other marking, MU (see [Table 1](#), Footnote b).

5.2 Designation examples

5.2.1 Designation example of a piston ring in accordance with ISO 6622-1

For a straight-faced rectangular ring (R) of nominal diameter $d_1 = 90$ mm (90) and nominal ring width $h_1 = 2,5$ mm (2,5), made of grey cast iron, non heat treated material subclass 11 (MC11):

Piston ring ISO 6622-1 R - 90 × 2,5 - MC11.

Parameters in parentheses are used in the ISO ring designation.

5.2.2 Designation example of a piston ring in accordance with ISO 6624-1

For a keystone ring 6° , taper faced $60'$ (TM3) of nominal diameter $d_1 = 105$ mm (105) and nominal ring width $h_1 = 2,5$ mm (2,5) made of spheroidal graphite cast iron, martensitic type, material subclass 51

(MC51), ring shape round (Z) with a selected closed gap of 0,3 mm (S030), inside edges chamfered (KI), and peripheral surface chromium plated, with plating thickness 0,1 mm minimum (CR2):

Piston ring ISO 6624-1 TM3 – 105 × 2,5 – MC51 / Z S030 KI CR2

Parameters in parentheses are used in the ISO ring designation.

5.2.3 Designation example of a piston ring in accordance with ISO 6626-1

For a coil spring loaded, bevelled edge oil control ring, chromium plated and profile ground (DSF-C), with nominal diameter $d_1 = 125$ mm (125) and nominal ring width $h_1 = 5$ mm (5) made of grey cast iron, non heat treated, material subclass 11 (MC11) with a selected closed gap of 0,2 mm (S020) having a chromium plating thickness on the lands of 0,15 mm minimum (CR3), phosphated on all cast iron surfaces to a depth of 0,002 mm minimum (PO) with reduced slot length (WK), a coil spring with reduced heat set (WF) having a variable pitch with coil diameter, d_7 ground (CSE), tangential force, F_t , according to the medium nominal contact pressure class (PNM) marked with manufacturer's mark (MM):

Piston ring ISO 6626-1 DSF-C – 125 × 5 – MC11 / S020 CR3 PO WK WF CSE PNM MM

Parameters in parentheses are used in the ISO ring designation.

6 Marking of piston rings

6.1 General

The requirements and recommendations for piston ring marking according to [6.2](#) and [6.3](#) apply to piston rings of 1,6 mm radial wall thickness and above. Marking of piston rings of less than 1,6 mm is at the discretion of the manufacturer.

6.2 Mandatory topside identification marking

All rings requiring orientation shall be marked to indicate the top side only (i.e. the side nearest the combustion chamber).

In the absence of any other mark agreed upon between manufacturer and customer, the mark "TOP" should be used.

Marking of the top side applies to *all* the following types of ring:

- taper faced rings;
- asymmetrical barrel-faced rings;
- rings with reduced peripheral bottom edge;
- internally bevelled or stepped rings;
- semi-inlaid rings;
- scraper rings;
- half keystone rings;
- directional oil control rings.

All such rings requiring marking are specified in the relevant International Standards (see Foreword and Bibliography).

6.3 Additional marking

6.3.1 Additional marking of piston rings is optional or at the customer's request. Such additional marking may comprise of the following:

- manufacturer's mark;
- mark for required ring shape;
- oversize rings;
- material mark (for alternative materials);
- any other additional mark agreed upon between manufacturer and customer.

6.3.2 Colour marking on the running surface is in common use. Colour marking may be used to identify the following:

- assembling orientation;
- groove assignment;
- oversize diameters;
- supplier identification;
- engine identification.

The choice of colour and acceptance conditions may be agreed upon between ring manufacturer and customer.

7 General characteristics

7.1 Ring shape

Degrees of ovality only apply to rectangular rings,[1] [2] scraper rings,[3] and keystone rings.[4] [5] [6] [7] The following are forms of ovality:

- positive ovality, without code;
- round, Code Z;
- negative ovality, Code Y.

Values are given in [Table 2](#).

Table 2 — Ovality

Dimensions in millimetres

Nominal diameter d_1	Positive ovality	Round ^a Code: Z	Negative ovality ^b Code: Y
$30 \leq d_1 < 60$	0 ... +0,60	-0,30 ... +0,30	-0,60 ... 0
$60 \leq d_1 < 100$	+0,05 ... +0,85	-0,35 ... +0,35	-0,70 ... 0
$100 \leq d_1 < 150$	+0,10 ... +1,10	-0,45 ... +0,45	-0,95 ... -0,05
$150 \leq d_1 \leq 200$	+0,15 ... +1,35	-0,50 ... +0,50	-1,10 ... -0,10

^a For taper-faced coated and uncoated rings with lapped land, the recommended ring shape is round.

^b Not applicable for material Class 10 of ISO 6621-3.

7.2 Light tightness

At least 90 % of the circumference of the piston ring peripheral surface shall be light-tight.

At least 95 % of the circumference on the peripheral surface of a taper-faced ring with plated/coated or nitrided and ground peripheral surface shall be light-tight.

100 % of the circumference on the peripheral surface of the following piston ring designs shall be light-tight:

- piston rings with machined land over the whole circumference of the peripheral surface;
- taper-faced piston rings with machined land over the whole circumference of the peripheral surface.

In the case of piston rings with a treated surface, the light tightness is normally measured prior to surface treatment. When it is checked after treatment, rotation of the ring in the gauge will be required. In the case of rings with negative point deflection, visible light is permitted at the butt ends but should be confined to the angle θ as defined in ISO 6621-2.

7.3 Closed gap

Whenever the selected closed gap differs from that given in the dimensional tables of the relevant International Standard, [Table 3](#) shall apply and the tolerances shall remain the same.

Table 3 — Closed gap

Dimensions in millimetres

Code	S005	S010	S015	S020	S025	S030	S035	S040	S045	S050	S055	S060	S070	S080	S090	S100
Closed gap	0,05	0,10	0,15	0,20	0,25	0,30	0,35	0,40	0,45	0,50	0,55	0,60	0,70	0,80	0,90	1,00

7.4 Tangential force, F_t , and diametral force, F_d , of single piece piston rings

NOTE The individual types of piston rings are given in Reference [1] to Reference [8]. The definitions of F_t and F_d are given in ISO 6621-2.

7.4.1 Calculation of F_t and F_d values in dimension tables of dimensional standards

The tangential and diametral forces of piston rings are tabulated in the dimension tables of the dimensional standards.

The values are calculated for the following:

- the basic feature of each piston ring type;
- nominal radial wall thickness a_1 , and mean ring width h_1 or h_3 ;
- piston rings made of cast iron with a modulus of elasticity of 100 GN/m² (100 GN/m² = 100 000 MPa = 100 000 N/mm²);
- piston rings made of steel with a modulus of elasticity of 210 GN/m²;
- ratio of total free gap to nominal diameter [$m/(d_1 - a_1)$], according to [Table 4](#).

NOTE The calculation of tangential forces and diametral forces of rectangular rings made of steel (ISO 6622-2) is based on a theoretical contact pressure of $0,16 \pm 0,01$ N/mm². The calculation of tangential forces and diametral forces of keystone rings (ISO 6624-3) and half keystone rings (ISO 6624-4) made of steel is based on the same ratio $m/(d_1 - a_1)$ used for rectangular rings (ISO 6622-2). The ratio $m/(d_1 - a_1)$ for rings made of steel is quite different from the values given in [Table 5](#) for rings made of cast iron and depends on the nominal diameter and the special radial wall thickness. This radial wall thickness is not in a constant ratio to nominal diameter because there are steps of wall thickness which belong to a range of nominal diameters (e.g. $a_1 = 2,1$ mm for $d_1 = 57 \dots 61$ mm).

7.4.2 Correction of F_t and F_d values

7.4.2.1 General

The F_t and F_d values shall be corrected whenever the following are being used:

- a) additional features such as rings with
 - coated peripheral surface, and/or
 - inside chamfered edges, and/or
 - outside chamfered edges, and/or
 - taper, and/or
 - internal step or internal bevel;
- b) piston ring materials with a modulus of elasticity other than 100 GN/m²;
- c) ratio of total free gap to nominal diameter [$m/(d_1 - a_1)$] other than that given in [Table 4](#).

The values for the regular ratio of free gap to nominal diameter $m/(d_1 - a_1)$ regular are given in [Table 4](#).

Table 4 — Regular ratio of total free gap to nominal diameter

Dimensions in millimetres

Nominal diameter d_1	$m/(d_1 - a_1)$	
	Cast iron	Steel ^a
$30 \leq d_1 < 60$	0,15	0,10 ... 0,14
$60 \leq d_1 < 100$		
$100 \leq d_1 < 160$	0,17 to 0,000 2 d_1	0,11 ... 0,13
$160 \leq d_1 \leq 200$		
^a Variation of $m/(d_1 - a_1)$ depends on contact pressure and radial wall thickness.		

7.4.2.2 Multiplier factors for common features

For common features, the necessary multiplier correction factors are tabulated in the dimensional standards Reference [1] to Reference [8], under “Force factors”.

7.4.2.3 Multiplier force correction factors for materials

For materials specified in ISO 6621-3, the force correction factors given in [Table 5](#) should be used.

Table 5 — Material force correction factors

Material class	Material force correction factor
10	0,9 to 1 ^a
20	1,1 to 1,3 ^a
^a Force correction factors for material depend on the modulus of elasticity in the manufacturer's material specification: Correction factor = $\frac{\text{Typical modulus of elasticity in GN/m}^2}{100 \text{ GN/m}^2}$.	

Table 5 (continued)

Material class	Material force correction factor
30	1,45
40	1,6
50	1,6
<p>^a Force correction factors for material depend on the modulus of elasticity in the manufacturer's material specification:</p> $\text{Correction factor} = \frac{\text{Typical modulus of elasticity in GN/m}^2}{100 \text{ GN/m}^2} .$	

7.4.2.4 Multiplier force correction factors for ratio $m/(d_1 - a_1)$

Piston rings made of materials in Class 30 to Class 50 increase the tangential force and diametral force in relationship to the modulus of elasticity (see [Table 5](#)) when ratio $m/(d_1 - a_1)$ regular is used.

For limitation of such increased forces, it is common to use reduced values of $m/(d_1 - a_1)$. See [Table 6](#) for the recommended correction factors $m/(d_1 - a_1)$ regular and $m/(d_1 - a_1)$ reduced.

Table 6 — Force correction factors for ratio $m/(d_1 - a_1)$

Material class	Factor	
	$m/(d_1 - a_1)$ regular	$m/(d_1 - a_1)$ reduced Code: MR
10	1	—
20	1	—
30	1	0,825
40	1	0,75
50	1	0,75
<p>NOTE For the calculation of the real force correction values, the correction factor for the material given in Table 5 shall be applied first, and then the correction factor of Table 6 shall be applied.</p>		

7.4.3 Examples for correction of F_t and F_d

7.4.3.1 First example — Selected piston ring type: ISO 6622-1 B - 95 × 2,5 - MC53 / MR CR2 IW

7.4.3.1.1 Multiplying factors

- 1,6 for material Subclass 53
- 0,75 for ratio $m/(d_1 - a_1)$ reduced
- 0,88 for peripheral surface chromium plated CR2
- 0,78 for internal step IW

7.4.3.1.2 Calculation

Total force correction factors: $1,6 \times 0,75 \times 0,88 \times 0,78 = 0,824$.

Basic values F_t and F_d according to ISO 6622-1: $F_t = 18,5$ N and $F_d = 39,8$ N.

Corrected values: $F_t = 0,824 \times 18,5 \text{ N} \pm 20 \%$ and $F_d = 0,824 \text{ N} \times 39,8 \text{ N} \pm 20 \%$;

$$F_t = 15,2 \text{ N} \pm 20 \text{ and } F_d = 32,8 \text{ N} \pm 20 \%$$

$$F_t = 12,2 \text{ N} \dots 18,2 \text{ N} \text{ and } F_d = 26,2 \text{ N} \dots 39,4 \text{ N}.$$

7.4.3.2 Second example — Selected piston ring type: ISO 6623 N – 70 × 2 D22 – MC24 / SC2F

7.4.3.2.1 Multiplying factors

- 1,15 for material subclass 24
- 1 for ratio $m/(d_1 - a_1)$ regular
- 0,9 for peripheral surface spray coated SC2F (inlaid type)

7.4.3.2.2 Calculation

Total force correction factor: $1,15 \times 1 \times 0,9 = 1,035$.

Basic values F_t and F_d according to ISO 6623: $F_t = 9,3 \text{ N}$ and $F_d = 20,0 \text{ N}$.

Corrected values: $F_t = 1,035 \text{ N} \times 9,3 \text{ N} \pm 30 \%$ and $F_d = 1,035 \text{ N} \times 20,0 \text{ N} \pm 30 \%$;

$$F_t = 9,6 \text{ N} \pm 30 \% \text{ and } F_d = 20,7 \text{ N} \pm 30 \%;$$

$$F_t = 6,7 \text{ N} \dots 12,5 \text{ N} \text{ and } F_d = 14,5 \text{ N} \dots 26,9 \text{ N}.$$

7.4.3.3 Third example — Selected piston ring type: ISO 6624-1 KB – 140 × 4 – MC42 / SC4 KI

7.4.3.3.1 Multiplying factors

- 1,6 for material subclass 42
- 0,85 for peripheral surface spray coated SC4 (fully faced type)
- 0,96 for inside chamfered edges KI

7.4.3.3.2 Calculation

Total force correction factor: $1,6 \times 0,85 \times 0,96 = 1,306$.

Basic values F_t and F_d according to ISO 6624-1: $F_t = 29,3 \text{ N}$ and $F_d = 63 \text{ N}$.

Corrected values: $F_t = 1,306 \times 29,3 \text{ N} \pm 20 \%$ and $F_d = 1,306 \times 63 \text{ N} \pm 20 \%$;

$$F_t = 38,3 \text{ N} \pm 20 \% \text{ and } F_d = 82,3 \text{ N} \pm 20 \%;$$

$$F_t = 30,6 \text{ N} \dots 46,0 \text{ N} \text{ and } F_d = 65,8 \text{ N} \dots 98,8 \text{ N}.$$

7.4.3.4 Fourth example — Selected piston ring type: ISO 6625 G – 120 × 5 – MC11 / KI

7.4.3.4.1 Multiplying factors

- 0,9 for material subclass 11
- 0,98 for inside chamfered edges, KI

7.4.3.4.2 Calculation

Total force correction factor: $0,9 \times 0,98 = 0,882$.

Basic values F_t and F_d according to ISO 6625: $F_t = 24,7$ N and $F_d = 53,1$ N.

Corrected values: $F_t = 0,882 \times 24,7$ N ± 20 % and $F_d = 0,882 \times 53,1$ N ± 20 %;

$$F_t = 21,8$$
 N ± 20 % and $F_d = 46,8$ N ± 20 %;

$$F_t = 17,4$$
 N ... 26,2 N and $F_d = 37,4$ N ... 56,2 N.

7.5 Tangential force F_t of multipiece oil control rings as specified in ISO 6626-1, ISO 6626-2, and ISO 6626-3

7.5.1 General

The tangential force of a coil spring loaded oil control ring depends on the following:

- piston ring type;
- class of nominal contact pressure;
- specific tangential force F_{tc} for unit contact pressure of forces, tabulated in ISO 6626-1 and ISO 6626-2.

NOTE The formula for calculating the actual tangential force is also given in ISO 6626-1 and ISO 6626-2.

7.5.2 Rounding of values

Actual values of tangential force should be rounded up or down as follows:

- $F_t < 50$ N, to the nearest 0,5 N;
- $F_t > 50$ N, to the nearest 1 N, where 0,5 N is rounded up.

7.5.3 Examples for calculating tangential force F_t

7.5.3.1 First example — Selected piston ring type: ISO 6626-1 DSF-C - 100 × 4 - MC11/CR1 CSG PNM

7.5.3.1.1 Pressure class and specific tangential force

Class of nominal contact pressure: PNM = 1,49 N/mm².

Specific tangential force for unit contact pressure of 1 N/mm²: $F_{tc} = 40,4$ N.

7.5.3.1.2 Calculation

Tangential force: $F_t = 1,49$ N $\times 40,4$ N ± 20 %;

$$F_t = 60,2$$
 N ± 20 %;

$$F_t = 48$$
 N ... 72 N.

7.5.3.2 Second example — Selected type of piston ring: ISO 6626-1 SSF - 175 × 6 - MC11/CSG PNE

7.5.3.2.1 Pressure class and specific tangential force

Class of nominal contact pressure: $PNE = 0,59 \text{ N/mm}^2$.

Specific tangential force for unit contact pressure of 1 N/mm^2 : $F_{tc} = 192,5 \text{ N}$.

7.5.3.2.2 Calculation

Tangential force: $F_t = 0,59 \times 192,5 \text{ N} \pm 20 \%$;

$$F_t = 113,6 \text{ N} \pm 20 \%$$

$$F_t = 91 \text{ N} \dots 136 \text{ N}.$$

7.6 Tangential force F_t of expander/segment oil control rings as specified in ISO 6627

7.6.1 General

The tangential force of an expander/segment oil control ring depends on the following:

- nominal contact pressure, p_o ;
- segment width h_{12} ;
- specific tangential force F_{tc} for a unit contact pressure of 1 N/mm^2 .

The values for nominal contact pressure and specific tangential forces are tabulated in ISO 6627.

7.6.2 Example for calculating the tangential force F_t — Selected type of piston ring: ISO 6627 - ES3 - 85 × 3 - MC67 MC68/CR1 PNH

7.6.2.1 Pressure class and specific tangential force

Class of nominal contact pressure: $p_o = 1,2 \text{ N/mm}^2$; multiplying factor = 1,2.

Specific tangential force F_{tc} for unit contact pressure of $p_{ou} = 1 \text{ N/mm}^2$ and segment width 0,45 (e.g. $F_{tc} = 38,2$).

7.6.2.2 Calculation

Tangential force: $F_t = 1,2 \times 38,2 \text{ N} \pm 20 \%$;

$$F_t = 45,8 \text{ N} \pm 20 \%$$

$$F_t = 36,5 \text{ N} \dots 55 \text{ N}.$$

8 Notches for preventing ring rotation

8.1 Ring joint with internal notch (only for compression rings as specified in ISO 6622 and ISO 6624)

See [Figure 1](#), [Figure 2](#), [Table 7](#), and [Table 8](#).

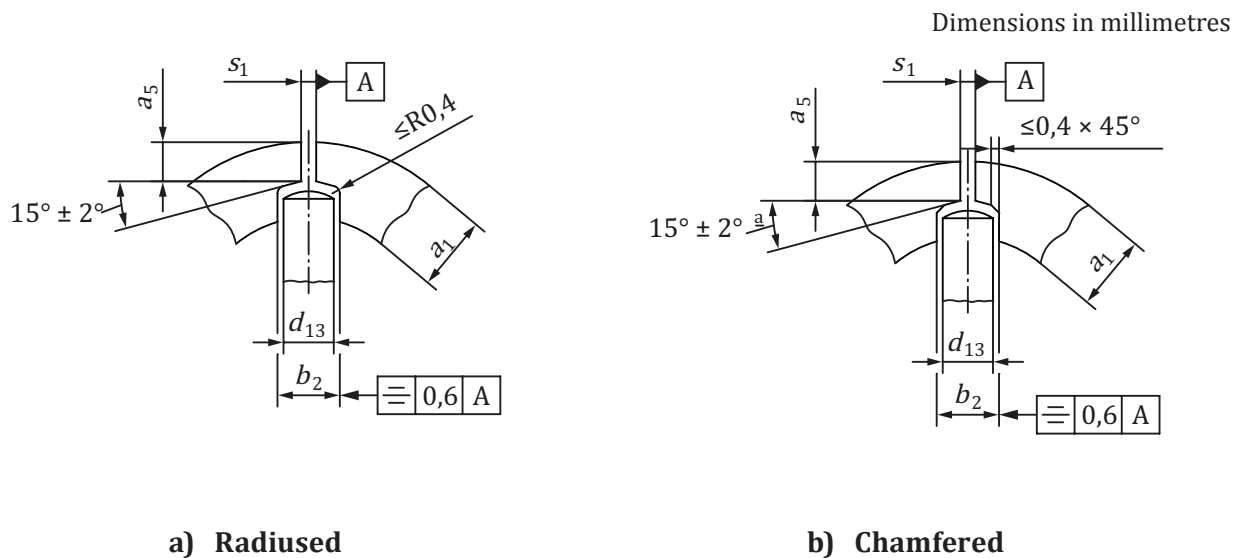


Figure 1 — Internal notch

Table 7 — Dimensions of internal notch

Dimensions in millimetres

Code	Pin diameter d_{13}	Notch ^a			
		b_2	tol.	r_6 ^b	tol.
NH1	1,5	2	+0,2 -0,1	0,8	±0,1
NH2	2	2,5		0,9	
NH3	2,5	3		1	

^a $b_2 - d_{13} > s_1$ nom.
^b r_6 applies only to notch design according to [Figure 2](#).

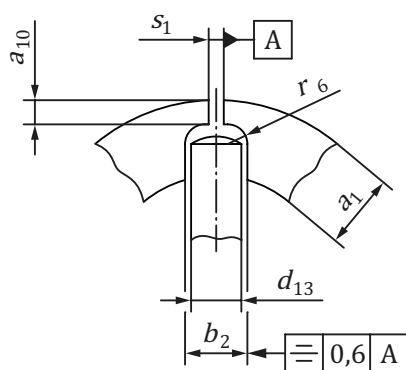


Figure 2 — Internal notch: Option for piston rings with radial wall thickness $a_1 > 2,1$

Table 8 — Width of overlap a_5 and optional a_{10} for internal notch

Dimensions in millimetres

Radial wall thickness a_1	Overlap			
	a_5	tol.	a_{10}	tol.
$1,5 \leq a_1 < 2,1$	0,6	±0,1	—	±0,1
$2,1 \leq a_1 < 2,7$	0,7		0,6	
$2,7 \leq a_1 < 3,1$	1		0,7	
$3,1 \leq a_1 < 3,5$	1,2		0,8	
$3,5 \leq a_1 < 3,9$	1,4		0,9	
$3,9 \leq a_1 < 4,1$	1,6		1	

8.2 Ring joint with side notch (only for compression rings as specified in ISO 6622)

See [Figure 3](#) and [Table 9](#).

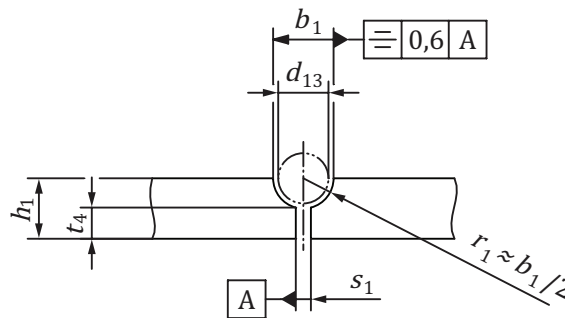


Figure 3 — Side notch

Table 9 — Dimensions of side notch

Dimensions in millimetres

Code	Ring width	Pin diameter	Notch ^a				
	h_1		d_{13}	b_1	tol.	t_4	tol.
NE1	1,2 ^b	1,5	2			0,5	
	1,5					0,7	
	1,75					0,95	
	2					1,2	
	2,5					1,7	
NE2	1,5	2	2,3	+0,2 -0,1		0,7	0 -0,15
	2		2,5			0,9	
	2,5		2,5			1,4	
	3		2,5			1,9	
NE3	2,5	2,5	3			1	
	3	2,5	3			1,5	

^a $b_1 - d_{13} > s_1$ nom.
^b Not applicable for material Class 10 according to ISO 6621-3.

9 Machining of surfaces

9.1 Peripheral surfaces

Standard machined: no code required. See [Table 10](#).

Table 10 — Standard machined peripheral surfaces

Ring Type	Ring description	Standard machining methods of peripheral surfaces
All Types	All unplated/uncoated rings made of cast iron	Fine turned
R; B; BA; BM; BAM; N; E; T; TB; TBA; K; KB; KBA HK; HKB; HKBA	Plated/spray coated peripheral surface Straight or barrel faced On rectangular, napier/scrapper, or keystone rings Made of cast iron or steel	Machined (i.e. ground, lapped, or polished) over full face
R; B; BA; BM; BAM; T; TB; TBA; K; KB; KBA; HK; HKB; HKBA	Nitrided peripheral surface on straight or barrel faced rectangular or keystone rings made of steel	Machined (i.e. ground, lapped, or polished) over full face
M; NM, EM; TM; KM	Plated/spray coated or nitrided peripheral surface on taper faced rings made of cast iron or steel	Witness machined (i.e. ground, lapped, or polished) on part of the width of the peripheral surface only
ES1 ... ES4	Plated or nitrided peripheral surfaces on segments for expander/segment oil control rings made of steel	Machined (= lapped) over part of the width Or machined (= polished) over full face of the peripheral surface
DSF-C; DSF-CNP	Plated lands on oil control rings made of cast iron	Machined (i.e. ground, lapped, or polished) over full face
NOTE Roughness values and measurement method may be agreed upon between manufacturer and customer as there is no standard method available which is applicable in all cases.		

9.2 Side faces

The standard method of machining is by grinding of side faces: no code required.

The standard side face finish is Rz 4 or Ra 0,8, and for steel nitrided, Rz 3,2 or Ra 0,6

In the case of piston rings with treated surfaces (FE, PO, PR), the roughness shall be measured before surface treatment.

Segments for expander/segment oil control rings made of steel are without machining.

9.3 Other surfaces

See [Table 11](#).

Table 11 — Standard machined other surfaces

Surface description	Standard machining methods
Inside surface: rings made of cast iron rings made of steel	Turned Without machining
Gap faces	Ground or milled
Oil control rings OD profile	Turned or ground (DSF-C)
Coil spring	Ground or without machining
Expander	Without machining
Other surfaces	Turned, ground, or milled
NOTE Roughness values and measurement method may be agreed upon between manufacturer and customer as there is no standard method available which is applicable in all cases.	

10 Plated, coated, and treated surfaces

10.1 Chromium plating on peripheral surfaces

10.1.1 General

Codes are required for chromium plated surfaces as specified in the dimensional standards.

10.1.2 Chromium plating thickness

See [Table 12](#).

Table 12 — Chromium plating thickness

Dimensions in millimetres

Code	Thickness min	Tolerance guideline ^a	
		$d_1 < 160$	$160 \leq d_1 \leq 200$
CRF	0,005	—	—
CR1/CR1E/CR1F	0,05	+0,15 0	+0,2 0
CR2/CR2E/CR2F	0,1		
CR3	0,15		
CR4	0,2		
^a Usually, a minimum specification does not call for tolerances. If a tolerance is required on the plating thickness, this guideline is recommended.			

10.1.3 Chromium plated rings of fully faced design


Code: CRF ... CR4.

Piston rings with plated peripheral surfaces are normally designed fully faced.

10.1.4 Chromium plated rings of semi-inlaid design

Code: CR1E ... CR2E.

See [Figure 4](#) and [Table 13](#).

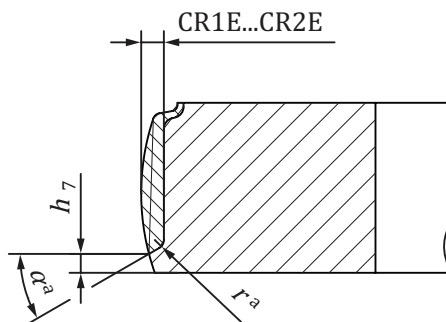

a At the manufacturer's discretion.

Figure 4 — Chromium plated ring semi-inlaid

Table 13 — Land dimensions h_7 of peripheral edges for chromium plated rings semi-inlaid


Dimensions in millimetres

Ring width h_1	Land dimension h_7	
	MC 10, 20, 30	MC 40, 50, 60
≤ 2	0,15 ... 0,45	0,1 ... 0,4
$2 < h_1 < 3,5$	0,15 ... 0,5	0,1 ... 0,45
$3,5 \leq h_1 \leq 4,5$	0,15 ... 0,55	0,1 ... 0,5

10.1.5 Chromium plated rings of inlaid design

Code: CR1F ... CR2F.

See [Figure 5](#) and [Table 14](#).

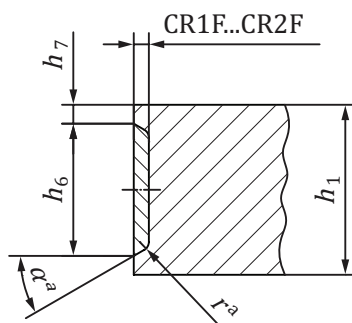

a At the manufacturer's discretion.

Figure 5 — Chromium plated ring inlaid

Table 14 — Dimensions of groove and land of peripheral edges for chromium plated rings

Dimensions in millimetres

Ring width h_1	Groove dimension h_6 min.	Land dimension h_7	
		MC 10, 20, 30	MC 40, 50, 60
2	1,3	0,15 ... 0,45	0,1 ... 0,4
2,5	1,7	0,15 ... 0,5	0,1 ... 0,45
3	2,2		
3,5	2,5	0,15 ... 0,55	0,1 ... 0,5
4	3		
4,5	3,5		

10.1.6 RADIUSING, chamfering, and dimensions of peripheral edges of chromium plated rings

NOTE Values do not apply to chromium plated oil control rings and segments.

Rings of Code CRF to CR4, both peripheral edges, and rings of Code CR1E to CR2E, the upper peripheral edge, may be radiused or chamfered before plating.

See [Figure 6](#) to [Figure 8](#) and [Table 15](#).

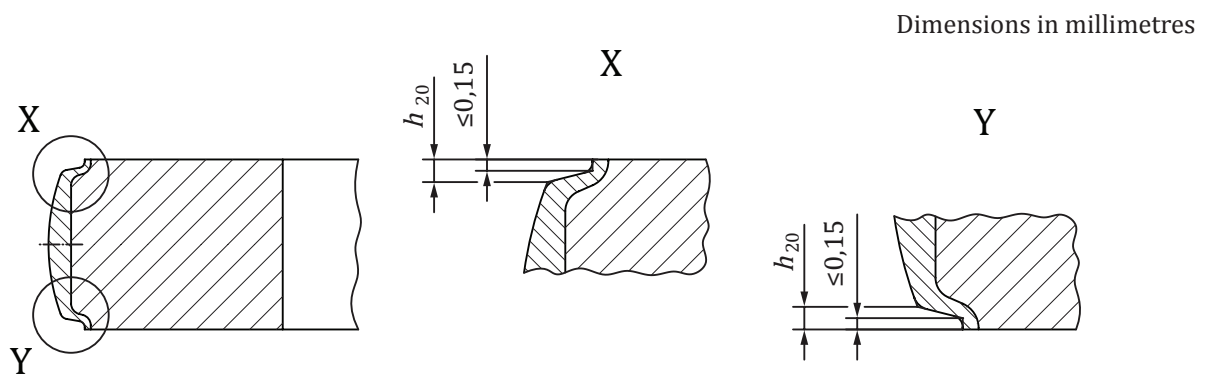


Figure 6 — Chromium plated ring fully faced

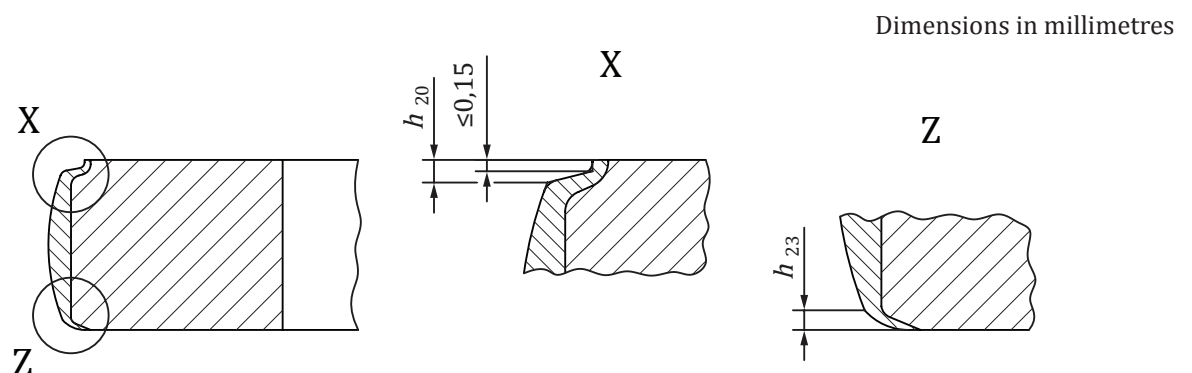


Figure 7 — Chromium plated ring fully faced, reduced peripheral bottom edge — Code: KU

Dimensions in millimetres

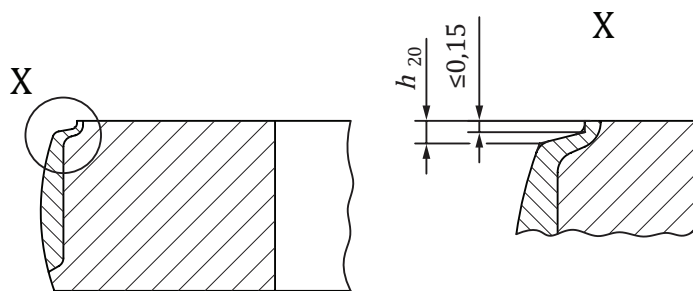


Figure 8 — Chromium plated ring semi-inlaid

Table 15 — Axial dimensions, h_{20} and h_{23} (acc. code KU) of peripheral edges of chromium plated rings

Dimensions in millimetres

Ring width h_1	Axial dimension	
	h_{20} max.	h_{23} max.
$1,0 \leq h_1 < 3,5$	0,3	0,2
$3,5 \leq h_1 \leq 4,5$	0,4	0,3

10.1.7 Peripheral edges at the gap of chromium plated rings and segments

After plating, the peripheral edges at the gap shall be radiused or chamfered. See [Table 16](#).

Table 16 — Circumferential dimensions of peripheral edges at gap of chromium plated rings and segments

Dimensions in millimetres

Ring width h_1, h_{12}	Circumferential dimension	
	s_3 max.	reduced s_3 (Code: KG) max.
<6	0,4	0,15
≥ 6	0,6	0,25

10.1.8 Hardness of chromium plating

The hardness of chromium plating shall be 800 HV 0,1 minimum, in accordance with ISO 6507-3.

10.2 Spray coated peripheral surfaces

10.2.1 Codes

Codes are required for spray-coated surfaces as specified in the dimensional standards.

10.2.2 Spray coating thickness

See [10.2.8](#) and [Table 17](#).

10.2.3 Spray-coated rings of fully faced design

Code: SC1 to SC4.

10.2.4 Spray coated rings of semi-inlaid design

Code: SC1E to SC4E.

See [Figure 9](#).


The dimensions of the land at the bottom of the peripheral edge for spray coated rings of semi-inlaid design shall be those given for h_7 in [Table 18](#).

Table 17 — Spray coating thickness

Dimensions in millimetres

Code	Thickness min.	Tolerance guideline ^a	
		$d_1 < 160$	$160 \leq d_1 \leq 200$
SC1/SC1E/SC1F	0,05	+0,2 0	+0,25 0
SC2/SC2E/SC2F	0,1		
SC3/SC3E/SC3F	0,15		
SC4/SC4E/SC4F	0,2		

^a Usually, minimum specification does not call for tolerances. If a tolerance is required on the coating thickness, this guideline is recommended.

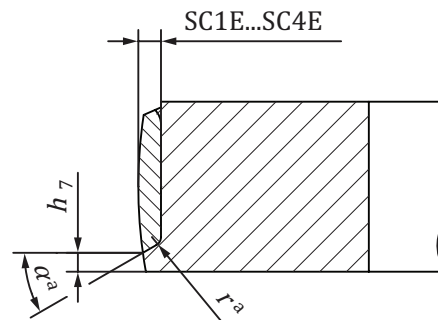


^a At the manufacturer's discretion.

Figure 9 — Spray coated ring semi-inlaid

10.2.5 Spray-coated rings of inlaid design

Code: SC1F to SC4F.

See [Figure 10](#) and [Table 18](#).

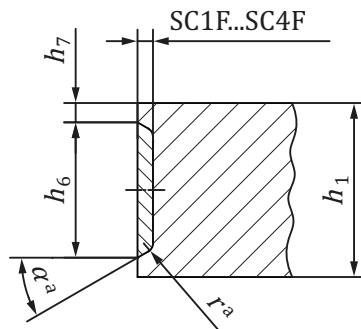

^a At the manufacturer's discretion.

Figure 10 — Spray coated ring inlaid design

Table 18 — Dimensions of groove and land of peripheral edges for spray-coated rings


Dimensions in millimetres

Ring width h_1	Groove dimension h_6 min.	Land dimension h_7	
		MC 10, 20, 30	40, 50, 60
1,2	0,6	0,15 ... 0,45	0,1 ... 0,4
1,5	0,8		
1,75	1,05		
2	1,3		
2,5	1,7	0,15 ... 0,5	0,1 ... 0,45
3	2,2		
3,5	2,5		
4	3	0,15 ... 0,55	0,1 ... 0,5
4,5	3,5		

10.2.6 RADIUSING, CHAMFERING OF PERIPHERAL EDGES OF SPRAY-COATED RINGS

Rings of Codes SC1 to SC4, both peripheral edges, and rings of Codes SC1E to SC4E, the upper peripheral edge, may be radiused or chamfered at the choice of the manufacturer. See [Figure 11](#), [Figure 12](#), and [Table 19](#).


Dimensions in millimetres

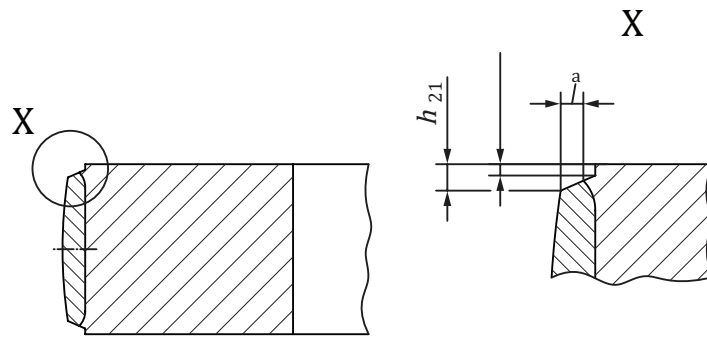

a ≥ 50 % of minimum layer thickness.

Figure 11 — Spray-coated ring of fully faced design — Codes SC1 to SC4

Dimensions in millimetres

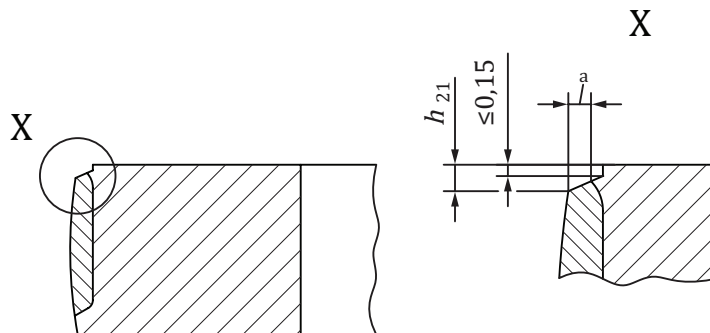

a ≥ 50 % of minimum layer thickness.

Figure 12 — Spray-coated ring of semi-inlaid design — Codes SC1E to SC4E

Table 19 — Axial dimensions h_{21} of peripheral edges of spray coated rings

Dimensions in millimetres

Ring width h_1	Axial dimension	
	h_{21}	tol.
$1 \leq h_1 < 2$	0,2	$\pm 0,1$
$2 \leq h_1 < 3,5$	0,3	$\pm 0,1$
$3,5 \leq h_1 \leq 4,5$	0,35	$\pm 0,1$

10.2.7 Peripheral edges at gap of spray coated rings

The peripheral edges at the gap shall be radiused or chamfered. See [Table 20](#).

Table 20 — Circumferential dimensions of peripheral edges at the gap of spray coated rings

Dimensions in millimetres

Ring width h_1	Circumferential dimension max.	
	s_3	Reduced s_3 (Code: KG)
≤4,5	0,4	0,2

10.2.8 Hardness of spray-coating

The values for hardness of spray-coated rings can be obtained from the specification of the piston ring manufacturer.

10.3 Nitrided surfaces

10.3.1 Codes

Codes are required for nitrided surfaces, see [Table 21](#).

10.3.2 Nitrided case depth

See [Table 21](#).

Table 21 — Nitrided case depth

Dimensions in millimetres

Code	Peripheral surface min.	Tol. guide-line ^b	Bottom side face min.	Tol. guide-line ^b	Top side face min.	Tol. guide-line ^b	Inside surface min	Tol. guide-line ^b	Surface of expander	Relevant dimensional standard	
NT030	0,030	+0,040 0	0,010	+0,030 0	0,010	+0,030 0	a		—	ISO 6622-2	
NT050	0,050		0,015		0,015				—		
NT070	0,070	+0,050 0	0,020		0,020				—		ISO 6624-2
NT090	0,090		0,020		0,020				—		ISO 6624-4
NT110	0,110	+0,060 0	0,030		0,030				—		ISO 6626-3
NT130	0,130		0,030		0,030				—		
NB030	0,030	+0,040 0	0,010	+0,030 0	a	a		—	ISO 6624-2		
NB050	0,050		0,015					—			
NB070	0,070	+0,050 0	0,020					—		ISO 6624-4	
NB090	0,090		0,020					—		ISO 6624-4	
NB110	0,110	+0,060 0	0,030					—			
NB130	0,130		0,030					—			

^a Nitrided surface permissible.

^b Usually, a minimum specification does not call for tolerances. If a tolerance is required on the case depth, the tolerance guideline given here is recommended.

Table 21 (continued)

Code	Peripheral surface min.	Tol. guideline ^b	Bottom side face min.	Tol. guideline ^b	Top side face min.	Tol. guideline ^b	Inside surface min	Tol. guideline ^b	Surface of expander	Relevant dimensional standard		
NP030	0,030	+0,040 0	a						—	ISO 6624-2 ISO 6624-4		
NP050	0,050								—			
NP070	0,070	+0,050 0							—			
NP090	0,090								—			
NP110	0,110	+0,060 0							—			
NP130	0,130								—			
NS 010	0,010	+0,030 0	a		a				—	ISO 6627		
NS 020	0,020								0,005		—	
NS 030	0,030	+0,040 0							0,0100		+0,030 0	—
NS 050	0,050								0,020			—
NX	—	—	—	—	—	—	—	—	0,003 +0,012 0	ISO 6627		

a Nitrided surface permissible.
b Usually, a minimum specification does not call for tolerances. If a tolerance is required on the case depth, the tolerance guideline given here is recommended.

10.3.3 Radiusing and dimensions of outside and inside edges of nitrided steel rings

Nitrided steel rings have identical outside and inside rounded edges as plain steel rings. See dimensional standards.

10.3.4 Peripheral edges at the gap of nitrided steel rings and segments

The peripheral edges at the gap shall be radiused or chamfered, see [Table 22](#).

Table 22 — Circumferential dimensions of peripheral edges at the gap of nitrided steel rings and segments

Dimensions in millimetres

Ring width h_1, h_{12}	Circumferential dimension max.	
	s_3	Reduced s_3 (Code: KG)
$1 \leq h_1 < 1,5$	0,25	0,15
$1,5 \leq h_1 < 2,0$	0,30	0,20
$h_1 \geq 2,0$	0,35	0,25
$h_{12} \leq 0,6$	0,30	0,15

10.4 Treated surfaces

10.4.1 Ferro-oxidized all over — Code FE — Coating thickness 0,001 to 0,005mm

Only plain rings (i.e. uncoated) made of cast iron can be ferro-oxidized.

10.4.2 Phosphated all over — Code PO — Coating thickness 0,002 mm min.

This phosphating applies to piston rings made of cast iron and steel.

NOTE Except for stainless (or high Cr-alloyed) steel rings with spray-coated or chromium plated peripheral surfaces, which are not included.

10.4.3 Phosphated all over — Code PR — Coating thickness 0,002 mm max.

This phosphating is for rust protection purposes only and applies to piston rings made of cast iron and steel.

NOTE Except for stainless (or Cr-alloyed) steel rings with spray-coated or chromium plated peripheral surfaces, which are not included.

10.5 Physical vapour deposition coating (PVD)

10.5.1 Codes

Codes are required for PVD coated surfaces, see [Table 23](#).

10.5.2 PVD coating

PVD coating may consist of single or multiple layers.

10.5.3 PVD coating thickness

See [Table 23](#).

Table 23 — PVD coating thickness

Code	Peripheral surface min.
PC001	0,001
PC003	0,003
PC005	0,005
PC010 ^a	0,010
PC020 ^a	0,020
PC030 ^a	0,030
PC040 ^a	0,040
PC050 ^a	0,050
^a Not typical for Diamond Like Carbon coatings (DLC).	

10.5.4 Hardness of PVD coating

The value for hardness of PVD-coated rings can be obtained from the specification of the piston ring manufacturer.

10.5.5 Peripheral edges at the gap of PVD coated rings and segments

See [Figure 13](#) and [Table 24](#).

Table 24 — Peripheral edges at the gap of PVD coated rings and segments

Circumferential dimension max.	
s_3	reduced s_3 (Code KG)
0,40	0,20

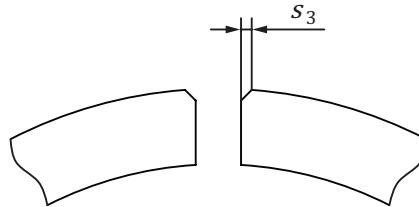


Figure 13 — Peripheral edges at the gap

11 Miscellaneous

11.1 Cleanliness

The piston rings shall be in a clean condition. Manufacturing residues, dirt, and the like are not allowable. Should limiting values for number and size of foreign particles or a test method for foreign particles be established, this is to be agreed upon between manufacturer and customer.

11.2 Corrosion protection

The piston rings shall be preserved such that they are reliably protected from corrosion while in normal dry storage for a minimum period of one year. The type and specification of the preservative are to be agreed upon between manufacturer and customer, taking into account storage life, storage conditions, assembly requirements, and all respective legal regulations.

11.3 Packaging

To accommodate automatic mounting, the package shall contain only one type of piston ring.

If orientation is required, all piston rings within one package shall be oriented in the same direction. In this case, a mark for the orientation shall be shown on the package.

12 Traceability (optional)

Traceability may be affected by suitable documentation or coding of individual ring batches.

In order to enable access to a piston ring manufacturer's quality and manufacturing data at any time after delivery prior first engine operation of piston rings, batch coding of each ring with a suitable identification code may be agreed upon. Traceability down to the single ring level is not intended. The scope of the data to be documented, as well as the coding methods, shall be agreed upon between customer and manufacturer.

Bibliography

- [1] ISO 6622-1, *Internal combustion engines — Piston rings — Part 1: Rectangular rings made of cast iron*
- [2] ISO 6622-2, *Internal combustion engines — Piston rings — Part 2: Rectangular rings made of steel*
- [3] ISO 6623, *Internal combustion engines — Piston rings — Scraper rings made of cast iron*
- [4] ISO 6624-1, *Internal combustion engines — Piston rings — Part 1: Keystone rings made of cast iron*
- [5] ISO 6624-2, *Internal combustion engines — Piston rings — Part 2: Half keystone rings made of cast iron*
- [6] ISO 6624-3, *Internal combustion engines — Piston rings — Part 3: Keystone rings made of steel*
- [7] ISO 6624-4, *Internal combustion engines — Piston rings — Part 4: Half keystone rings made of steel*
- [8] ISO 6625, *Internal combustion engines — Piston rings — Oil control rings*
- [9] ISO 6626-1:—,¹⁾*Internal combustion engines — Piston rings — Coil-spring-loaded oil control rings*
- [10] ISO 6626-2, *Internal combustion engines — Piston rings — Part 2: Coil-spring-loaded oil control rings of narrow width made of cast iron*
- [11] ISO 6626-3, *Internal combustion engines — Piston rings — Part 3: Coil-spring-loaded oil control rings made of steel*
- [12] ISO 6627, *Internal combustion engines — Piston rings — Expander/segment oil-control rings*

1) To be published. (Revision of ISO 6626:1989)

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™