

Aerospace — Test methods for polytetrafluoroethylene (PTFE) inner-tube hose assemblies

Part 1: Metallic (stainless steel) braid

ICS 49.080; 83.140.40

National foreword

This British Standard is the UK implementation of ISO 8829-1:2009.

The UK participation in its preparation was entrusted to Technical Committee ACE/69, Aerospace hydraulic systems, fluids and components.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2009

© BSI 2009

ISBN 978 0 580 55064 5

Amendments/corrigenda issued since publication

Date	Comments

INTERNATIONAL STANDARD

ISO
8829-1

First edition
2009-04-01

Aerospace — Test methods for polytetrafluoroethylene (PTFE) inner-tube hose assemblies —

Part 1: Metallic (stainless steel) braid

*Aéronautique et espace — Méthodes d'essai des tuyauteries flexibles à
tube intérieur en polytétrafluoroéthylène (PTFE) —*

Partie 1: Tresses métalliques (en acier inoxydable)



Reference number
ISO 8829-1:2009(E)

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword.....	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Tests of PTFE inner tubes	2
4.1 Density and relative density	2
4.2 Tensile tests	2
4.3 Rolling and proof pressure tests	4
4.4 Electrical conductivity test	6
5 Tests on hoses and hose assemblies	7
5.1 Stress degradation test	7
5.2 Pneumatic effusion test	7
5.3 Electrical conductivity test	8
5.4 Visual and dimensional inspection.....	10
5.5 Determination of elongation or contraction.....	10
5.6 Volumetric expansion test	11
5.7 Leakage test	12
5.8 Proof pressure test.....	12
5.9 Burst pressure tests	13
5.10 Impulse test	13
5.11 Flexure test.....	14
5.12 Fuel resistance test	14
5.13 Low temperature flexure testing	15
5.14 Pneumatic leakage test	15
5.15 Vacuum test.....	16
5.16 Pneumatic surge test	16
5.17 Thermal shock test	17
5.18 Fire test	17
Annex A (informative) Test fluids	18
Bibliography	19

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

ISO 8829-1 was prepared by Technical Committee ISO/TC 20, *Aircraft and space vehicles*, Subcommittee SC 10, *Aerospace fluid systems and components*.

ISO 8829 consists of the following parts, under the general title *Aerospace — Test methods for polytetrafluoroethylene (PTFE) inner-tube hose assemblies*:

- *Part 1: Metallic (stainless steel) braid*
- *Part 2: Non-metallic braid*

Aerospace — Test methods for polytetrafluoroethylene (PTFE) inner-tube hose assemblies —

Part 1: Metallic (stainless steel) braid

1 Scope

This part of ISO 8829 specifies test methods for flexible polytetrafluoroethylene (PTFE) inner tubes with metallic (stainless steel) braided hose and hose assemblies used in aircraft fluid systems, in the pressure and temperature ranges covered by pressure classes and temperature types, as specified in ISO 6771.

If performance requirements are not defined in this part of ISO 8829, they are defined in the performance specification.

This part of ISO 8829 is applicable when reference is made to it in a procurement specification or other definition document.

NOTE Fluids used for the tests are listed in Annex A. The requirements for non-metallic braid hose assemblies are given in ISO 8829-2.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2685, *Aircraft — Environmental test procedure for airborne equipment — Resistance to fire in designated fire zones*

ISO 6772, *Aerospace — Fluid systems — Impulse testing of hydraulic hose, tubing and fitting assemblies*

ISO 6773, *Aerospace — Fluid systems — Thermal shock testing of piping and fittings*

ISO 7258, *Polytetrafluoroethylene (PTFE) tubing for aerospace applications — Methods for the determination of the density and relative density*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

room temperature

temperature in the test laboratory between 15 °C (59 °F) and 32 °C (90 °F)

3.2

fire protection

flame- and heat-retardant element over the hose assembly

4 Tests of PTFE inner tubes

4.1 Density and relative density

4.1.1 Principle

This test is intended to control the crystallinity of PTFE inner tubes.

4.1.2 Test methods

The relative density of the PTFE tubing shall be measured in accordance with ISO 7258, method A or method B. The density of the PTFE tubing shall be measured in accordance with ISO 7258, method C.

4.2 Tensile tests

4.2.1 Principle

This test is intended to determine the mechanical properties of the PTFE tubing.

4.2.2 Test conditions

Test specimens shall be conditioned for at least 2 h at room temperature prior to testing.

4.2.3 Apparatus

4.2.3.1 Testing machine

The test shall be carried out using a power-driven machine which is capable of maintaining a uniform rate of jaw separation at 50 mm/min (2 in/min) and which has a suitable dynamometer and a device for measuring the force applied within $\pm 2\%$. If the capacity range cannot be changed during a test, as in the case of pendulum dynamometers, the force applied at breaking point shall be measured within $\pm 2\%$, and the smallest tensile force measured shall be accurate to within $\pm 10\%$.

If the dynamometer is of the compensating type for measuring tensile stress directly, means shall be provided to make adjustments for the cross-sectional area of the test specimen. The response of the recorder shall be sufficiently rapid that the force applied is measured accurately during the elongation of the test specimen to breaking point. If the test machine is not equipped with a recorder, a device shall be provided that indicates, after fracture, the maximum force applied during elongation. Testing machines shall be capable of measuring elongation in increments of 10 %.

4.2.3.2 Micrometer

The micrometer used for measuring flat test specimen thickness shall be capable of exerting a pressure of (25 ± 5) kPa [$(3,63 \pm 0,7)$ psi] on the test specimens and of measuring the thickness to within $\pm 0,025$ mm (0,001 in).

NOTE Dial micrometers exerting either a force of $(0,8 \pm 0,15)$ N [$(0,18 \pm 0,034)$ lbf] on a circular foot 6,35 mm (0,25 in) in diameter, or a force of $(0,2 \pm 0,04)$ N [$(0,045 \pm 0,009)$ lbf] on a circular foot 3,2 mm (0,125 in) in diameter, conform to the pressure requirement specified above. It is not advisable to use a micrometer to measure the thickness of test specimens narrower in width than the diameter of the foot unless the contact pressure is properly adjusted.

4.2.4 Calibration of testing machine

The testing machine shall be calibrated.

If the dynamometer is of the strain-gauge type, the test machine shall be calibrated at one or more forces at regular intervals.

4.2.5 Test specimens

The specimens shall be in accordance with Figure 1.

NOTE Careful maintenance of the cutting edges of the die is extremely important and can be achieved by light daily honing and touching up of the cutting edges with jeweller's hard honing stones. The condition of the die can be assessed by determining the breaking point on any series of broken test specimens. When broken test specimens are removed from the jaws of the test machine, it is advantageous to pile these test specimens and note if there is any tendency to break at or near the same portion of each test specimen. Breaking points consistently occurring at the same place can be an indication that the die is dull, nicked or bent at that particular position.

Dimensions in millimetres

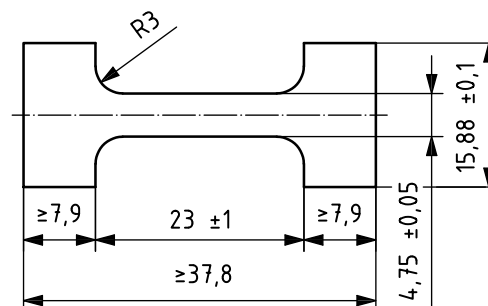


Figure 1 — Test specimen for tensile test

4.2.6 Determination of tensile strength and elongation

4.2.6.1 Procedure

Place the test specimens (see 4.2.5) in the jaws of the testing machine (see 4.2.3.1), taking care to adjust the specimen symmetrically so that the tension will be distributed uniformly over the cross-section. Start the machine and note continuously the distance between the jaws, taking care to avoid parallax. At fracture, measure and record the elongation to the nearest 10 % on the scale.

4.2.6.2 Expression of results

Calculate the tensile strength, R_m , expressed in newtons per square millimetre¹⁾, using Equation (1):

$$R_m = \frac{F}{S} \quad (1)$$

where

F is the measured force, in newtons, required to fracture the test specimens;

S is the cross-sectional area, in square millimetres, of the test specimen before application of force.

1) 1 N/mm² = 1 MPa.

Calculate the percentage total elongation at fracture, A_t , using Equation (2):

$$A_t = \left(\frac{L_u - L_o}{L_o} \right) \times 100 \quad (2)$$

where

L_u is the length measured between the jaws at fracture of the test specimen;

L_o is the original length measured between the jaws before application of force.

4.3 Rolling and proof pressure tests

4.3.1 Principle

This test is intended to check that there are no flaws in the sintered tube.

4.3.2 Rolling test — Procedure

Pass each tube, in a single pass, through six sets of metal rollers, so that it is subjected to the sequence of diametral flexings specified in Table 1. Rollers shall be arranged to prevent inadvertent rotation in the tube. It is assumed that the tube is in a horizontal position and that pressure of the first set of rollers is exerted vertically. Angles given for the final three sets of rollers may be taken as either clockwise or counter clockwise from the vertical diameter of the tube. Roller angles shall be as specified in Table 1. A tolerance of $\pm 2^\circ$ is allowed on each roller angle.

Table 1 — Roller functions and angles

Set of metal rollers	Type of action	Roller angle
1	Flattening	0°
2	Flattening	90°
3	Rounding	0°
4	Flattening	45°
5	Flattening	135°
6	Rounding	45°

The roller gap dimensions shall not be greater than those specified in Table 2 for each size.

Table 2 — Roller gap dimensions

Metric part	Hose size			Maximum flattening gap				Maximum rounding gap			
	Inch part Equivalent outside diameter of tube			Class B 10 500 kPa (1 523 psi) hose		Class D 21 000 kPa (3 046 psi) and higher hose		Class B 10 500 kPa (1 523 psi) hose		Class D 21 000 kPa (3 046 psi) and higher hose	
Size	Size	mm	(in)	mm	(in)	mm	(in)	mm	(in)	mm	(in)
DN05	–3	4,762	(0,187)	5,2	(0,205)	5,2	(0,205)	5,5	(0,216)	6,4	(0,252)
DN06	–4	6,350	(0,250)	5,5	(0,216)	7,1	(0,279)	5,5	(0,216)	6,4	(0,252)
DN08	–5	7,937	(0,312)	5,5	(0,216)	—	—	6,4	(0,252)	—	—
DN10	–6	9,525	(0,375)	5,5	(0,216)	7,1	(0,279)	7,9	(0,311)	8,3	(0,327)
DN12	–8	12,700	(0,500)	5,9	(0,232)	8,3	(0,327)	9,5	(0,374)	11,9	(0,468)
DN16	–10	15,875	(0,625)	6,4	(0,252)	8,3	(0,327)	12,7	(0,500)	14,7	(0,578)
DN20	–12	19,050	(0,750)	6,4	(0,252)	8,3	(0,327)	12,7	(0,500)	17,5	(0,689)
DN25	–16	25,400	(1,000)	6,4	(0,252)	8,3	(0,327)	19,1	(0,752)	21	(0,827)
DN32	–20	31,750	(1,250)	7,9	(0,311)	11,1	(0,437)	22,2	(0,874)	25,4	(1,000)
DN40	–24	38,100	(1,500)	9,5	(0,374)	—	—	31,8	—	—	—

NOTE Special size high pressure hose assembly callout utilizes the lower hose size value noted.

4.3.3 Proof pressure test — Procedure

After the roll test, hold the tube for not less than 2 min at proof pressures as shown in Table 3, using water or air as the test medium.

Table 3 — Proof pressures

Metric part	Hose size			Proof pressures			
	Inch part Equivalent outside diameter of tube			Class B 10 500 kPa (1 523 psi) hose		Class D 21 000 kPa (3 046 psi) and higher hose	
Size	Size	mm	(in)	kPa	(psi)	kPa	(psi)
DN05	–3	4,762	(0,187)	2 690	(390)	2 690	(390)
DN06	–4	6,350	(0,250)	2 480	(360)	2 620	(380)
DN08	–5	7,937	(0,312)	2 000	(290)	—	—
DN10	–6	9,525	(0,375)	1 590	(230)	1 930	(280)
DN12	–8	12,700	(0,500)	1 240	(180)	1 520	(220)
DN16	–10	15,875	(0,625)	1 170	(170)	1 170	(170)
DN20	–12	19,050	(0,750)	965	(140)	890	(130)
DN25	–16	25,400	(1,000)	621	(90)	660	(95)
DN32	–20	31,750	(1,250)	448	(65)	660	(95)
DN40	–24	38,100	(1,500)	310	(45)	—	—

NOTE Special size high pressure hose assembly callout utilizes the lower hose size value noted.

4.4 Electrical conductivity test

4.4.1 Preconditioning


The test specimen shall be a 350 mm (13,78 in) length of PTFE hose tube, with braid removed. The inner surface of the tube shall be washed first with solvent (test fluid No.1; see Annex A) and then with isopropyl alcohol (test fluid No.2; see Annex A) to remove surface contamination. The inside of the tube shall then be thoroughly dried at room temperature.

4.4.2 Procedure

Arrange the test specimen vertically as shown in Figure 2. The relative humidity shall be kept below 70 %. Apply $(1\ 000 \pm 10)$ V d.c. between the upper and lower electrodes (salt water solution). The salt water solution shall be a solution of sodium chloride in chemically pure water [$\rho(\text{NaCl}) = 450$ g/l].

Measure the current with an instrument having a sensitivity of at least $1\ \mu\text{A}^2$.

Dimensions in millimetres

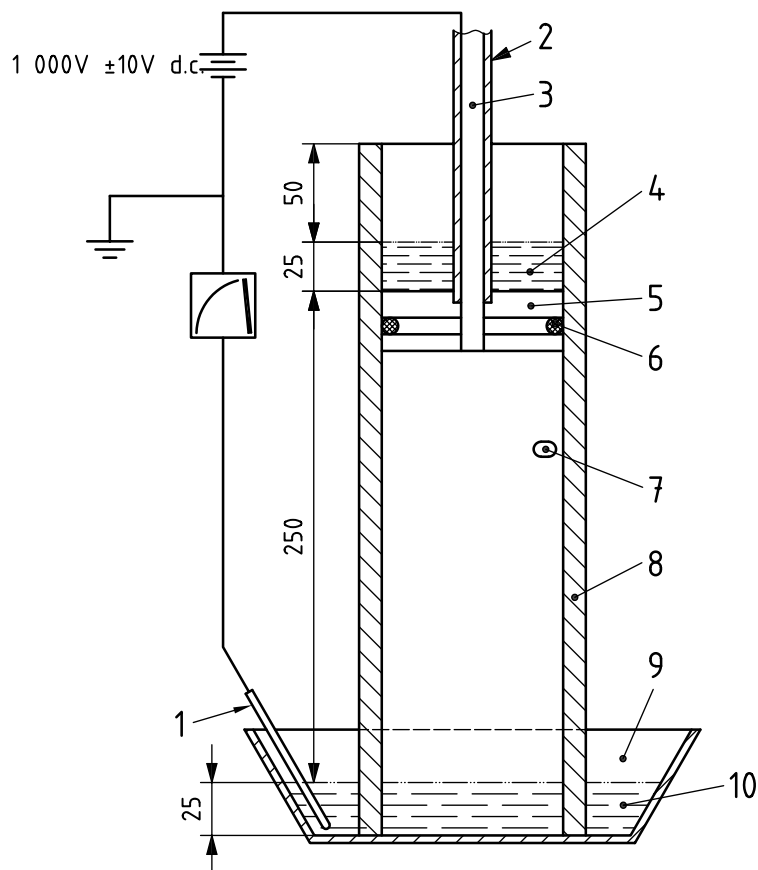

Key

- | | | | |
|---|--|----|--|
| 1 | probe | 6 | O-ring |
| 2 | conductor tube | 7 | vent (if any) |
| 3 | vent | 8 | polytetrafluoroethylene (PTFE) (tube hose inner liner) |
| 4 | upper electrode (mercury or salt water solution) | 9 | non-metallic container |
| 5 | non-metallic plug | 10 | lower electrode (mercury or salt water solution) |

Figure 2 — Test set-up for electrical conductivity test on inner tubes

2) $1\ \mu\text{A} = 1 \times 10^{-6}$ A.

5 Tests on hoses and hose assemblies

5.1 Stress degradation test

5.1.1 Principle

This test is intended to verify that the hose inner tube has been sintered and quenched to the proper crystallinity to eliminate stress cracking or creep with subsequent leakage.

5.1.2 Class D 21 000 kPa (3 046 psi) and higher hose — Procedure

5.1.2.1 Fill the hose assemblies with a high-temperature test fluid (test fluid No.3; see Annex A) and place in an oven maintained at $(204 \pm 5) ^\circ\text{C}$ [$(400 \pm 9) ^\circ\text{F}$]. Apply to the hose assemblies the nominal working pressure specified in the procurement specification.

Precautions shall be taken to ensure that the hose assemblies do not come into contact with parts of the oven that are at a higher temperature.

5.1.2.2 After at least 20 h at $204 ^\circ\text{C}$ ($400 ^\circ\text{F}$), gradually release the pressure, remove the assemblies from the oven, drain and cool to room temperature. Then flush the assemblies with a quantity of fresh high-temperature test fluid (test fluid No.3; see Annex A), equivalent in volume to at least twice the volume of the test specimen volume, and drain.

5.1.2.3 Fill the hose assemblies with hydraulic test fluid (test fluid No.4; see Annex A). Apply to the hose assemblies the nominal working pressure specified in the procurement specification and hold that pressure for at least 2 h at room temperature.

5.1.2.4 Repeat the procedure specified in 5.1.2.1 to 5.1.2.3 a total of three times.

5.1.2.5 Within 4 h after the final pressurization period of 2 h, drain the hose assemblies, flush with trichlorotrifluoroethane (test fluid No.5; see Annex A) and place in an oven for at least 1 h at a temperature of $(70 \pm 5) ^\circ\text{C}$ [$(158 \pm 9) ^\circ\text{F}$].

5.1.2.6 Within 8 h after the drying process has been completed, remove the hose assemblies from the oven, cool to room temperature, and then subject to a pneumatic effusion (air under water) test. For this test, install the hose assemblies in a test set-up constructed similarly to that shown in Figure 3.

5.1.2.7 Immerse the test set-up with the hose assemblies installed in water. Apply nominal pressure for at least 15 min to allow any entrapped air in the hose to escape.

5.1.2.8 Hold the pressure for a further period of 5 min, during which time collect the gas escaping from the test specimen, including the juncture of the hose and the fitting, but not including the fitting nut. After the pressurization period of 5 min, calculate the average rate of effusion through the hose and two fittings expressed as millilitres per minute per metre of the hose length.

5.1.3 Class B 10 500 kPa (1 523 psi) hose – Procedure

The hose assemblies shall be tested in the same manner as specified in 5.1.2, except that the test temperature shall be $(232 \pm 5) ^\circ\text{C}$ [$(450 \pm 9) ^\circ\text{F}$].

5.2 Pneumatic effusion test


5.2.1 Principle

This test is intended to show that the hose inner tube does not have excessive porosity.

5.2.2 Procedure

Subject the hose assemblies for 1 h to nominal pressure using dry air or nitrogen gas (N₂) at room temperature. Collect and measure the gas escaping from the hose assembly during the second half-hour, using the water displacement method and an air-collecting device similar to that shown in Figure 3.

The fluid in the test set-up shall be water which has been treated for pH control and wetting of the hose by adding 1,5 % (v/v) of water softener or wetting agent.

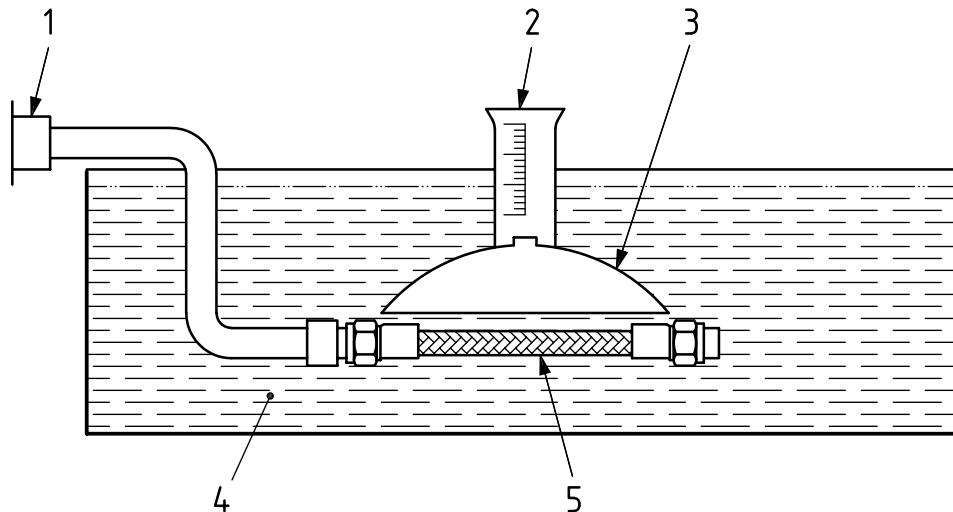

Key

- 1 air or nitrogen gas source
- 2 inverted graduated flask
- 3 funnel to cover hose plus one-half of each socket
- 4 water bath
- 5 hose assembly under test

Figure 3 — Test set-up for pneumatic effusion tests

5.3 Electrical conductivity test

5.3.1 Principle

This test is intended to show that the hose is sufficiently conductive to prevent build-up of excessive electrostatic charges which could cause arcing and pin holes.

5.3.2 Preconditioning


The test specimen shall be a length of hose (with braid and one end fitting) as shown in Figure 4 a) or b). The inner surface of the tube shall be washed first with solvent (test fluid No.1; see Annex A), and then with isopropyl alcohol (test fluid No.2; see Annex A) to remove surface contamination. The hose shall then be thoroughly dried at room temperature. The wire braid shall flare out as shown in Figure 4 to prevent contact with the end of the PTFE hose. One steel adaptor of appropriate size shall be fitted as shown in Figure 4.

5.3.3 Procedure

Arrange the test specimen vertically as shown in Figure 4. The relative humidity shall be kept below 70 %. Apply $(1\ 000 \pm 10)$ V d.c. between the upper (salt water solution) electrode and the lower (adaptor) electrode. The salt water solution shall be a solution of sodium chloride in chemically pure water [$\rho(\text{NaCl}) = 450$ g/l].

Measure the current with an instrument having a sensitivity of at least 1 μA .

Dimensions in millimetres

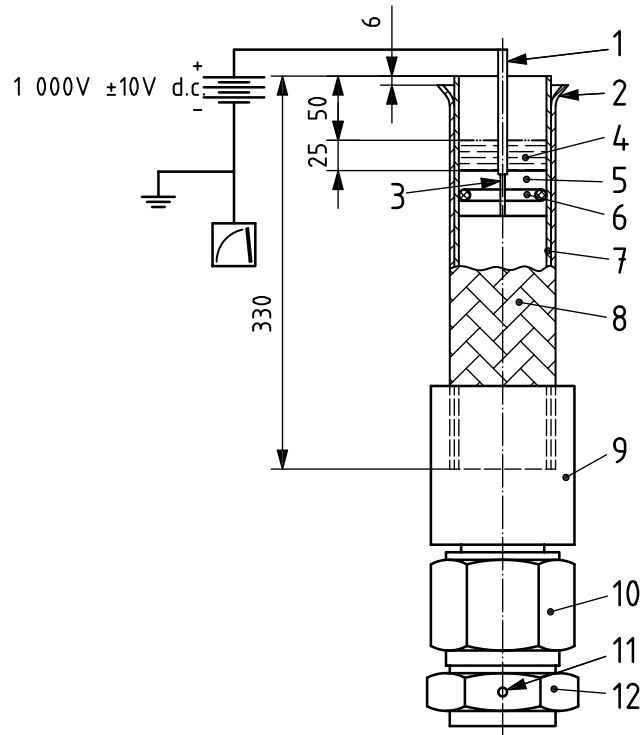


Key

- | | |
|--|---|
| 1 conductor threaded into ring | 7 PTFE hose |
| 2 flare braid(s)/spiral | 8 hose braid/spiral |
| 3 vent | 9 fitting body |
| 4 upper electrode (mercury or salt water solution) | 10 fitting nut |
| 5 non-metallic ring | 11 vent (alternative) |
| 6 O-ring | 12 adaptor (insulate electrode from ground) |

a) Option 1

Figure 4 (continued)

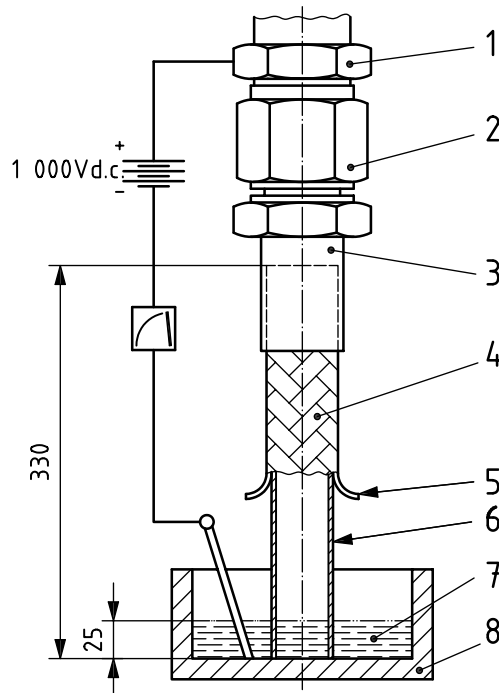

Key

- 1 electrode (vented mating fitting adaptor)
- 2 fitting nut
- 3 fitting body
- 4 hose braid
- 5 flared braid
- 6 polytetrafluoroethylene tube
- 7 electrode (salt water solution)
- 8 non-metallic container

b) Option 2

Figure 4 — Test set-up for electrical conductivity test on hoses and hose assemblies

5.4 Visual and dimensional inspection

Hose assemblies shall be inspected using the normal tools and procedures.

5.5 Determination of elongation or contraction

5.5.1 Principle

This test is intended to check the proper reinforcing. Braid angle is used to minimize axial motion due to pressurization.

5.5.2 Procedure

Hold the unpressurized hose in a straight position, mark off on the hose a gauge length of 250 mm (10 in), and then subject the hose to the nominal operating pressure specified in the procurement specification. After at least 5 min and with the hose length still pressurized, measure the gauge length and calculate the change in length.

5.6 Volumetric expansion test


5.6.1 Principle

This test is intended to determine the increase in volume that occurs when a hose assembly is pressurized.

5.6.2 Apparatus

The test set-up, shown in Figure 5, shall be designed in such a way that air pockets cannot form. There shall be only one low point between the reservoir and the pump. The internal passages shall not have constrictions or surface roughness that could allow air pockets. The hose end fittings and system tubes shall be both strong and rigid enough to allow only negligible expansion under test pressure. The test fluid shall be distilled water. The pump pressure shall be increased at a rate of 2 000 kPa/s (290 psi/s) to 4 000 kPa/s (580 psi/s).

Before installing the hose assembly, measure the volumetric expansion of the test set-up (see 5.6.3.9).

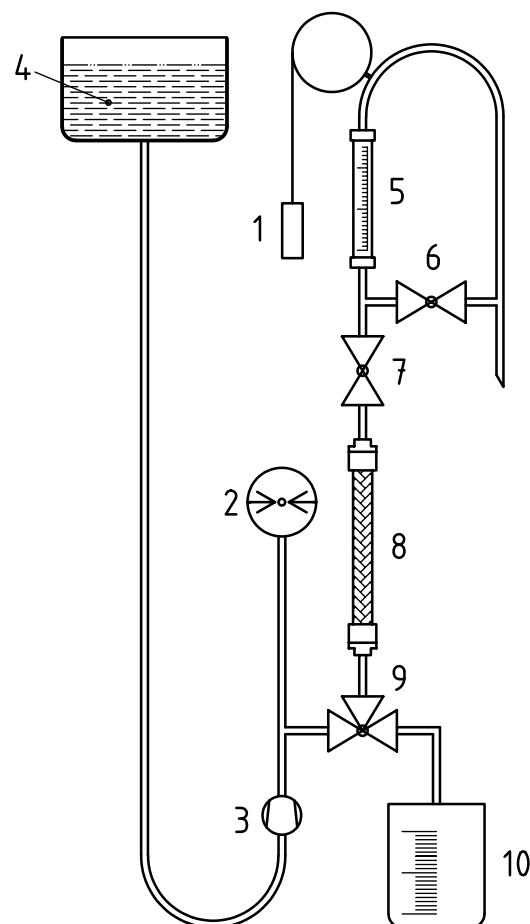

Key

- | | |
|---|------------------------------|
| 1 counter-weight for that part of the installation which is located above the hose assembly | 6 valve A |
| 2 pressure gauge | 7 valve B |
| 3 pump | 8 hose assembly under test |
| 4 tank of distilled water | 9 three-way valve |
| 5 graduated glass tube | 10 graduated glass container |

Figure 5 — Test set-up for volumetric expansion test

5.6.3 Procedure

- 5.6.3.1 Install the hose assembly to be tested in the test set-up as shown in Figure 5.
- 5.6.3.2 Set the three-way valve to the position indicated in Figure 5.
- 5.6.3.3 Open valve B and close valve A.
- 5.6.3.4 Operate the pump until the water is visible in the graduated glass tube.
- 5.6.3.5 Close valve B. Subject the hose assembly to the appropriate proof pressure for 3 min and check the system for leakage.
- 5.6.3.6 Close valve B. Bring the water level in the graduated glass tube to zero, using the pump and valve A.
- 5.6.3.7 Close valve B. Raise the pressure in the system to the appropriate test pressure and hold for 3 min to 6 min.
- 5.6.3.8 Close the three-way valve, and open valve B.
- 5.6.3.9 The increase in the volume of the hose assembly is indicated by the difference in level in the graduated tube. Subtract from the value obtained the value for the expansion of the rest of the test system, which has been measured beforehand (see 5.6.2).

5.7 Leakage test

5.7.1 Principle

This test is intended to demonstrate that the hose will not leak or rupture at 70 % of the minimum required burst pressure.

5.7.2 Procedure

Pressurize the hose assemblies with water or system fluid to 70 % of the minimum burst pressure at the room temperature specified in the procurement specification and hold for at least 5 min. Reduce the pressure to 0 kPa (0 psi), then raise the pressure again to 70 % of the minimum burst pressure at room temperature for a final check lasting 5 min.

5.8 Proof pressure test

5.8.1 Principle

This test is intended to verify the structural integrity of a hose assembly prior to use.

5.8.2 Procedure

5.8.2.1 All hose assemblies

The test fluid may be either water or system fluid. Test all hose assemblies to the proof pressure specified in the procurement specification for at least 30 s, and not more than 5 min.

5.8.2.2 Hose assemblies having fire sleeves or cuffs

Water shall be used as the test medium for proof pressure testing of hose assemblies having fire sleeves. Prior to the installation of cuffs or sleeves on the fittings, hold the proof pressure for at least 2 min, during which time any fire sleeves installed on the test specimens shall be pulled back from the end fittings.

The proof test shall be repeated if the temperature is applied when fitting fire cuffs or sleeves.

5.9 Burst pressure tests

5.9.1 Principle

These tests are intended to establish failure mode under over-pressure at room temperature and at high temperature.

5.9.2 Test conditions

The hose assemblies shall be tested in the straight condition, the end opposite to the pressure source being left free. The assemblies shall be observed throughout the tests.

5.9.3 Burst pressure test at room temperature

The test fluid shall be hydraulic fluid or water.

Fill the hose assemblies with the test fluid to pressure and increase the pressure at a rate of $(150\,000 \pm 37\,500)$ kPa/min [$(21\,755 \pm 5\,439)$ psi/min] until the assemblies burst. Record the type of failure and the pressure at which it occurred.

The hose assemblies for fluid systems of burst pressure at room temperature shall be as specified in the procurement specification. For class B 10 500 kPa (1 532 psi) and over, the burst pressure at room temperature shall never be less than four times the nominal pressure.

5.9.4 Burst pressure test at high temperature

Fill the hose assemblies with a suitable test fluid.

Soak hose assemblies and maintain for at least 1 h at ambient and fluid temperatures of (232 ± 5) °C [(450 ± 9) °F], unless otherwise specified. After 1 h, raise the pressure to the rated operating pressure and hold there for 5 min. Increase the pressure at a rate of $(150\,000 \pm 37\,500)$ kPa/min [$(21\,755 \pm 5\,439)$ psi/min] until rupture or leakage occurs. Record the type of failure and the pressure at which it occurred.

The burst pressure at high temperature shall be as specified in the procurement specification. For hose assemblies for fluid systems of class B 10 500 kPa (1 532 psi) and over, the burst pressure at high temperature shall never be less than three times the nominal pressure.

5.10 Impulse test

5.10.1 Principle

This test is intended to verify the service life of a hose assembly when exposed to hydraulic pressure cycling and surging.

5.10.2 Preconditioning

Prior to testing, the hose assemblies shall be aged and/or exposed to a salt solution soak test, if so specified in the procurement specification.

5.10.3 Procedure

5.10.3.1 Connect the hose assemblies to rigid supports in the test rig and bend through 180° to the appropriate minimum bend radius specified in the procurement specification.

5.10.3.2 Using system fluid or a high-temperature test fluid (test fluids Nos. 3, 6 and 7 or equivalent; see Annex A), subject hose assemblies for fluid systems of class B 10 500 kPa (1 532 psi) and above to impulse testing in accordance with ISO 6772. During the test, the fluid and ambient temperatures shall vary as specified in ISO 6772. The test shall be run in such a manner that the hose assemblies are submitted to at least two complete temperature cycles.

5.11 Flexure test

5.11.1 Principle

This test is intended to demonstrate the flexure fatigue performance of hose braids and fitting attachments.

5.11.2 Procedure

5.11.2.1 Fill the hose assemblies with system fluid (test fluids Nos. 6 and 7, or equivalent; see Annex A) and mount in the flexure test set-up shown in Figure 6.

5.11.2.2 Maintain the test assemblies without pressure and without flexing at a temperature of $(-55 \pm 1) ^\circ\text{C}$ [$(-67 \pm 1,8) ^\circ\text{F}$] for at least 1 h.

5.11.2.3 Without flexing and with the temperature maintained still at $(-55 \pm 1) ^\circ\text{C}$ [$(-67 \pm 1,8) ^\circ\text{F}$], pressurize for at least 5 min; this shall be done for the first cycle only.

5.11.2.4 While the test assemblies are pressurized to the nominal pressure, with the temperature maintained at $(-55 \pm 1) ^\circ\text{C}$ [$(-67 \pm 1,8) ^\circ\text{F}$], begin flexing at a rate of (70 ± 10) cycles/min for at least 4 000 flex cycles.

5.11.2.5 With the pressure reduced to 0 kPa (0 psi) and with the temperature still maintained at $(-55 \pm 1) ^\circ\text{C}$ [$(-67 \pm 1,8) ^\circ\text{F}$], continue flexing at the same rate as specified in 5.11.2.4 for a further 1 000 flex cycles.

5.11.2.6 Increase the temperature to $(204 \pm 5) ^\circ\text{C}$ [$(400 \pm 9) ^\circ\text{F}$] and flex the hose assemblies at the same rate as specified in 5.11.2.4 for a further 1 000 cycles with the pressure at 0 kPa (0 psi). With the temperature maintained at $(204 \pm 5) ^\circ\text{C}$ [$(400 \pm 9) ^\circ\text{F}$], increase the pressure to the specified nominal pressure. Continue flexing at the same rate at that pressure and temperature for an additional 74 000 cycles until an accumulated total of 80 000 cycles is reached.

5.11.2.7 Repeat the procedure specified in 5.11.2.2, 5.11.2.4, 5.11.2.5 and 5.11.2.6 for a total of five test sequences (i.e. 400 000 flexing cycles).

5.11.2.8 After the procedure specified in 5.11.2.7 has been completed, without flexing and with the temperature maintained at $(204 \pm 5) ^\circ\text{C}$ [$(400 \pm 9) ^\circ\text{F}$], pressurize the test assemblies to the specified proof pressure for at least 5 min; this shall be done for the final cycle only.


5.12 Fuel resistance test

This test is intended to demonstrate the suitability of hydraulic hose for fuel system use.

5.12.1 Procedure

5.12.1.1 Fill the hose assemblies with solvent (test fluid No. 1; see Annex A) or fuel (test fluid No. 9; see Annex A) and place in an oven maintained at a temperature of $(125 \pm 5) ^\circ\text{C}$ [$(257 \pm 9) ^\circ\text{F}$] for a period of at least 48 h. Throughout the 48 h, apply to the hose assemblies the nominal pressures specified in the procurement specification.

Precautions shall be taken to ensure that the hose assemblies do not come into contact with parts of the oven that are at a higher temperature.

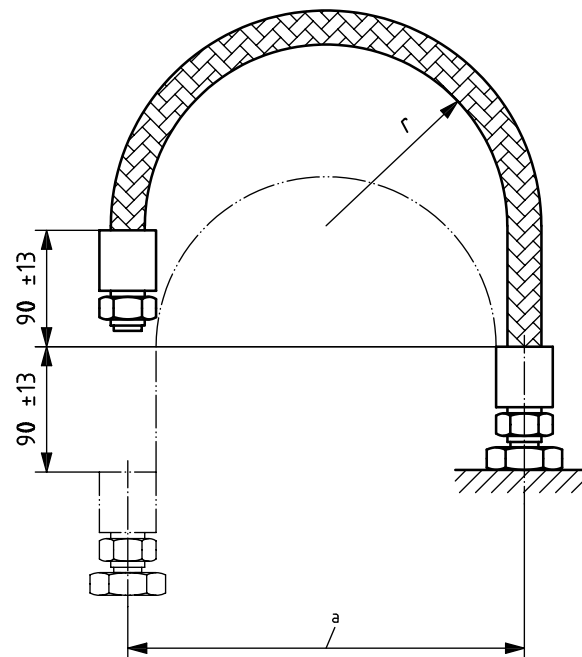

r minimum inside bend radius $\pm 10\%$ ^a

^a Dimensions specified in the procurement specification.

Figure 6 — Test set-up for flexure test

5.12.1.2 After 48 h, depressurize the hose assemblies, drain, and allow to cool for 20 min at room temperature. Then fill the hose assemblies with appropriate test fluid (test fluid No. 10; see Annex A) and apply the rated nominal pressure and maintain at room temperature for at least 2 h.

5.13 Low temperature flexure testing

5.13.1 Principle

This test is primarily intended to verify usability for fuel systems.

5.13.2 Procedure

5.13.2.1 Fill the hose assemblies with appropriate test fluid (test fluid No. 10, see Annex A) and place in a cold chamber maintained at a temperature of $(-55 \pm 1)^\circ\text{C}$ [$(-67 \pm 1,8)^\circ\text{F}$] for at least 24 h.

5.13.2.2 After 24 h, and with the temperature maintained at $(-55 \pm 1)^\circ\text{C}$ [$(-67 \pm 1,8)^\circ\text{F}$], bend the hose assemblies around a mandrel with a radius equal to the minimum bend radius specified in the procurement specification. Then bend in the reverse direction and return to the straight position. Repeat this cycle for a total of five times, allowing a maximum of 10 s per cycle.

5.14 Pneumatic leakage test

5.14.1 Principle

This test is intended to verify usability of a hose assembly in areas where no pneumatic leakage is permissible.

5.14.2 Procedure

At room temperature, test the hose assemblies, submerged under water, with air or nitrogen gas (N₂) at nominal pressure for at least 5 min.

5.15 Vacuum test

5.15.1 Principle

This test is intended to verify hose assemblies for applications where negative pressures could occur.

5.15.2 Procedure

Empty the hose assemblies, bend to the minimum bend radius specified for the hose, and place in an oven maintained at $(232 \pm 5) ^\circ\text{C}$ [$(450 \pm 9) ^\circ\text{F}$], unless otherwise specified in the procurement specification. Then apply the specified negative pressure to the assemblies and maintain. At the end of 4 h, remove the hose assemblies from the oven with the negative pressure maintained. When the samples have cooled to room temperature, release the pressure and inspect the hose assembly for collapse or defects.


Cut off one end of each hose assembly within 25 mm (1 in) of a fitting and roll a ball of the appropriate diameter, as specified in the procurement specification, through the length of the hose.

5.16 Pneumatic surge test

Install the hose assembly in a gas system (air or nitrogen) fitted with rapid-action valves, as shown in Figure 7. The gas shall be clean and dry. The test, carried out at room temperature, shall comprise 16 times the following cycle:

- a) hold nominal pressure in the hose assembly for at least 25 min;
- b) then rapidly reduce to atmospheric pressure and hold there for at least 5 min.

After this test, subject the hose assembly to proof pressure testing and visually examine internally and externally.

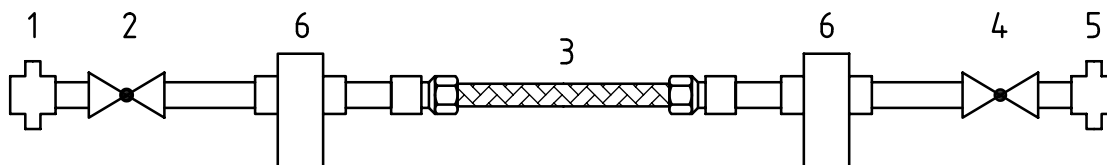

Key

- 1 air or nitrogen gas source
- 2 inlet valve
- 3 hose assembly under test
- 4 outlet valve
- 5 exhaust
- 6 filter (optional)

Figure 7 — Test set-up for pneumatic surge test

5.17 Thermal shock test

5.17.1 Preconditioning

Hose assemblies shall be air-aged or unaged as specified in the procurement specification. The assemblies shall be subjected to the specified proof pressure for at least 5 min.

5.17.2 Procedure

5.17.2.1 Proof pressure phase

Mount the empty hose assemblies in a high-temperature test fixture, as shown in ISO 6773, and reduce the ambient temperature to $(-55 \pm 1) ^\circ\text{C}$ [$(-67 \pm 1,8) ^\circ\text{F}$] for at least 2 h. At the end of this period and with the temperature maintained at $(-55 \pm 1) ^\circ\text{C}$ [$(-67 \pm 1,8) ^\circ\text{F}$], suddenly introduce a high-temperature of $(204 \pm 5) ^\circ\text{C}$ [$(400 \pm 9) ^\circ\text{F}$] at a minimum pressure of 350 kPa (50,8 psi). Immediately after the high-temperature test fluid has filled the assembly, raise the pressure to the specified proof pressure for at least 5 min. Not more than 15 s shall elapse between the introduction of the high-temperature test fluid at 350 kPa (50,8 psi) and the raising of the pressure to proof pressure.

5.17.2.2 Burst pressure phase

Fill the hose assemblies with a suitable high-temperature test fluid at a pressure of $(525 \pm 175) \text{ kPa}$ [$(76,1 \pm 25,4) \text{ psi}$] and maintain the test chamber and fluid temperature at $(204 \pm 5) ^\circ\text{C}$ [$(400 \pm 9) ^\circ\text{F}$] for 1 h. At the end of this period, pressurize the hose assemblies to the specified proof pressure for at least 5 min. Then release pressure and, with the temperature maintained at $(204 \pm 5) ^\circ\text{C}$ [$(400 \pm 9) ^\circ\text{F}$], or as specified in the procurement specification, increase the pressure at a rate of $(150\,000 \pm 37\,500) \text{ kPa/min}$ [$(21\,755 \pm 5\,439) \text{ psi/min}$] until failure occurs. Throughout the test, observe the hose assemblies continuously and record the type of failure and the pressure at which the failure occurred.

5.18 Fire test

Hose assemblies having fire-protective elements, such as fire cuffs, or fire sleeves, shall be tested in accordance with the hose assembly test specified in ISO 2685.

Annex A (informative)

Test fluids

International Standards have not yet been developed which provide specifications for appropriate test fluids to be used when testing hose assemblies in aircraft fluid systems. Consequently, at present, for the purposes of this part of ISO 8829, test fluids as specified in some national standards are given in Table A.1.

Test fluids of equivalent properties and characteristics as specified in other national standards may be used. However, when selecting test fluids, it should be borne in mind that non-equivalent test fluids may cause differences in test results and, more importantly, in the performance of hose assemblies.

In due course, references to national standards will be deleted and replaced by references to International Standards when these become available.

Table A.1 — Equivalent test fluids

Test Fluid No.	Equivalent test fluids					
	France		United Kingdom		USA	
	National standard applicable	Description	National standard applicable	Description	National standard applicable	Description
1	NF M 15-006	White spirit	BS 245	White spirit	MIL-PRF-680	Dry clean solvent
2	AIR 3660	2-Propanol (isopropyl alcohol)	BS 1595	2-Propanol (isopropyl alcohol)	TT-I-735	2-Propanol (isopropyl alcohol)
3	AIR 3514	Synthetic oil, aviation	(Same as for USA)		MIL-PRF-7808	Lubricating oil, aircraft turbine engine, synthetic base
4	AIR 3520	Hydraulic fluid	DEF STAN 91-48 Grade OM-18	Hydraulic fluid, petroleum, normal	MIL-PRF-5606	Hydraulic fluid, petroleum base, aircraft missile and ordnance
5	—	—	(Same as for USA)		MIL-PRF-83282	Hydraulic fluid, fire resistant, synthetic hydrocarbon base, aircraft
6	AIR 3407	Turbine fuel, aviation	DERD 2454	Turbine fuel, aviation	MIL-DTL-5624	Turbine fuel, aviation, Grade JP4
7	—	—	(Same as for USA)		ASTM D471	Standard test fluid, hydrocarbon, type III

Bibliography

- [1] ISO 6771, *Aerospace — Fluid systems and components — Pressure and temperature classifications*
- [2] ISO 8829-2, *Aerospace — Test methods for polytetrafluoroethylene (PTFE) inner-tube hose assemblies — Part 2: Non-metallic braid*
- [3] FD M 15-006, *Combustibles minéraux liquides — Caractéristiques du White-spirit*
- [4] AIR 3660/A, *Alcool isopropylique dénaturé (propanol 2) (symbole OTAN S-737)*
- [5] AIR 3514, *Huile synthétique, type 3 mm²/s (centistokes) à 100 °C pour turbomachines d'aviation (Symbole OTAN O-150)*
- [6] AIR 3407, *Carburant type «large coupe» pour turbomachines d'aviation (Symbole OTAN F-40)*
- [7] AIR 3520, *Liquide minéral type 5 centistokes à 100 °C pour transmissions hydrauliques (Symbole OTAN H-515 et H-520)*
- [8] BS 245, *Specification for mineral solvents (white spirit and related hydrocarbon solvents) for paints and other purposes*
- [9] BS 1595, *Propan-2-ol (Isopropyl Alcohol) for Industrial Use*
- [10] DEF STAN 91-48, *Hydraulic Fluid, Petroleum: Superclean NATO Code No: H-515 Joint Service Designation: OM-15 Hydraulic Fluid, Petroleum: Normal NATO Code No: H-520 Joint Service Designation: OM-18 — Issue 2; 12.97*
- [11] DERD 2454, *Aviation Turbine Fuel AVTAG/FSII F-40 — Issue 4; Amendment 1; 02/1979*
- [12] MIL-PRF-680, *Degreasing Solvent*
- [13] TT-I-735, *Isopropyl Alcohol*
- [14] MIL-PRF-7808, *Lubricating Oil, Aircraft Turbine Engines, Synthetic Base*
- [15] MIL-PRF-5606, *Hydraulic Fluid, Petroleum Base; Aircraft, Missile, and Ordnance*
- [16] MIL-PRF-83282, *Hydraulic Fluid, Fire Resistant, Synthetic Hydrocarbon Base, Metric, NATO Code Number H-537*
- [17] MIL-DTL-5624, *Turbine Fuel, Aviation, Grades JP-4 and JP-5*
- [18] ASTM D471, *Standard Test Method for Rubber Property Effect of Liquids*

BSI - British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001 Email: orders@bsigroup.com You may also buy directly using a debit/credit card from the BSI Shop on the Website <http://www.bsigroup.com/shop>

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact Information Centre. Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048 Email: info@bsigroup.com

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001 Email: membership@bsigroup.com

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsigroup.com/BSOL>

Further information about BSI is available on the BSI website at <http://www.bsigroup.com>

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright and Licensing Manager. Tel: +44 (0)20 8996 7070 Email: copyright@bsigroup.com