

BS ISO 9563:2015



BSI Standards Publication

# **Belt drives — Electrical conductivity of antistatic endless synchronous belts — Characteristics and test method**

**bsi.**

...making excellence a habit.™

### **National foreword**

This British Standard is the UK implementation of ISO 9563:2015.

The UK participation in its preparation was entrusted to Technical Committee MCE/10, Belts & Pulley Drive.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015.  
Published by BSI Standards Limited 2015

ISBN 978 0 580 85341 8

ICS 21.220.10

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 September 2015.

### **Amendments/corrigenda issued since publication**

Date	Text affected
------	---------------

---

---

---

**Belt drives — Electrical conductivity of  
antistatic endless synchronous belts  
— Characteristics and test method**

*Transmissions par courroies — Conductibilité électrique des  
courroies synchrones sans fin, anti-électrostatiques — Spécification  
et méthode d'essai*





## **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Electrical resistance — specification</b> .....	<b>1</b>
3.1 General.....	1
3.2 Resistance value.....	2
3.3 Minimum value of electrical resistance.....	2
<b>4 Selection and preparation of belts for test</b> .....	<b>2</b>
4.1 Laboratory test.....	2
4.2 Production test.....	2
<b>5 Test method</b> .....	<b>3</b>
5.1 Apparatus — insulation tester.....	3
5.2 Electrodes and contacts for laboratory and production tests.....	3
5.3 Test procedures.....	3
5.3.1 Laboratory test.....	3
5.3.2 Production test.....	3
5.3.3 Test timing.....	3
5.3.4 Interpretation of results.....	3
<b>Annex A (informative) Electrical conductive coating</b> .....	<b>5</b>
<b>Bibliography</b> .....	<b>6</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 41, *Pulleys and belts (including veebelts)*, Subcommittee SC 4, *Synchronous belt drives*.

This second edition cancels and replaces the first edition (ISO 9563:1990), which has been technically revised.

# Belt drives — Electrical conductivity of antistatic endless synchronous belts — Characteristics and test method

## 1 Scope

This International Standard specifies the maximum and minimum electrical resistance of antistatic endless and open ended synchronous belts. This International Standard provides guidelines to allow testing of synchronous belts to prove their static conductive (dissipative) properties as well as a corresponding production control test method.

The application of this International Standard is limited to new belts intended to be used in an explosive atmosphere or in situations where there is a fire risk. The test is intended to ensure that the belt is sufficiently conductive to dissipate charges of electricity which may form on it in service.

In the case of a production control test, the decision is left to national standards or agreement between interested parties as to whether the test shall be carried out on each belt in a batch or on only a percentage of belts in a batch.

For each proof test, the belt manufacturer shall determine which type of electrode and conductive coating material shall be used.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

## 3 Electrical resistance — specification

### 3.1 General

In general, the resistance of new antistatic belts should not exceed the maximum value as calculated in [3.2](#).

### 3.2 Resistance value

The electrical resistance in Ohms of a belt measured in accordance with [Clause 5](#) should not exceed  $R$ , calculated using the Formula (1):

$$R = \frac{6 \times 10^5 \times L}{W} \quad (1)$$

where

$R$  is the electrical resistance, in ohms ( $\Omega$ );

$L$  is the dry distance measured in a straight line between the electrodes, see [5.2](#) and [Figure 1](#);

$W$  is the width of the electrode (or belt if narrower than the electrodes).

NOTE 1 The resistance value relates to the initial resistance of new belts.

NOTE 2 The dimensions  $L$  and  $W$  are expressed in the same units.

### 3.3 Minimum value of electrical resistance

Belts with values of resistance below  $1 \times 10^4 \Omega$  should be classified as conductive. In such cases, it is the end user's responsibility to ensure that values of resistance below this recommended value do not present a hazard in the environment where the belts are being used.

Marking on belts needs to be indelible and clearly visible, but of the smallest practicable area to avoid introducing unnecessary insulation materials. The position of the marking should be such that it does not materially affect the electrical resistance of the discharge path across the belt surface.

## 4 Selection and preparation of belts for test

### 4.1 Laboratory test

Belts shall be tested no less than 8 h after production.

Prior to test, the following conditions shall be met.

- a) The belt shall be maintained in an unstrained state, for a period of not less than 2 h in a standard atmosphere 23/50, in accordance with ISO 23529 at a temperature of  $(23 \pm 2)^\circ\text{C}$  and  $(50 \pm 5)\%$  relative humidity.
- b) Belt surfaces shall not be buffed, abraded or cleaned with organic materials which attack or swell the materials to be tested.

### 4.2 Production test

Belts can be tested after production with belt temperature between  $15^\circ\text{C}$  and  $30^\circ\text{C}$ .

Prior to test the following conditions shall be met:

Belt surfaces shall not be buffed, abraded or cleaned with organic materials which attack or swell the materials to be tested.

NOTE Where laboratory/production control testing is carried out on numerous belt widths it can be impractical to have electrodes for each belt width. In these cases it is acceptable to test belts and calculate maximum resistance values based on belt width while using narrower or wider electrodes.



## 5 Test method

### 5.1 Apparatus — insulation tester

The test should be made preferably with an insulation tester (ohm-meter) having a nominal open circuit voltage of 500 V d.c. or with any suitable instrument known to give comparable results. The instrument should be sufficiently accurate to determine the resistance to within 10 % and not dissipate more than 3 W in the specimen.

**NOTE** Insulation testers have an inherent characteristic of limited power output; therefore the voltage which they apply to the test piece is less than their open circuit voltage at low resistance values of the test piece. This is a useful characteristic as it reduces the risk of shock and of overheating the test piece. Insulation testers of this type may be manually or power-driven generators or battery- or mains-operated multi-range instruments with similar electrical characteristics.

### 5.2 Electrodes and contacts for laboratory and production tests

Electrodes shall be used that have a profile which fits that of the belt being tested. Electrodes shall be made of a suitable conducting material. Care shall be taken to avoid use of materials which may form a non-conducting layer under exposure to the environment (e.g. oxidation).

Two electrodes shall be applied to the belt so that they each cover the top surface of 3 adjacent teeth and the sides and bottom of two grooves.

The distance between the two electrodes shall span seven grooves and six teeth. Electrodes shall have a minimum width of 20 mm ([Figure 1](#)).

The electrodes may be mounted on an insulating handle to allow ease of use and to ensure that the correct distance is used for each test. This necessitates a dedicated set of suitable electrodes for each pitch and tooth profile.

### 5.3 Test procedures

#### 5.3.1 Laboratory test

A test belt of known width shall be placed teeth uppermost on an insulated surface. The electrodes shall be applied to the toothed surface as per [5.2](#) and a pressure between 10 kPa to 40 kPa applied.

A conductive solution/gel/powder may be applied to the belt surface to ensure optimum contact between electrode and belt (see [Annex A](#)). Care should be taken to ensure that the conductive medium is only applied in the area of contact for the electrodes.

#### 5.3.2 Production test

A test belt of known width shall be placed teeth uppermost on an insulated surface. The electrodes shall be applied to the toothed surface as per [5.2](#). The pressure applied shall be constant with each type of belt used and such that it does not allow deformation or damage to the belt surface. This procedure is intended for general production testing so hand pressure is sufficient.


#### 5.3.3 Test timing

Measure the electrical resistance between the contacts using the insulation tester (see [5.1](#)). Take the reading  $5 \text{ s} \pm 1 \text{ s}$  after the application of the meter voltage.

#### 5.3.4 Interpretation of results

Verify that the value measured in [5.3.1](#) and [5.3.2](#) is not greater than the resistance value calculated in [3.2](#).

If the results of the production test are greater than the resistance value calculated in 3.2, then the belt may be re-tested in line with the laboratory test method.

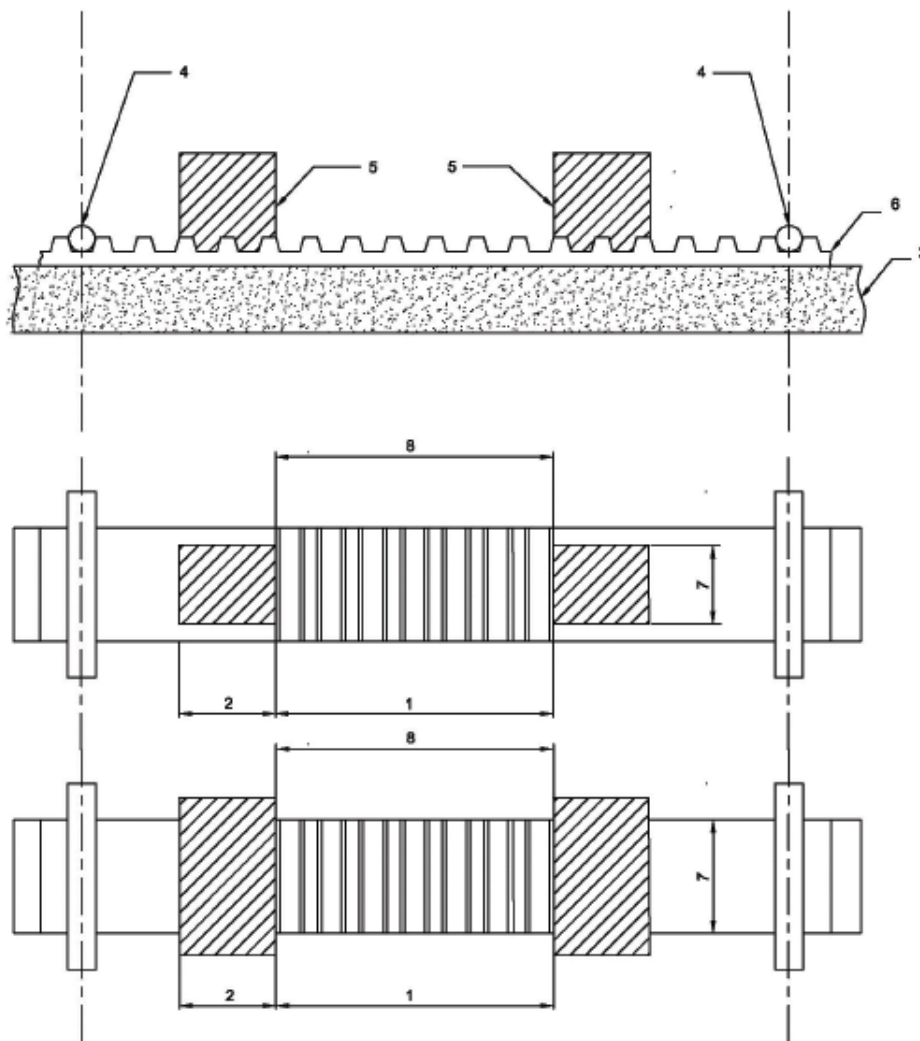

**Key**

- 1 7 grooves, 6 teeth between contacts
- 2 electrodes and contacts cover top of 3 teeth and all of 2 grooves
- 3 insulating surface
- 4 insulated clamp
- 5 contacts
- 6 belt
- 7  $W$
- 8  $L$

NOTE Dimensions  $L$  and  $W$  are expressed in the same units.

**Figure 1 — Layout of belt and contacts**

## Annex A (informative)

### Electrical conductive coating

To ensure minimum electrical resistance between the test metal electrodes and the test belt surfaces, a conductive coating may be provided comprising either

- a) a conductive silver lacquer or colloidal graphite which shall be of the type that dries at room temperature with a surface resistivity of the dried film below  $10 \Omega \cdot \text{m}$ , or
- b) a conductive liquid consisting of
  - 800 parts of anhydrous polyethylene glycol of molecular mass 600,
  - 200 parts of water,
  - 1 part of wetting agent, and
  - 10 parts of potassium chloride.

In the latter case, the electrode contact areas shall be completely wetted and remain so until the end of the test.

## Bibliography

- [1] ISO 1813, *Belt drives — V-ribbed belts, joined V-belts and V-belts including wide section belts and hexagonal belts — Electrical conductivity of antistatic belts: Characteristics and methods of test*
- [2] ISO 5296, *Synchronous belt drives — Belts with pitch codes MXL, XXL, XL, L, H, XH and XXH — Metric and inch dimensions*
- [3] ISO 9010, *Synchronous belt drives — Automotive belts*
- [4] ISO 13050, *Synchronous belt drives — Metric pitch, curvilinear profile systems G, H, R and S, belts and pulleys*







# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™