

BS ISO 9649:2016



BSI Standards Publication

Metallic materials — Wire — Reverse torsion test

National foreword

This British Standard is the UK implementation of ISO 9649:2016.

The UK participation in its preparation was entrusted to Technical Committee ISE/101/2, Ductility testing.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016. Published by BSI Standards Limited 2016

ISBN 978 0 580 85214 5

ICS 77.040.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2016.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

BS ISO 9649:2016

ISO
9649

Second edition
2016-05-15

**Metallic materials — Wire — Reverse
torsion test**

Matériaux métalliques — Fils — Essai de torsion alternée



Reference number
ISO 9649:2016(E)

© ISO 2016



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Symbols and designations	1
3 Principle	1
4 Testing equipment	2
5 Test piece	2
6 Test conditions	3
7 Procedure	3
8 Test report	3
Bibliography	4

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 164, *Mechanical testing of metals*, Subcommittee SC 2, *Ductility testing*.

This second edition cancels and replaces the first edition (ISO 9649:1990), which has been technically revised.


Metallic materials — Wire — Reverse torsion test

1 Scope

This International Standard specifies a method for determining the ability of metallic wire of diameter dimension from 0,3 mm to 10,0 mm inclusive to undergo plastic deformation during reverse torsion. This test is used to detect surface defects, as well as to assess ductility.

2 Symbols and designations

The symbols and designations used in the reverse torsion test of wires are shown in [Figure 1](#) and specified in [Table 1](#).

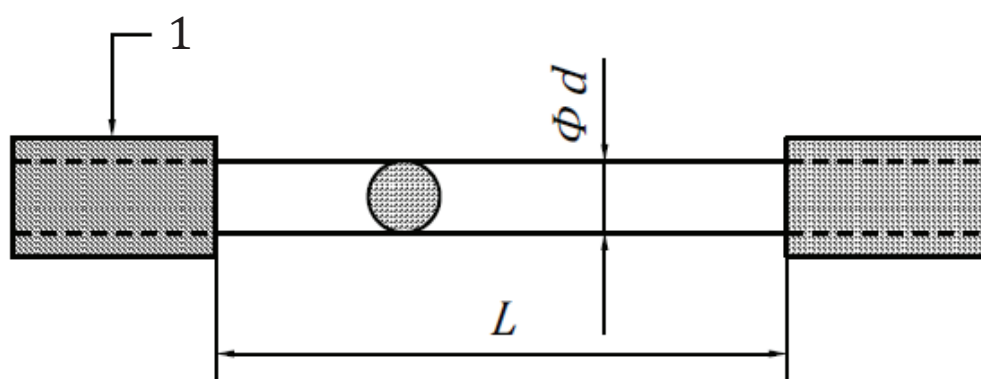

Key

1 grip

Figure 1 — Reverse torsion test of wires

Table 1 — Symbols and designations

Symbol	Designation	Unit
d	Diameter of a round wire	mm
L	Free length between grips	mm
N_1	Number of turns in one direction	—
N_2	Number of turns in the opposite direction	—

3 Principle

A test piece of wire is twisted a specified number of turns through 360° around its own axis in one direction, and then a specified number of turns through 360° in the opposite direction.

4 Testing equipment

4.1 The grips shall have a minimum hardness of 55HRC to provide rigidity and/or resistance to abrasion. The grip shall be arranged in the testing machine in such a way that, during testing, they remain on the same axis and do not apply any bending force to the piece.

One of the grips shall be capable of being rotated around the axis of the test piece in two opposite directions while the other shall not be subject to any angular deflection, except for such deflection as may be necessary to measure the torque.

The distance between the grips shall be capable of adjustment for different test piece lengths.

4.2 The machine shall be constructed so that a change in length between the grips, caused by deformation of the test piece during the test, is not prevented.

The machine shall be constructed so that an appropriate tensile stress (see 7.1) may be applied to the test piece.

4.3 The testing speed shall be able to be adjusted, and the number of turns shall be recorded.

4.4 A protective shield shall be provided to protect the operator from flying fragments in cases when the wire breaks into more than two pieces.

5 Test piece

5.1 The length of wire to be used as the test piece shall be as straight as possible.

If straightening is necessary, it shall be done by using suitable methods.

During straightening, the surface of the wire shall not be damaged and the test piece shall not be subject to any twisting.

Wire with a localized sharp curvature or kink shall not be used in the test.

5.2 Unless otherwise specified in the relevant standard, the nominal free length between the grips (L) of the test piece shall be as given in Table 2.

When testing for surface defects, a fixed free length between grips may be used. This length shall be as specified in the relevant standard and shall be stated in the test report.

Table 2 — Dependence of free length between the grips on nominal diameter of the wire

Nominal diameter d mm	Free length between grips L mm (nominal)
$0,3 \leq d < 1,0$	$200d$
$1,0 \leq d < 5,0$	$100d^a$
$5,0 \leq d \leq 10,0$	$50d^b$
a $50d$ may be used by special agreement.	
b $30d$ may be used by special agreement.	

6 Test conditions

In general, the test is carried out at an ambient temperature between 10 °C and 35 °C. Tests carried out under controlled conditions, where required, shall be made at a temperature of (23 ± 5) °C.

7 Procedure

7.1 Place the test piece in the testing machine in such a way that its longitudinal axis coincides with the axis of the grips and so that it remains straight during the test. Unless otherwise specified, this may be ensured by applying to the test piece a constant tensile stress not exceeding 2 % of the nominal tensile strength of the wire.

7.2 After placing the test piece in the testing machine, rotate one grip at a speed not exceeding 1 turn per second (or not exceeding 0,5 turns per second when the diameter d is 5 mm or greater) through the number of turns, N_1 , in one direction and then the other number of turns, N_2 , in the opposite direction. In general, N_1 and N_2 are specified in the relevant standard. One turn comprises 360°.

After the test, the free length of wire between the grips shall be examined by eyes unless otherwise specified in the relevant standard.

7.3 If the number of turns, N_2 , meets the requirement of the relevant standard, the test piece is considered as having passed the test. If the number of turns, N_2 , reached does not meet the requirement of the relevant standard and the failure is within a distance of $2d$ from the grip, the test shall be considered invalid and shall be repeated.

NOTE There is an example for this test in ISO 8458-3.

8 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 9649;
- b) all details necessary for the identification of the test piece (type of the material, heat number, etc.);
- c) the diameter d of the test piece;
- d) all details regarding the test piece preparation (method of straightening, etc.);
- e) the test conditions (the free length between the grips, the tensile stress applied, test speed, etc.);
- f) the number of turns (N_1 , N_2).

Bibliography

- [1] ISO 8458-3, *Steel wire for mechanical springs — Part 3: Oil-hardened and tempered wire*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK