

# Cylindrical cork stoppers — Physical tests —

## Part 4: Determination of dimensional recovery after compression

ICS 55.100; 79.100



## National foreword

This British Standard was published by BSI. It is the UK implementation of ISO 9727-4:2007.

The UK participation in its preparation was entrusted to Technical Committee PRI/81, Cork.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 29 June 2007

© BSI 2007

### Amendments issued since publication

Amd. No.	Date	Comments

ISBN 978 0 580 52943 6



INTERNATIONAL  
STANDARD

ISO  
9727-4

First edition  
2007-05-15

---

---

**Cylindrical cork stoppers — Physical tests —**

Part 4:

**Determination of dimensional recovery after compression**

*Bouchons cylindriques en liège — Essais physiques —*

*Partie 4: Détermination du taux de retour dimensionnel après compression*



Reference number  
ISO 9727-4:2007(E)

This document is now  
**POOBLIC**

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 9727-4 was prepared by Technical Committee ISO/TC 87, *Cork*.

This first edition of ISO 9727-4, together with the other parts of ISO 9727:2007, cancels and replaces ISO 9727:1991, which has been technically revised.

ISO 9727 consists of the following parts, under the general title *Cylindrical cork stoppers — Physical tests*:

- *Part 1: Determination of dimensions*
- *Part 2: Determination of mass and apparent density for agglomerated cork stoppers*
- *Part 3: Determination of humidity content*
- *Part 4: Determination of dimensional recovery after compression*
- *Part 5: Determination of extraction force*
- *Part 6: Determination of liquid tightness*
- *Part 7: Determination of dust content*



**This document is now  
PUBLIC**

*blank*

# Cylindrical cork stoppers — Physical tests —

## Part 4:

# Determination of dimensional recovery after compression

## 1 Scope

This part of ISO 9727 specifies a test method for determining the percentage of diameter recovery of cylindrical cork stoppers, after compression.

It is applicable to all types of cylindrical cork stoppers ready for use or semi-worked, intended to be completely inserted in the bottle neck (straight cork stoppers).

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 633, *Cork — Vocabulary*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 633 and the following apply.

### 3.1

#### straight cork stopper

«*ras de bague*»

stopper which is completely introduced in the bottle neck, its superior end reaching the top border of the bottle

## 4 Apparatus

**4.1 Vernier gauge**, with a constant contact force and a maximum resolution of 0,05 mm, or any other device allowing the same precision to be reached.


**4.2 Bottling machine with 4 jaws**, with a jaw compression diameter regulated between 15,5 mm and 16 mm.

## 5 Test conditions

### 5.1 Environment

The test shall be carried out in an environment with the following characteristics:

- temperature 21 °C ± 4 °C;
- relative humidity of air 60 % ± 20 %.

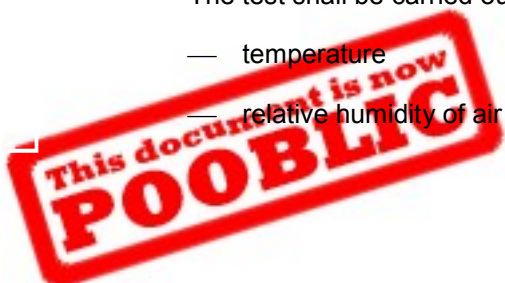

## 5.2 Cork stoppers

### 5.2.1 Temperature

At the beginning of the test, confirm that the stoppers of the test sample are at a temperature of  $21\text{ °C} \pm 4\text{ °C}$ .

### 5.2.2 Humidity

At the beginning of the test, confirm that the stoppers of the test sample are at a humidity of  $6\% \pm 2\%$ .

When the humidity is not between 4 % and 8 %, the result of the humidity obtained shall be referred to in the test report.

## 6 Sampling

From each lot, take the quantity of stoppers that correspond to the sampling plan previously agreed between the interested parties.

Stoppers from the sample shall not show visible defects that may interfere with the performance of the measurement, namely:

- stoppers with an abnormal shape (asymmetric, truncated, bevelled);
- stoppers with gutters or belly irregularities.

## 7 Procedure

Before testing, each stopper shall be numerated.

Measure the diameter of each stopper from the sample with the vernier gauge (4.1). The diameter of natural cork stoppers is measured at the perpendicular to the cork growth layers. Measurements are carried out according to ISO 9727-1.

Register the result. The result of this first measurement is called  $D_1$ .

Using a pen or any other appropriate object, mark the contact points of the vernier gauge stand on the stopper.

Introduce the stopper into the bottling machine (4.2). Compress the stopper (diameter of compression jaws between 15,5 mm and 16 mm). Then eject the stopper, as though this happens during bottling.

Take the stopper from the bottling machine jaws.

Three minutes later, measure the stopper diameter again, on the marked contact points. Register the value obtained. The result of this second measurement is called  $D_2$ .

## 8 Results

The percentage of diameter recovery after compression of the stopper is given by the equation:

$$\frac{D_2}{D_1} \times 100$$

rounded off to the nearest unit.

The final test result is the arithmetic average of the results obtained with each stopper from the test sample, expressed in percentage, rounded off to the nearest unit, and also the standard deviation.



## 9 Test report

The test report shall include the following information:

- a) a reference to this part of ISO 9727;
- b) complete identification of the sample, including its type and origin;
- c) sampling report;
- d) results obtained;
- e) any deviation from this part of ISO 9727 that may have affected the results.



---

---

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.  
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.  
Fax: +44 (0)20 8996 7001. Email: [orders@bsi-global.com](mailto:orders@bsi-global.com). Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.  
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: [info@bsi-global.com](mailto:info@bsi-global.com).

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.  
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.  
Email: [membership@bsi-global.com](mailto:membership@bsi-global.com).

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.  
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.  
Email: [copyright@bsi-global.com](mailto:copyright@bsi-global.com).

BSI

389 Chiswick High Road  
London  
W4 4AL

This document is now  
**PUBLIC**