

BS ISO 9940:2015



BSI Standards Publication

# Aerospace series — Fluid, hydraulic, phosphate ester- base, fire resistant — Technical specification

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of ISO 9940:2015.

The UK participation in its preparation was entrusted to Technical Committee ACE/69, Aerospace hydraulic systems, fluids and components.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015. Published by BSI Standards Limited 2015

ISBN 978 0 580 72835 8

ICS 49.080

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 August 2015.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

INTERNATIONAL  
STANDARD

**ISO**  
**9940**

First edition  
2015-08-01

---

---

**Aerospace series — Fluid, hydraulic,  
phosphate ester-base, fire resistant —  
Technical specification**

*Série aérospatiale — Fluide, hydraulique, esters phosphoriques,  
résistant au feu — Spécification technique*



Reference number  
ISO 9940:2015(E)



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

Page

Foreword .....	v
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Technical requirements .....</b>	<b>3</b>
3.1 General .....	3
3.2 Fluid types .....	3
3.3 Physical and chemical properties .....	3
3.4 Products and manufacturers qualification .....	4
3.5 Approved laboratories .....	4
<b>4 Qualification requirements .....</b>	<b>5</b>
4.1 Absolute kinematic viscosity " $\nu$ " .....	5
4.2 Water content "[H <sub>2</sub> O]" .....	6
4.3 Density " $\rho$ " .....	6
4.4 Acidity index " $AI$ " — Acid number " $AN$ " .....	6
4.5 Electrical conductivity " $\gamma$ " .....	6
4.6 Chemical content .....	7
4.6.1 Chlorine .....	7
4.6.2 Other components .....	7
4.7 Pour point temperature .....	7
4.8 Flash point and fire point temperatures .....	8
4.9 Auto-ignition temperature .....	8
4.10 Flammability test .....	8
4.10.1 Determination of wick flame persistence .....	8
4.10.2 Spray ignition test .....	8
4.10.3 Manifold-Ignition test on a hot element .....	8
4.11 Colour — Condition .....	9
4.12 Bulk modulus (Isothermal secant) .....	9
4.13 Thermal expansion coefficient " $\alpha$ " .....	11
4.14 Dielectric resistance .....	11
4.15 Specific heat " $C_p$ " .....	11
4.16 Solid particulate contamination .....	11
4.16.1 General .....	11
4.16.2 Particle counting .....	11
4.16.3 Filterability " $F$ " .....	12
4.17 Foaming .....	12
4.18 Toxicity .....	12
4.19 Stability .....	13
4.19.1 Shear stability .....	13
4.19.2 Thermal, corrosion and oxidation stability .....	13
4.20 In-service lifetime .....	15
4.20.1 General .....	15
4.20.2 Ampoule test method .....	16
4.20.3 "1 Litre-Container" Test method for fire resistance requirement in accordance with 4.8 .....	18
4.21 Material compatibility with qualified fluids (see list provided by the airframe manufacturer) .....	18
4.21.1 Compatibility with qualified fluids .....	18
4.21.2 Compatibility with elastomeric materials .....	19
4.21.3 Compatibility with paints .....	20
4.21.4 Compatibility with electrical aircraft components .....	20
4.21.5 Compatibility with structural elements: adhesive, metallic parts (including tubes), composites .....	20
4.22 Lubrication .....	20

4.23	Erosion tests of the hydraulic fluid.....	21
4.23.1	General.....	21
4.23.2	Test 1 — Erosion System Test Bench representative of one aircraft hydraulic system.....	21
4.23.3	Test 2 — Pumping Test.....	21
4.23.4	Test 3 — Erosion Resistance Tests.....	21
<b>5</b>	<b>Batches.....</b>	<b>21</b>
<b>6</b>	<b>Quality control.....</b>	<b>21</b>
6.1	Hydraulic fluid acceptance tests.....	21
6.2	Physical characteristics.....	21
6.3	Chemical characteristics.....	22
<b>7</b>	<b>Recommended limits.....</b>	<b>22</b>
<b>8</b>	<b>Marking.....</b>	<b>22</b>
<b>9</b>	<b>Packing and storage.....</b>	<b>22</b>
<b>Annex A</b>	<b>(normative) Elastomer compatibility.....</b>	<b>24</b>
<b>Annex B</b>	<b>(informative) Erosion tests.....</b>	<b>26</b>
<b>Annex C</b>	<b>(normative) Fluid monitoring after A/C delivery.....</b>	<b>27</b>
<b>Bibliography</b>	<b>.....</b>	<b>28</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 20, *Aircraft and space vehicles*, Subcommittee SC 10, *Aerospace fluid systems and components*.





# Aerospace series — Fluid, hydraulic, phosphate ester-base, fire resistant — Technical specification

## 1 Scope

This International Standard defines technical requirements, qualification and quality control conditions (product qualification, batch control, acceptance) test and measurement methods to be used by manufacturers for qualification of fire-resistant phosphate-ester-base fluids used for hydraulic transmissions in aircrafts.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 37, *Rubber, vulcanized or thermoplastic — Determination of tensile stress-strain properties*

ISO 48, *Rubber, vulcanized or thermoplastic — Determination of hardness (hardness between 10 IRHD and 100 IRHD)*

ISO 1817, *Rubber, vulcanized or thermoplastic — Determination of the effect of liquids*

ISO 2592, *Determination of flash and fire points — Cleveland open cup method*

ISO 2921, *Rubber, vulcanized — Determination of low-temperature retraction (TR test)*

ISO 3016, *Petroleum products — Determination of pour point*

ISO 3104, *Petroleum products — Transparent and opaque liquids — Determination of kinematic viscosity and calculation of dynamic viscosity*

ISO 3116, *Magnesium and magnesium alloys — Wrought magnesium alloys*

ISO 3675, *Crude petroleum and liquid petroleum products — Laboratory determination of density — Hydrometer method*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

ISO 4407, *Hydraulic fluid power — Fluid contamination — Determination of particulate contamination by the counting method using an optical microscope*

ISO 6247, *Petroleum products — Determination of foaming characteristics of lubricating oils*

ISO 6618, *Petroleum products and lubricants — Determination of acid or base number — Colour-indicator titration method*

ISO 6619, *Petroleum products and lubricants — Neutralization number — Potentiometric titration method*

ISO 11171, *Hydraulic fluid power — Calibration of automatic particle counters for liquids*

ISO 11218, *Aerospace — Cleanliness classification for hydraulic fluids*

ISO 11500, *Hydraulic fluid power — Determination of the particulate contamination level of a liquid sample by automatic particle counting using the light-extinction principle*

ISO 12185, *Crude petroleum and petroleum products — Determination of density — Oscillating U-tube method*

ISO 12937, *Petroleum products — Determination of water — Coulometric Karl Fischer titration method*

ISO 13357-2, *Petroleum products — Determination of the filterability of lubricating oils — Part 2: Procedure for dry oils*

ISO 13573:2012, *Corrosion of metals and alloys — Test method for thermal-cycling exposure testing under high-temperature corrosion conditions for metallic materials*

ISO 14935, *Petroleum and related products — Determination of wick flame persistence of fire-resistant fluids*

ISO 15029-1, *Petroleum and related products — Determination of spray ignition characteristics of fire-resistant fluids — Part 1: Spray flame persistence — Hollow-cone nozzle method*

ISO 15597, *Petroleum and related products — Determination of chlorine and bromine content — Wavelength-dispersive X-ray fluorescence spectrometry*

ISO 20823, *Petroleum and related products — Determination of the flammability characteristics of fluids in contact with hot surfaces — Manifold ignition test*

EN 1652, *Copper and copper alloys — Plate, sheet, strip and circles for general purposes*

EN 2395, *Aerospace series — Aluminium alloy AL-P2024A — T4 or T42 — Sheet and strip —  $0,4 \text{ mm} \leq a \leq 6 \text{ mm}$*

EN 10130, *Cold rolled low carbon steel flat products for cold forming — Technical delivery conditions*

ASTM D 92<sup>1)</sup>, *Standard Test Method for Flash and Fire Points by Cleveland Open Cup Tester*

ASTM D 97<sup>1)</sup>, *Standard Test Method for Pour Point of Petroleum Products*

ASTM D 445<sup>1)</sup>, *Standard Test Method for Kinematic Viscosity of Transparent and Opaque Liquids (and Calculation of Dynamic Viscosity)*

ASTM D 664<sup>1)</sup>, *Standard Test Method for Acid Number of Petroleum Products by Potentiometric Titration*

ASTM D 877<sup>1)</sup>, *Standard Test Method for Dielectric Breakdown Voltage of Insulating Liquids Using Disk Electrodes*

ASTM D 892<sup>1)</sup>, *Standard Test Method for Foaming Characteristics of Lubricating Oils*

ASTM D 974<sup>1)</sup>, *Standard Test Method for Acid and Base Number by Color-Indicator Titration*

ASTM D 1217<sup>1)</sup>, *Standard Test Method for Density and Relative Density (Specific Gravity) of Liquids by Bingham Pycnometer*

ASTM D 1298<sup>1)</sup>, *Standard Test Method for Density, Relative Density, or API Gravity of Crude Petroleum and Liquid Petroleum Products by Hydrometer Method*

ASTM D 2155<sup>1)</sup>, *Standard Test Method for Determination of Fire Resistance of Aircraft Hydraulic Fluids by Autoignition Temperature*

ASTM D 4052<sup>1)</sup>, *Standard Test Method for Density, Relative Density, and API Gravity of Liquids by Digital Density Meter*

ASTM D 4172<sup>1)</sup>, *Standard Test Method for Wear Preventive Characteristics of Lubricating Fluid (Four-Ball Method)*

ASTM D 4636<sup>1)</sup>, *Standard Test Method for Corrosiveness and Oxidation Stability of Hydraulic Oils, Aircraft Turbine Engine Lubricants, and Other Highly Refined Oils*

---

1) Published by: ASTM International [www.astm.org](http://www.astm.org)

ASTM D 5621<sup>1)</sup>, *Standard Test Method for Sonic Shear Stability of Hydraulic Fluids*

ASTM D 6304<sup>1)</sup>, *Standard Test Method for Determination of Water in Petroleum Products, Lubricating Oils, and Additives by Coulometric Karl Fischer Titration*

ASTM D 6443<sup>2)</sup>, *Test Method for Determination of Calcium, Chlorine, Copper, Magnesium, Phosphorus, Sulfur, and Zinc in Unused Lubricating Oils and Additives by Wavelength Dispersive X-ray Fluorescence Spectrometry (Mathematical Correction Procedure)*

ASTM D 6793<sup>2)</sup>, *Standard Test Method for Determination of Isothermal Secant and Tangent Bulk Modulus*

ASTM E 1269<sup>2)</sup>, *Standard Test Method for Determining Specific Heat Capacity by Differential Scanning Calorimetry*

DEF STAN 03-19<sup>3)</sup>, *Electro-Deposition of Cadmium*

### 3 Technical requirements

#### 3.1 General

The product shall be a fire resistant, phosphate ester-base fluid for hydraulic power transmissions. Its chemical composition (additives, contaminants) and intrinsic physical and chemical properties shall be in strict compliance with the requirements of this International Standard.

All delivered hydraulic fluids shall be fully compatible with any other phosphate ester-base fluid already qualified, whatever the mixture proportions.

In the following clauses, the International Standard appearing in brackets shall be considered as an alternative method to the preceding standard, e.g. ISO 3104 (ASTM D 445); ASTM D 445 is an alternative standard to ISO 3104.

#### 3.2 Fluid types

Fluids types covered by this International Standard are listed in the [Table 1](#) with their corresponding properties.

**Table 1 — Type of fluid and properties**

Type of fluid		Fluid properties
IV	"HD" (High Density)	Fire resistant, low water content, anti-erosion, high viscosity at low temperature and high density
	"LD" (Low Density)	Fire resistant, low water content, anti-erosion, low density
V	(Low Density)	Fire resistant, low water content, low density, anti-erosion, improved thermal stability and in service lifetime.

#### 3.3 Physical and chemical properties

The main physical and chemical properties of the fluid covered by this International Standard are listed in the [Table 2](#).

2) Published by: ASTM International [www.astm.org](http://www.astm.org)

3) Published by: MINISTRY OF DEFENCE (United Kingdom) [www.gov.uk/government/organisations/ministry-of-defence](http://www.gov.uk/government/organisations/ministry-of-defence)

### 3.4 Products and manufacturers qualification

The qualified products list appears in the AMM (Aircraft Maintenance Manual).

### 3.5 Approved laboratories

All laboratories used should be ISO 9001 registered and AS/EN/JIS Q 9100 compliant.

**Table 2 — Main characteristics and properties**

Property	Unit	Condition	Requirements		Test method(s)		Sub clause
	Symbol		TYPE IV	TYPE V	Preferred International Standard	Alternative International Standard	
Absolute kinematic viscosity	mm <sup>2</sup> ·s <sup>-1</sup> (centiStokes) "ν"	-54 °C (-65 °F) 38 °C (100 °F) 99 °C (210 °F) Atmospheric pressure	HD: ≤ 2 900 LD: ≤ 2 000	LD: ≤ 2 000	ISO 3104	ASTM D 445	<a href="#">4.1</a>
			∈ [ 9,00; 12,50] ∈ [3,00; 4,00]				
Water content	H <sub>2</sub> O % mass or ppm <sup>a</sup>	—	≤0,20 or 2 000		ISO 12937 <sup>b</sup>	ASTM D 6304	<a href="#">4.2</a>
Density	kg·m <sup>-3</sup> "ρ"	(23 ± 3) °C	1 021 ≤ HD ≤ 1 066 LD: ≤ 1 020	LD: ≤ 1 020	ISO 3675 or ISO 12185	ASTM D 1298 D 4052 or D 1217	<a href="#">4.3</a>
Acid number Acidity index	mg KOH per g of fluid	—	≤0,10		ISO 6618 or ISO 6619	ASTM D 974 or D 664	<a href="#">4.4</a>
Electrical conductivity	μS·cm <sup>-1</sup> "γ"	20 °C (-10 °C to 100 °C)	≥0,30 ∈ [0,02 ; 6,00]		ISO 9940	—	<a href="#">4.5</a>
Chlorine content	Cl <sup>-</sup> ppm <sup>a</sup>	Tot. chlorine	≤50		ISO 15597	ASTM D 6443	<a href="#">4.6</a>
Pour point temperature	°C (°F)	—	≤ -62 (-80)		ISO 3016	ASTM D 97	<a href="#">4.7</a>
Flash point temperature			≥160 ( 320)		ISO 2592	ASTM D 92	<a href="#">4.8</a>
Fire point temperature			≥177 (350)				
Auto ignition temperature			≥399 (750) ≥460 (860) for HD	≥399 (750)	ASTM D 2155	—	<a href="#">4.9</a>
Flammability	Seconds	5 s, 10 s, 20 s and 30 s	Mean persistence time of the flame < 7,5 s		ISO 14935	—	<a href="#">4.10.1</a>
	Seconds	—	Time elapsed between removal of the igniting flame and extinction of the spray along the spray pattern ≤ 4 s		ISO 15029-1	—	<a href="#">4.10.2</a>
	Ignition category	700 °C ± 5 °C	k <sub>m</sub> ≥ 10		ISO 20823	—	<a href="#">4.10.3</a>

<sup>a</sup> ppm = parts per million = μg·g<sup>-1</sup> (10<sup>-6</sup>).

<sup>b</sup> Deviation to ISO 12937 is granted for water content above 0,1.

Table 2 (continued)

Property	Unit	Condition	Requirements		Test method(s)		Sub clause
	Symbol		TYPE IV	TYPE V	Preferred International Standard	Alternative International Standard	
Colour condition	—	—	Purple Clear appearance		—	—	4.11
Isothermal secant Bulk Modulus	Pa	38 °C, 20,6·10 <sup>6</sup> Pa	Mini value: 1 450·10 <sup>6</sup> Pa		ASTM D 6793	—	4.12
Thermal expansion	°C <sup>-1</sup> “α”	-25 °C to 99 °C	≤1·10 <sup>-3</sup>		ASTM D 1217	—	4.13
		-54 °C to 110 °C	Curve to provide				
Solid particulate contamination (counting)	Cleanliness class	—	≤7		ISO 11218 ISO 11171 ISO 11500 or ISO 4407	—	4.16
			Filterability				
			∈ [1,00 ; 1,60]		ISO 13357-2	—	
Foaming	cm <sup>3</sup>	24 °C	After 5 min ≤250 ≤150 ≤450	Persistence ≤100 s ≤50 s 250 s	ISO 6247	ASTM D 892	4.17
		93 °C					
		24 °C					

a ppm = parts per million = μg·g<sup>-1</sup> (10<sup>-6</sup>).

b Deviation to ISO 12937 is granted for water content above 0,1.

## 4 Qualification requirements

### 4.1 Absolute kinematic viscosity “ν”

Absolute kinematic viscosity “ν” of the fluid shall be determined at the temperatures indicated below and at atmospheric pressure using viscosimetric capillary tubes in accordance with ISO 3104 (ASTM D 445). The limits values are in mm<sup>2</sup>·s<sup>-1</sup> (centiStokes), see Table 3.

Table 3 — Viscosity limit values

Temperatures		Type	
°C	°F	IV High Density	IV & V Low Density
-54	-65	ν ≤ 2 900	ν ≤ 2 000
-40	-40	Values to be measured and provided	
-15	5		
38	100	9,00 ≤ ν ≤ 12,50	
99	210	3,00 ≤ ν ≤ 4,00	

Measurements shall be taken in a thermostatic bath at accurate temperatures, controlled using an accurate contacting thermometer in accordance with ISO 3104 (ASTM D 445).

NOTE At low temperatures, viscosimetric tubes may be connected to dehydration tubes to avoid condensation forming inside.

An evolution curve “Viscosity vs. Temperature” from -54 °C to 99 °C is requested.

#### 4.2 Water content “[H<sub>2</sub>O]”

The water content [H<sub>2</sub>O] shall be determined

- by using the electrochemical method “KARL FISCHER” in compliance with ISO 12937 (ASTM D 6304).

The limit value shall be

- [H<sub>2</sub>O] ≤ 0,20 % mass, or
- [H<sub>2</sub>O] ≤ 2 000 ppm.

#### 4.3 Density “ $\rho$ ”

The density “ $\rho$ ” shall be determined at (23 ± 3) °C in compliance with ISO 3675 (ASTM D 1298) or ASTM D 1217 (Pycnometer) or ISO 12185 (ASTM D 4052) (this method is based on the measurement of the harmonic period of fluid in a U-shape tube).

The corrected limit values at 20 °C, in kg·m<sup>-3</sup>, shall be as follows:

- Type IV High Density: 1 021 ≤  $\rho$  ≤ 1 066;
- Type IV & V Low Density:  $\rho$  ≤ 1 020.

An evolution curve “Density vs. Temperature” from -40 °C to 100 °C is requested.

#### 4.4 Acidity index “*AI*” — Acid number “*AN*”

The Acid number “*AN*” of the fluid shall be determined using the colour indicator titration method in accordance with ISO 6618 (ASTM D 974) or the Acidity index “*AI*” of the fluid shall be determined using the potentiometric titration method in accordance with ISO 6619 (ASTM D 664).

The limit value, in mg KOH per gram of fluid shall be:

*AI* or *AN* ≤ 0,10

#### 4.5 Electrical conductivity “ $\gamma$ ”

Test equipment:

- cell immersed in hydraulic fluid
- impedance bridge (conductimeter)

Measurement conditions:

- frequency: 50 Hz
- temperature = (20 ± 3) °C
- cell constant  $K \in [0,7; 1,2]$  cm

Electrical resistance “*R*” shall be measured across the terminals of the cell.

The electrical conductivity is:

$$\gamma = L \cdot R^{-1} \cdot S^{-1} = K \cdot R \quad (1)$$

where

- $R$  is the resistance, in Ohms ( $\Omega$ );
- $K$  is the cell constant, in  $\text{cm} = S \cdot L^{-1}$ ;
- $S$  is the surface area of electrodes, in  $\text{cm}^2$ ;
- $L$  is the gap between electrodes, in cm.

The corrected value at 20 °C in  $\mu\text{S cm}^{-1}$ , shall be

- Normal limit:  $\gamma \geq 0,30$ .

The value between -10 °C and 100 °C in  $\mu\text{S cm}^{-1}$ , shall be

- $\gamma \in [0,02; 6,00]$  ( $\mu\text{S} = \text{microSiemens} = 10^{-6} \text{ Siemens} = 10^{-6} \Omega^{-1} = 10^{-6} \text{ Mho}$ ).

An evolution curve “Conductivity vs. Temperature” from -40 °C to 100 °C is requested.

## 4.6 Chemical content

### 4.6.1 Chlorine

The Total Chlorine concentration limit shall be:

Total Chlorine  $\leq 50$  ppm

Methods to be used are Wavelength dispersive X-ray fluorescence spectrometry (see ISO 15597 or ASTM D 6443) or other methods provided acceptable to aircraft manufacturer.

### 4.6.2 Other components

During qualification, chemical contents (all fluids) in ppm (parts per million) or  $\mu\text{g}\cdot\text{g}^{-1}$  ( $10^{-6}$ ) as Calcium, Potassium, Sulphur, Sodium shall be duly identified when these elements are formulation additives and their fluid limit concentration shall be determined by fluid manufacturers. All other additives not duly identified in the fluid manufacturer formulation will be considered as contaminant and consequently prohibited, except total chlorine when its concentration is as follows:

- TYPE IV/[CL]  $\leq 50$  ppm;
- TYPE V/[CL]  $\leq 50$  ppm.

Method to be used is Wavelength Dispersive X-Ray Fluorescence spectrometry (ASTM D 6443) or other methods provided acceptable to aircraft manufacturer.

## 4.7 Pour point temperature

Pour point temperature shall be determined in compliance with ISO 3016 (ASTM D 97).

- Pour point  $\leq -62$  °C ( $-80$  °F)



## 4.8 Flash point and fire point temperatures

Flash point and fire point temperatures shall be determined in an open vessel using the CLEVELAND method in compliance with ISO 2592 (ASTM D 92).

- Flash point:  $\geq 160$  °C (320 °F)
- Fire point:  $\geq 177$  °C (351 °F)

To determine degradation of these characteristics, fluid shall be tested in laboratory conditions in accordance with "1 Litre-Container" test method described in [4.20.3](#) until an Acidity index of  $1,5 \pm 0,3$  has been reached (in keeping with the required time-temperature exposure under linked water and chlorine contamination conditions).

## 4.9 Auto-ignition temperature

Auto-ignition temperature shall be determined in compliance with ASTM D 2155.

- Auto-ignition:  $\geq 399$  °C (750 °F) Type IV Low Density and Type V
- Auto-ignition:  $\geq 460$  °C (860 °F) Type IV High Density

## 4.10 Flammability test

### 4.10.1 Determination of wick flame persistence

This determination of wick flame persistence is in accordance with ISO 14935, except the limits and pass criteria.

The limits and pass criteria shall be

- mean persistence time of flame MP  $< (7,5 \pm 0,1)$  s.

### 4.10.2 Spray ignition test

This spray ignition test is in accordance with ISO 15029-1, except the limits and pass criteria.

Limits and pass criteria shall be as follows:

- flashes readily and self-extinguishes;
- maximum time, to the nearest 0,1 s, between removal of the igniting flame and extinction of the spray combustion, at different positions along the length of a pressurized spray of fluid under the conditions specified in ISO 15029-1 shall not exceed 4 s.

### 4.10.3 Manifold-Ignition test on a hot element

The test equipment is in accordance with ISO 20823, except the limits and pass criteria.

The limits and pass criteria  $k_m$  (Points of Part a + Part b) shall be in accordance with [Table 4](#), with the exposure of the fluid within  $(35 \pm 5)$  s on to the surface.



**Table 4 — Flammability conditions and criteria**

Fluid poured on	Part	Appreciation	Points	$k_m$
a) the tube	a	Burns does not burn	0 +5	$a + b \geq +10$
b) the bottom of the protector	b	Burns lights up does not burn	0 +5 +10	

#### 4.11 Colour — Condition

The new fluid shall be of a purple colour.

New fluid shall be clear and homogeneous without any solid suspended matter.

The colour and condition of the new fluid shall be inspected under white light shone through a glass test tube approximately 45 mm in diameter, filled with fluid.

#### 4.12 Bulk modulus (Isothermal secant)

The average bulk modulus will be determined in accordance with method given below, or by an alternate method described and based on ASTM D 6793.

The isothermal secant bulk modulus  $\beta_{is}$  is defined by Formula (2).

$$\beta_{is} = - \left[ V_0 \cdot \left( \frac{\Delta P}{\Delta V} \right) \right]_T \quad (2)$$

where

$\Delta P$  is the difference between final and initial pressure;


$\Delta V$  is the difference between final and initial volumes of the hydraulic fluid;

$V_0$  is the initial volume of the hydraulic fluid.

Test set-up:

- A coil of  $(12,7 \pm 0,254)$  mm by  $(1,244\ 6 \pm 0,050\ 8)$  mm [ $(0,5 \pm 0,01)$  inch by  $(0,049 \pm 0,002)$  inch] 304 stainless steel tubing is used as the fluid receiver. This coil is installed in an oven, which is used as a heat source.
- The test fluid is pumped into the receiver with an air driven pump and the pressure is read on a pressure gauge (graduated in 0,69 bar increments). The fluid temperature is monitored with thermocouples inserted into the top and bottom of the coil.

Bulk modulus determination set-up shall be in accordance with [Figure 1](#).

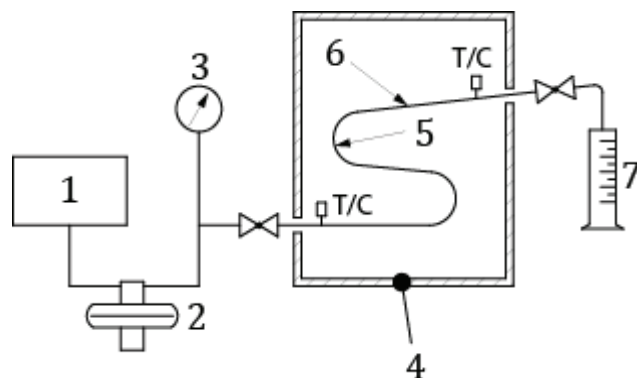

**Key**

- |   |   |   |  |
|---|---|---|--|
| 1 | reservoir   | 5 | 0,50 inch long by 0,049 inch diameter tubing |
| 2 | pump  | 6 | $V_0 = 1\,195\text{ cm}^3$                   |
| 3 | pressure gauge(0 to $34,47 \cdot 10^6$ ) Pa [(0 to 350) bars] | 7 | 100 ml graduated cylinder                    |
| 4 | temperature controlled chamber                                |   |  |

**Figure 1 — Bulk modulus determination set-up**

**Test procedure:**

- After determining the volume of the fluid receiver by filling it with water and then draining into a beaker, determine the coefficient of expansion of the test fluid. This is done by heating  $(60 \pm 1)\text{ cm}^3$  of the test fluid in a 100 ml graduated cylinder and recording the increase in temperature required to increase the volume  $1\text{ cm}^3$ .
- After the receiver has been filled and bled of air, adjust the system to  $(20,6 \pm 0,17)\text{ MPa}$  and  $(38 \pm 3)\text{ }^\circ\text{C}$ . Then close the inlet valve and open the outlet valve.
- The compressed fluid expands to atmospheric pressure, and the volume of fluid associated with raising the pressure in the receiver to the desired level is recorded. Collect the effluent until the temperature of the fluid in the coil returns to  $38\text{ }^\circ\text{C}$  ( $100\text{ }^\circ\text{F}$ ). Special attention shall be made to the time required for the fluid to return to  $38\text{ }^\circ\text{C}$ . This time shall be as short as possible preventing any influence of the fluid relaxation (thermoviscoelasticity) on the measured volume. Record this value along with the temperature of the effluent at the time of reading.

**Method of computation:**

- The secant bulk modulus is the total change in fluid pressure, divided by the total change in fluid volume per unit volume, under pressure.

$$B = -V_0 \cdot \left( \frac{P - P_0}{V - V_0} \right) \quad (3)$$

where

- $B$  is the isothermal secant bulk modulus, in Pa;
- $P$  is the pressure, in Pa;
- $P_0$  is the initial pressure, in Pa (usually atmospheric pressure);
- $V_0$  is the volume at  $P_0$  (receiver volume);
- $V$  is the volume at  $P$  ( $V_0$  minus effluent volume).

- b) Correct the volume of the receiver for changes due to pressure and temperature. Correct the effluent volume for the difference between its temperature at the time of reading and its temperature when it is in the receiver.
- c) Report the average Isothermal secant bulk modulus.

#### **4.13 Thermal expansion coefficient “ $\alpha$ ”**

Thermal expansion shall be determined in compliance with the method described in ASTM D 1217.

Thermal expansion “ $\alpha$ ” shall be  $\leq 1 \cdot 10^{-3} \text{ } ^\circ\text{C}^{-1}$  for  $\Delta t$  of between  $-25 \text{ } ^\circ\text{C}$  to  $99 \text{ } ^\circ\text{C}$ .

The complete curve between  $-54 \text{ } ^\circ\text{C}$  and  $110 \text{ } ^\circ\text{C}$  has to be provided.

#### **4.14 Dielectric resistance**

Dielectric resistance shall be determined in compliance with the method ASTM D 877.

The fluid manufacturer shall indicate the value measured on the test fluid.

#### **4.15 Specific heat “ $C_p$ ”**

Specific heat “ $C_p$ ” shall be determined at atmospheric pressure in compliance with ASTM E 1269 method (Differential Scanning Calorimetric method).

—  $C_p$  isothermal curve for the following temperatures:  $(-15; 20; 38; 99; 120) \text{ } ^\circ\text{C}$ .

The manufacturer shall indicate the values measured on the test fluid. No limit value is set.

#### **4.16 Solid particulate contamination**

##### **4.16.1 General**

The filtering membranes compatible with phosphate esters (PA 6.6, PTFE, POM...) with a pore dimension of  $1 \text{ } \mu\text{m}$  will be used with trichloroethylene or petroleum spirit filtered at  $1 \text{ } \mu\text{m}$  as a solvent.

##### **4.16.2 Particle counting**

Particle counting shall be determined in compliance with the method described in ISO 4407 for an optical microscope particle counts and in ISO 11171 and ISO 11500 for an automatic particle counting. Contamination class expressed according to ISO 11218 shall be less than or equal to class 7 as described in [Table 5](#).

**Table 5 — Characteristics for new fluid**

Particle size $\mu\text{m}^{\text{a}}$ or $\mu\text{m}(\text{c})^{\text{b}}$	Particles/100 $\text{cm}^3$
(5 incl. to 15 incl.) $\mu\text{m}$ or (6 incl. to 14 incl.) $\mu\text{m}(\text{c})$	$\leq 32\ 000$
(15 excl. to 25 incl.) $\mu\text{m}$ or (14 excl. to 21 incl.) $\mu\text{m}(\text{c})$	$\leq 5\ 700$
(25 excl. to 50 incl.) $\mu\text{m}$ or (21 excl. to 38 incl.) $\mu\text{m}(\text{c})$	$\leq 1\ 012$
(50 excl. to 100 incl.) $\mu\text{m}$ or (38 excl. to 70 incl.) $\mu\text{m}(\text{c})$	$\leq 180$
Over 100 $\mu\text{m}$ (Including fibres) — or over 70 $\mu\text{m}(\text{c})$	$\leq 32$
Contamination class	$\leq 7$
NOTE Limits: incl. = included excl. = excluded <sup>a</sup> Size range, optical microscope particle counts, based on longest dimension as measured per ISO 4407. <sup>b</sup> Size range, automatic particle count with an APC calibrated per ISO 11171 and used per ISO 11500 or an optical or electron microscope with image analysis software, based on projected area equivalent diameter.	

#### 4.16.3 Filterability “F”

The filterability test is performed in accordance with ISO 13357-2, with the exception that only membranes, compatible with phosphate esters, are to be used.

Suggestion use: PTFE filtering membranes welded to a polyethylene grid, pore dimension 1  $\mu\text{m}$ ,  $\varnothing = 47$  mm, (example: MILLIPORE/Type FA/Ref. FALP 047FI).

NOTE Filterability is not strictly an intrinsic physical property of the fluid but rather a means of gauging its hydraulic behaviour. The method, with a repeatability of 5 %, consists in comparing the flow rate under constant pressure of a fluid through different filters, during the test.

#### 4.17 Foaming

A foaming test shall be performed in accordance with ISO 6247 (ASTM D 892) on a first test sample at 24 °C, and on a second test sample at 93 °C and at 24 °C once the foam has disappeared.

Test equipment: bubbling apparatus

- a) Tendency to foam: Volume of foam shall be measured after bubbling for 5 min. Maximum volume of foam is given in [Table 6](#).
- b) Foam persistence: No foam shall remain after bubbling past a certain period of time given in [Table 6](#).

**Table 6 — Foaming conditions and criteria**

Sample	Temperature °C	Tendency to foam $\text{cm}^3$	Foam persistence time s
First	24	$\leq 250$	$\leq 100$
Second	93	$\leq 150$	$\leq 50$
	24	$\leq 450$	$\leq 250$

#### 4.18 Toxicity

The manufacturer shall specify the toxicity characteristics of the hydraulic fluid according to the local and national regulations.

## 4.19 Stability

### 4.19.1 Shear stability

Shear stability using a sonic oscillator shall be determined in compliance with ASTM D 5621.


After testing, the absolute kinematic viscosity of the fluid shall be measured at  $(38 \pm 0,02) \text{ }^\circ\text{C}$  and atmospheric pressure as indicated in [4.1](#).

The value measured shall not vary by more than 25 % with respect to that obtained with a new fluid, also at  $(38 \pm 0,02) \text{ }^\circ\text{C}$ .

### 4.19.2 Thermal, corrosion and oxidation stability

#### 4.19.2.1 Test conditions and requirements

The fluid shall be tested after immersion of metal test pieces (see [Table 7](#)) assembled in accordance with [Figure 2](#).

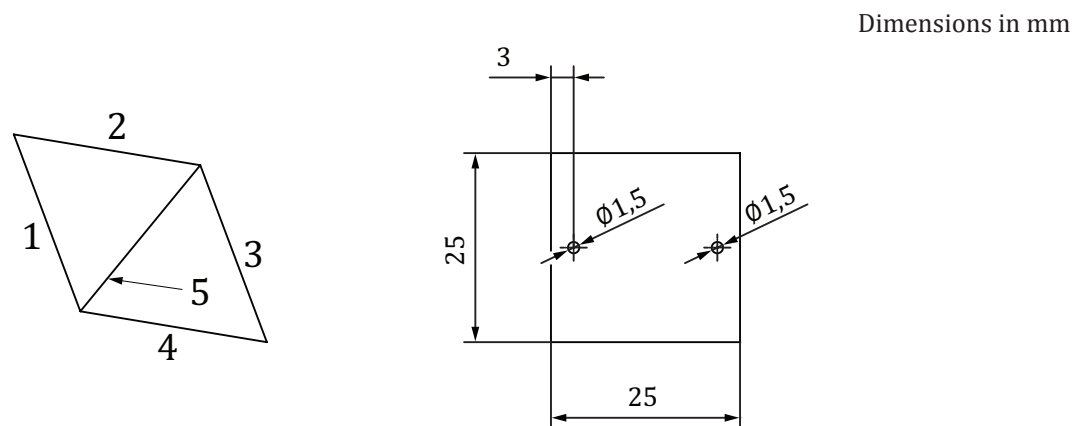

#### Key

1	Al	4	Cu
2	Mg	5	Cadmium-plated steel
3	Steel		

**Figure 2 — Arrangement of metal test pieces**

The metal test pieces materials definitions are described in [Table 7](#). The polishing of the metal test pieces shall be finished by machining in accordance with ISO 13573:2012, 4.1.1.

**Table 7 — Metal test piece material definition**

Tests conditions	Surface finish	Requirements in accordance with ASTM D 4636		Figure 2 reference
Materials	Polished	Cu-ETP R240	According to EN 1652	4
	Polished	Al-P2024A-T4	According to EN 2395	1
	Polished	ISO-MgAl3Zn1(A)-0 (annealed)	According to ISO 3116	2
	Polished	Steel DC04	According to EN 10130	3
	Unpolished	Cadmium plated but not passivated	According to DEF-STAN 03-19	5

Tests shall be performed on metal test pieces after immersion in the fluid. The magnesium, aluminium, copper and steel test pieces shall be placed so that they form a diamond, and the cadmium-plated steel test piece placed diagonally, keeping strictly to the order indicated. The edges around the holes of the metal test pieces may be touching, but the magnesium test piece shall not touch the copper piece under any circumstances in order to avoid galvanic coupling. The metal test pieces assembly shall be held in place by threads that are not affected by phosphate esters (polyamide 6.6, flax fibre, etc.).

Perform the following at the end of each immersion cycle indicated in [4.19.2.2](#).

- Examine each metal test piece for corrosion.
- Determine the fluid's oxidation resistance.
- Evaluate the physical and chemical characteristics of the unfiltered fluid.
- Metal test pieces shall be examined for corrosion after removing any traces of grease, and their corrosion stability determined by measuring the variation in mass per surface area in  $\text{mg}\cdot\text{cm}^{-2}$ . No pitting, corrosion attacks or discoloration shall be visible on the surface of the metals when examined at a magnification of 20.
- The fluid's oxidation resistance shall be determined by identifying variations in its viscosimetric properties, acidity index, visual appearance (precipitation of insoluble substances, gumming, turbidity, etc.) and discoloration.
- Fluid loss through evaporation shall be  $\leq 8\%$  in weight.
- Absolute kinematic viscosity measured as defined in [4.1](#) above shall not deviate from the value measured on new fluid by more than
  - a)  $\pm 3,00 \text{ mm}^2\cdot\text{s}^{-1}$  maximum at  $(38 \pm 0,02)^\circ\text{C}$ , and
  - b)  $\pm 1,00 \text{ mm}^2\cdot\text{s}^{-1}$  maximum at  $(99 \pm 0,02)^\circ\text{C}$ .
- The increase of acid number per gram of fluid, measured as defined in [4.4](#), shall be:  $\Delta AN \leq 0,5 \text{ mg KOH/g}$ .

The test conditions will be specified subsequently.

#### 4.19.2.2 Thermal stability

The test shall be performed in initial condition with a maximum value of: i.e.  $[\text{H}_2\text{O}] = 1\,000 \text{ ppm}$  and the set-up conditions are defined in [4.19.2.1](#).

Test containers: flasks containing 1 litre of unfiltered fluid in delivery condition and divided into equal quantities in glass flasks, with air present above the fluid. The flasks shall be sealed with a tapered, ground glass stopper.

Test soaks:

- (135 ± 5) °C;
- (0; 150; 300; 600; 1 000; 1 500) h.

Six test flasks shall be exposed to dry heat at (135 ± 5) °C and soaked at each duration indicated above.

After each artificial ageing, soak

- absolute kinematic viscosity at (38 ± 0,02) °C and (99 ± 0,02) °C shall be measured (see 4.1), criteria is given in 4.19.2.1,
- the water content shall be measured (see 4.2), and
- acid number shall be measured (see 4.4), criteria is given in 4.19.2.1.

#### 4.19.2.3 Corrosion and oxidation stability

The set-up conditions for metal test pieces are defined in 4.19.2.1.

Test shall be performed in accordance with ASTM D 4636 standard for 168 h at the temperature of (80 ± 1) °C.

The following items shall be measured:

- absolute kinematic viscosity at (38 ± 0,02) °C and (99 ± 0,02) °C (see 4.1), criteria is given in 4.19.2.1;
- the water content (see 4.2);
- acid number (see 4.4), criteria is given in 4.19.2.1;
- metal test pieces variation in weight per surface area, see Table 8.

**Table 8 — Acceptable variation in weight per surface area**

Metals in contact with the fluid	Acceptable variation in weight per surface area (mg·cm <sup>-2</sup> )
Electrolytic copper	≤0,4
Aluminium 2024	≤0,1
Magnesium G-A3Z1	≤0,2
Steel XC18S	≤0,1
Cadmium-plated steel	≤0,4

## 4.20 In-service lifetime

### 4.20.1 General

Hereafter, both methods shall be used: the first, to determine the hydraulic fluid lifetime curves in Ampoules; and the second, to determine the Flash and Fire Point Temperature values in a 1 litre (L) container (due to the need of sufficient quantity of fluid for testing).

Therefore, the 1 litre container will be opened to measure the Flash and Fire Point Temperatures once the acid number reaches (1,5 ± 0,3) mg KOH/g.

## 4.20.2 Ampoule test method

### 4.20.2.1 General

This test method determines the time necessary for obtaining a variation of chemical properties of the fluid at a defined temperature. This method of test can be repeated at different isotherms.

### 4.20.2.2 Equipment

- borosilicate glass test tubes (50 ml);
- hypodermic syringe (50 ml with 90 mm needle);
- test tube rack;
- pipe cleaner;
- tweezers;
- glass paper (600 grain);
- paper towels;
- water complying with ISO 3696 grade 3;
- four glass pipettes with polyethylene capsules;
- rubber stopper;
- goggles;
- indelible marker pen “ONYX”;
- 250 ml glass beaker;
- acetone;
- steel wire, diameter 1,60 mm<sup>4)</sup>;
- copper wire, diameter 1,60 mm<sup>4)</sup>;
- ruler;
- cotton cloth;
- metal file;
- eight flasks (2 ml).

### 4.20.2.3 Test method

- Obtain the required fluid water content (following measurement method in [4.2](#)).
- Fill test tubes until approximately 85 % of fluid.
- Put a piece of copper wire and steel wire each test tube (cut to length to fit inside tube) and seal.
- Place the test tubes in an oven pre-heated to the required constant temperature and remove each test tube after exposing for the required period of time.

---

4) Used to simulate the metals in hydraulic systems that would tend to catalyse the hydrolysis reactions.



#### 4.20.2.4 Measurement (after fluid exposure)

- Absolute kinematic viscosity “ $\nu$ ”, following measurement method in [4.1](#)
- Acid number “AN”, following measurement method in [4.4](#)
- Electrical conductivity “ $\gamma$ ”, following measurement method in [4.5](#)


Fluid Lifetime curves shall be provided to show the evolution of fluid intrinsic characteristics  $\nu = f, g(t, T)$ ,  $AN = f, g(t, T)$  and  $\gamma = f, g(t, T)$ , up to reach their respective limit values, as specified in [Clause 7](#) of this International Standard, at  $(60 \pm 3)^\circ\text{C}$  ( $140^\circ\text{F}$ ) and  $(125 \pm 3)^\circ\text{C}$  to  $200^\circ\text{C}$  ( $392^\circ\text{F}$ ), with the hereafter water  $[\text{H}_2\text{O}]$  and Chlorine  $[\text{Cl}]$  concentrations (ppm):

$[\text{H}_2\text{O}] = [2\ 000; 3\ 500; 5\ 000]$  and  $[\text{Cl}] = [25\ \text{to}\ 50]$

$[\text{H}_2\text{O}] = [2\ 000; 3\ 500; 5\ 000]$  and  $[\text{Cl}] = [200]$

(Adjust the Chlorine content by adding 1,1,1 Trichloroethane or equivalent chlorinated solvent.)

For example, the requirement for fluid lifetime is: for  $[\text{H}_2\text{O}] = 5\ 000$  ppm and  $[\text{Cl}] = [25\ \text{to}\ 50]$  ppm minimum, type IV and type V fluid lifetime requirements are shown in [Figure 3](#).

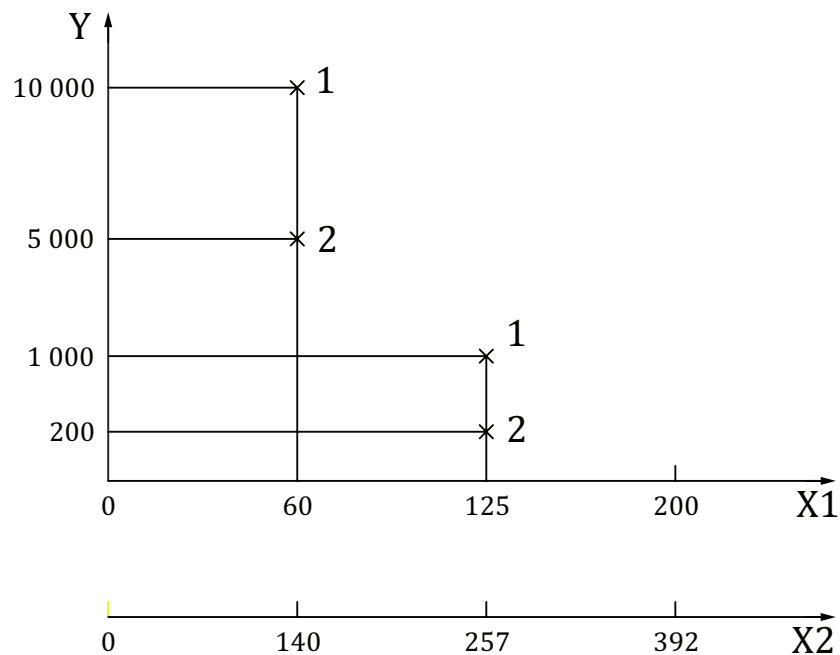

#### Key

- 1 Type V fluids
- 2 Type IV fluids
- X1 test temperature  $t$  in  $^\circ\text{C}$
- X2 test temperature  $t$  in  $^\circ\text{F}$
- Y required Fluid Life Time  $T$  (h Log Scale) in h

**Figure 3 — Requirement on lifetime comparison between Type IV and Type V hydraulic fluids**

### 4.20.3 “1 Litre-Container” Test method for fire resistance requirement in accordance with 4.8

#### 4.20.3.1 Equipment

- 1 litre sample vessel (i. e. Whitey 304L-HDF8-1000 fitted with plug, Swagelok SS-8-P, and male connector and plug, Swagelok SS-1210-1-8 and SS-1210-P);
- oven(s) capable of maintaining samples at required temperature.

#### 4.20.3.2 Sample preparation

- Adjust moisture content of test fluid to  $(0,50 \pm 0,03)$  % H<sub>2</sub>O (by weight).
- Adjust to 25 ppm to 75 ppm of Chlorine by adding 1,1,1 Trichloroethane or other chlorinated solvent (dichloromethane), in accordance with the national legislation.

#### 4.20.3.3 Procedure for laboratory

- Add  $(900 \pm 10)$  ml of prepared fluid to a clean sample vessel.
- Close sample vessel with a thermosetting screwed caps (example: phenoplast).
- Heat the vessels in the oven until the fluid in the vessels ages, reaching an *AN* of  $(1,5 \pm 0,3)$  mg KOH/g (to be measured at regular intervals).

#### 4.20.3.4 Fire resistance measurement (after fluid exposure)

The aim of the laboratory test is to ensure that ageing of the fluid-in service shall still maintain the fire resistant properties in accordance with values required in [4.8](#).

The “1 Litre-Container” test shall be carried out with hydraulic fluid contaminated with [H<sub>2</sub>O] = 5 000 ppm and with [Cl] = 25 ppm to 50 ppm, reaching an *AN* of  $(1,5 \pm 0,3)$  mg KOH/g (measured in the “1 Litre-container”), created by testing at the following temperatures:

- 110 °C (230 °F), 125 °C (257 °F), 140 °C (284 °F).

The minimum temperature values required for flash and fire points after ageing shall be

- 149 °C (300 °F) for Flash Point Temperature, and
- 165 °C (329 °F) for Fire Point Temperature.

NOTE It has been experienced that the results of the above laboratory tests performed in conditions more severe than the in-service conditions were able to meet the required in-service minimum values given in [Annex C](#).

### 4.21 Material compatibility with qualified fluids (see list provided by the airframe manufacturer)

#### 4.21.1 Compatibility with qualified fluids

##### 4.21.1.1 General

Different phosphate ester-base hydraulic fluid mixtures shall be placed in clean glass receptacles, in proportions of (25/75) %, (50/50) % and (75/25) % by volume, and any visible reactions noted.

The fluid mixtures shall be conditioned in accordance with the following requirements.

- Temperature conditions: (130 to 135) °C exposure
- Duration: all types: 168 h

Leave to cool at room temperature.

#### 4.21.1.2 Miscibility

After mixing the previously qualified fluids in the proportions given above and following conditioning as stated, the fluids shall be observed for colour, turbidity, foaming, suspended particles and any other visual sign of incompatibility. A change in colour is an acceptable reaction.

#### 4.21.1.3 Foaming

Foaming tests shall be performed using the method described in [4.17](#) on qualified fluids mixed in the three proportions indicated above, and on fluids mixed in equal proportions.

Test equipment: bubbling apparatus

Tendency to foam: Volume of foam shall be measured after bubbling for 5 min. Maximum volume of foam is given in [Table 9](#).

Foam persistence: No foam shall remain after bubbling past a certain period of time given in [Table 9](#).

**Table 9 — Foaming conditions and criteria**

Sample	Temperature °C	Tendency to foam cm <sup>3</sup>	Foam persistence time s
First	24	≤400	≤250
Second	93	≤425	≤200
	24	≤425	≤220

#### 4.21.2 Compatibility with elastomeric materials

Tests are performed on O-Ring of EPR (ethylene-propylene rubber) or EPT (Ethylene Propylene Ter Polymer) and nowadays with EPDM (Ethylene Propylene Diene Monomer) types. The tests are performed in accordance with hereafter requirements (refer to [A.1](#) and [A.2](#)). The types of seal to be tested will be specified by the aircraft manufacturer.

Standardized test pieces shall be immersed in the fluid according to the ratio

— test piece volume/fluid volume = 1/30.

Initial characteristics shall be determined before immersing the test pieces as per [A.1](#).

Immersion cycles:

- 70 h at (71 ± 5) °C
- 1 000 h at (100 ± 5) °C
- 750 h at (120 ± 5) °C
- 1 440 h at (120 ± 5) °C

Permissible characteristics and variations for elastomeric EPR, EPT or EPDM after immersion in the fluid are given in [A.1](#).

Permissible and other studied characteristics:

- international hardness (IRHD), in accordance with ISO 48 Method M;
- relative mass variations, ΔM%, and volume variations ΔV% in accordance with ISO 1817 Method;

- tensile stress-strain properties in accordance with ISO 37;
- low-temperature retraction procedure (TR test) in accordance with ISO 2921;

NOTE For the characteristics of international hardness, relative mass and volume variations, curves (see [A.2](#)) will be provided, to demonstrate the stability of tested Elastomeric materials (plateau to be reached in minimum 200 h).

#### 4.21.3 Compatibility with paints

The test has to be performed according to A/C manufacturer qualified paint system.

It is the responsibility of each A/C manufacturer to define the following:

- the list of paint systems to be tested;
- the conditions of immersion under temperature (duration, temperature, samples size and preparation...);
- the tests to be performed on the paint system samples (before and after immersion);
- the criteria.

#### 4.21.4 Compatibility with electrical aircraft components

It is the responsibility of each A/C manufacturer to define the following:

- the list of electrical components to be tested;
- the conditions of immersion under temperature (duration, temperature, samples size and preparation, cycles...);
- the tests to be performed on the electrical components samples (before and after immersion);
- the criteria.

#### 4.21.5 Compatibility with structural elements: adhesive, metallic parts (including tubes), composites

It is the responsibility of each A/C manufacturer to define the following:

- the list of structural elements to be tested;
- the conditions of immersion under temperature (duration, temperature, samples size and preparation, cycles...);
- the tests to be performed on structural elements samples (before and after immersion);
- the criteria.

NOTE The high temperature effects on metallic parts could be fulfilled according to SAE AS 1241, 4.6.

### 4.22 Lubrication

The lubrication test shall be carried out on a 4-ball wear tester in accordance with ASTM D 4172 with the conditions noted.

Test conditions:

- temperature:  $(75 \pm 3)$  °C;
- rotation speed: 600 r/min;

- loads: 4 kg, 10 kg, and 40 kg;
- duration:  $(60 \pm 1)$  min.

## 4.23 Erosion tests of the hydraulic fluid

### 4.23.1 General

This is to be performed after satisfactory results of preliminary stage of qualification.

The aim of the erosion test is to compare the performances of new type fluid to be qualified, to that any type IV fluid already qualified (high and low density), particularly regarding the electro-chemical phenomena on the hydraulic equipment.

The three hereafter-mentioned tests have to be performed and passed, according to specific aircraft manufacturer requirements.

### 4.23.2 Test 1 — Erosion System Test Bench representative of one aircraft hydraulic system

Performed in accordance with [B.1](#).

### 4.23.3 Test 2 — Pumping Test

Performed in accordance with [B.2](#).

### 4.23.4 Test 3 — Erosion Resistance Tests

Performed in accordance with [B.3](#).

## 5 Batches

A manufacturing batch is constituted with a quantity of fluid derived from a same manufacturing cycle.

## 6 Quality control

### 6.1 Hydraulic fluid acceptance tests

The manufacturer will carry out the manufacturing tests described in [6.2](#) and [6.3](#) on each manufacturing batch.

The results will be set out in an inspection document and transmitted to the buyer on delivery with the certificate of compliance.

The manufacturer will carry out the following tests, described in [Clause 4](#), on each batch and will provide a Material Safety Data Sheet with each batch.

### 6.2 Physical characteristics

- Absolute kinematic viscosity (see [4.1](#)) at  $(-54 \pm 0,05)$  °C,  $(38 \pm 0,02)$  °C and  $(99 \pm 0,02)$  °C
- Density at  $(23 \pm 3)$  °C (see [4.3](#))
- Pour point temperature (see [4.7](#))
- Flash point and fire point temperatures in an open vessel (see [4.8](#))
- Contamination class (see [4.16](#))

### 6.3 Chemical characteristics

- Water content (see [4.2](#))
- Acidity index (see [4.4](#))
- Chemical contaminants (see [4.6](#))
- Material Safety Data Sheet

**Check test procedure:** if a test result does not comply with the values requested, the test will be repeated on three other samples in different recipients which nevertheless belong to the same batch.

This batch will only be accepted if the three check tests are satisfactory.

NOTE The recipient containing the non-compliant product will be withdrawn from the batch.

## 7 Recommended limits

The hydraulic fluid criterion values in [Table 2](#) are the permissible limits for all fluids.

The In-Service limits values (after A/C delivery) are also specified in the Aircraft Maintenance Manuals; see [Annex C, Table C.1](#).

## 8 Marking

Unless otherwise specified by contract, marking shall include the following:

- a) on recipients:
  - 1) the manufacturing batch number;
  - 2) the fill-up date;
- b) on the label for each recipient:
  - 1) the manufacturer's name;
  - 2) the manufacturer's reference of the fluid (trade mark), with "High Density" mention when applicable;
  - 3) aircraft manufacturer's reference;
  - 4) contents (volume) and quantity (mass);
  - 5) conforms to ISO 9940;
- c) plus, where applicable:
  - 1) sampling precautions;
  - 2) handling and storage instructions.

## 9 Packing and storage

The fluid will be delivered and stored in properly sealed containers.

The storage conditions shall be as follows.

- Keep the containers firmly closed.

- Avoid any contact with solvents, particularly those belonging to the halogen family (Chlorine for example) and Methanol.
- Avoid contamination by water.
- Avoid contamination by solid particles.
- Avoid contamination by other fluids, including hydraulic fluids.
- Do not expose the fluid to the open air for any long period of time or to temperature exceeding 35 °C.

Shipments from fluid manufacturers shall be marked with caution regarding health and toxicity in keeping with current regulation directives applicable for delivery country.

## Annex A (normative)

### Elastomer compatibility

#### A.1 Compatibility with EPDM-EPR or EPT – Permissible characteristics and variations after fluid immersion tests


Designation of test conditions in the fluid to be qualified	Criteria max. variations after immersion
<b>1. Reference tests before immersion</b>	
1.1 — International hardness (IRHD)	∈ [76 ; 85]
1.2 — Tensile test	
1.2.1 — Tensile at break, $\sigma_r$ , (MPa)	≥12
1.2.2 — Elongation at break, A %	≥125
1.3 — Temperature (°C) at 10 % shrink (TR <sub>10</sub> )	≤ -45
<b>2. After (1 000 ± 2) h immersion at 100 °C</b>	
2.1 — IRHD variations	∈ [-20; 0]
2.1 — Tensile test	
2.2 — Tensile at break, $\sigma_r$ , (MPa)	≥12
2.2.1 — Elongation at break, A %	≥125
2.3 — Swelling	
2.3.1 — Relative volume variation, $\Delta V$ %	∈ [0; +20]
2.3.2 — Relative mass variation, $\Delta M$ %	∈ [0; +17]
2.4 — Temperature (°C) at 10 % shrink (TR <sub>10</sub> )	≤ -45
<b>3. After (750 ± 2) h immersion at 120 °C</b>	
3.1 — IRHD variations	∈ [-30; 0]
3.2 — Tensile test	
3.2.1 — Tensile at break, $\sigma_r$ , (MPa)	≥12
3.2.2 — Elongation at break, A %	≥125
3.3 — Swelling	
3.3.1 — Relative volume variation, $\Delta V$ %	∈ [0; +20]
3.3.2 — Relative mass variation, $\Delta M$ %	∈ [0; +17]
3.4 — Temperature at 10 % shrink (TR <sub>10</sub> ), (°C)	≤ -45
<b>4. After (1 440 ± 2) h immersion at 120 °C</b>	
4.1 — IRHD variations	∈ [-40; 0]
4.2 — Tensile test	
4.2.1 — Tensile at break, $\sigma_r$ , (MPa)	≥12
4.2.2 — Elongation at break, A %	≥125
4.3 — Swelling	
4.3.1 — Relative volume variation, $\Delta V$ %	∈ [0; +20]



Designation of test conditions in the fluid to be qualified	Criteria max. variations after immersion
4.3.2 — Relative mass variation, $\Delta M$ %	$\in [0; +17]$
4.4 — Temperature at 10 % shrink ( $TR_{10}$ ), ( $^{\circ}C$ )	$\leq -45$

## A.2 Compatibility with EPDM-EPR or EPT -typical characteristics curves

Evolution of physico-chemical characteristics of EPDM- EPR or EPT versus immersion time see [Figure A.1](#).

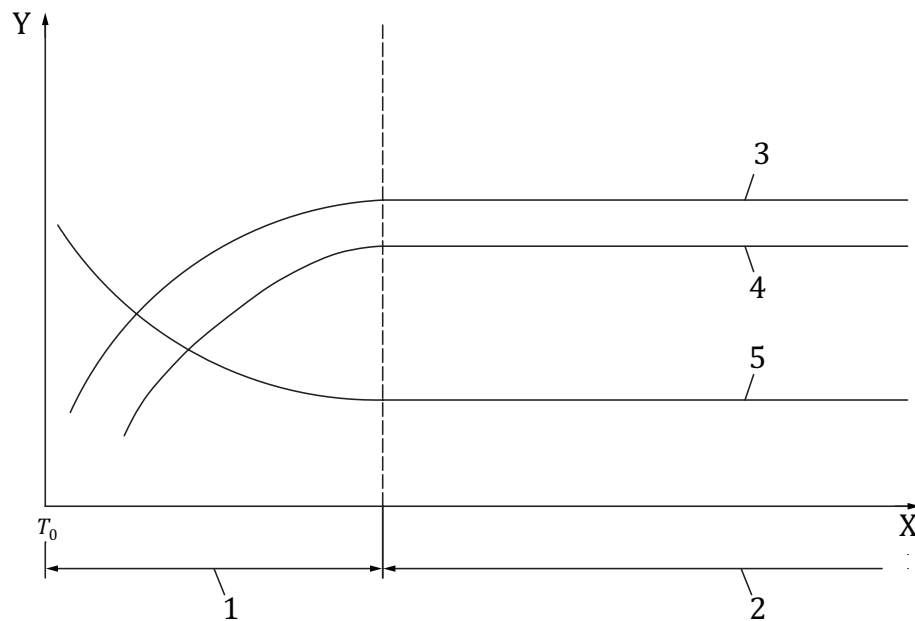

### Key

- 1 establishment zone of equilibrium state
- 2 equilibrium state zone
- 3 volume
- 4 mass
- 5 IRHD
- X time (days)
- Y characteristic variation

**Figure A.1 — Evolution of physico-chemical characteristics of EPDM- EPR or EPT versus immersion time**

Fluid manufacturer has to provide this test because this test identifies the zone of equilibrium state in swelling.

## **Annex B** **(informative)**

### **Erosion tests**

#### **B.1 Erosion system test bench equipment**

Procedure and exact requirements are available at aircraft manufacturer.

#### **B.2 Pumping test**

Procedure and exact requirements are available at aircraft manufacturer.

#### **B.3 Erosion resistance tests**

Procedure and exact requirements are available at aircraft manufacturer.

## Annex C (normative)

### Fluid monitoring after A/C delivery

**Table C.1 — Fluid monitoring after A/C delivery**

Fluid characteristic	Unit	Subclause	After A/C delivery
Absolute Kinematic Viscosity “ $\nu$ ” at $(38 \pm 0,02)$ °C	$\text{mm}^2 \cdot \text{s}^{-1}$	<a href="#">4.1</a>	$\in [6,00; 12,50]$
Water content [ $\text{H}_2\text{O}$ ]	%	<a href="#">4.2</a>	$\leq 0,80$ limit and $\leq 0,5$ maximum recommended
Density “ $\rho$ ” at $(23 \pm 3)$ °C	$\text{kg} \cdot \text{m}^{-3}$	<a href="#">4.3</a>	$\in [970; 1\ 066]$
Acid number “AN” per g of fluid or Acidity index “AI” per g of fluid	$\text{mg} \cdot \text{KOH}/\text{g}$	<a href="#">4.4</a>	$\leq 1,50$
Electrical Conductivity “ $\gamma$ ” at $(20 \pm 0,5)$ °C	$\mu\text{S} \cdot \text{cm}^{-1}$	<a href="#">4.5</a>	$\geq 0,30$ (0,18 accepted as minimum value under condition. See <a href="#">4.5</a> )
Chlorine content [ $Cl$ ]	ppm	<a href="#">4.6.1</a>	$\leq 200$
Flash Point Temperature	°C (°F)	<a href="#">4.8</a>	160 (320) minimum
Fire Point Temperature	°C (°F)	<a href="#">4.8</a>	177 (351) minimum
Cleanliness Class in accordance with ISO 11218	Class	<a href="#">4.16.1</a>	$\leq 9$

## Bibliography

- [1] ISO 1518-1, *Paints and varnishes — Determination of scratch resistance — Part 1: Constant-loading method*
- [2] ISO 1518-2, *Paints and varnishes — Determination of scratch resistance — Part 2: Variable-loading method*
- [3] ISO 2409, *Paints and varnishes — Cross-cut test*
- [4] ISO 2812 (all parts), *Paints and varnishes — Determination of resistance to liquids*
- [5] ISO 9001, *Quality management systems — Requirements*
- [6] EN 2243-1, *Aerospace series — Non-metallic materials — Structural adhesives — Test method — Part 1: Single lap shear*
- [7] EN 2243-2, *Aerospace series — Non-metallic materials — Structural adhesives — Test method — Part 2: Peel metal-metal*
- [8] EN 2562, *Aerospace series — Carbon fibre reinforced plastics — Unidirectional laminates — Flexural test parallel to the fibre direction*
- [9] EN 2563, *Aerospace series — Carbon fibre reinforced plastics — Unidirectional laminates — Determination of the apparent interlaminar shear strength*
- [10] EN 2591-315, *Aerospace series — Elements of electrical and optical connection — Test methods — Part 315: Fluid resistance*
- [11] EN 3475-411, *Aerospace series — Cables, electrical, aircraft use — Test methods — Part 411: Resistance to fluids*
- [12] AS/EN/JISQ 9100, *Quality Management Systems — Requirements for Aviation, Space and Defense Organizations*
- [13] ARP 785, *Aerospace — Procedure for the Determination of Particulate Contamination in Hydraulic Fluids By the Control Filter Gravimetric Procedure*
- [14] AS/ARP 598, *Aerospace Microscopic Sizing and Counting of Particulate Contamination for Fluid Power Systems*
- [15] NF L 17-106, *Aerospace industry — NFL standardized rubber materials — Technical specification*
- [16] NF L 17-241, *Aerospace series — Ethylene — Propylene rubbers — Class 41 — Characteristics*
- [17] NF L 41-101, *Hydraulic systems contamination by solid particules — Leading particulars*
- [18] NF L 41-102, *Hydraulic systems contamination by solid particules — Inspection methods*
- [19] SAE AS 1241<sup>5)</sup>, *Fire Resistant Phosphate Ester Hydraulic Fluid for Aircraft*

---

5) Published by: SAE International [www.sae.org](http://www.sae.org)







# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™