

BS ISO 11093-7:2011



BSI Standards Publication

Paper and board — Testing of cores

Part 7: Determination of flexural modulus by the three-point method

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 11093-7:2011. It supersedes BS ISO 11093-7:1997 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PAI/11, Methods of test for paper, board and pulps.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 68907 9

ICS 85.060; 85.080.30

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2011.

Amendments issued since publication

Date	Text affected
------	---------------

Paper and board — Testing of cores —
Part 7:
Determination of flexural modulus by the
three-point method

Papier et carton — Essais des mandrins —

Partie 7: Détermination du module de flexion par la méthode à trois points





COPYRIGHT PROTECTED DOCUMENT

© ISO 2011

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents		Page
Foreword		iv
1 Scope		1
2 Normative references		1
3 Terms and definitions		1
4 Principle		1
5 Apparatus		2
5.1 Test-piece support		2
5.2 Measuring device		2
5.3 Load		3
6 Test piece		4
6.1 Sampling		4
6.2 Test-piece size		4
6.3 Conditioning		4
7 Procedure		4
7.1 General		4
7.2 Positioning of bearings and measuring device		5
7.3 Application of loading		5
7.4 Determination		5
8 Calculation of the flexural modulus		5
9 Estimation of required force		6
10 Test report		6
Bibliography		7

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 11093-7 was prepared by Technical Committee ISO/TC 6, *Paper, board and pulps*.

This second edition cancels and replaces the first edition (ISO 11093-7:1997), which has been technically revised. The following amendments have been made compared with ISO 11093-7:1997:

- a) adaptation to editorial rules for International Standards;
- b) as the effect of transverse frame on deflection is so low with usual reel core measurements that it can be neglected given the usual variation in materials, the Timoshenko factor has been deleted along with the corresponding equation.

ISO 11093 consists of the following parts, under the general title *Paper and board — Testing of cores*:

- *Part 1: Sampling*
- *Part 2: Conditioning of test samples*
- *Part 3: Determination of moisture content using the oven drying method*
- *Part 4: Measurement of dimensions*
- *Part 5: Determination of characteristics of concentric rotation*
- *Part 6: Determination of bending strength by the three-point method*
- *Part 7: Determination of flexural modulus by the three-point method*
- *Part 8: Determination of natural frequency and flexural modulus by experimental modal analysis*
- *Part 9: Determination of flat crush resistance*

Paper and board — Testing of cores —

Part 7:

Determination of flexural modulus by the three-point method

1 Scope

This part of ISO 11093 specifies a method for the determination, by the three-point method, of the flexural modulus of cylindrical paper and board cores which meet the following criteria:

- internal diameter: 50 mm to 350 mm;
- minimum wall thickness: $0,05 \times$ internal diameter, but not less than 10,0 mm;
- minimum length of core: $10 \times$ internal diameter, but not less than 1 000 mm.

If the flexural modulus has to be used for the calculation of a paper core's natural frequency, ISO 11093-8^[2] applies instead of this International Standard.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 11093-1, *Paper and board — Testing of cores — Part 1: Sampling*

ISO 11093-3, *Paper and board — Testing of cores — Part 3: Determination of moisture content using the oven drying method*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

flexural modulus

E

material property which, together with core dimensions, describes the resistance of the core to traction or bending deflection

4 Principle

In order to determine the flexural modulus, a static bending test is conducted on the test piece. The test piece is considered as a “beam” and the classic beam theory for the deflection of “slender beams” is applied. During the test, the test piece is supported at its ends and loaded transversally by a load applied by a hanging weight. Special measures are undertaken to avoid permanent deformation of the test piece and to ensure the validity of the equation, used for calculation.

The flexural modulus is calculated as described in Clause 8.

5 Apparatus

5.1 Test-piece support

The test piece is supported at each end by two rolls arranged like a vee, referred to as the *lower bearings* (see Figure 1). The angle between the two rolls shall be $120^\circ \pm 2^\circ$. The diameter a of the rolls shall be (30 ± 1) mm. The width b shall be large enough to allow the test piece to rest on the lateral surface area of the rolls. At an angle of 120° , the theoretical minimum value of b is half the outer diameter D of the core.

Dimensions in millimetres

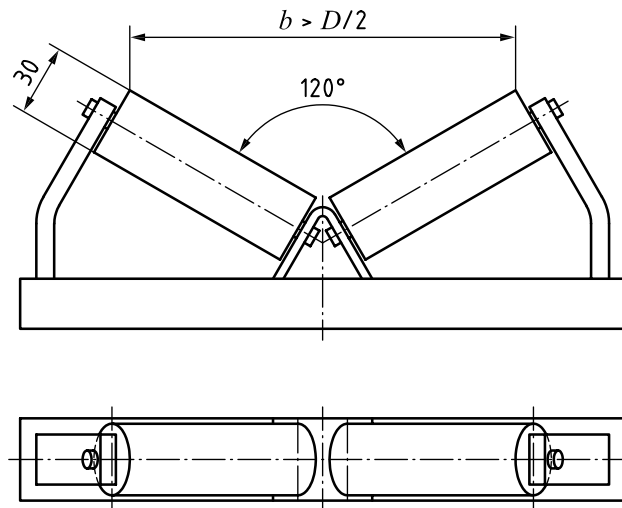


Figure 1 — Schematic drawing of the bearings

5.2 Measuring device


The measuring device consists of two rolls arranged like a vee, referred to as the *upper bearings*, a support bar on which the upper bearings are mounted, and a displacement gauge. The lower and upper bearings are arranged with mirror-image symmetry. The measuring device is placed on the test piece.

The change in deflection f of the test piece is measured in the direction of the applied force using a displacement gauge (see Figure 2).

If a material-testing machine is used to apply the load (see 5.3), it may also be used to measure the deflection of the test piece. It shall be accurate to $\pm 0,01$ mm.

The tolerances of the distances and the force F are defined in Clause 7.

Dimensions in millimetres

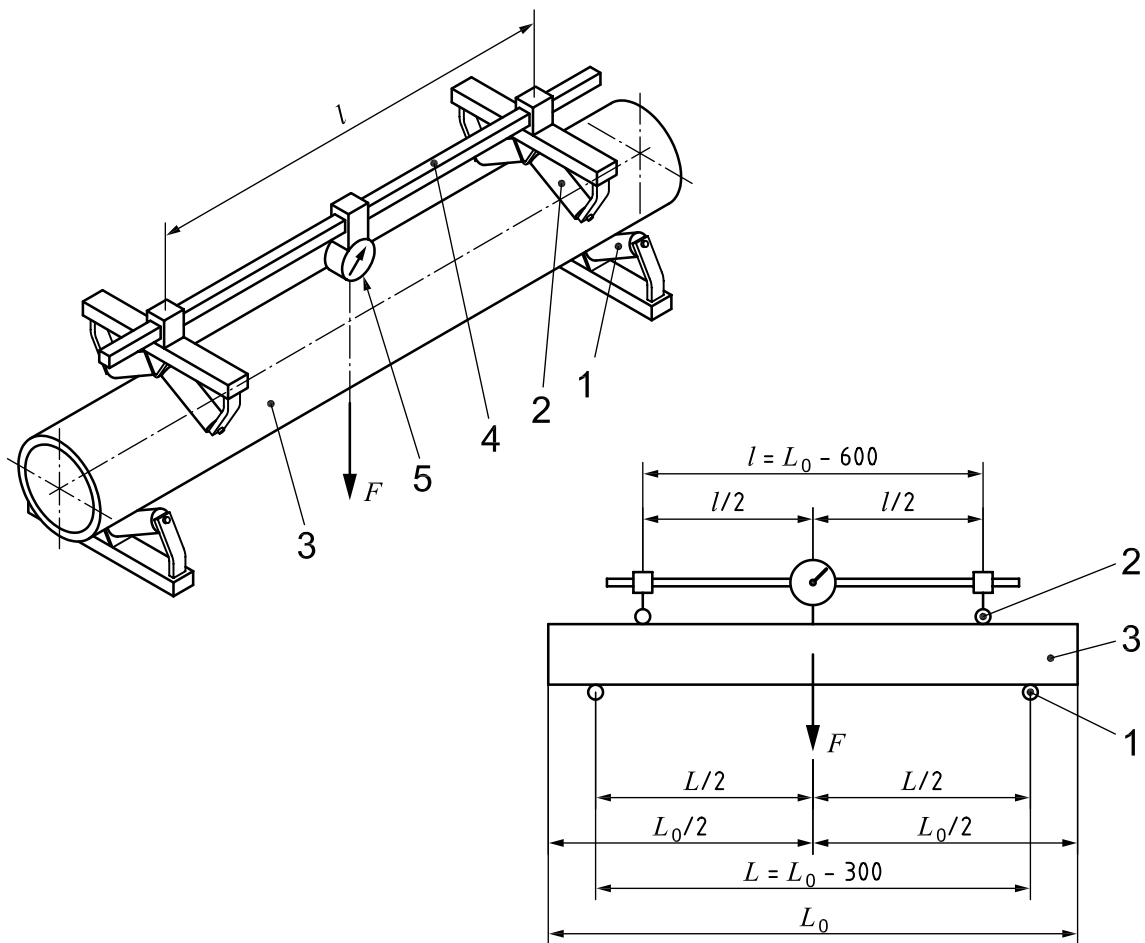

Key

- 1 lower bearing
- 2 upper bearing
- 3 test piece
- 4 support bar
- 5 dial gauge
- F load (force)
- L_0 length of test piece, length of paper core
- L centre-to-centre distance of the lower bearings
- l centre-to-centre distance of the upper bearings

Figure 2 — Schematic drawing of the measuring set-up

5.3 Load

The magnitude of the load to be used in the test can be estimated using Equation (2). The load F is applied to the test piece by a belt loaded with hanging weights. The width of the belt shall be approximately 50 mm (see Figure 3). The belt shall have an opening to allow the shaft of the displacement gauge to rest on the test piece.

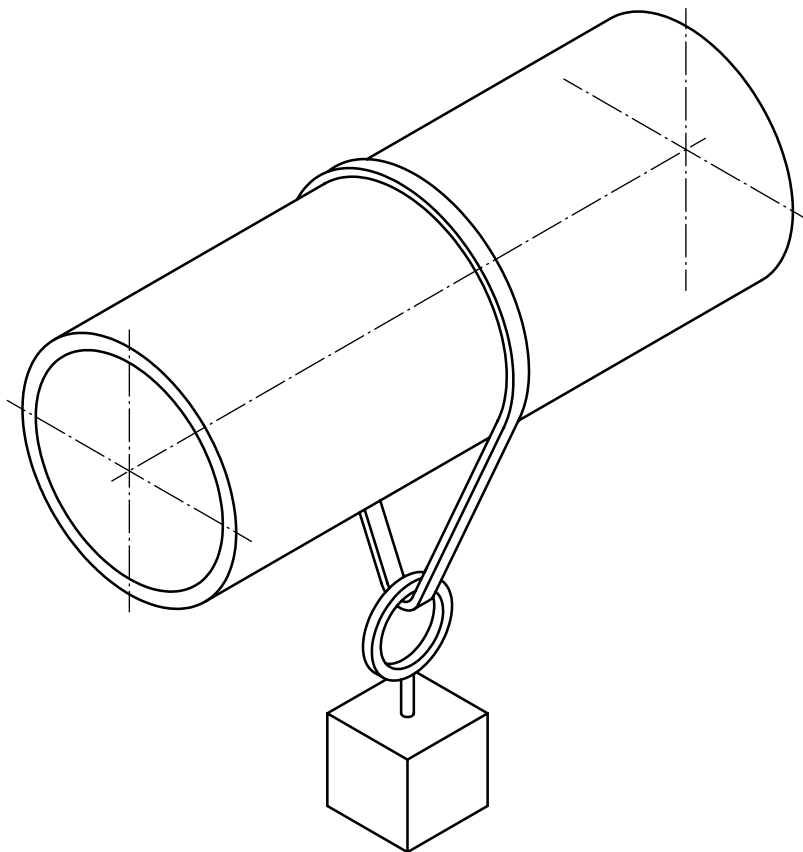


Figure 3 — Schematic drawing of the loading system

Alternatively, the load can be applied by a testing machine capable of applying the load using a displacement rate of $(10 \pm 0,1)$ mm/min and measuring the load to an accuracy of $\pm 0,1$ N.

6 Test piece

6.1 Sampling

Samples shall be taken in accordance with ISO 11093-1.

6.2 Test-piece size

Prepare at least five test pieces such that their lengths L_0 are 10 times the internal diameter of the paper or board core. If the calculated length is less than 1 000 mm, the test piece length shall be $(1\ 000 \pm 2)$ mm.

6.3 Conditioning

In practice, the test piece shall be dried such that the moisture content measured in accordance with ISO 11093-3 shall be equal to that specified for the lot.

7 Procedure

7.1 General

Carry out the test under the same atmospheric conditions as those used to condition the test piece.

The core's outer and inner diameter, D and d respectively, shall be determined with an accuracy of $\pm 0,1$ mm.

7.2 Positioning of bearings and measuring device

The length of the test piece L_0 shall be determined with an accuracy of ± 1 mm. The test piece shall be centred on the lower bearings with a tolerance of ± 2 mm.

Position the lower bearings such that their centre-to-centre distance L is 300 mm less than the length of the test piece L_0 and the upper bearings such that their centre-to-centre distance l is 600 mm less than the length of the test piece, each with an accuracy of ± 2 mm.

The centres of the lower and upper bearings, and the positions of the displacement gauge and the application of force in the direction of the test piece's axis shall be centred with respect to the centre of the test piece to an accuracy of ± 2 mm.

The displacement gauge is positioned centrally on the test piece. The displacement gauge is vertically attached on a support bar. The deflection is measured on the upper side of the test piece.

7.3 Application of loading

Apply the load F by hanging an appropriate weight on the belt which is placed at the midpoint of the measuring length L of the test piece (see Figure 3). The hanging weight shall be applied slowly.

Alternatively, the loading can be applied in a material-testing machine. The loading rate (rate of advance) shall be 10 mm/min.

The load shall be such that the deflection f is between 0,20 mm and 0,70 mm (see Clause 9).

7.4 Determination

If the load is applied by a hanging weight, within 2 s after application of the loading, the deflection recorded by the displacement gauge shall be read. If the load is applied by a material-testing machine, determine the load required to produce a deflection f between 0,20 mm and 0,70 mm. By applying the values F , L , l and f to be used in Equation (1), the flexural modulus for each test piece shall be calculated.

Repeat 7.2 to 7.4 for additional test pieces.

8 Calculation of the flexural modulus

The flexural modulus E , or Young's modulus, is calculated according to Equation (1), which is developed from the bending theory for slender beams.

$$E = \frac{2Fl^2(3L-l)}{3\pi f(D^4 - d^4)} \quad (1)$$

where

- F is the applied transversal load on the test piece, expressed in newtons; the load shall be positioned in such a way that the deflection f lies between 0,20 mm and 0,70 mm;
- L is the centre-to-centre distance of the lower bearings, expressed in millimetres;
- l is the centre-to-centre distance of the upper bearings, expressed in millimetres;
- f is the difference, expressed in millimetres, between the loaded and unloaded deflection measured in the direction of the applied load;
- D is the external diameter of the core, expressed in millimetres;
- d is the internal diameter of the core, expressed in millimetres.

The flexural modulus shall be specified in newtons per square millimetre, to the nearest integer.

EXAMPLE $F = 200 \text{ N}$, $L = 1\,700 \text{ mm}$, $l = 1\,400 \text{ mm}$, $f = 0,54 \text{ mm}$, $D = 106 \text{ mm}$, $d = 76 \text{ mm}$.

The calculation using Equation (1) gives: $E = 6\,136 \text{ N/mm}^2$.

9 Estimation of required force

On the assumption of a deflection of about 0,5 mm and an assumed flexural modulus E_{ass} , the required load F , in newtons, can be approximately calculated using Equation (2):

$$F \approx \frac{3\pi}{2} \times 0,5 \times E_{\text{ass}} \frac{(D^4 - d^4)}{l^2(3L - l)} \quad (2)$$

where

E_{ass} is the assumed value for the flexural modulus, expressed in newtons per square millimetre;

D , d , L and l are defined after Equation (1).

EXAMPLE $E_{\text{ass}} = 6\,000 \text{ N/mm}^2$, $L = 1\,700 \text{ mm}$, $l = 1\,400 \text{ mm}$, $D = 106 \text{ mm}$, $d = 76 \text{ mm}$.

The calculation using Equation (2) gives: $F \approx 181 \text{ N}$.

10 Test report

The test report shall include the following information:

- a) a reference to this part of ISO 11093;
- b) type and designation of the cores tested;
- c) place and date of sampling;
- d) place and date of testing;
- e) number of test pieces tested;
- f) measured moisture content;
- g) core dimensions L_0 , D and d ;
- h) L , l (actual sizes), F and f ;
- i) individual and mean values for E ;
- j) whether the load was applied with a hanging weight or a material-testing machine;
- k) any deviation from this part of ISO 11093 that may have affected the results.

Bibliography

- [1] ISO 11093-2, *Paper and board — Testing of cores — Part 2: Conditioning of test samples*
- [2] ISO 11093-8, *Paper and board — Testing of cores — Part 8: Determination of natural frequency and flexural modulus by experimental modal analysis*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™