



BSI Standards Publication

**Iron ores for shaft direct-
reduction feedstocks —
Determination of the
reducibility index, final degree
of reduction and degree of
metallization**

National foreword

This British Standard is the UK implementation of ISO 11258:2015. It supersedes BS ISO 11258:2007 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/58, Iron ores.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015. Published by BSI Standards Limited 2015

ISBN 978 0 580 79293 9

ICS 73.060.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 September 2015.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

ISO
11258

Third edition
2015-08-15

**Iron ores for shaft direct-reduction
feedstocks — Determination of the
reducibility index, final degree of
reduction and degree of metallization**

*Minerais de fer pour charges utilisées dans les procédés par réduction
directe — Détermination de l'indice de réductibilité, du degré final de
réduction et du degré de métallisation*



Reference number
ISO 11258:2015(E)

© ISO 2015



COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword.....	iv
Introduction.....	v
1 Scope.....	1
2 Normative references.....	1
3 Terms and definitions.....	1
4 Principle.....	1
5 Sampling, sample preparation, and preparation of test portions.....	2
5.1 Sampling and sample preparation.....	2
5.2 Preparation of test portions.....	2
6 Apparatus.....	2
6.1 General.....	2
7 Test conditions.....	3
7.1 General.....	3
7.2 Reducing gas.....	3
7.2.1 Composition.....	3
7.2.2 Purity.....	3
7.2.3 Flow rate.....	3
7.3 Heating and cooling gas.....	3
7.4 Temperature of the test portion.....	4
8 Procedure.....	4
8.1 Number of determinations for the test.....	4
8.2 Chemical analysis.....	4
8.3 Reduction.....	4
8.4 Chemical analysis after reduction.....	4
9 Expression of results.....	5
9.1 Calculation of the final degree of reduction (R_{90}).....	5
9.2 Calculation of the reducibility indices $dR/dt(R=40)$ and $dR/dt(R=90)$	5
9.2.1 Reduction curve.....	5
9.2.2 Reducibility index for 40 % reduction.....	5
9.2.3 Reducibility index for 90 % reduction.....	6
9.3 Calculation of the degree of metallization (M).....	6
9.3.1 Determination of the degree of metallization from chemical analysis (M).....	6
9.3.2 Determination of the degree of metallization from R_{90} (MR).....	6
9.4 Repeatability for R_{90} and acceptance of test results.....	7
10 Test report.....	7
11 Verification.....	7
Annex A (normative) Flowsheet of the procedure for the acceptance of test results.....	11
Annex B (informative) Derivation of formula for reducibility.....	12
Annex C (informative) Derivation of formula for degree of metallization from R_{90}.....	14
Bibliography.....	16

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 102, *Iron ore and direct reduced iron*, Subcommittee SC 3, *Physical testing*.

This third edition cancels and replaces the second edition (ISO 11258:2007), of which it constitutes a minor revision to contemplate the outcomes of the studies on mass definition, as well as minor editorial improvements.

Introduction

This International Standard concerns one of a number of physical test methods that have been developed to measure various physical parameters and to evaluate the behaviour of iron ores, including reducibility, disintegration, crushing strength, apparent density, etc. This method was developed to provide a uniform procedure, validated by collaborative testing, to facilitate comparisons of tests made in different laboratories.

The results of this test have to be considered in conjunction with other tests used to evaluate the quality of iron ores as feedstocks for direct reduction processes.

This International Standard can be used to provide test results as part of a production quality control system, as a basis of a contract, or as part of a research project.

Iron ores for shaft direct-reduction feedstocks — Determination of the reducibility index, final degree of reduction and degree of metallization

CAUTION — This International Standard can involve hazardous operations and equipment. This International Standard does not purport to address all of the safety issues associated with its use. It is the responsibility of the user of this International Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to its use.

1 Scope

This International Standard specifies a method to provide a relative measure for evaluating the extent to and ease to which oxygen can be removed from iron ores, when reduced under conditions resembling those prevailing in shaft direct-reduction processes. It specifies the determination of the reducibility, final degree of reduction, and degree of metallization.

This International Standard is applicable to lump ores and hot-bonded pellets.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2597-1, *Iron ores — Determination of total iron content — Part 1: Titrimetric method after tin(II) chloride reduction*

ISO 2597-2, *Iron ores — Determination of total iron content — Part 2: Titrimetric methods after titanium(III) chloride reduction*

ISO 3082, *Iron ores — Sampling and sample preparation procedures*

ISO 5416, *Direct reduced iron — Determination of metallic iron — Bromine-methanol titrimetric method*

ISO 9035, *Iron ores — Determination of acid-soluble iron(II) content — Titrimetric method*

ISO 11323, *Iron ore and direct reduced iron — Vocabulary*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11323 apply.

4 Principle

The test portion is isothermally reduced in a fixed bed, at 800 °C, using a reducing gas consisting of H₂, CO, CO₂, and N₂, and is weighed continuously or at specified time intervals until 90 min of reduction is reached. The rate of reduction is calculated at the oxygen/iron ratio of 0,9 and the final degree of reduction is calculated from the oxygen mass loss after 90 min (R_{90}). The degree of metallization is calculated either by a formula based on R_{90} or by chemical analysis of the reduced product.

5 Sampling, sample preparation, and preparation of test portions

5.1 Sampling and sample preparation

Sampling of a lot and preparation of a test sample shall be in accordance with ISO 3082.

The size range for pellets shall be 50 % - 16,0 mm + 12,5 mm and 50 % - 12,5 mm + 10,0 mm.

The size range for lump ores shall be 50 % - 20,0 mm + 16,0 mm and 50 % - 16,0 mm + 10,0 mm.

A test sample of at least 2,5 kg, on dry basis, of the sized material shall be obtained.

Oven-dry the test sample to constant mass at $105\text{ °C} \pm 5\text{ °C}$ and cool it to room temperature before preparation of the test portions.

NOTE Constant mass is achieved when the difference in mass between two subsequent measurements becomes less than 0,05 % of the initial mass of the test sample.

5.2 Preparation of test portions

Collect each test portion by taking ore particles at random.

NOTE Manual methods of division recommended in ISO 3082, such as riffing, can be applied to obtain the test portions.

At least five test portions, each of approximately 500 g (\pm the mass of 1 particle) shall be prepared from the test sample: four test portions for testing and one for chemical analysis.

Weigh the test portions to the nearest 1 g and register the mass of each test portion on its recipient label.

6 Apparatus

6.1 General

The test apparatus shall comprise the following:

- a) ordinary laboratory equipment, such as an oven, hand tools, and safety equipment;
- b) reduction-tube assembly;
- c) furnace, equipped with a balance for permitting the mass loss of the test portion to be read at any time during the test;
- d) system to supply the gases and regulate the flow rates;
- e) weighing device.

[Figure 1](#) shows an example of the test apparatus.

6.2 Reduction tube, made of non-scaling, heat-resistant metal to withstand temperatures higher than 800 °C and resistant to deformation.

The internal diameter shall be $75\text{ mm} \pm 1\text{ mm}$. A removable perforated plate, made of non-scaling, heat-resistant metal to withstand temperatures higher than 800 °C shall be mounted in the reduction tube to support the test portion and to ensure uniform gas flow through it. The perforated plate shall be 4 mm thick, with its diameter 1 mm less than the internal diameter of the tube. The holes in the plate shall be 2 mm to 3 mm in diameter at a pitch centre distance of 4 mm to 5 mm.

[Figure 2](#) shows an example of a reduction tube.

6.3 Furnace, having a heating capacity and temperature control able to maintain the entire test portion, as well as the gas entering the bed, at $800\text{ °C} \pm 5\text{ °C}$.

6.4 Balance, capable of weighing the reduction tube assembly, including the test portion, to an accuracy of 1 g. The balance shall have an appropriate device to suspend the reduction tube assembly.

6.5 Gas-supply system, capable of supplying the gases and regulating gas flow rates.

It shall be ensured that a frictionless connection between the gas-supply system and the reduction tube does not affect the weight loss determination during reduction.

6.6 Weighing device, capable of weighing the test sample and test portions to an accuracy of 1 g.

7 Test conditions

7.1 General

Volumes and flow rates of gases used are as measured at a reference temperature of 0 °C and at a reference atmospheric pressure of $101,325\text{ kPa}$ ($1,013\ 25\text{ bar}$).

7.2 Reducing gas

7.2.1 Composition

The reducing gas shall consist of the following:

CO	$30\% \pm 1\%$ (volume fraction)
CO ₂	$15\% \pm 1\%$ (volume fraction)
H ₂	$45\% \pm 1\%$ (volume fraction)
N ₂	$10\% \pm 1\%$ (volume fraction)

7.2.2 Purity

Impurities in the reducing gas shall not exceed the following:

O ₂	$0,1\%$ (volume fraction)
H ₂ O	$0,2\%$ (volume fraction)

7.2.3 Flow rate

The flow rate of the reducing gas, during the entire reducing period, shall be maintained at $50\text{ L/min} \pm 0,5\text{ L/min}$.

7.3 Heating and cooling gas

Nitrogen (N₂) shall be used as the heating and cooling gas. Impurities shall not exceed $0,1\%$ (volume fraction).

The flow rate of N₂ shall be maintained at 25 L/min until the test portion reaches 800 °C and at 50 L/min during temperature-equilibration period. During cooling, it shall be maintained at 25 L/min .

7.4 Temperature of the test portion

The temperature of the entire test portion shall be maintained at $800\text{ °C} \pm 5\text{ °C}$ during the entire reducing period and, as such, the reducing gas shall be preheated before entering the test portion.

8 Procedure

8.1 Number of determinations for the test

Carry out the test as many times as required by the procedure in [Annex A](#).

8.2 Chemical analysis

Take, at random, one of the test portions prepared in [5.2](#) and use it for the determination of the iron(II) oxide content (w_1) in accordance with ISO 9035 and the total iron content (w_2) in accordance with ISO 2597-1 or ISO 2597-2.

8.3 Reduction

Take, at random, another test portion prepared in [5.2](#) and record its mass (m_0). Place it in the reduction tube ([6.2](#)) and level its surface.

NOTE In order to achieve a more uniform gas flow, a double-layer bed of porcelain balls sized between 10,0 mm and 12,5 mm can be placed between the perforated plate and the test portion.

Close the top of the reduction tube. Connect the thermocouple, ensuring that its tip is in the centre of the test portion, as shown in [Figure 1](#).

Insert the reduction tube into the furnace ([6.3](#)) and suspend it centrally from the balance ([6.4](#)), ensuring that there is no contact with the furnace wall or heating elements.

Connect the gas-supply system ([6.5](#)).

Pass a flow of N_2 through the test portion at a rate of at least $25\text{ L/min} \pm 0,5\text{ L/min}$ and commence heating. When the temperature of the test portion approaches 800 °C , increase the flow rate to $50\text{ L/min} \pm 0,5\text{ L/min}$. Continue heating while maintaining the flow of the N_2 until the balance reading is constant and the temperature is constant at $800\text{ °C} \pm 5\text{ °C}$ for 10 min.

In the case of lump ores, the temperature of the test portion should be raised to 800 °C over more than 60 min to reduce decrepitation.

DANGER — Carbon monoxide and the reducing gas, which contains carbon monoxide, are toxic and therefore hazardous. Testing shall be carried out in a well-ventilated area or under a hood. Precautions should be taken for the safety of the operator in accordance with the safety codes of each country.

Tare the balance, start the time control device and immediately introduce the reducing gas at a flow rate of $50\text{ L/min} \pm 0,5\text{ L/min}$ to replace the N_2 . Record the mass loss of the test portion (Δm_t) at least every 3 min for the first 15 min and thereafter at 10 min intervals. After 90 min of reduction, record the mass loss of the test portion (Δm), turn off the power and stop the flow of the reducing gas. Introduce N_2 at a flow rate of 25 L/min until the test portion is below 50 °C .

8.4 Chemical analysis after reduction

Pulverise the entire reduced material and determine its total iron content (w_t) in accordance with ISO 2597-1 or ISO 2597-2, and its metallic iron content (w_0) in accordance with ISO 5416.

NOTE If desired, the mass percentage of combined carbon in the reduced test portion can be determined by applying ISO 9686.

9 Expression of results

9.1 Calculation of the final degree of reduction (R_{90})

The final degree of reduction, R_{90} , expressed as a percentage by mass, is calculated from Formula (1)¹⁾:

$$R_{90} = \left(\frac{0,111 w_1}{0,430 w_2} + \frac{\Delta m}{m_0 \times 0,430 w_2} \times 100 \right) \times 100 \quad (1)$$

where

m_0 is the mass, in grams, of the test portion;

Δm is the mass loss, in grams, of the test portion after 90 min of reduction;

w_1 is the iron(II) oxide content, expressed as a percentage by mass, of the test portion prior to the test, determined in accordance with ISO 9035. It is calculated from the iron(II) content by multiplying it by the oxide conversion factor $\text{FeO/Fe(II)} = 1,286$;

w_2 is the total iron content, expressed as a percentage by mass, of the test portion prior to the test, determined in accordance with ISO 2597-1 and ISO 2597-2.

Record the result to one decimal place.

9.2 Calculation of the reducibility indices $dR/dt(R=40)$ and $dR/dt(R=90)$

9.2.1 Reduction curve

Prepare the reduction curve by plotting the degree of reduction, R_t , against time, t , using Formula (2):

$$R_t = \left(\frac{0,111 w_1}{0,430 w_2} + \frac{\Delta m_t}{m_0 \times 0,430 w_2} \times 100 \right) \times 100 \quad (2)$$

where

Δm_t is the mass loss, in grams, of the test portion, after reduction time, t .

Using the reduction curve, obtain and express the reducibility indices to two decimal places.

9.2.2 Reducibility index for 40 % reduction

Read off, from the reduction curve, the time, in minutes, to attain degrees of reduction of 30 % and 60 %.

1) The derivation of the formula is given in [Annex B](#).

The reducibility index $\frac{dR}{dt}_{(R=40)}$ for 40 % reduction ($O/Fe = 0,9$), expressed as the rate of reduction, in %/min, is calculated from Formula (3)²⁾:

$$\frac{dR}{dt}_{(R=40)} = \frac{33,6}{t_{60} - t_{30}} \quad (3)$$

where

t_{30} is the time, in minutes, to attain a degree of reduction of 30 %;

t_{60} is the time, in minutes, to attain a degree of reduction of 60 %;

33,6 is a constant.

9.2.3 Reducibility index for 90 % reduction

Read off, from the reduction curve, the time, in minutes, to attain degrees of reduction of 80 % and 95 %.

The reducibility index $\frac{dR}{dt}_{(R=90)}$ for 90 % reduction ($O/Fe = 0,15$), expressed as the rate of reduction, in %/min, is calculated from Formula (4):

$$\frac{dR}{dt}_{(R=90)} = \frac{13,9}{t_{95} - t_{80}} \quad (4)$$

where

t_{80} is the time, in minutes, to attain a degree of reduction of 80 %;

t_{95} is the time, in minutes, to attain a degree of reduction of 95 %;

13,9 is a constant.

9.3 Calculation of the degree of metallization (*M*)

9.3.1 Determination of the degree of metallization from chemical analysis (*M*)

The degree of metallization, *M*, expressed as a percentage by mass, is calculated from Formula (5):

$$M = \frac{w_0}{w_t} \times 100 \quad (5)$$

where

w_0 is the metallic iron content, expressed as a percentage by mass, of the reduced test portion;

w_t is the total iron content, expressed as a percentage by mass, of the reduced test portion.

Express the result to one decimal place.

9.3.2 Determination of the degree of metallization from R_{90} (*MR*)

During the preparation of the reduced test portion for chemical analysis, some reoxidation can occur. If the iron(II) oxide content before reduction (w_1) is less than 2 %, the chemical analysis can be avoided

2) The derivation of the formula is given in [Annex C](#).

and the degree of metallization M_R , expressed as a percentage by mass, can be calculated directly from R_{90} using Formula (6)³⁾:

$$M_R = 1,43 \times R_{90} - 43 \quad (6)$$

Express the result to one decimal place.

9.4 Repeatability for R_{90} and acceptance of test results

Follow the procedure in [Annex A](#) by using the repeatability values for R_{90} given in [Table 1](#). The results shall be reported to one decimal place.

Table 1 — Repeatability (r) for R_{90}

Type of iron ore	r %, absolute
Pellets	2,0
Lump ores	3,5

10 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 11258:2015;
- b) all details necessary for the identification of the sample;
- c) the name and address of the test laboratory;
- d) the date of the test;
- e) the date of the test report;
- f) the signature of the person responsible for the test;
- g) the details of any operation and any test conditions not specified in this International Standard or regarded as optional, as well as any incident which may have had an influence on the results;
- h) the reducibility indices $\frac{dR}{dt}_{(R=40)}$ and $\frac{dR}{dt}_{(R=90)}$;
- i) the degree of metallization, M or M_R ;
- j) the final degree of reduction, R_{90} ;
- k) the total iron and iron(II) contents of the test portion before reduction.

11 Verification

Regular checking of the apparatus is essential to ensure test result reliability. The frequency of checking is a matter for each laboratory to determine.

The conditions of the following items shall be checked:


- weighing device;
- reduction tube;

3) The derivation of this formula is given in [Annex C](#).

- temperature control and measurement devices;
- balance;
- gas flow meters;
- purity of gases;
- recording system;
- time-control device.

It is recommended that internal reference material be prepared and used periodically to check test repeatability.


Appropriate records of verification activities shall be maintained.

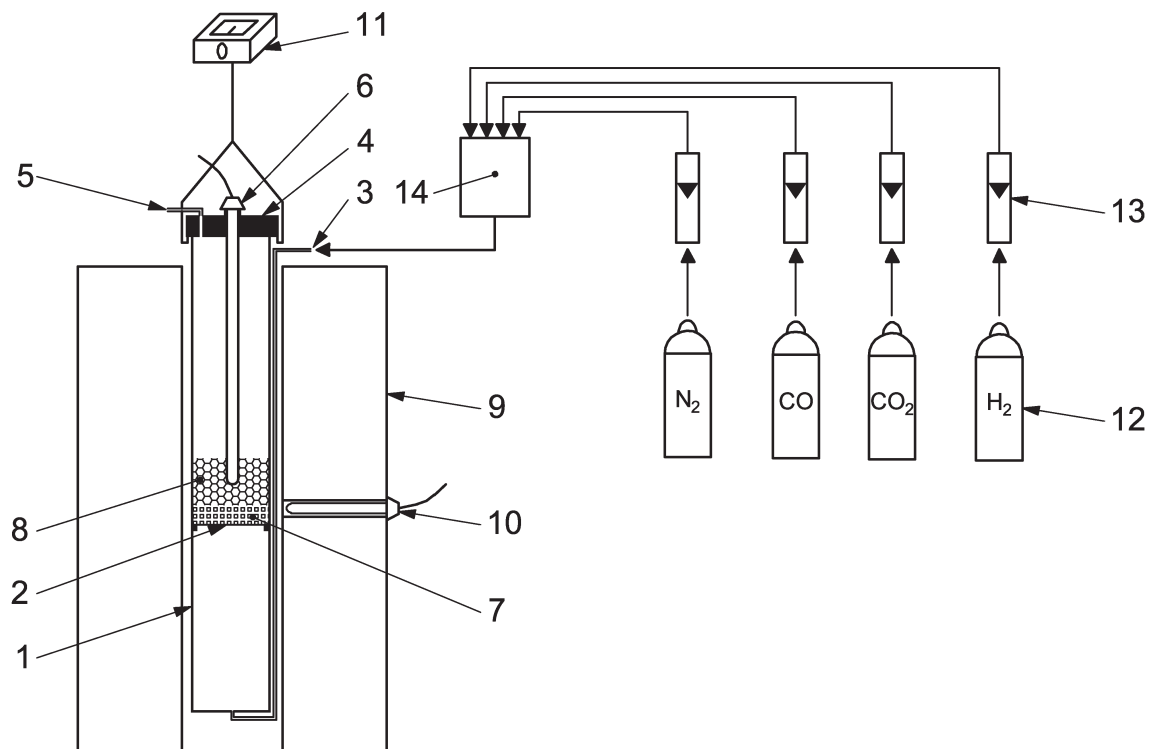

Key

- | | | | |
|-----------------------|--|--------------------------|--|
| Reduction tube | | Furnace | |
| 1 | reduction tube wall | 9 | electrically heated furnace |
| 2 | perforated plate | 10 | thermocouple for temperature regulation of furnace |
| 3 | gas inlet | 11 | balance |
| 4 | lid | Gas-supply system | |
| 5 | gas outlet | 12 | gas cylinders |
| 6 | thermocouple for measuring the reduction temperature | 13 | gas flow meters |
| 7 | porcelain ball layer | 14 | mixing vessel |
| 8 | test portion | | |

Figure 1 — Example of test apparatus (schematic diagram)

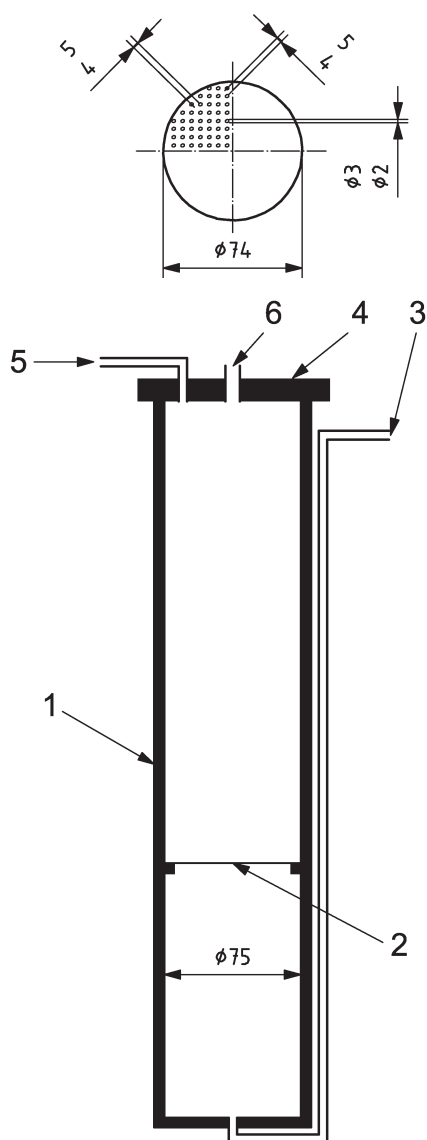

Key


- 1 reduction tube wall
- 2 perforated plate
- 3 opening for gas inlet
- 4 lid
- 5 opening for gas outlet
- 6 opening for thermocouple insertion

NOTE Dimensions not specified in the apparatus clause are shown for information only.

Figure 2 — Example of reduction tube (schematic diagram)

Annex A (normative)

Flowsheet of the procedure for the acceptance of test results

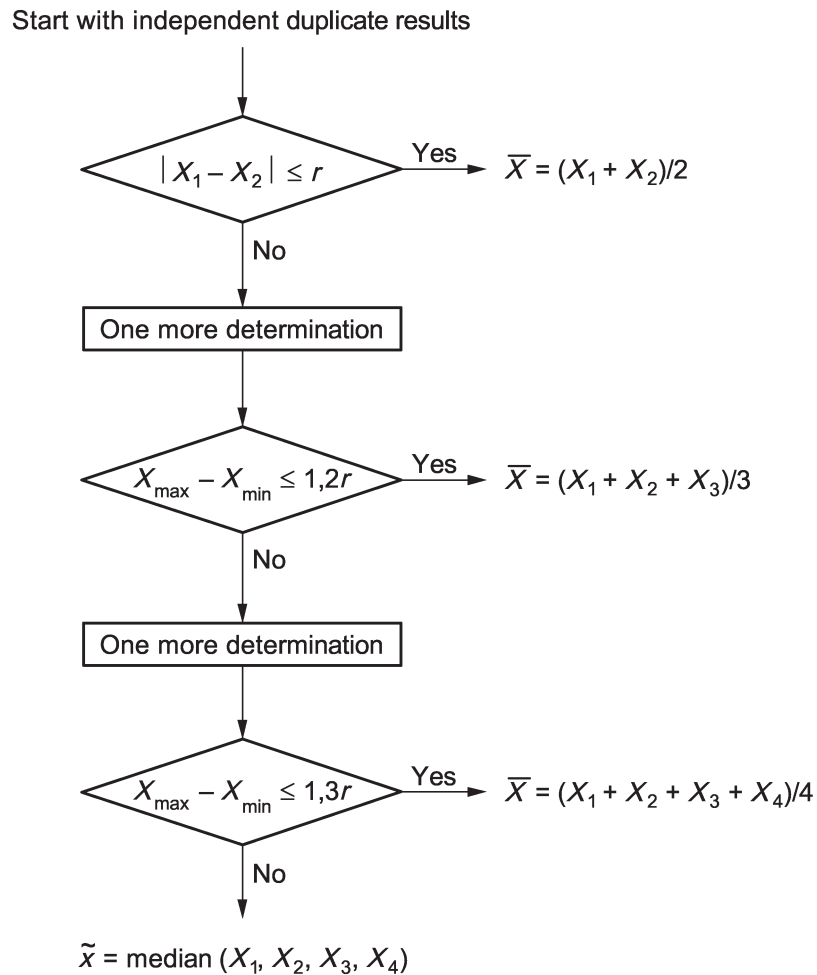

r: see [Table 1](#)

Annex B (informative)

Derivation of formula for reducibility

The “Degree of reduction” describes the extent to which oxygen has been removed from iron oxides and is defined generally as shown below:

$$\text{Degree of reduction} = \frac{\text{Oxygen removed from iron oxide}}{\text{Original oxygen combined with iron}} \quad (\text{B.1})$$

Formula (1) in 9.1 is derived on the assumption that all oxygen combined with iron is present in the form of hematite (Fe_2O_3) whereas, for most iron ore materials, some magnetite (Fe_3O_4), wustite (FeO), and metallic iron are also present. Therefore, the degree of reduction is estimated from the loss in mass of the test portion during reduction plus the difference between the theoretical oxygen content of the original sample, based on all iron being associated as Fe_2O_3 , and the true oxygen content based on actual amounts of Fe_2O_3 , Fe_3O_4 , and FeO in the sample.

$$R_t = \frac{m_0 w_1 \times \frac{8}{71,85}}{m_0 w_2 \times \frac{48}{111,7}} \times 100 + \frac{\Delta m_t}{m_0 \times \frac{w_2}{100} \times \frac{48}{111,7}} \times 100 \quad (\text{B.2})$$

Formula (3) in 9.2.2 is derived on the assumption that the rate of oxygen removed from iron ore is a first-order reaction with respect to the prevailing oxygen concentration.

$$-\frac{dO}{dt} = k \times O_v \quad (\text{B.3})$$

$$dO = -dR \times \frac{O_{\text{total}}}{100} \quad (\text{B.4})$$

$$\frac{O_v}{O_{\text{total}}} = 1 - \frac{R}{100} \quad (\text{B.5})$$

where

O_v is the prevailing oxygen content;

O_{total} is the total oxygen combined with iron (as Fe_2O_3);

R is the degree of reduction.

From Formulae (B.3), (B.4), and (B.5), the rate of reduction is derived:

$$\frac{dR}{dt} = k \times \left(1 - \frac{R}{100}\right) \times 100 \quad (\text{B.6})$$

Integration of Formula (B.6) gives

$$\log_{10} \left(1 - \frac{R}{100}\right) = -0,434 kt + C$$

For R between 30 % and 60 %.

$$k = \frac{-\log_{10} (1 - 60 / 100) + \log_{10} (1 - 30 / 100)}{0,434 (t_{60} - t_{30})} = \frac{0,56}{t_{60} - t_{30}} \quad (\text{B.7})$$

In the case of hematite, the oxygen/iron ratio of 0,9 has the same meaning as $R = 40$ %. By substituting $R = 40$ % and Formula (B.7) into Formula (B.6), the value of dR/dt (at $O/Fe = 0,9$) is obtained:

$$\frac{dR}{dt} (O/Fe = 0,9) = \frac{33,6}{t_{60} - t_{30}}$$

Annex C (informative)

Derivation of formula for degree of metallization from R_{90}

The degree of metallization is the ratio of the content of metallic iron to the total content of iron expressed as a percentage.

The iron content can be expressed as a percentage by mass of the reduced test portion or in absolute terms as follows:

$$M_R = 100 \times \frac{m_{\text{FeM}}}{m_{\text{FeT}}} \quad (\text{C.1})$$

where

M_R is the degree of metallization of the test portion after 90 min of reduction, expressed as a percentage by mass;

m_{FeM} is the mass of metallic iron in the test portion after 90 min of reduction, in grams;

m_{FeT} is the mass of total iron in the test portion, in grams.

Considering that the amount of iron (III) in the test portion after 90 min of reduction is very small, the following can be assumed:

$$m_{\text{FeM}} = m_{\text{FeT}} - M_{\text{Fe}^{+2}} \quad (\text{C.2})$$

where

$M_{\text{Fe}^{+2}}$ is the mass of iron (II) in the test portion after 90 min of reduction, in grams.

$$M_{\text{Fe}^{+2}} = \left(\frac{55,8}{16,8} \right) \times m_{\text{O}} = 3,32 m_{\text{O}} \quad (\text{C.3})$$

where

m_{O} is the mass of oxygen in $\text{FeO}_{1,05}$ in the test portion after 90 min of reduction, in grams.

$$m_{\text{O}} = \left(1 - \frac{R_{90}}{100} \right) \times m_{\text{O},1} \quad (\text{C.4})$$

where

$m_{\text{O},1}$ is the mass of oxygen in the test portion before reduction, in grams.

Assuming that the amount of iron (II) oxide content in the test portion is very small

$$m_{O,1} = 0,43 \times FeT \quad (C.5)$$

Substituting Formula (C.5) in Formula (C.4)

$$m_O = \left(1 - \frac{R_{90}}{100}\right) \times 0,43 \times m_{FeT} \quad (C.6)$$

Substituting Formula (C.6) in Formula (C.3)

$$M_{Fe^{+2}} = 3,32 \times 0,43 \times m_{FeT} \times \left(1 - \frac{R_{90}}{100}\right) \quad (C.7)$$

Substituting Formula (C.7) in Formula (C.2)

$$m_{FeM} = m_{FeT} - 3,32 \times 0,43 \times m_{FeT} \times \left(1 - \frac{R_{90}}{100}\right) \quad (C.8)$$

Substituting Formula (C.8) in Formula (C.1)

$$M_R = 100 \times \frac{m_{FeT} - 3,32 \times 0,43 \times m_{FeT} \times \left(1 - \frac{R_{90}}{100}\right)}{m_{FeT}} \quad (C.9)$$

$$M_R = 1,43 \times R_{90} - 43 \quad (C.10)$$

Bibliography

- [1] ISO 9686, *Direct reduced iron — Determination of carbon and/or sulfur — High-frequency combustion method with infrared measurement*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™