

BS ISO 11358-3:2013



BSI Standards Publication

Plastics — Thermogravimetry (TG) of polymers

Part 3: Determination of the activation energy using the Ozawa-Friedman plot and analysis of the reaction kinetics

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 11358-3:2013.

The UK participation in its preparation was entrusted to Technical Committee PRI/21, Testing of plastics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 69418 9

ICS 83.080.01

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 28 February 2014.

Amendments issued since publication

Date	Text affected
------	---------------

**Plastics — Thermogravimetry (TG) of
polymers —**

Part 3:

**Determination of the activation
energy using the Ozawa-Friedman plot
and analysis of the reaction kinetics**

Plastiques — Thermogravimétrie (TG) des polymères —

*Partie 3: Détermination de l'énergie d'activation à l'aide du
graphique d'Ozawa-Friedman et analyse cinétique de la réaction*





COPYRIGHT PROTECTED DOCUMENT

© ISO 2013

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
6 Test specimens	2
7 Mass and temperature calibration	2
7.1 Mass calibration.....	2
7.2 Temperature calibration.....	3
8 Procedure	3
8.1 General.....	3
8.2 Non-oxidative reactions.....	4
8.3 Oxidative reactions.....	4
9 Expression of results	4
9.1 Graphical presentation.....	4
9.2 Determination of activation energy.....	5
9.3 Master curves.....	6
10 Precision	9
11 Test report	9
Annex A (informative) Mathematical background	10
Bibliography	13

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

ISO 11358 consists of the following parts, under the general title *Plastics — Thermogravimetry (TG) of polymers*:

- *Part 1: General principles*
- *Part 2: Determination of activation energy*
- *Part 3: Determination of the activation energy using the Ozawa-Friedman plot and the reaction kinetic analysis*

Introduction

Controlled rate thermogravimetry (CRTG) is used to study the decomposition of polymers. The Ozawa-Friedman method is typically applied to the analysis of data obtained by CRTG and also to that obtained by the combined use of isothermal thermogravimetry (iso-TG) with conventional linear heating rate thermogravimetry (LHTG), i.e. using a constant heating rate.

Plastics — Thermogravimetry (TG) of polymers —

Part 3:

Determination of the activation energy using the Ozawa-Friedman plot and analysis of the reaction kinetics

1 Scope

This International Standard specifies an analysis method for determining the activation energy using the Ozawa-Friedman plot. It also specifies the preparation of master plots for verification of the reaction kinetics determined by thermogravimetry.

The Ozawa-Friedman plot (logarithm of the rate of mass loss versus the reciprocal of absolute temperature at a given mass loss) is a derivative method that can be applied to data obtained by any mode of temperature change in thermal analysis; e.g. isothermal, constant heating rate, sample-controlled thermal analysis, temperature jump, and repeated temperature scanning.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 11358-1, *Plastics — Thermogravimetry (TG) of polymers — Part 1: General principles*

ISO 11358-2, *Plastics — Thermogravimetry (TG) of polymers — Part 2: Determination of activation energy*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 11358-1, ISO 11358-2 and the following apply.

3.1 conversion

$$C = (m_t - m_i) / (m_f - m_i)$$

where

m_i is the initial quantity, in mg;

m_t is the quantity at a particular time and temperature, in mg;

m_f is the final quantity, in mg.

See ISO 11358-1 and ISO 11358-2.

Note 1 to entry: It is also referred to as the mass loss fraction.

3.2 generalized time

$$t_{\text{gen}} = \int_0^t \exp\left(-\frac{E_a}{RT}\right) dt$$

where

- E_a is the activation energy, expressed in kJ/mol;
- R is the gas constant, expressed as 8.314 J/(mol K);
- T is the absolute temperature, expressed in Kelvin;
- t is time, expressed in minutes.

3.3 generalized rate of conversion

$$\frac{dC}{dt_{\text{gen}}} = \exp\left(\frac{E_a}{RT}\right) \frac{dC}{dt}$$

3.4 master curve

plot that can be used to evaluate the results and investigate the reaction kinetics models

Note 1 to entry: Examples of master curves are conversion versus the generalized time, conversion versus the generalized rate of conversion, generalized time versus the generalized rate of conversion.

4 Principle

Test specimens are heated using any temperature profile and the change in mass is measured as a function of temperature and time. At a given conversion, the logarithm of the rate of conversion is plotted versus the reciprocal of the absolute temperature, and the activation energy is calculated from the slope of the straight line fit to the data thus obtained.

At least two of the master curves enable verification of the reaction kinetics analysis.

5 Apparatus

The apparatus shall be in accordance with ISO 11358-1.

6 Test specimens

Test specimens shall be in the form of powder, pellets, flakes, filaments, or film. The test specimens shall be prepared by cutting the material, as necessary, to a size appropriate for the apparatus (see ISO 11358-1).

7 Mass and temperature calibration

7.1 Mass calibration

The procedure of mass calibration is given in ISO 11358-1.

7.2 Temperature calibration

The procedure of temperature calibration is given in ISO 11358-1.


8 Procedure

8.1 General

The determination of the rate of conversion dC/dt is necessary for the analysis in this International Standard. The rate of conversion versus absolute temperature shall be determined.

See ISO 11358-1 and ISO 11358-2.

Perform tests using either an isothermal run, constant rate heating and cooling, sample mass controlled rate thermal analysis, temperature jump, repeated temperature scanning, or any combination of the above, using specimens of similar mass ($\pm 1\%$). For examples of linear heating rate thermogravimetry (LHTG) and sample mass controlled rate thermogravimetry (CRTG), see [Figures 1a](#) and [1b](#), respectively.

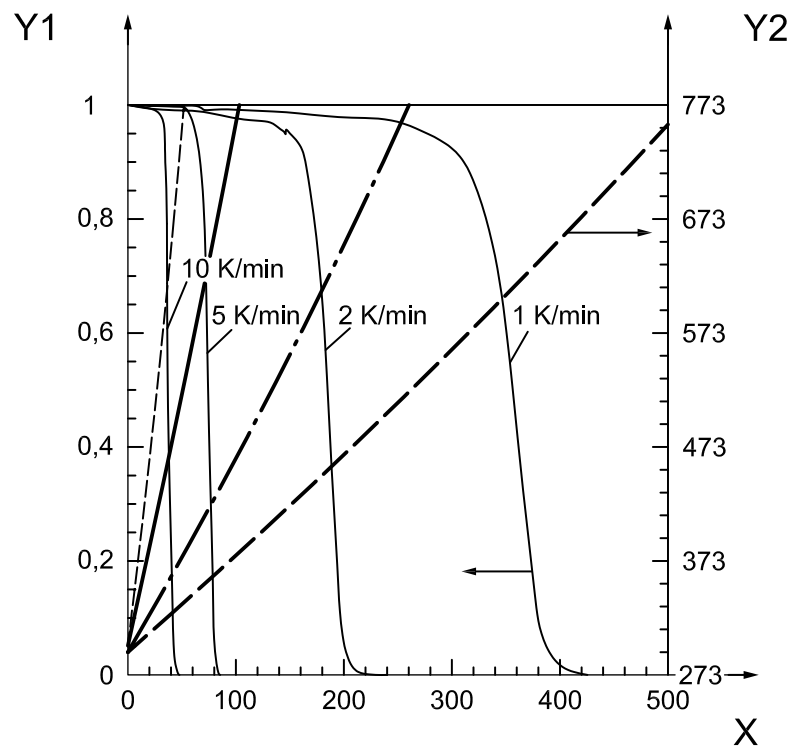


Key

X t/min

Y1 $(1 - C)$

Y2 T/K

Figure 1a — Example of linear heating rate thermogravimetry (LHTG) measurements of PMMA

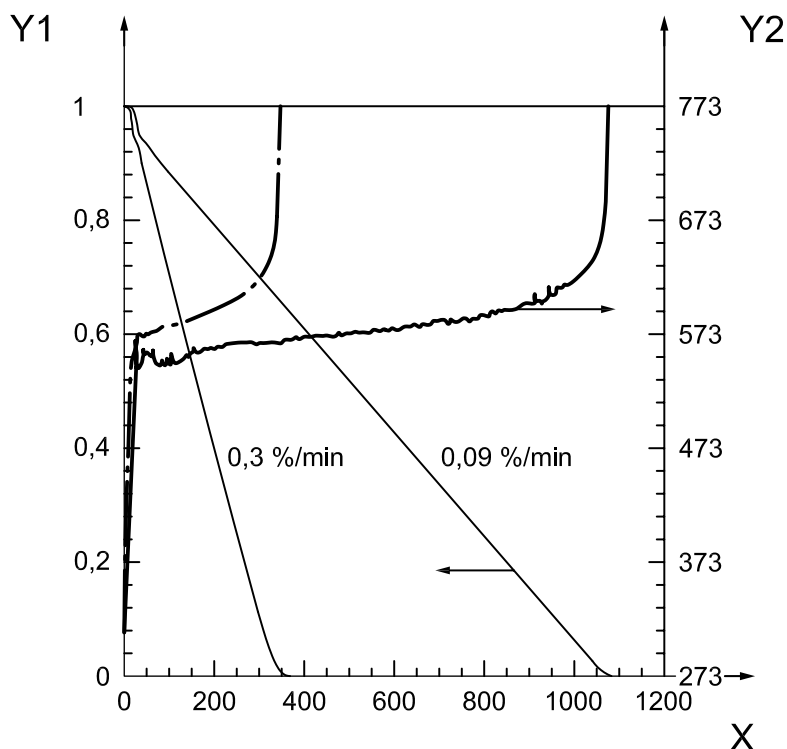

Key

X t/min
 Y1 $(1 - C)$
 Y2 T/K

NOTE The units of %/min indicate the percentage weight loss per minute of the mass controlled rate.

Figure 1b — Example of sample mass controlled rate thermogravimetry (CRTG) measurements of PMMA

Preferably, the specimen mass should be between 1 mg and 10 mg and the temperature scanning rate between 2 K min^{-1} and 10 K min^{-1} .

Determine the rate of conversion (or rate of change of mass loss fraction with time) at a given conversion (or given mass loss fraction).

8.2 Non-oxidative reactions

The procedure of non-oxidative reactions is given in ISO 11358-2.

8.3 Oxidative reactions

The procedure of oxidative reactions is given in ISO 11358-2.

9 Expression of results

9.1 Graphical presentation

For a given conversion (or mass loss fraction), present the thermogravimetry data in the form of a plot of the logarithm of the rate of conversion (or rate of change of mass loss fraction with time) versus the reciprocal of the absolute temperature, i.e. the Ozawa-Friedman plot, see [Figure 2](#).

9.2 Determination of activation energy

The conversion (or the mass loss fraction) is not directly related to the quantity of reacted pieces, for example as in the random scission of the main chain of polymers. Generally, the rate formulae are as follows:

$$C = f(\alpha) \quad (1)$$

and

$$\frac{d\alpha}{dt} = A \exp\left(\frac{-E_a}{RT}\right) g(\alpha) \quad (2)$$

where

- α is the reacted fraction at time t ;
- $f(\alpha)$ is an arbitrary function;
- A is the pre-exponential factor;
- $g(\alpha)$ is a function describing the reaction mechanism.

By taking the logarithm of both sides of Formula (2) then


$$\ln\left(\frac{d\alpha}{dt}\right) = \ln\{Ag(\alpha)\} - \frac{E_a}{RT} \quad (3)$$

When plotted for fixed values of α , with various conversion rate values determined for different experimental temperature control profiles, the slope of the plot of $\ln\left(\frac{d\alpha}{dt}\right)$ versus $\frac{1}{T}$ has the value $-E_a/R$ and is used to determine the activation energy E_a , as the first term in the right side of Formula (3) is constant.

As an example, the experimental data presented in [Figures 1a](#) and [1b](#) have been analysed, assuming an n^{th} order type reaction and thus $C = f(\alpha) = \alpha$ ([Annex A](#)), the results of which are presented in [Table 1](#) and [Figure 2](#).

Table 1 — The rate of conversion dC/dt and the estimated activation energy E_a at different conversion levels, determined from the controlled rate thermogravimetry (CRTG) data presented in [Figure 1b](#)

	1000/T (K ⁻¹)	ln(dC/dt (% min ⁻¹)) at C = 0,2	1000/T (K ⁻¹)	ln(dC/dt (% min ⁻¹)) at C = 0,5	1000/T (K ⁻¹)	ln(dC/dt (% min ⁻¹)) at C = 0,8
CRTG, 0,09 %/min	1,779	-2,425	1,735	-2,411	1,677	-2,448
CRTG, 0,3 %/min	1,731	-1,161	1,693	-1,183	1,641	-1,288
Activation Energy (kJmol ⁻¹)						
Ozawa-Friedman plot		207,3	232,8		261,9	

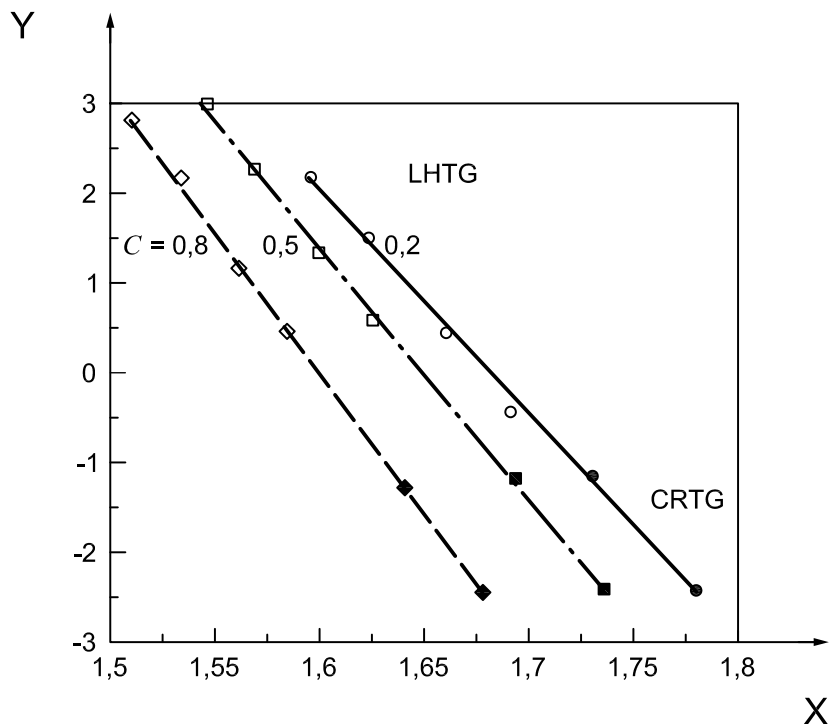

Key

X 1 000/T K⁻¹

Y ln (dC/dt / % min⁻¹)

Figure 2 — Ozawa-Friedman plot of the LHTG data determined from Figure 1a (open symbols), and CRTG data from Table 1 (closed symbols) at conversion values of 0,2, 0,5 and 0,8

9.3 Master curves

Given Formulae (1) and (2), the assumed models of the method, then

$$\frac{dC}{dt} = \frac{df(\alpha)}{d\alpha} \frac{d\alpha}{dt} = \frac{df(\alpha)}{d\alpha} A \exp\left(\frac{-E_a}{RT}\right) g(\alpha) \tag{4}$$

Thus, using the generalized rate of conversion in 3.3,

$$\frac{dC}{dt_{gen}} = Ag(\alpha) \frac{df(\alpha)}{d\alpha} \tag{5}$$

The master curve, the plot of

$$\frac{dC}{dt_{gen}} = \exp\left(\frac{E_a}{RT}\right) \frac{dC}{dt} \tag{6}$$

can be used to demonstrate how consistent the reaction being analysed is with the assumed models of Formulae (1) and (2).

Similarly, other relations between C, t_{gen} and dC/dt_{gen} can be derived. According to Formula (6) and Formula (A.7) in Annex A, the generalized rate of conversion dC/dt_{gen} has the following relationship to


the experimental kinetic data via the generalized rate of the reacted fraction $d\alpha/dt_{\text{gen}}$ for an n^{th} order reaction where $C = f(\alpha) = \alpha$, as shown in [Table A.1](#):

$$\frac{dC/dt_{\text{gen}}}{(dC/dt_{\text{gen}})_{C=0,5}} = \frac{d\alpha/dt_{\text{gen}}}{(d\alpha/dt_{\text{gen}})_{C=0,5}} = \frac{d\alpha/dt}{(d\alpha/dt)_{C=0,5}} \cdot \frac{\exp(E_a/RT)}{\exp(E_a/RT_{0,5})} \quad (7)$$

where

$T_{0,5}$ is the reaction temperature at $C = 0,5$.

For calculating the experimental values of $(dC/dt_{\text{gen}})/(dC/dt_{\text{gen}})_{C=0,5}$, the experimental kinetic data have to be used, e.g. [Figure 3](#).

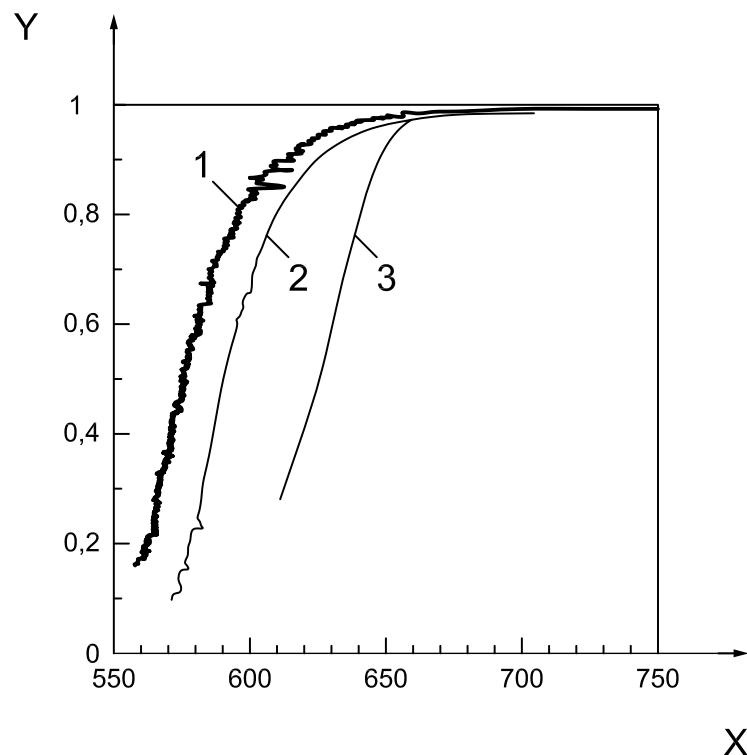

Key

- X T / K
- Y Conversion C
- 1 CRTG 0,09 %/min
- 2 CRTG 0,3 %/min
- 3 LHTG 2 K/min

Figure 3 — Experimental conversion curves of CRTG (0,3 %/min and 0,09 %/min) and LHTG (2 K/min) of PMMA plotted as a function of temperature

Furthermore, master curves can be used to help identify the reaction mechanism model, $g(\alpha)$, and the relation between the conversion and the reaction species, $f(\alpha)$, by fitting theoretical models to the experimental data, and revising the model as necessary to achieve a good fit of experimental data with theoretical values.


In the case of $C = f(\alpha) = \alpha$, Formula (5) gives

$$\frac{dC}{dt_{\text{gen}}} = Ag(\alpha) \quad (8)$$

Using the conversion of $\alpha = 0,5$ as a reference value, the following formula is derived from Formula (2) and (7):

$$\frac{d\alpha / dt_{\text{gen}}}{(d\alpha / dt_{\text{gen}})_{\alpha=0,5}} = \frac{g(\alpha)}{g(0,5)} \quad (9)$$

Formula (9) states that, at a given conversion α , the experimentally determined $(d\alpha/dt_{\text{gen}})/(d\alpha/dt_{\text{gen}})_{\alpha=0,5}$ and the theoretically calculated $g(\alpha)/g(0,5)$ are equivalent when an appropriate function $g(\alpha)$ for describing the reaction process under investigation is applied. Figure 4 compares the theoretical plot of $g(\alpha)/g(0,5)$ versus α with the experimental master plots of $(d\alpha/dt_{\text{gen}})/(d\alpha/dt_{\text{gen}})_{\alpha=0,5}$ versus α calculated using the experimental data of Figure 3. In this case an n^{th} order reaction with a reaction order $n = 1,9$ has been assumed and used to generate the theoretical plot and provides a good fit to the experimental master plot data as shown in Figure 4.

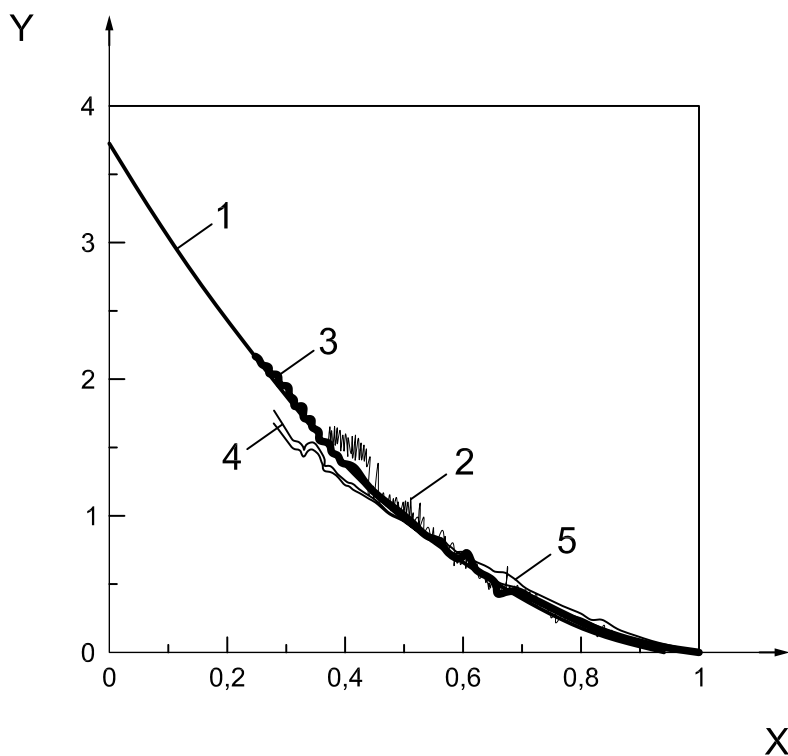

Key

- X α
- Y $(d\alpha/dt_{\text{gen}})/(d\alpha/dt_{\text{gen}})_{\alpha=0,5}$
- 1 $g(\alpha)/g(0,5)$
- 2 CRTG 0,09 %/min
- 3 CRTG 0,3 %/min
- 4 LHTG 2 °K/min
- 5 LHTG 5 °K/min

NOTE It was assumed that $C = \alpha$ as for an n^{th} order reaction as listed in Table A.1 and thus $dC/dt_{\text{gen}} = d\alpha/dt_{\text{gen}}$.

Figure 4 — A comparison of the experimental master plots of $(d\alpha/dt_{\text{gen}})/(d\alpha/dt_{\text{gen}})_{\alpha=0,5}$ versus α with the theoretical master curves $g(\alpha)/g(0,5)$ versus α for the thermal decomposition of PMMA

10 Precision

The standard deviations of the estimated activation energy E_a and the generalized rate of conversion dC/dt_{gen} are reported for the specific case analysed to be less than 5 %.^[4]

11 Test report

The test report shall include the following information:

- a) a reference to this part of ISO 11358 (i.e. ISO 11358-3);
- b) the details necessary for complete identification of the material analysed;
- c) the form and dimensions of the test specimen;
- d) the mass of the test specimen;
- e) details of the conditioning of the specimen prior to the test;
- f) the specimen pan size, mass and material of construction;
- g) the atmosphere and gas-flow rate used;
- h) the details of the temperature profile used;
- i) the standard reference material(s) used for temperature calibration;
- j) the activation energy, determined from a linear slope in the plot of the logarithm of the rate of mass loss versus the reciprocal absolute temperature at a given mass loss, and the mass loss (see [Figure 1](#));
- k) the reaction order determined with a fitting function of the kinetics, if required (see [Table 1](#)).
- l) any observations regarding equipment, test conditions or test specimen behaviour;
- m) the date of the determination.

Annex A (informative)

Mathematical background

In thermal analysis, the property P of the sample, for example the mass, or the rate of change of the property, dP/dt (or dP/dT) are recorded as a function of time t or temperature T . In order to estimate the kinetic parameters by this method, the property measured should be described only by the parameter, α . Thus the conversion, C , which is equal to $(P-P_0)/(P_\infty-P_0)$, (where P_0 and P_∞ are the property values before and after the reaction, respectively), is a function of α :

$$C = f(\alpha) \tag{A.1}$$

The parameter α is assumed to change following ordinary reaction kinetics:

$$\frac{d\alpha}{dt} = A \exp\left(-\frac{E_a}{RT}\right) g(\alpha) \tag{A.2}$$

where

A , E_a and R are the pre-exponential factor, the activation energy and the gas constant, respectively.

Formula (A.2) is rearranged as:

$$\int_0^\alpha \frac{d\alpha}{g(\alpha)} = A \int_0^t \exp\left(-\frac{E_a}{RT}\right) dt \tag{A.3}$$

or

$$G(\alpha) = At_{\text{gen}} \tag{A.4}$$

where

$$G(\alpha) = \int_0^\alpha \frac{d\alpha}{g(\alpha)} \tag{A.5}$$

and t_{gen} is the generalized time defined as

$$t_{\text{gen}} = \int_0^t \exp\left(-\frac{E_a}{RT}\right) dt \tag{A.6}$$

In principle, from Formulae (A.1) and (A.5) and given the functions $f(\alpha)$ and $g(\alpha)$, the relationship between P and At_{gen} can be derived. The relationship between C and At_{gen} is dependent only on the functions $f(\alpha)$ and $g(\alpha)$, i.e. the mechanism of the reaction and the relationship of P with α and can be theoretically derived.

Similar theoretical relationships of derivative type can also be derived:

$$\frac{dC}{dAt_{\text{gen}}} = \frac{df(\alpha)}{d\alpha} \frac{d\alpha}{dAt_{\text{gen}}} = \frac{df(\alpha)}{d\alpha} \frac{d\alpha}{dt} \frac{dt}{dAt_{\text{gen}}} = g(\alpha) \frac{df(\alpha)}{d\alpha} \tag{A.7}$$

as

$$\frac{dAt_{\text{gen}}}{dt} = A \exp\left(-\frac{E_a}{RT}\right) \quad (\text{A.8})$$

Thus, the theoretical relationship between dC/dAt_{gen} and C and between dC/dAt_{gen} and At_{gen} can be derived and depend only on the functions $f(\alpha)$ and $g(\alpha)$. For some typical cases, dC/dAt_{gen} is shown as a function of At_{gen} in [Table A.1](#).

In the random degradation of high polymer, α is the fraction of bonds broken, and L is a measure of the least length of the polymer not volatilized. When the conversion follows a reaction of n^{th} order, $C = \alpha$.

Table A.1 — Relationship between C , α and dC/dt_{gen} for typical reaction models

Type of reaction	$C = f(\alpha)$	$g(\alpha)$	$G(\alpha)$	$d\alpha/dAt_{\text{gen}}$	dC/dAt_{gen}
n th order	A	$(1-C)^n$	$\frac{1}{n-1} \left\{ (1-C)^{1-n} - 1 \right\}$	$(1-C)^n$	$\left\{ 1 + (n-1) At_{\text{gen}} \right\}^{n/(1-n)}$
1st order	A	$1-C$	$-\ln(1-C)$	$1-C$	$\exp(-At_{\text{gen}})$
Random scission	$(1-x)^{L-1} \left\{ 1 + (L-1)\alpha \right\}$	$1-\alpha$	$-\ln(1-\alpha)$	$-L(L-1)(1-\alpha)^{L-1} \alpha$	$L(L-1) \exp\left\{ -(L-1) At_{\text{gen}} \right\} \left\{ 1 - \exp(-At_{\text{gen}}) \right\}$

Bibliography

- [1] OZAWA T. A new method of analyzing thermogravimetric data. *Bull. Chem. Soc. Jpn.* 1965, **38** p. 1881
- [2] OZAWA T. Kinetic analysis of derivative curves in thermal analysis. *J. Therm. Anal.* 1970, **2** pp. 301–324
- [3] OZAWA T. Applicability of Friedman plot. *J. Therm. Anal.* 1986, **31** pp. 547–551
- [4] OZAWA T. Controlled rate thermogravimetry. *J. Therm. Anal. Calorim.* 2000, **59** pp. 375–384
- [5] OZAWA T. Non-isothermal kinetics (1) Single elementary process. *Netsu Sokutei.* 2004, **31** pp. 125–132
- [6] GOTOR F.J., & CRIADO J.M. Malek, Jiri, Koga, N., Kinetic analysis of Solid state reactions: The universality plots for analyzing isothermal and nonisothermal experiments. *J. Phys. Chem. A.* 2000, **104** pp. 10777–10782
- [7] ARII T., ICHIHARA S., NAKAGAWA H., FUJII N. A kinetic study of the thermal decomposition of polyesters by controlled rate thermogravimetry. *Thermochim. Acta.* 1998, **319** pp. 139–149
- [8] BIPM, IEC, IFCC, ISO, IUPAC, IUPAP, OIML. “Guide to the expression of uncertainty in measurement”. International Organization for Standardisation, Geneva, First edition 1995. Switzerland. ISBN 92-67-10188-9

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™