

BS ISO 11359-1:2014



BSI Standards Publication

Plastics — Thermomechanical analysis (TMA)

Part 1: General principles

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 11359-1:2014. It supersedes BS ISO 11359-1:1999 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/21, Testing of plastics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 77734 9

ICS 83.080.01

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 January 2014.

Amendments issued since publication

| Date | Text affected |
|------|---------------|
|------|---------------|

INTERNATIONAL
STANDARD

ISO
11359-1

Second edition
2014-01-15

**Plastics — Thermomechanical
analysis (TMA) —**

**Part 1:
General principles**

Plastiques — Analyse thermomécanique (TMA) —

Partie 1: Principes généraux



Reference number
ISO 11359-1:2014(E)

© ISO 2014



COPYRIGHT PROTECTED DOCUMENT

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

| | Page |
|--------------------------------------|-----------|
| Foreword | iv |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 1 |
| 4 Principle | 1 |
| 5 Apparatus | 1 |
| 6 Test specimens | 2 |
| 7 Procedure | 3 |
| 7.1 Calibration | 3 |
| 7.2 Blank run..... | 4 |
| 7.3 Determination | 4 |
| 8 Test report | 4 |
| Bibliography | 5 |

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

This second edition cancels and replaces the first edition (ISO 11359-1:1999), which has been technically revised with the following changes:

- clarification that deformations shall occur under constant load;
- inclusion of reference to ISO 472 in Definitions and cancellation of duplicate and trivial definitions;
- revision of apparatus requirements following guidelines specified in ISO 11357-1 and update of accuracy specifications;
- revision of specification of temperature calibration;
- revision of specification of displacement and sample length measurement.

ISO 11359 consists of the following parts, under the general title *Plastics — Thermomechanical analysis (TMA)*:

- *Part 1: General principles*
- *Part 2: Determination of coefficient of linear thermal expansion and glass transition temperature*
- *Part 3: Determination of penetration temperature*

Plastics — Thermomechanical analysis (TMA) —

Part 1: General principles

1 Scope

This part of ISO 11359 specifies the general conditions for the thermomechanical analysis of thermoplastics and thermosetting materials, filled or unfilled, in the form of sheet or moulded parts.

Thermomechanical analysis consists of the determination of deformations of a test specimen under constant load as a function of temperature and/or time.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 472, *Plastics — Vocabulary*

ISO 11359-2, *Plastics — Thermomechanical analysis (TMA) — Part 2: Determination of coefficient of linear thermal expansion and glass transition temperature*

ISO 11359-3, *Plastics — Thermomechanical analysis (TMA) — Part 3: Determination of penetration temperature*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 472 and the following apply.

3.1

thermodilatometry

technique in which one dimension (or the volume) of a substance under negligible constant stress is measured as a function of temperature while the substance is subjected to a controlled temperature programme

Note 1 to entry: A distinction is made between linear thermodilatometry (in which one dimension is measured) and volume thermodilatometry (in which the volume is measured).

4 Principle

The deformation of a material under constant stress is measured as a function of time at a constant temperature or as a function of temperature.

5 Apparatus

The components of a basic thermomechanical analyser consist of the following:

5.1 Temperature-programmable furnace, capable of:

- a) generating constant heating or cooling rates for the intended measurements;
- b) covering a temperature range in line with the experimental requirements;
- c) maintaining the temperature variation at a given location to within ± 1 K over time;
- d) measuring the temperature with an accuracy of ± 1 K over time;
- e) maintaining a controlled purge gas atmosphere.

5.2 Displacement transducer, with an accuracy of $\pm 0,1$ % or better.

5.3 Measurement probe, rod made of a material of low thermal-expansion coefficient (e.g. silica, ceramics, quartz glass, etc.), linked mechanically to the displacement transducer, with one end in contact with the test specimen, and with a shape suited to the type of measurement.

The apparatus shall include a means of compensating for the probe mass, either through calibration or tarring.

5.4 Load application device, shall be suitable for the intended measurement, e.g. compression, penetration, tension, flexure, etc.

The magnitude of the load applied to the rod depends on the type of measurement required. It is necessary to determine the force actually applied to the specimen.

5.5 Cooling device, capable of generating and maintaining controlled and reproducible low temperatures.

5.6 Inert or oxidising gas supply, type, purity, and flow rates of purge gas shall be suitable for the intended measurements.

5.7 Micrometers or callipers, with an accuracy of ± 2 μm or better.

6 Test specimens

Cut test specimens from a sheet or moulded article in such a way that any heating will not modify its structure. The test specimen can be of any shape but shall have a thickness suitable for the intended measurement and specimen holder.

Ensure that the lower and upper surfaces of the specimen are parallel and smooth, smoothing down if necessary with abrasive paper (e.g. No. 200 grade).

NOTE Removal (smoothing) of the surface of specimens moulded or formed from some materials might change the relative amount of oriented skin layers which, in turn, might affect the mechanical response.

If specimens are taken from a moulded article, report the sampling procedure used, i.e. method of extracting the specimen from the article, type of the article, and the location and orientation of specimen.

Unless otherwise specified in the appropriate material standard, condition the specimen under one of the sets of conditions specified in ISO 291.

A visual examination, by eye, shall be done to make sure that there are no imperfections or defects inside or on the surface of the specimen, for instance bubbles, holes, or scratches.

7 Procedure

7.1 Calibration


7.1.1 Furnace

Calibrate the furnace (5.1) using two or more metallic calibration materials covering the temperature range to be used for the test specimen. Calibration materials shall either be certified or chosen from those listed in Table 1, provided their purity is 99,99 % or better. The thickness of the specimens prepared from calibration materials shall be approximately 0,1 mm. Carry out the determinations of the melting point of the calibration materials under the same experimental conditions as those which will be used for the test specimen.

Measure, under the same load as will be used for the test specimen, the point at which penetration of the calibration material by the probe (5.3) occurs due to melting (see Figure 1). Determine the penetration temperature of the calibration material in accordance with ISO 11359-3.

Table 1 — Metallic calibration materials

| Metal | Melting point [5] [6] [Z] °C |
|---------|---------------------------------|
| Gallium | 29,76 |
| Indium | 156,60 |
| Tin | 231,93 |
| Lead | 327,46 |
| Zinc | 419,53 |

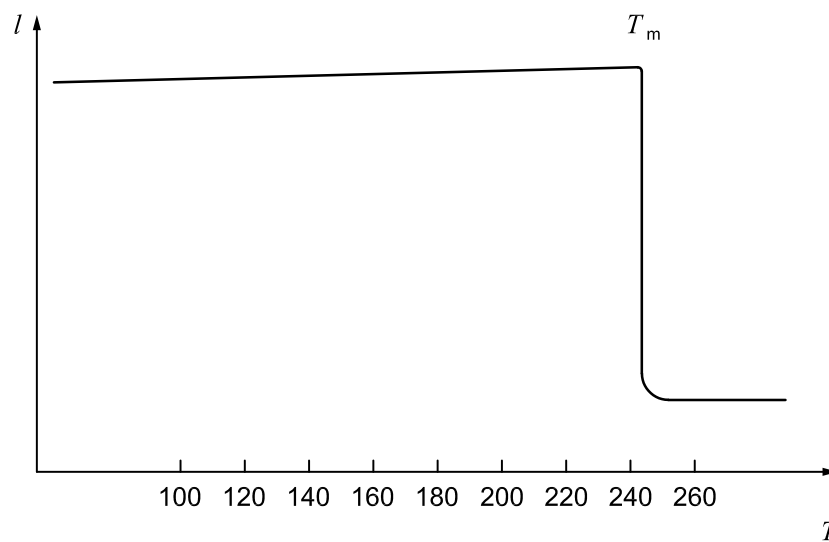

Key

- l displacement
- T temperature
- T_m melting point

Figure 1 — Determination of the melting point

7.1.2 Displacement transducer

Calibrate the displacement transducer (5.2) using a certified micrometer (5.7) or set of certified thickness gauges.

7.1.3 Load-application device

Calibrate the load-application device (5.4) by means of certified calibration masses or using a certified force gauge.

7.2 Blank run

Carry out a blank run, recording the TMA curve under the same conditions as those to be used for the test specimen, but without the test specimen.

The data obtained for the test specimen shall be corrected using the data obtained from the blank run.

7.3 Determination

Measure the length l_0 of the test specimen at one of the standard temperatures specified in ISO 291 using a micrometer or calliper (see 5.7).

Place the test specimen on the sample holder.

The details of the test conditions and procedures for TMA determinations are specified in ISO 11359-2 and ISO 11359-3. Select the temperature range, the heating and/or cooling rate, and the load to be applied as given in those International Standards, or as required in the relevant material standard.

Record the displacement as a function of temperature and/or time.

After completion of the run, cool down the specimen to room temperature.

8 Test report

The test report shall include the following:

- a) a reference to this part of ISO 11359;
- b) all details necessary for complete identification of the material or product tested (lot number, etc.);
- c) the type of test specimen used, its dimensions, the method of preparation, and its orientation with reference to the sheet or article it was taken from;
- d) details of the conditioning of the test specimen, if applicable;
- e) the type of TMA equipment used;
- f) the shape and dimensions of the probe;
- g) the materials used for calibration purposes and the values obtained;
- h) the experimental conditions used for the determination;
- i) the results of the test, including the TMA curves obtained (if necessary);
- j) the date(s) of testing.

Bibliography

- [1] ICTA, Nomenclature for Thermal Analysis, 1992 (see also Annex A)
- [2] TURI E.A. *Thermal Characterization of Polymeric Materials*. Academic Press, New York, 1981
- [3] WUNDERLICH B. *Thermal Analysis*. Academic Press, New York, 1990
- [4] ICTA. *For Better Thermal Analysis*. Third Edition, 1991
- [5] CAMMENGA H.K., EYSEL W., GMELIN E., HEMMINGER W., HÖHNE G.W.H., SARGE S.M. The temperature calibration of scanning calorimeters: Part 2: Calibration substances. *Thermochim. Acta*. 1993, **219** p. 333
- [6] SARGE S.M., HEMMINGER W., GMELIN E., HÖHNE G.W.H., CAMMENGA H.K., EYSEL W. Metrologically based procedures for the temperature, heat and heat flow rate calibration of DSC. *J. Therm. Anal.* 1997, **49** p. 1125
- [7] PRESTON-THOMAS H. The International temperature scale of 1990 (ITS-90). *Metrologia*. 1990, **27** pp. 3-10

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™