

Plastics pipes and fittings — Preparation of polyethylene (PE) pipe/pipe or pipe/fitting test piece assemblies by butt fusion

ICS 23.040.60

National foreword

This British Standard is the UK implementation of ISO 11414:2009. It supersedes BS 2782-11 MET1150B:1998 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/88/4, Test methods.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 28 February 2009

© BSI 2009

ISBN 978 0 580 60187 3

Amendments/corrigenda issued since publication

Date	Comments

INTERNATIONAL STANDARD

ISO
11414

Second edition
2009-02-01

Plastics pipes and fittings — Preparation of polyethylene (PE) pipe/pipe or pipe/fitting test piece assemblies by butt fusion

*Tubes et raccords en matières plastiques — Préparation d'éprouvettes
par assemblage tube/tube ou tube/raccord en polyéthylène (PE) par
soudage bout à bout*



Reference number
ISO 11414:2009(E)

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2009

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 11414 was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 5, *General properties of pipes, fittings and valves of plastic materials and their accessories — Test methods and basic specifications*.

This second edition cancels and replaces the first edition (ISO 11414:1996), which has been technically revised.

Plastics pipes and fittings — Preparation of polyethylene (PE) pipe/pipe or pipe/fitting test piece assemblies by butt fusion

1 Scope

This International Standard specifies a method for preparing butt-fusion-jointed test piece assemblies between polyethylene (PE) pipes and spigot-ended fittings.

This International Standard specifies the assembly parameters involved, such as the ambient temperature, joint geometry and fusion parameters, taking into account the service condition limits specified in the relevant product standards, as well as the type of pipe to be used.

This International Standard is intended to enable the effect of site assembly variables on joint performance to be determined. The fusion-jointing procedures and parameters used in the field can differ from those in this International Standard, depending on the manufacturer's written procedures and/or local standards.

NOTE The assembly and fusion-jointing technique specified in this International Standard is applicable whatever the polyethylene resin employed, provided it is used in accordance with ISO/TR 11647^[1]. Deviations from the fusion cycle specified, in order to demonstrate joint performance, can be considered in accordance with the notes in Annexes A and B.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4427-2, *Plastics piping systems — Polyethylene (PE) pipes and fittings for water supply — Part 2: Pipes*

ISO 4427-3, *Plastics piping systems — Polyethylene (PE) pipes and fittings for water supply — Part 3: Fittings*

ISO 4437, *Buried polyethylene (PE) pipes for the supply of gaseous fuels — Metric series — Specifications*

ISO 8085-2, *Polyethylene fittings for use with polyethylene pipes for the supply of gaseous fuels — Metric series — Specifications — Part 2: Spigot fittings for butt fusion, for socket fusion using heated tools and for use with electrofusion fittings*

ISO 12176-1, *Plastics pipes and fittings — Equipment for fusion jointing polyethylene systems — Part 1: Butt fusion*

3 Symbols

3.1 Symbols used in more than one phase of the fusion-jointing cycle

e_n nominal pipe wall thickness

d_n nominal external diameter of the pipe

p pressure applied to the butt-fusion joint interface

t duration of each phase in the fusion cycle

T_{nom} nominal temperature, (23 ± 2) °C

T_{max} maximum permissible ambient temperature

T_{min} minimum permissible ambient temperature

3.2 Joint geometry

Δa misalignment between the pipes or fittings to be butt-fused, expressed in terms of the difference, in millimetres, between the external diameters;

Δw maximum clearance between the fusion faces, expressed in terms of the gap, in millimetres, between the prepared faces.

3.3 Ambient temperature

T_a ambient temperature at which the joint is made

NOTE The ambient temperature may vary from the minimum temperature, T_{min} , to the maximum temperature, T_{max} , defined either in the system standards or by agreement between the manufacturer and purchaser.

3.4 Butt-fusion cycle parameters

3.4.1 General

T heater-plate temperature, measured in the zone of the heater-plate surface in contact with the pipe or spigot ends to be butt-fused

3.4.2 Phase 1: Heating

p_1 interface pressure, in megapascals¹⁾, during the heating phase, i.e. the pressure applied in the contact zone

B_1 initial bead width, in millimetres, taken as the bead width at the end of the heating phase

t_1 heating time, taken as the time necessary to obtain a bead of width B_1 in the joint region during the heating phase

3.4.3 Phase 2: Heat soak

p_2 pressure, in megapascals, between the heater plate and the pipe or spigot ends during the heat soak phase

t_2 duration, in seconds, of internal heating during the heat soak phase

3.4.4 Phase 3: Withdrawal of heater plate

t_3 time, in seconds, between the moment when the heater plate is removed from the pipe and/or spigot ends and the moment when the pipe and/or spigot ends are placed in contact with each other

1) 1 MPa = 1 N/mm²

3.4.5 Phase 4: Pressure increase

t_4 time, in seconds, required to establish the butt-fusion pressure

3.4.6 Phase 5: Butt fusion

p_5 pressure, in megapascals, applied to the contact zone during the butt-fusion phase

t_5 time, in minutes, during which the assembly remains under the butt-fusion pressure in the machine

3.4.7 Phase 6: Cooling

t_6 cooling time, in minutes, during which the butt-fused assembly is not subjected to any rough handling; this cooling can take place outside the machine

B_2 bead width, in millimetres, obtained at the end of the cooling phase

4 Pipes used for test assemblies

The pipes used for test assemblies shall be taken from straight lengths.

5 Conditioning

Condition the pipes used for test assemblies at temperature T_a (refer to Table B.1) for a period of time according to Table 1.

Table 1 — Conditioning periods

Thickness, e_n mm	Minimum conditioning period h
$e_n < 8$	3
$8 \leq e_n < 16$	6
$16 \leq e_n < 32$	10
$32 \leq e_n$	16

6 Apparatus

The butt-fusion machine shall conform to ISO 12176-1, which means that a fusion-pressure controller is present enabling the pressure to be kept constant during the whole of phases 1, 2 and 5 of the fusion cycle.

7 Jointing procedure

Using straight pipes and fittings conforming to ISO 4427-2, ISO 4427-3, ISO 4437 or ISO 8085-2, as applicable, join the components as follows, deviations from the procedure being permitted to demonstrate improvements in joint performance (appearance or mechanical properties).


- a) Fix the pipes and/or fittings in the butt-fusion machine in such a manner as to obtain a misalignment, Δa , of at the most, 0,5 mm when $d_n < 200$ mm or at the most 0,1 e_n or 1 mm, whichever is the greater, when $d_n \geq 200$ mm.

- b) Prepare and plane the butt-fusion faces by means of a planing machine to obtain a maximum clearance, Δw , of 0,3 mm when $d_n < 200$ mm or 0,5 mm when $d_n \geq 200$ mm.
- c) Perform the butt-fusion using the parameters specified in Annex A, repeating the procedure on fresh test assemblies while varying the parameters within the limits given in Annex B.
- d) Proceed to the tests as given in the relevant product standards.

Annex A (normative)

Butt-fusion cycle and parameters

Figure A.1 illustrates the butt-fusion cycle and Tables A.1 and A.2 give reference values for the parameters in each phase.

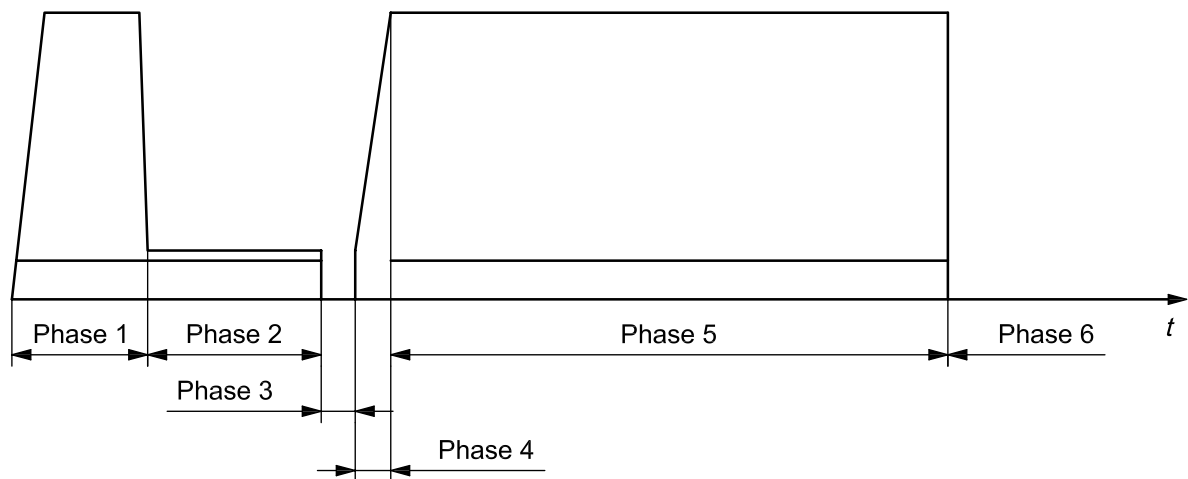

Key

t time

Figure A.1 — Butt-fusion cycle

Table A.1 — Butt-fusion cycle and parameters

Parameters		Values	Units
Heater-plate temperature, T		200 to 230	°C
Phase 1	Pressure, p_1^a	$0,15 \pm 0,02$	MPa
	Time, t_1	Measured as the time until B_1 is reached	s
	Bead width, B_1^b	See Table A.2	mm
Phase 2	Pressure, p_2^a	$\leq 0,03$	MPa
	Time, t_2	$10e_n$, see Table A.2	s
Phase 3	Time, t_3	Maximum value, see Table A.2	s
Phase 4	Time, t_4	Maximum value, see Table A.2	s
Phase 5	Pressure, p_5^a	$0,15 \pm 0,02$	MPa
	Time, t_5	Minimum value, see Table A.2	min
Phase 6	Time, t_6	$= t_5$	min

^a This pressure is the interface pressure and is related to d_n , e_n and the butt-fusion equipment used.

^b Minimum value obtained around the complete circumference of the pipe.

Table A.2 — Wall thickness dependent butt-fusion parameters ^a

Wall thickness, e_n mm	B_1 mm	t_2 s	t_3 s	t_4 s	t_5 min
$\leq 4,5$	0,5	45	5	5	6
$4,5 < e_n \leq 7$	1,0	45 to 70	5 to 6	5 to 6	6 to 10
$7 < e_n \leq 12$	1,5	70 to 120	6 to 8	6 to 8	10 to 16
$12 < e_n \leq 19$	2,0	120 to 190	8 to 10	8 to 11	16 to 24
$19 < e_n \leq 26$	2,5	190 to 260	10 to 12	11 to 14	24 to 32
$26 < e_n \leq 37$	3,0	260 to 370	12 to 16	14 to 19	32 to 45
$37 < e_n \leq 50$	3,5	370 to 500	16 to 20	19 to 25	45 to 60
$50 < e_n \leq 70$	4,0	500 to 700	20 to 25	25 to 35	60 to 80
^a If other parameters are considered, they have to be agreed between the pipe/fitting manufacturer and the end-user.					

Annex B (normative)

Limits on values of butt-fusion parameters

Table B.1 gives the limits placed on the values of the parameters used in evaluating the jointing procedure.

Table B.1 — Limits on values of butt-fusion parameters ^a

Set of conditions	Condition	Ambient temperature ^b		Heater-plate temperature, <i>T</i> °C	Butt-fusion pressure, <i>p</i> MPa
		Symbol	Value °C		
1	Normal	T_{nom}	23 ± 2	215 ± 5	$0,15 \pm 0,02$
2	Minimum	T_{min}	-5 ± 2	205 ± 5	$0,13 \pm 0,02$
3	Maximum	T_{max}	40 ± 2	230 ± 5	$0,17 \pm 0,02$

^a If other parameters are considered, they have to be agreed between the pipe/fitting manufacturer and the end-user.
^b Other values may be used if specified in the appropriate system standard.

Bibliography

- [1] ISO/TR 11647, *Fusion compatibility of polyethylene (PE) pipes and fittings* ²⁾

2) Withdrawn.

BSI - British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001 Email: orders@bsigroup.com You may also buy directly using a debit/credit card from the BSI Shop on the Website <http://www.bsigroup.com/shop>

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact Information Centre. Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048 Email: info@bsigroup.com

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001 Email: membership@bsigroup.com

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsigroup.com/BSOL>

Further information about BSI is available on the BSI website at <http://www.bsigroup.com>

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright and Licensing Manager. Tel: +44 (0)20 8996 7070 Email: copyright@bsigroup.com