

BS ISO 11527:2010



BSI Standards Publication

Building construction — Sealants — Test method for the determination of stringiness

bsi.

...making excellence a habit.™

Version correct as of 03/01/2015. (c) The British Standards Institution 2013 Licensed copy: Lee Shau Kee Library, HKUST. Version correct as of 03/01/2015. (c) The British Standards Institution 2013 Licensed copy: Lee Shau Kee Library, HKUST.

National foreword

This British Standard is the UK implementation of ISO 11527:2010.

The UK participation in its preparation was entrusted to Technical Committee B/547, Sealants for building and construction.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2010

ISBN 978 0 580 65514 2

ICS 91.100.50

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2010.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL STANDARD

BS ISO 11527:2010

ISO
11527

First edition
2010-11-15

Building construction — Sealants — Test method for the determination of stringiness

*Construction immobilière — Mastics — Méthode d'essai pour la
détermination du pouvoir filant*



Reference number
ISO 11527:2010(E)

© ISO 2010

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.



COPYRIGHT PROTECTED DOCUMENT

© ISO 2010

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 11527 was prepared by Technical Committee ISO/TC 59, *Buildings and civil engineering works*, Subcommittee SC 8, *Sealants*.

Building construction — Sealants — Test method for the determination of stringiness

1 Scope

This International Standard specifies a method for the determination of the stringiness of a wet-applied sealant.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6927, *Building construction — Jointing products — Vocabulary for sealants*¹⁾

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 6927 apply.

4 Principle

This method determines the stringiness of a sealant by measuring the maximum length of a strand or string which can be pulled from a wet sealant sample. A probe (tip) is forced into the wet sealant sample. After a short time, the probe is removed from the sample using a constant rate of pull. An extensometer or similar apparatus is used to provide a constant rate of pull, and the maximum travel before the “string” breaks is reported in millimetres.

5 Apparatus

5.1 Extensometer or similar apparatus

Extensometer or other apparatus, e.g. pneumatic piston, which allows a grip to be pulled at a constant rate and provides a reading of the distance between the grips to the nearest millimetre.

5.2 Probe

- Tip 1 (round) according to Figure 1.
- Tip 2 (conical) according to Figure 2.
- Tip made of aluminium.

1) Under revision.

Dimensions in millimetres

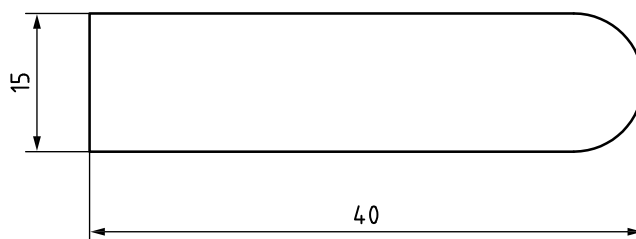


Figure 1 — Tip 1

Dimensions in millimetres

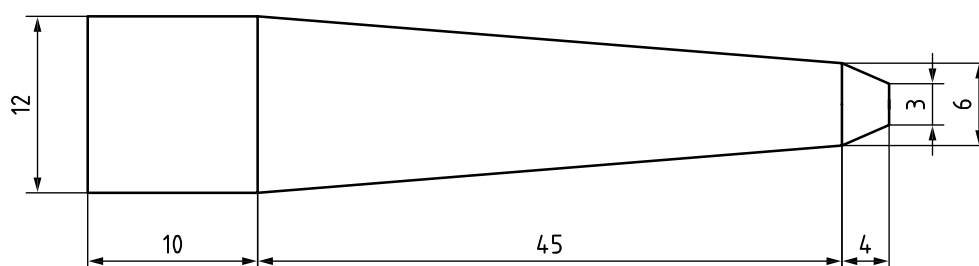


Figure 2 — Tip 2

5.3 Container

Container from any suitable source, with a minimum depth of 30 mm and a minimum diameter of 30 mm.

6 Conditioning

The sealant shall be shelf-aged for a minimum of 1 d from production. Prior to preparation of the specimen, the sealant, the container and the probe (tip) shall be conditioned for 6 h in the unopened container at the test temperature, e.g. $(23 \pm 2) ^\circ\text{C}$.

7 Preparation of test specimens

Fill the container with the sample and remove excess with a spatula to provide a clean, smooth surface free of bubbles.

8 Test procedure

Attach the probe (tip) to the upper clamp of the extension device (e.g. the extensometer). Fix the container to the lower clamp of the extension device. Slowly raise the container with the wet sealant or move the probe downwards until the nozzle just touches the sample surface. This is the “zero” reading. Alternatively, the “zero” reading can be determined by placing a sheet of paper on the container (assuming the sealant is tooled evenly with the upper edges of the container). Raise the container with the wet sealant further or move the tip downwards at a rate of 60 mm/min until the tip of the nozzle is submerged a minimum of 10 mm into the sample. Begin the test by moving either the probe upwards or the container with the sealant sample downwards at a rate of 700 mm/min. Stop the extension machine when the string formed between the sealant in the container and the tip breaks and report the length of the string at break (L_{max}). Do not clean the tip.

Repeat the test two more times (it is not necessary to smooth the surface and to clean the tip between tests). Then take another specimen (container with wet sealant) and repeat the test (making three new measurements), i.e. generate six measurements in total.

NOTE For slow-curing sealants, sequential measurements can be carried out on the same sealant specimen.

9 Expression of results

Report the individual readings and the average over the second, third, and fourth trials to the nearest millimetre. The repeatability of the value reported (the maximum difference between two independent results) should not exceed 4 mm at the 95 % confidence level. If the sample surface cures before measurements are complete, results will be in error. If either the highest or lowest of the three measurements is greater than ± 15 % from the median, discard the data and repeat the test from the initial preparation.

10 Test report

The test report shall include at least the following information:

- a) name of test laboratory, number and date of test report;
- b) reference to this International Standard;
- c) name, type (chemical family) and colour of sealant;
- d) batch of sealant from which the test specimens were produced, if possible;
- e) test temperature;
- f) individual and average measurement values for stringiness;
- g) any deviations from the specified test conditions.

ICS 91.100.50

Price based on 3 pages

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK



Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

...making excellence a habit.™