

BS ISO 11706:2012



BSI Standards Publication

**Carbonaceous materials for
the production of aluminium
— Prebaked anodes —
Determination of the
fracture energy**

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 11706:2012.

The UK participation in its preparation was entrusted to Technical Committee CII/24, Raw materials for the aluminium industry.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012.
Published by BSI Standards Limited 2012.

ISBN 978 0 580 66497 7

ICS 71.100.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 September 2012.

Amendments issued since publication

Date	Text affected
------	---------------

**Carbonaceous materials for the
production of aluminium — Prebaked
anodes — Determination of the
fracture energy**

*Produits carbonés pour la production de l'aluminium - Anodes
précuites - Détermination de l'énergie de rupture*





COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 11706 was prepared by Technical Committee ISO/TC 226, *Materials for the production of primary aluminium*.

Carbonaceous materials for the production of aluminium — Prebaked anodes — Determination of the fracture energy

1 Scope

This International Standard describes a method for the determination of the fracture energy at room temperature. This property is relevant for the thermal shock resistance of prebaked anodes used in the electrolytic cell.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 8007-2, *Carbonaceous materials used in the production of aluminium — Sampling plans and sampling from individual units — Part 2: Prebaked anodes*

ISO 12986-1, *Carbonaceous materials used in the production of aluminium — Prebaked anodes and cathode blocks — Part 1: Determination of bending/shear strength by a three-point method*

ISO 12985-1, *Carbonaceous materials used in the production of aluminium — Baked anodes and cathode blocks — Part 1: Determination of apparent density using a dimensions method*

3 Principle

The amount of energy needed to fracture a notched cylindrical test piece is determined by integrating the force-displacement signals of the testing machine.

Notching of the test piece allows to minimize the elastic energy stored in the specimen and therefore guarantees controlled and smooth crack propagation.

The same arrangement and testing equipment as required for the determination of the bending/shear strength by a 3-point method can be used, see ISO 12986-1.

A length measurement device for the vertical displacement, a data acquisition system and software able to integrate the force-displacement curve are additionally needed.


4 Apparatus

4.1 Testing equipment

The testing machine has a hydraulic system that can be adjusted to control the load increase rate. The maximum achieved load should lie above 1 kN and the precision of the load sensor better than 5 N.

The 3-point cell complies with ISO 12986-1. The displacement measurement unit shall cover a range of 10 mm with a precision better than 5 μm .

The arrangement of the cell with the notched sample and the recorded signals are shown in the following figure.

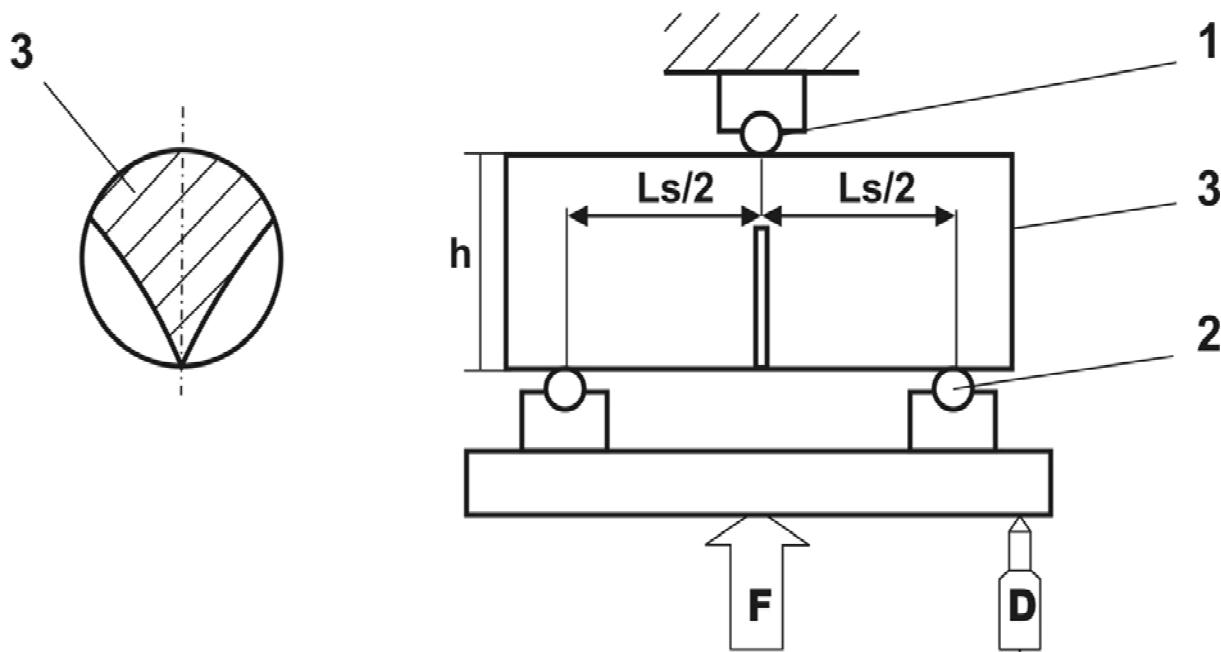

- Key**
- 1 pier bar (\varnothing 5 to 10 mm)
 - 2 support bar (\varnothing 5 to 10 mm)
 - 3 test piece (\varnothing 50 mm, length 130 mm, 60° notched, 2 mm slots)
 - L_s = 100 mm
 - F = force applied to the bottom table
 - D = displacement sensor

Figure 1 — 3-point testing set-up

The maximum load reached for typical anodes lies in the range of 500 N to 1000 N while a typical displacement difference between the load increase and the total fracture of the sample is around 0,5 mm and 1 mm. The typical value of the fracture energy of worldwide anodes is around 200 J/m².

5 Sampling

The sampling program and the drilling location of the sample shall be agreed between the seller and buyer in accordance with ISO 8007-2.

6 Preparation of the test pieces

6.1 Drilling and cutting

Cylindrical test pieces with a circular cross-section only shall be used. The test pieces shall have a diameter of 50 mm \pm 1 mm and a minimum length of 130 mm.

Drilling shall be performed with a machine and set-up guaranteeing a uniform diameter throughout the sample length.

Cutting is made by using a saw unit providing parallel end-faces of the test piece.

6.2 Notching

A 60° angle notched cross-sectional area shall be prepared. The slot thickness shall be 2 mm.

A convenient and simple way to prepare the notch is to use a saw having a 2 mm thick blade of 250 mm diameter. The sample positioning is given by fixing the test pieces to a support fitting in the saw table. After sawing the first slot reaching the precise highest position of the cylinders, the support device with its fixed test piece is turned by 180° for preparing the second slot.

6.3 Drying

The test pieces are cleaned and dried overweight at 120 °C and cooled to room temperature.

7 Testing procedure

The diameter of the test piece is measured using a caliper according to ISO 12985-1.

Set up the piece, with the notch tip aligned to the bottom support bars, on the testing table.

Increase the force steadily and smoothly in such a way that the sample breaks totally in a time period between 5 s and 10 s. Record continuously the load and the displacement of the table.

8 Expression of results

Calculate the fracture energy in J/m² by integrating the force/displacement signals according to the following principle and equations:

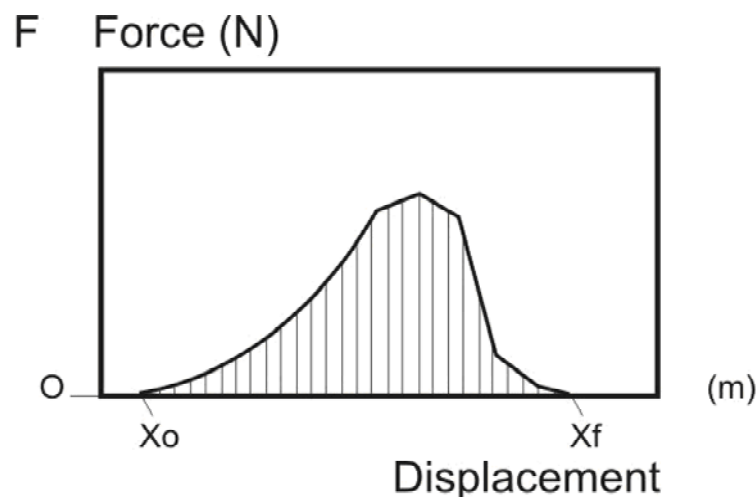


Figure 2 — Integration of the force/displacement curve

The zero displacement X_0 corresponds to the table position where the first significant sign of load is noticed. The displacement X_f corresponds to the table position where the decreasing load still had a significant positive value.

The fracture energy FE can be calculated using the integral formula shown below:

$$FE = \frac{1}{2 \cdot S} \cdot \int_{X_0}^{X_f} F \cdot dx$$

where

F = force in newtons

X = displacement in metres

S = broken surface area, equal for an angle of 60° to $0,478 h^2$ (h = sample diameter)

Report the result rounded to the unit of J/m^2 .

9 Precision

The repeatability of this destructive method cannot be tested.

The reproducibility of the mean value of a given sample population, with a minimum number of test pieces above 30, is $20 \text{ J}/\text{m}^2$. (RDC round robin 1997 on anodes.)

10 Test report

The test report shall contain the following information:

- a) a reference to this International Standard;
- b) type, position and orientation of test specimens during the sampling;
- c) designation of the test piece;
- d) single fracture energy value of each test piece;
- e) number of test piece, average and the standard deviation of the population;
- f) additionally agreed conditions deviating from the standard method;
- g) sampling and test date.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™