

BS ISO 12230:2012



BSI Standards Publication

Polybutene-1 (PB-1) pipes — Effect of time and temperature on the expected strength

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 12230:2012.

The UK participation in its preparation was entrusted to Technical Committee PRI/88/4, Test Methods - Plastic Piping.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012. Published by BSI Standards Limited 2012

ISBN 978 0 580 74676 5

ICS 23.040.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 August 2012.

Amendments issued since publication

Date	Text affected
------	---------------

**Polybutene-1 (PB-1) pipes — Effect of time
and temperature on the expected strength**

*Tubes en polybutène-1 (PB-1) — Influence du temps et de la
température sur la résistance espérée*



COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Basic equations	2
4.1 General	2
4.2 Polybutene homopolymer (PB-H)	2
4.3 Polybutene random copolymer (PB-R)	2
5 Expected strength	5
5.1 General	5
5.2 Extrapolation limits	5
5.3 Graphical representation	5
5.4 Tabulated values	5
Annex A (normative) Demonstrating conformance of pipes to the reference lines	8
Bibliography	9

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 12230 was prepared by Technical Committee ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 5, *General properties of pipes, fittings and valves of plastic materials and their accessories — Test methods and basic specifications*.

This second edition cancels and replaces the first edition (ISO 12230:1996), which has been technically revised.

Introduction

The development of new polybutene-1 compounds based on random copolymers called PB-R means there is a need to rename the existing PB-1 homopolymer compounds PB-H. At the same time a new set of reference lines and tabulated expected hoop strength values for various times and temperatures needs to be included.

The main changes since the previous edition of this International Standard are

- new definition of PB-1 compounds PB-H (homopolymer) and PB-R (copolymers),
- new set of reference lines (coefficients and diagram),
- new table containing calculated expected hoop strength values,
- recalculation of hoop strength data of PB-H and specifying values rounded down to one decimal place,
- clearer specification of showing conformance to reference lines, and
- conformance to reference lines can be shown by not failed data points running at sufficiently high hoop stress, too.

Polybutene-1 (PB-1) pipes — Effect of time and temperature on the expected strength

1 Scope

This International Standard specifies minimum values for the expected strength as a function of time and temperature in the form of reference lines and tabulated data, for use in calculations on pipes made of

- polybutene-1 homopolymer (PB-H), and
- polybutene-1 random copolymer (PB-R).

For the sake of simplicity the designation polybutene and the abbreviation PB are used throughout.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1167-1, *Thermoplastics pipes, fittings and assemblies for the conveyance of fluids — Determination of the resistance to internal pressure — Part 1: General method*

ISO 1167-2, *Thermoplastics pipes, fittings and assemblies for the conveyance of fluids — Determination of the resistance to internal pressure — Part 2: Preparation of pipe test pieces*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 reference line

minimum long-term hydrostatic strength to be expected from a particular polymer

NOTE 1 Reference lines are not to be considered as characteristic of a specific grade or of material from a specific supplier.

NOTE 2 The lines are described by a mathematical equation which permits interpolation and extrapolation in an unambiguous way at various temperatures.

NOTE 3 The reference lines for polybutene (PB) have been agreed upon by a group of experts after considering experimental data, and have been accepted by the relevant technical committees in ISO.

3.2 polybutene-1 homopolymer PB-H

compound prepared by polymerization of no less than 95 % butene-1 by weight

3.3 polybutene-1 random copolymer PB-R

compound prepared by polymerization of no less than 85 % butene-1 and no less than 95 % of total olefins by weight

4 Basic equations

4.1 General

The reference lines are based on the four-parameter model and are described by the following equations:

$$\text{First branch: } \lg t = A_1 + (B_1/T)\lg \sigma + C_1/T + D_1\lg \sigma \quad (1)$$

$$\text{Second branch: } \lg t = A_2 + (B_2/T)\lg \sigma + C_2/T + D_2\lg \sigma \quad (2)$$

where

t is the time, in hours;

T is the temperature, in kelvins;

σ is the hoop stress, in megapascals.

The lower value obtained from Equation (1) or Equation (2), respectively, represents the expected minimum hoop strength.

4.2 Polybutene homopolymer (PB-H)

The following coefficients are valid for the reference lines of PB-H in the temperature range between 10 °C and 110 °C:

$$A_1 = -430,866 \quad A_2 = -129,895$$

$$B_1 = -125\,010 \quad B_2 = -37\,262,7$$

$$C_1 = 173\,892,7 \quad C_2 = 52\,556,48$$

$$D_1 = 290,056\,9 \quad D_2 = 88,567\,35$$

Figure 1 represents the reference lines calculated with the above coefficients in graphical form.

4.3 Polybutene random copolymer (PB-R)

The following coefficients are valid for the reference lines of PB-R in the temperature range between 10 °C and 95 °C:


$$A_1 = -367,801\,9$$

$$B_1 = -104\,096,6$$

$$C_1 = 145\,940,231$$

$$D_1 = 245,538\,6$$

The line at 110 °C has been determined separately and is only used for obtaining the extrapolation time limits.

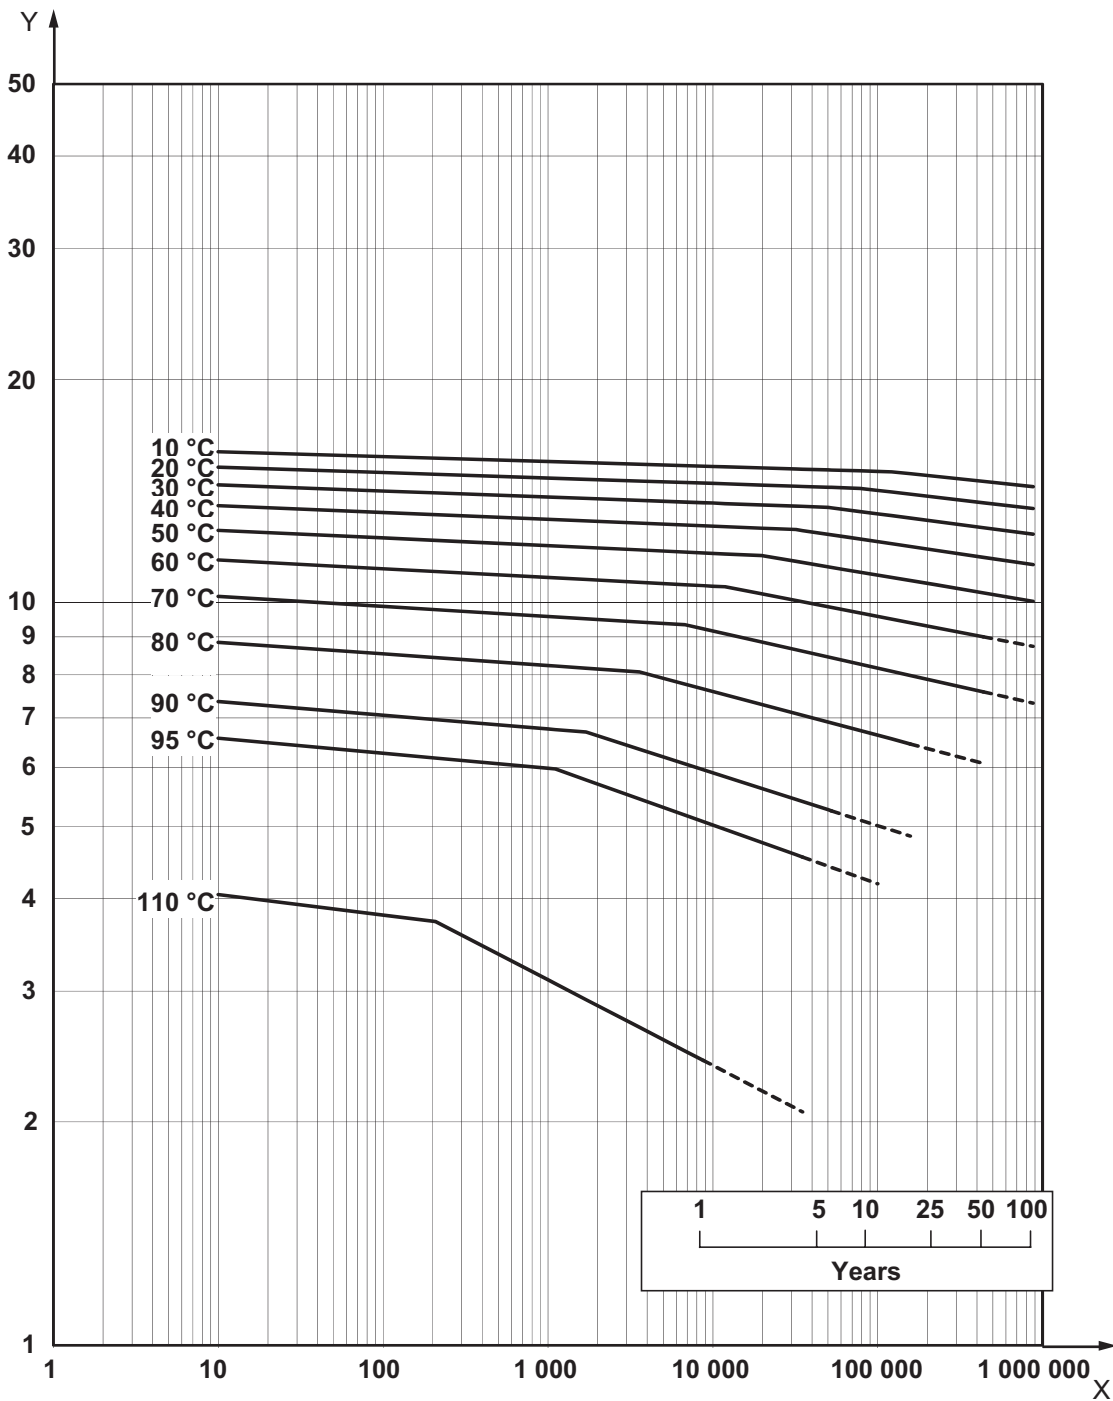


Key

Y hoop stress (MPa)

X time (h)

Figure 1 — Expected strength of polybutene homopolymer (PB-H) pipes

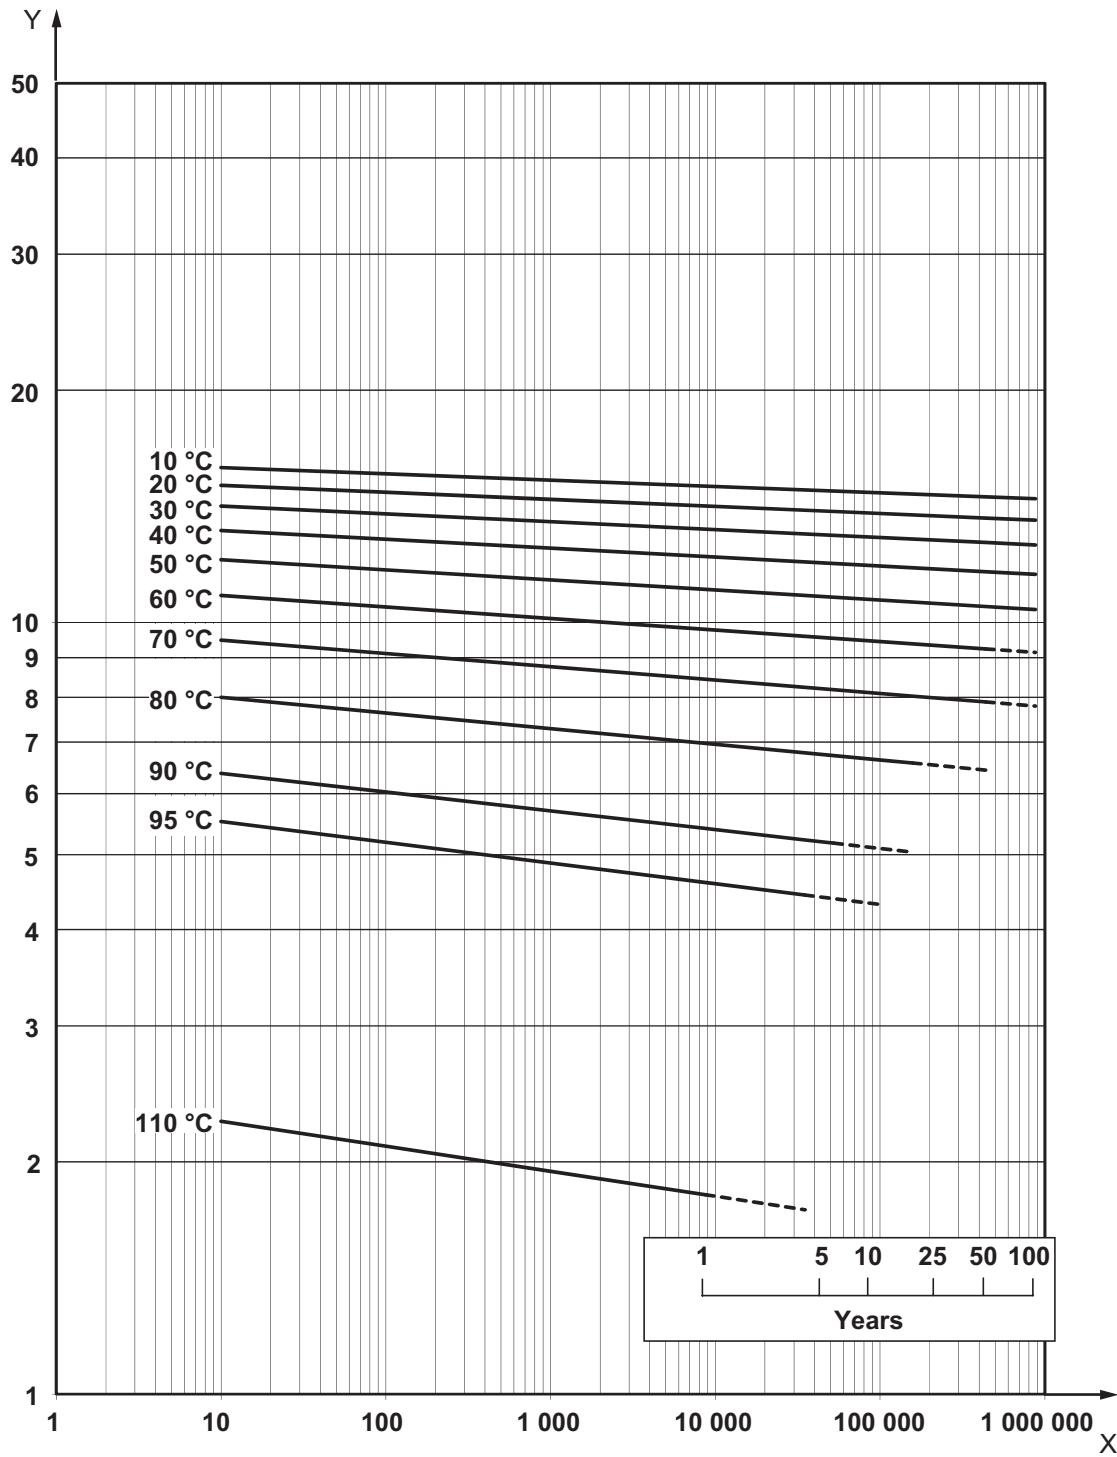

Key

Y hoop stress (MPa)
 X time (h)

Figure 2 — Expected strength of polybutene random copolymer (PB-R) pipes

5 Expected strength

5.1 General

Prior to testing, pipes prepared from PB-H and PB-R compounds shall be conditioned in accordance with recommendations obtained from the manufacturer.

Pipes prepared from PB-R compounds shall be annealed for 96 h at 95 °C prior to thermal stability testing at 110 °C.

5.2 Extrapolation limits

The extrapolation limits (the end points of the reference lines) are based on an experimentally determined life at 110 °C for PB-H and for PB-R, respectively, and an Arrhenius equation for the temperature dependence with an activation energy of 110 kJ/mole (≈ 26 kcal/mole). This yields the values given in Table 1 for the extrapolation factor k_x (i.e. the expected lifetime at a given temperature divided by the lifetime at 110 °C for PB-H and for PB-R).

Table 1 — Extrapolation time factors for PB-H and PB-R

k_x	T [°C]
2,5	$100 \geq T > 95$
4	$95 \geq T > 90$
6	$90 \geq T > 85$
10	$85 \geq T > 80$
18	$80 \geq T > 75$
30	$75 \geq T > 70$
50	$T \leq 70$

With a life of one year at 110 °C, these values are therefore the number of years the pipes would be expected to last at each of the temperatures given.

For temperatures up to and including 50 °C, an extrapolation factor k_x of 100 is acceptable.

5.3 Graphical representation

Figures 1 and 2 contain the reference lines for PB-H and PB-R, respectively, corresponding to the values of the parameters given in this clause, which shall be used for demonstrating conformance to this specification in accordance with Annex A.

The broken lines represent the extrapolation of the reference lines, applicable when longer failure times are obtained at 110 °C, extrapolation being permitted up to the limits given by the extrapolation factors in Table 1.

5.4 Tabulated values

The calculated hoop strength values to be used for various temperatures and times are given in Table 2 for PB-H and Table 3 for PB-R and do not include design factors.

The times at 80 °C, 90 °C and 95 °C not in brackets in the “time” column in Table 2 for PB-H and Table 3 for PB-R are based on a lifetime of one year at 110 °C. Proof of a longer lifetime at 110 °C allows a corresponding extension of the times at lower temperatures. Such values are given in brackets in Tables 2 and 3.

Table 2 — Expected hoop strength values of PB-H pipes for various values of time and temperature

Temperature °C	Time years	Expected strength MPa	Temperature °C	Time years	Expected strength MPa
20	1	14,5	70	1	9,2
	5	14,3		5	8,5
	10	14,2		10	8,2
	25	13,9		25	7,8
	50	13,6		50	7,6
	100	13,4			
30	1	13,6	80	1	7,6
	5	13,4		5	6,9
	10	13,2		10	6,7
	25	12,9		18	6,4
	50	12,6		(25)	(6,3)
	100	12,3			
40	1	12,7	90	1	5,9
	5	12,4		4	5,4
	10	12,1		6	5,2
	25	11,8		(10)	(5,0)
	50	11,5		(15)	(4,9)
	100	11,2			
50	1	11,6	95	1	5,1
	5	11,2		4	4,5
	10	10,9		(6)	(4,4)
	25	10,6		(10)	(4,2)
	50	10,3			
	100	10,0			
60	1	10,5			
	5	9,9			
	10	9,6			
	25	9,2			
	50	9,0			

Table 3 — Expected hoop strength values of PB-R pipes for various values of time and temperature

Temperature °C	Time years	Expected strength MPa	Temperature °C	Time years	Expected strength MPa
20	1	14,1	70	1	8,4
	5	13,9		5	8,2
	10	13,8		10	8,1
	25	13,7		25	8,0
	50	13,6		50	7,9
	100	13,5			
30	1	13,2	80	1	6,9
	5	13,0		5	6,7
	10	12,9		10	6,6
	25	12,7		18	6,5
	50	12,7		(25)	(6,5)
	100	12,6			
40	1	12,1	90	1	5,4
	5	11,9		4	5,2
	10	11,8		6	5,1
	25	11,7		(10)	(5,1)
	50	11,6		(15)	(5,0)
	100	11,5			
50	1	11,0	95	1	4,6
	5	10,8		4	4,4
	10	10,7		(6)	(4,4)
	25	10,6		(10)	(4,3)
	50	10,5			
	100	10,4			
60	1	9,8			
	5	9,5			
	10	9,4			
	25	9,3			
	50	9,2			

Annex A (normative)

Demonstrating conformance of pipes to the reference lines

At each of the following temperatures, specimens shall be tested at various hoop stresses such that, at each of the temperatures given, at least three failure times fall in each of the following time intervals:

Temperatures: 20 °C, 60 °C to 82 °C, 95 °C

Time intervals: 10 h to 100 h

100 h to 1 000 h

1 000 h to 8 760 h

> 8 760 h

In accordance with ISO 9080 failure points at 20 °C up to 1,000 h may be neglected.

If there are difficulties obtaining failures in some of the time intervals any running data point above the reference line can be accepted as showing conformance to the reference line.

For tests lasting longer than 8 760 h without failure, the actual test time can be considered as the failure time, provided it is on or above the reference line.

Testing shall be carried out in accordance with ISO 1167-1 and ISO 1167-2.

Conformance to the reference lines shall be demonstrated by plotting the individual experimental results on the graph. At least 97,5 % of them shall lie on or above the reference lines.

Bibliography

- [1] ISO 9080, *Plastics piping and ducting systems — Determination of the long-term hydrostatic strength of thermoplastics materials in pipe form by extrapolation*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™