



BSI Standards Publication

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for rolling contact fatigue of silicon nitride ceramics at room temperature by balls-on-flat method

National foreword

This British Standard is the UK implementation of ISO 14628:2012.

The UK participation in its preparation was entrusted to Technical Committee RPI/13, Advanced technical ceramics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012. Published by BSI Standards Limited 2012

ISBN 978 0 580 70809 1

ICS 81.060.30

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2012.

Amendments issued since publication

Date	Text affected
------	---------------

**Fine ceramics (advanced ceramics,
advanced technical ceramics) — Test
method for rolling contact fatigue
of silicon nitride ceramics at room
temperature by balls-on-flat method**

*Céramiques techniques — Méthode d'essai de fatigue de contact
de roulement des céramiques au nitrure de silicium à température
ambiante par la méthode des billes sur surface plane*





COPYRIGHT PROTECTED DOCUMENT

© ISO 2012

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Testing machine	2
5.1 Structure of testing machine	2
5.2 Loading precision	4
6 Test specimens	4
6.1 Test specimen geometry	4
6.2 Fixation of test specimen	5
6.3 Specimen thickness	5
6.4 Surface finish	5
6.5 Number of test specimens	5
7 Test method	5
7.1 Balls	5
7.2 Loading method	5
7.3 Lubrication	6
7.4 Detection of surface failure	6
8 Treatment of test result	7
8.1 Mean effective load	7
8.2 Mean effective mechanical input	7
8.3 Flaking of ball surface	8
9 Test report	8
Annex A (informative) General information	10
Bibliography	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14628 was prepared by Technical Committee ISO/TC 206, *Fine ceramics*.

Introduction

Rolling contact fatigue (RCF) performance is essential for predicting the life of a rolling element. In general, RCF performance is evaluated from the life at a specific failure probability obtained by the Weibull analysis of test data under constant loading conditions. This International Standard specifies a fast and reliable method to compare RCF performance under stepwise loading as an alternative to accurate quantification by RCF tests under constant load. Ranking candidate materials, in other words comparison of performance among them, would be of value for choosing materials of required performance for bearings. In addition, material suppliers would receive feedback from the test results, allowing them to achieve a higher level of RCF performance.

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for rolling contact fatigue of silicon nitride ceramics at room temperature by balls-on-flat method

1 Scope

This International Standard specifies a test method for rolling contact fatigue of silicon nitride ceramics under stepwise loading that is carried out at room temperature. This test may be used as follows: relative comparison of the rolling contact fatigue performance, a pass/fail test for material qualification of rolling elements or choosing an appropriate load level for RCF testing under constant load.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3290-1:2008, *Rolling bearings — Balls — Part 1: Steel balls*

ISO 3290-2:2008, *Rolling bearings — Balls — Part 2: Ceramic balls*

ISO 3611:2010, *Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics*

ISO 4287:1997, *Geometrical Product Specification (GPS) — Surface texture: Profile method—Terms, definitions and surface texture parameters*

ISO/IEC 17025:2005, *General requirements for the competence of testing and calibration laboratories.*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

rolling contact

contact between rolling elements

NOTE Under pure rolling contact conditions, the relative velocity at the point of contact is zero. The relative velocity between real rolling elements is not, however, zero in most cases.

3.2

surface failure

flaking of test specimen surface

3.3

rolling contact fatigue

formation of surface failure due to cyclic rolling contact stress well below the stress when surface failure occurs under monotonic loading

3.4

rolling contact fatigue test

test where repeated rolling contact stress is applied to a test specimen, and the number of cycles to surface failure is measured

3.5
stepwise loading

loading method in which load is increased stepwise at regular intervals until the final failure of the test specimen

3.6
contact track

circular trail formed on a test specimen by repeated rolling contact of balls

3.7
mean effective load

constant load equivalent to stepwise loading

3.8
maximum Hertzian stress

maximum contact stress between two bodies using the elastic stress analyzing theory by Hertz

3.9
bearing-grade silicon nitride

silicon nitride ceramics specially designed for rolling elements

4 Principle

The life of flat plate under cyclic rolling contact stress, which is applied by balls rotating unidirectionally thereon, is determined by measuring the number of stress cycles to the final surface failure of the plate.

5 Testing machine

5.1 Structure of testing machine


A testing machine shall be so constructed that rolling contact stress can be applied to the surface of a flat plate test specimen by balls thereon equally spaced with a retainer (see Figure 1). The balls shall be rolling in a circle with the rotation of the shaft washer of a 90° contact angle thrust ball bearing of a specified bore diameter. The shaft washer shall be rotated unidirectionally.

The testing machine is shown schematically in Figure 2. Load is applied by dead weights at the end of loading arm.


The testing machine shall be equipped with an automatic shutoff with a device detecting the surface failure, an apparatus capable of obtaining the number of rotations until the stop of testing, and a mechanism where its automatic reactivation is prevented when the testing machine is stopped for reasons of power failure or others.

NOTE 1 The shaft washer should be chosen on the basis of diameters of the ball and main shaft of the testing machine.

NOTE 2 The dimensions of the retainer depend on those of the shaft washer, ball diameter and number of balls.

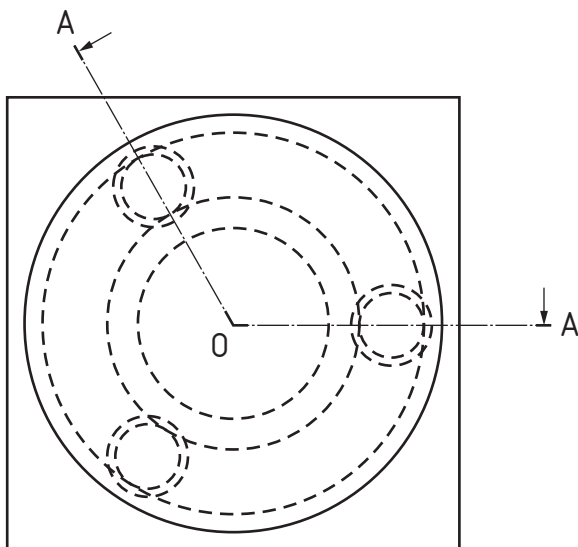


Section A-O-A

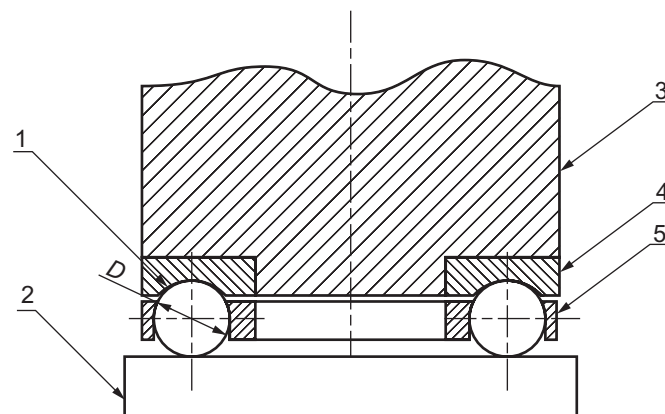

Key

- 1 ball of diameter D
- 2 test specimen
- 3 main shaft of a testing machine
- 4 shaft washer of a 90° contact angle thrust bearing
- 5 retainer

Figure 1 — Balls-on-flat configurations

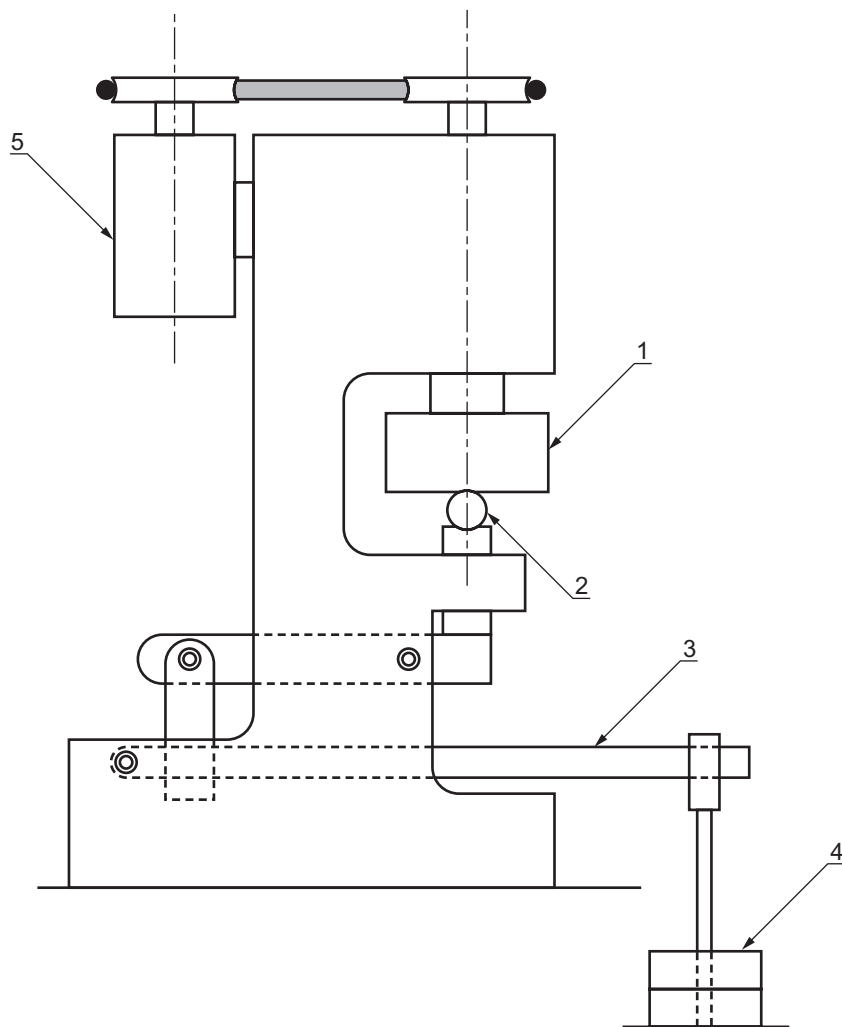

Key

- 1 oil bath (balls-on-flat configurations are inside)
- 2 ball for pivot point to sustain oil bath
- 3 loading lever
- 4 dead weight
- 5 motor

Figure 2 — Schematic of testing machine

5.2 Loading precision

The fluctuation of the test load shall be within $\pm 1\%$ of the chosen value.

NOTE The test load can be applied with a dead weight with accuracy thereof. Usually the load by dead weight(s) is increased with a lever by a specific factor.

6 Test specimens

6.1 Test specimen geometry

The test specimen shall be a flat plate. The parallelism tolerance on opposite surfaces of the plate is 0,015 mm. The use of test specimens having twisting or warpage, which may lead to oscillation of the testing apparatus, is not permitted. The test specimen shall have enough margin outside a contact track to be fixed, as well as to

prevent the effect of the edge of the test specimen on the stress distribution around the point of contact, which may cause chipping of material.

6.2 Fixation of test specimen

The test specimen shall be fixed on the bottom of an oil bath to be immobilized and to prevent oscillation.

Special care should be paid to the surface finish and flatness of the bottom of the oil bath to fix the test specimen firmly thereon.

6.3 Specimen thickness

The specimen shall have enough thickness to prevent flexural oscillation of a plate. The thickness should be measured with a micrometer such as that described in ISO 3611 or alternative-dimension measuring instruments with a resolution of 0,002 mm or finer. If the specimen is measured before the test, measure the thickness at around the central part to avoid unnecessary contact to a prospective contact track.

6.4 Surface finish

The test specimen shall have a ground and polished surface. The roughness shall be 0,1 μm R_a or smaller, as defined in ISO 4287. Subsurface damage during grinding shall be removed by subsequent polishing to eliminate the effect thereof on the test result.

The skewness R_{sk} , as defined in ISO 4287, of the test specimen should also be measured.

NOTE When the R_{sk} exhibits a large positive value, it implies that the measured surface has more convex area than concave. The R_{sk} of a large positive value is not recommended for RCF testing because the test result may be affected by the surface integrity of a test specimen

6.5 Number of test specimens

The number of test specimens shall be based on the agreement between the tester and the requester. If a threshold value for a pass/fail test is set, at least five test specimens should be prepared.

7 Test method

7.1 Balls

Balls made of bearing-grade silicon nitride should be used for testing materials for bearing applications. The ball grade of balls should be G5 or G3, as defined in ISO 3290-2. If the purpose of the test is a pass/fail test for material qualification of rolling elements, bearing balls made of steel as defined in ISO 3290-1 may also be used.

Balls shall be in a retainer to keep a fixed spacing.

The ball diameter and number of balls should be agreed between a tester and a requester.


NOTE Three or six balls are commonly used in the balls-on-flat configuration.

7.2 Loading method

The test load shall be applied under the stepwise loading condition where the load is increased stepwise at regular intervals until a final failure as shown schematically in Figure 3. The starting load of the loading step and the loading interval should be agreed between a tester and a requester.

NOTE 1 Some sorts of silicon nitride ceramics may exhibit a sensitivity to loading history. An excessively low starting load may lead to overestimating of rolling contact fatigue performance.

NOTE 2 If the objective of the test is the relative comparison with existing data of tests under constant loading, the test may be conducted under constant load as an alternative.

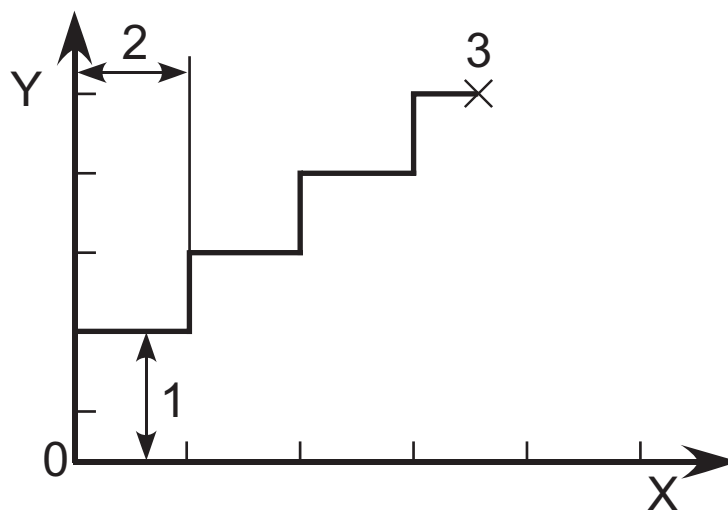

Key

- X number of revolutions
- Y load (kN)
- 1 starting load
- 2 regular interval of loading
- 3 final failure of a test specimen

Figure 3 — Stepwise loading

7.3 Lubrication

The test specimen and balls shall be immersed in lubricating oil during a test.

The kinematic viscosity of oil should be chosen to maintain the contact under partial or complete elastohydrodynamic lubrication.

NOTE To maintain the contact under partial or complete elastohydrodynamic lubrication, a paraffinic oil of higher kinematic viscosity, such as 68 mm²/s, should be chosen.

7.4 Detection of surface failure

The surface failure of a test specimen may be detected by the increase in vibrational acceleration of balls. An accelerometer should be mounted on a component where the vibration is mechanically amplified, such as the loading end of a loading lever. (See Figure 2.) If the acceleration exceeds a set threshold, the testing machine shall be automatically stopped.

NOTE To avoid automatic shutoff by noise, the set threshold may range from 2 to 3 times of the signal level for vibrational acceleration immediately after the start of testing at each loading step.

8 Treatment of test result

8.1 Mean effective load

Calculate the mean effective load P_m according to the following equation from loading conditions and number of rotations at each loading step until the stop of testing.

$$P_m = \left(\frac{\sum_{k=1}^k P_k^p N_k}{\sum_{k=1}^k N_k} \right)^{\frac{1}{p}} \quad (1)$$

where

P_k is the load per ball at k th loading step (N);

N_k is the number of revolution at k th loading step;

p is the exponential in the Lundberg and Palmgren theory equation shown below:

$$L = \left(\frac{C}{P} \right)^p \quad (2)$$

where

L is the basic rating life;

C is the basic dynamic load rating (N);

P is the dynamic equivalent load (N).

NOTE 1 Strictly, the exponential p should be determined experimentally for bearings made of each test material. Considering the scope of this International Standard, i.e. relative comparison of rolling contact fatigue performance, choosing a specified value for p is a practical solution.

NOTE 2 The p value may be taken as 3, which is widely accepted as the value for steel bearing balls used in commercially available hybrid ball bearings.

8.2 Mean effective mechanical input

Calculate the maximum Hertzian stress between a ball and test specimen at the load of $Q = P_m$ according to the following equation.

$$(p_{\max})_m = \frac{3Q}{2\pi a^2} = \frac{3P_m}{2\pi a^2} \quad (3)$$

where

Q is the load per ball (N);

a is the radius of the contact circle (m).

For contact between the ball and plate, a is expressed in terms of the following equation.

$$a = \left(\frac{3}{8} QD \left(\frac{1 - \varepsilon_1^2}{E_1} + \frac{1 - \varepsilon_2^2}{E_2} \right) \right)^{\frac{1}{3}} \quad (4)$$

where

- D is the diameter of the ball (m);
- E_1 is the elastic modulus of the ball (Pa);
- E_2 is the elastic modulus of the plate (Pa);
- ε_1 is the Poisson's ratio of the ball;
- ε_2 is the Poisson's ratio of the plate.

Multiplying the maximum Hertzian stress by the number of stress cycles N_c provides the mean effective mechanical input.

$$(M_{in})_m = N_c \cdot (p_{max})_m \quad (5)$$

where N_c is half the product of total number of revolutions until the failure and the number of balls.

NOTE The equation for the mean effective mechanical input implies that material of a higher $(M_{in})_m$ value withstands higher loads for longer cycles with the assumption that the entire $(M_{in})_m$ is consumed in the rolling contact fatigue.

8.3 Flaking of ball surface

Flaking on the ball surface may cause the automatic stop of the testing machine. If surface damage such as scratch thereby is observed on the contact track, the test shall be terminated. If not, change the ball(s) with flaking and lubricating oil, and resume the test.

9 Test report

The test report shall be in accordance with ISO/IEC 17025, unless there are valid reasons for not doing so. The report of the results of a rolling contact fatigue test shall include the following items:

- a) the name and address of the testing establishment;
- b) the date of the test, a unique identification of the report and of each page, customer name and address, signatory of the report;
- c) a reference to this International Standard, i.e. determined in accordance with ISO 14628.
- d) a description of the test material, elastic modulus, batch codes, date of manufacture, as appropriate;
- e) geometry and dimensions of test specimen;
- f) surface roughness of test specimen;
- g) a description of balls, diameter, ball grade, name of material, elastic modulus, etc.;
- h) loading conditions (load and interval of each loading step);
- i) a description of lubricating oil (name of manufacturer, product code, kinematic viscosity, etc.);
- j) a list of test results (the number of stress cycles, mean effective mechanical input, etc.).

The report of the results of a rolling contact fatigue test should preferably also include the following items:


- k) name of testing machine and its type;
- l) kinds of additives and sintering method of test material;
- m) sampling conditions of test specimen from material and its machining conditions (when a specimen is heat treated, its conditions are included);
- n) mechanical properties of test material, such as bending strength, fracture toughness value, etc..

Annex A (informative)

General information

A.1 The p value of silicon nitride for the calculation of mean effective load

The exponent p defined in the well-known Lundberg and Palmgren theory is experimentally determined. The p value is the reciprocal of the slope in empirical fit in the load versus stress cycles relation (see Figure A.1). For silicon nitrides, there is no generally accepted value for p , whereas the value of 3 is recognized as the p value for steel bearing balls. Some experimental attempts have been, however, made to determine this parameter and the mean value of p for silicon nitride has been reported in the range from 5,0 to 5,5; References [1,2].

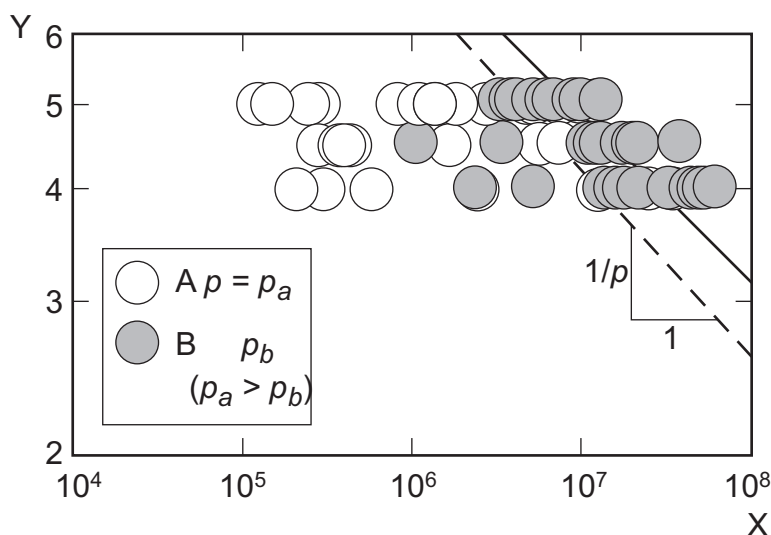

Key
 X life (stress cycles)
 Y load (kN)
 A material A
 B material B

Figure A.1 — Example of load versus stress cycles plot for the determination of p

A.2 Lubrication

In the balls-on-flat testing configuration, the motion of balls involves sliding. Wear behavior between balls and a test specimen is strongly influenced by lubricating conditions. In this International Standard, oil bath lubrication is adopted. Specimen and balls are immersed in the same lubricating oil for the duration of the test. To prevent wear by third body particles, balls and the shaft washer should be replaced with new ones and test fixtures should be ultrasonically cleaned in acetone before every test.

A.3 Handling of test specimen and balls

A test specimen and balls must be handled with special care until they are introduced to the testing setup to reduce the likelihood of surface damage caused by solid-solid contact between them. The use of balls, which

are the same as those used in hybrid bearings available commercially, is recommended because they should have been meticulously fabricated to minimize machining flaws which could cause ball failure during the rolling contact fatigue testing.

Bibliography

- [1] E. V. Zaretsky, "Ceramic Bearings for Use in Gas Turbine Engines," *Journal of Engineering for Gas Turbines and Power*, Vol. 111(January), 1989, pp. 146-157.
- [2] W. Kanematsu, "Relative comparison method of rolling contact fatigue performance of silicon nitrides by stepwise loading balls-on-flat test - Experimental verification of validity of some assumptions for the method," *J.ASTM International*, Vol.7, No.10, 2010, PaperID JAI103090.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™