

BS ISO 16365-2:2014



BSI Standards Publication

Plastics — Thermoplastic polyurethanes for moulding and extrusion

Part 2: Preparation of test specimens and
determination of properties

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 16365-2:2014.

The UK participation in its preparation was entrusted to Technical Committee PRI/82, Thermoplastic materials.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 74124 1

ICS 83.080.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2014.

Amendments issued since publication

Date	Text affected
------	---------------

**Plastics — Thermoplastic
polyurethanes for moulding and
extrusion —**

Part 2:
**Preparation of test specimens and
determination of properties**

*Plastiques — Polyuréthannes thermoplastiques pour moulage et
extrusion —*

Partie 2: Préparation des éprouvettes et détermination des propriétés





COPYRIGHT PROTECTED DOCUMENT

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Preparation of test specimens	2
3.1 Treatment of the material before moulding.....	2
3.2 Injection moulding.....	3
4 Conditioning of test specimens	4
5 Determination of properties	4
5.1 General.....	4
5.2 Biological resistance.....	4
5.3 TPU properties and test conditions.....	5
Annex A (informative) Material identification	10

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 9, *Thermoplastic materials*.

ISO 16365 consists of the following parts, under the general title *Plastics — Thermoplastic polyurethanes for moulding and extrusion*:

- *Part 1: Designation system and basis for specifications*
- *Part 2: Preparation of test specimens and determination of properties*
- *Part 3: Distinction between ether and ester polyurethanes by determination of the ester group content*

Introduction

Thermoplastic elastomer materials are classified into groups by the primary elastomeric property Hardness and with this as result of some relation with modulus, as shown in [Figure 1](#). The classification on basis of hardness considers the special position of TPE's between the rubber materials on the one side and the plastic materials on the other.

Each class is subdivided in standard properties and special properties. The standard properties for a class are not only connected with the adjacent group(s) by many of the specified properties but also by special properties specified in the adjacent class(es). A standard property in a class can be a special property in an adjacent class and vice versa.

Special properties are those properties which are in wide use or of particular significance in the practical characterization of a specific material.

For each type of thermoplastic elastomer, refer to the relevant material standard.

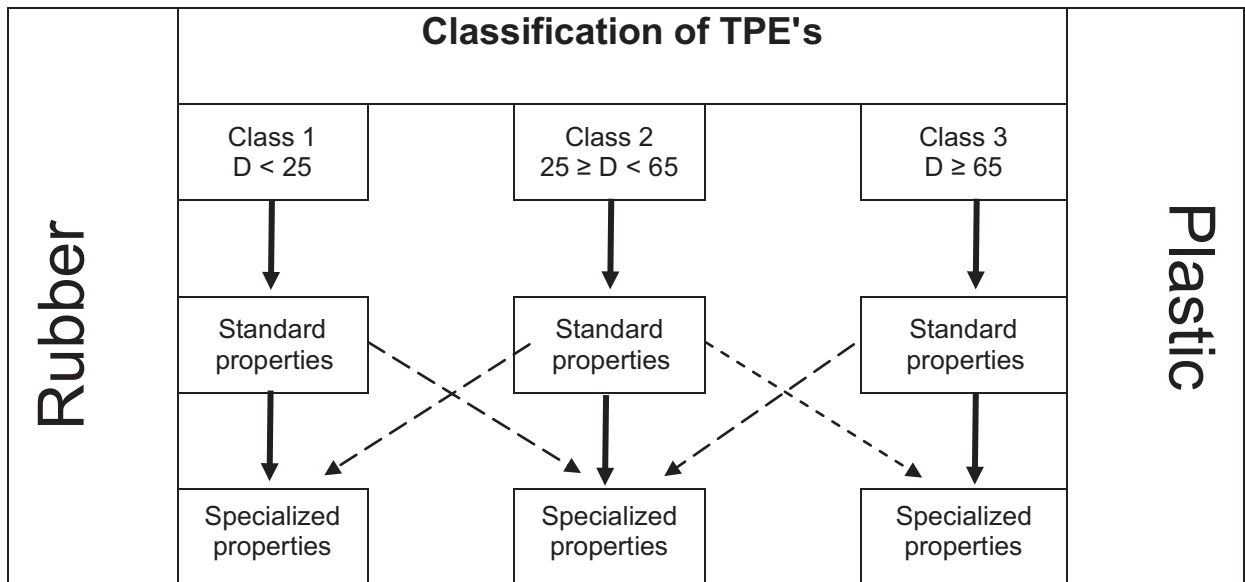


Figure 1 — Structure of thermoplastic elastomer (TPE) material standards

Plastics — Thermoplastic polyurethanes for moulding and extrusion —

Part 2: Preparation of test specimens and determination of properties

1 Scope

This part of ISO 16365 specifies the methods of preparation of test specimens and the standard test methods to be used in determining the properties of thermoplastic polyurethane moulding and extrusion materials. Requirements for handling test material and for conditioning both the test material before moulding and the specimens before testing are also given.

Procedures and conditions for the preparation of test specimens in a specified state and procedures for measuring properties of the materials from which these specimens are given. Properties and test methods which are suitable and necessary to characterize thermoplastic polyester/polyurethane and polyether/polyurethane (TPU) moulding and extrusion materials, are listed.

The properties have been selected from the general test methods in ISO 10350. Other test methods in wide use or of particular significance to these moulding and extrusion materials are also included in this part of ISO 16365, as are the designatory properties specified in ISO 16365-1.

In order to obtain reproducible and comparable test results, it is necessary to use the methods of preparation and conditioning, the specimen dimensions, and the test procedures specified in this part of ISO 16365. Values determined are not necessarily identical to those obtained using specimens of different dimensions or prepared using different procedures.

NOTE This part of ISO 16365 has been developed on the basis of ISO 10350-1 as at the time of publication a standard on 'acquisition and presentation of comparable single point data' for thermoplastic elastomers' does not exist yet. After acceptance and publication of this part of ISO 16365, it is the intention to develop ISO 10350-3, based on the two International Standards mentioned before, as starting point for the development of thermoplastic elastomer material standards.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 34-1, *Rubber, vulcanized or thermoplastic — Determination of tear strength — Part 1: Trouser, angle and crescent test pieces*

ISO 37, *Rubber, vulcanized or thermoplastic — Determination of tensile stress-strain properties*

ISO 179-1, *Plastics — Determination of Charpy impact properties — Part 1: Non-instrumented impact test*

ISO 179-2, *Plastics — Determination of Charpy impact properties — Part 2: Instrumented impact test*

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 294-1, *Plastics — Injection moulding of test specimens of thermoplastic materials — Part 1: General principles, and moulding of multipurpose and bar test specimens*

ISO 294-3, *Plastics — Injection moulding of test specimens of thermoplastic materials — Part 3: Small plates*

ISO 294-4, *Plastics — Injection moulding of test specimens of thermoplastic materials — Part 4: Determination of moulding shrinkage*

ISO 472, *Plastics — Vocabulary*

ISO 527-1, *Plastics—Determination of tensile properties—Part 1: General principles*

ISO 527-2, *Plastics — Determination of tensile properties — Part 2: Test conditions for moulding and extrusion plastics*

ISO 815, (all parts), *Rubber, vulcanized or thermoplastic — Determination of compression set*

ISO 846, *Plastics — Evaluation of the action of microorganisms*

ISO 868, *Plastics and ebonite — Determination of indentation hardness by means of a durometer (Shore hardness)*

ISO 1133-2, *Plastics — Determination of the melt mass-flow rate (MFR) and melt volume-flow rate (MVR) of thermoplastics — Part 2: Method for materials sensitive to time-temperature history and/or moisture*

ISO 1183 (all parts), *Plastics-Methods for determining the density and relative density of non-cellular plastics*

ISO 4649, *Rubber, vulcanized or thermoplastic — Determination of abrasion resistance using a rotating cylindrical drum device*

ISO 15512, *Plastics — Determination of water content*

ISO 16365-1, *Plastics — Thermoplastic polyurethanes for moulding and extrusion — Part 1: Designation system and basis for specifications*

ISO 10350-1, *Plastics — Acquisition and presentation of comparable single-point data — Part 1: Moulding materials*

IEC 60093, *Methods of test for volume resistivity and surface resistivity of solid electrical insulation materials*

IEC 60112, *Method for determining of the proof and the comparative and the proof tracking indices of solid insulation materials under moist conditions*

IEC 60243-1, *Electric strength of insulating materials-Test methods-Part 1:Tests at power frequencies*

IEC 60250, *Recommended methods for the determination of the permittivity and dielectric dissipation factor of electrical insulating materials at power, audio and radio frequencies including metre wavelengths*

IEC 60695-11-10, *Fire hazard testing — Part 11-10 Flammability—11-10: Test flames — 50 W horizontal and vertical flame*

3 Preparation of test specimens

3.1 Treatment of the material before moulding

The granules/moulding compound shall have reached room temperature and the moisture content shall not exceed 0,02 % (m/m).

For drying a dehumidified air dryer is recommended, but an oven with circulating air can also be used provided that the drying temperature is increased by 20 °C. For a dehumidified air dryer 3 h at 100 °C might be sufficient, but for several products longer times up to 1 day and a temperature of 110 °C can be used for drying without checking the water content for each sample, if proven to give a moisture content < 0,02 % (m/m). If colour master batches, pigments, or other additives are added, it

is recommended to prepare a premix with the granules before drying. If the material tends to become sticky it might be necessary to choose a lower temperature in order to be able to handle the material.

The water content can be measured after evaporation (see ISO 62 and ISO 10101) or extraction (see ASTM E1064 and ISO 12937), of the water from the sample using solvents like water-free alcohols and subsequent water determination e.g. by Karl Fisher titration, ISO 15512 or any other suitable method to determine moisture content in the range of 0,02 % (m/m) accurately. The moisture content of filled or reinforced materials shall be expressed as a percentage of the total mass of the compound.

To ensure that the moisture content remains low, it is recommended that the sample material in the feed hopper of the injection-moulding machine be blanketed with a suitable gas (dried air, nitrogen, or argon, for example). Better results can be obtained using a dehumidifier hopper drier. Drying for the preparation of test specimen is recommended if the container has been opened several times after delivery of dry product or drying.

Excessive moisture content in the granule can lead to degradation during preparation of test specimen and thus to wrong results. Foaming and formation of gas bubbles are indications that the moisture content is excessively high.

Thermoplastic polyurethanes absorb moisture from air. Storage of granules in dry conditions is therefore recommended before processing. In order to prevent condensation on the granule if storing at low temperatures, material should be brought to room temperature before opening the container. Containers should be tightly closed after use. The granules should be exposed to the surrounding air only as long as absolutely essential.

3.2 Injection moulding

Injection-moulded specimens shall be prepared in accordance with ISO 294-1, using the conditions specified in [Table 1](#). The specimens shall be prepared by injection moulding from dry granules. Test specimen can be cut out from the sample plates using cutting blades.

It is essential that specimens are always prepared by the same procedure using the same processing conditions. The material shall be kept in moisture-proof containers until it is required for use.

Table 1 — Conditions for injection moulding of test specimens

Material Shore D hardness	Heating zone temperature °C	Nozzle temperature °C	Melt temperature °C
Soft: D < 25	200–220	210–230	205–225
Medium: 25 ≥ D < 65	205–225	215–235	210–230
Rigid: D ≥ 65	210–230	220–240	215–235
Injection pressure: 10–100 MPa Holding pressure: 10–100 MPa Back pressure: 0,5–2 MPa			

The processing parameters and temperatures are chosen in a way to minimize differences of mechanical properties in flow direction and crosswise. If the differences are higher than 5 % (mean value) the direction needs be indicated together with the test results.

The flow behaviour of the melt is important for optimizing the processing parameters. The melt flow rate/melt volume rate, using the specified temperature and load in [Table 3](#) can be used for determination of differences in melt flow behaviour (see ISO 1133-2). Only MFR/MVR data measured under exactly the same conditions are comparable. Load and temperatures are chosen in a way to obtain a MVR in the range between 5 cm³/10 min and 100 cm³/10 min, but preferably between 10 cm³/10 min and 40 cm³/10 min.

4 Conditioning of test specimens

Moulded parts made of thermoplastic polyurethane require several weeks of storage at room temperature to attain full mechanical properties. To achieve optimal functional properties in a shorter period, annealing of the finished parts or test specimens is necessary. The recommended duration and temperature of annealing is 20 h at 100 °C. The annealing treatment can be carried out in a circulating air oven immediately after moulding. The tests can be carried out after the test specimen have been stored 24 h at 23 °C and 50 % relative humidity (standard atmosphere).

NOTE During annealing articles or test specimen with low dimensional stability should be stored in a way that deformation is avoided.

5 Determination of properties

5.1 General

In order to obtain reproducible and comparable test results, it is necessary to use the methods of preparation and conditioning, the specimen dimensions and the test procedures specified in this part of ISO 16365. Values determined will not necessarily be identical to those obtained using specimens of different dimensions or prepared using different procedures.

All tests shall be carried out in the standard atmosphere of (23 ± 2) °C and (50 ± 10) % relative humidity unless specifically stated otherwise in [Tables 2](#) and [3](#).

Table 2 is compiled from ISO 10350-1 (see [Clause 1](#)) and the properties listed are those, which are appropriate to thermoplastic polyester/ester and polyether/ester moulding and extrusion materials. These properties are those considered useful for comparisons of data generated for different thermoplastic elastomers.

[Tables 3](#) and [5](#) contain those properties that are considered to be standard properties for the relevant hardness class. [Tables 4](#) and [6](#) contain those properties that are considered a special property for that relevant hardness class, in wide use and/or of particular significance in the practical characterization of the thermoplastic elastomer moulding and extrusion material (see Introduction).

[Tables 3](#) and [4](#) comprise the properties for both hardness classes 1 and 2, up to and including shore D ≤ 65 . [Tables 5](#) and [6](#) comprise the properties for the hardness class 3, Shore D > 65 .

Thermoplastic polyurethanes are used for very different applications. Therefore, type and required values can differ considerably depending on the specific application.

As an example, the following data can be represented by curves or sets of values not by single values.

Content of legally restricted substances, rigidity, torsion behaviour, tear strength, long-term behaviour, creep behaviour, thermal expansion, low-temperature behaviour, softening temperatures, aging, thermal stability, flame classes and burning behaviour, influence of solvents such as swelling, chemical stability, hydrolysis, volatile matter or fogging, electrical properties, undesired substances for a certain application, mould flow behaviour, crystallization behaviour, permeability, etc.

5.2 Biological resistance

The resistance of polyurethanes against microorganisms is dependent on the content of ester bonds in TPU and chemical structure.

For evaluation of the stability against microorganisms ISO 846-Method D (biologically active earth) can be used.

NOTE Since this test takes several months it can be substituted by analysing the content of ester bonds in accordance with ISO 16365-3.

5.3 TPU properties and test conditions

Table 2 — Overview of standard properties and special properties for the characterization of thermoplastic polyurethane materials

Properties	Test method	Shore D ≤ 25		25 < Shore D ≤ 65		Shore D > 65	
		Standard	Special	Standard	Special	Standard	Special
Rheological		Standard	Special	Standard	Special	Standard	Special
MVR/MFR	ISO 1133-2	X		X		X	
Mechanical		Standard	Special	Standard	Special	Standard	Special
Hardness, shore A, D	ISO 868	X		X		X	
Tensile modulus	ISO 527-1/ ISO 527-2	X		X		X	
Tensile stress							
at 20 %, 100 %, 300 % strain		X		X		X	
at > 300 % strain			X		X		X
Stress at break		X				X	
Stress at break/hot water treatment			X		X		X
Strain at break		X		X			X
Strain at break/hot water treatment			X		X		X
Tensile creep modulus	ISO 899-1		X		X		X
Charpy notched impact strength	ISO 179		X		X		X
Tear strength	ISO 34-1; B/b	X		X			X
Compression set	ISO 815	X		X			X
Abrasion loss	ISO 4649A	X		X			X
Biological resistance	ISO 846		X		X		X
Thermal		Standard	Special	Standard	Special	Standard	Special
Glass transition temperature	ISO 11357-1 and ISO 11357-2		X		X	X	
Burning behaviour	IEC 60695-11-10		X		X		X
Electrical		Standard	Special	Standard	Special	Standard	Special
Surface resistivity	IEC 60093		X		X		X
Relative permittivity	IEC 60250		X		X		X
Volume resistivity	IEC 60093		X		X		X
Dissipation factor tan	IEC 60250		X		X		X
Dielectrical strength	IEC 60243-1		X		X		X
Comparative tracking index CTI	IEC 60112		X		X		X
Other		Standard	Special	Standard	Special	Standard	Special
Density	ISO 1183	X		X		X	
Moisture content	ISO 15512	X		X		X	

Table 3 — Standard properties and test conditions^a — Shore hardness classification D ≤ 65

Property	Units	Standard	Specimen type mm	Specimen preparation ^a	Test conditions and supplementary conditions
Rheological properties					
MFR/MVR	g/10 min/ cm ³ /10 min	ISO 1133-2	Moulding compound	Dry, moisture con- tent < 0,03 % (m/m)	Load 2,16 kg, 5 kg, 10 kg, 21,6 kg T-melt + 10 °C = T-MFR
Mechanical properties					
Hardness	Shore D	ISO 868	≥ 80 × ≥ 10 × ≥ 6	M	5 measurements ≥ 9 mm from any edge, ≥ 6mm apart. 3 specimens of 2 mm stacked
Tensile modulus	MPa	ISO 527-2	1A (equal ISO 3167A)	M	Speed 1 mm/min
Tensile stress at x % elongation	MPa		1BA or 5A thickness 2 mm	M	20 %, 100 %, 300 % elonga- tion
Stress at break	MPa			M	Speed 200 mm/min
Strain at break	%			M	Speed 200 mm/min
Tear strength	kN/m	ISO 34-1	ISO 31-1 method B procedure A	M	Speed 500 mm/min
Compression set	%	ISO 815	Ø 13 mm × 6mm	M	23°C, 70°C
Abrasion loss	mm ³	ISO 4649 A	Thickness 6 mm	M	
Other properties					
Density	g/cm ³	ISO 1183			
Moisture content	%	ISO 15512	Granules/moulding compound	Before and/or after drying	
^a M: Injection moulding					

Table 4 — Specialized properties and test conditions — Shore hardness classification D ≤ 65

Property	Unit	Standard	Specimen type mm	Specimen prepara- tion ^a	Test conditions and sup- plementary instruc- tions
Mechanical properties					
Tensile stress at > 300 % strain	MPa	ISO 37 or ISO 527-2	Type to be specified and documented	M	To be agreed between stakeholders. Elongation and applied standard to be specified and documented
Tensile creep	MPa	ISO 899	ISO 3167A	M	To be agreed between customer and supplier. Times to be specified and documented
Charpy notched Impact Strength	kJ/m ²	ISO 179	80 × 10 × 4 V-notch r=1	M	Method 1eA, edgewise impact
Biological resistance		ISO 846 variant D and ISO 527-2	ISO 527-2 type 1BA Thickness 2 mm	M	Tensile test for comparison purposes for ester containing TPU, but not needed for 100 % TPU-ARET or TPU-ALET
Thermal properties					
Glass transition temperature		ISO 11357-1 and ISO 11357-2	Moulding compound	M	Record midpoint temperature Use 10 °C/min
Burning behaviour		IEC 60695-11-10	125 × 13 × 3	M	0,91 mm, 3,0 mm
Electrical properties					
Relative permittivity		IEC 60250	≥ 60 × ≥ 60 × 2	M	100 Hz, 1 MHz
Dissipation factor tan		IEC 60250		M	100 Hz, 1 MHz
Volume resistivity	Ω m	IEC 60093		M	
Surface resistivity	Ω	IEC 60093		M	
Dielectrical strength	kV/mm	IEC 60243-1	≥ 60 × ≥ 60 × 1	M	
Comparative tracking index CTI	V	IEC 60112	≥ 20 × ≥ 20 × 4	M	
^a M: Injection moulding					

Table 5 — Standard properties and test conditions^a — Shore hardness classification D > 65

Property	Units	Standard	Specimen type mm	Specimen preparation ^a	Test conditions and sup- plementary conditions
Rheological properties					
MFR / MVR	g/10 min/ cm ³ /10 min	ISO-1133-2	Moulding com- pound	Dry, mois- ture con- tent < 0,03 % (m/m)	Load 2,16 kg, 5 kg, 10 kg, 21,6 kg T-melt + 10 °C = T-MFR
Mechanical properties					
Hardness	Shore D	ISO 868	≥ 80 × ≥ 10 × ≥ 6	M	5 measurements ≥ 9 mm from any edge, ≥ 6mm apart. 3 Specimens of 2 mm stacked
Tensile modulus	MPa	ISO 527-2	1A (equal ISO 3167A)	M	Speed 1 mm/min
Tensile stress at x % elongation	MPa		1BA thickness 2 mm	M	20 %, 100 %, 300 % elon- gation
Stress at break	MPa		M	M	Speed 200 mm/min
Tensile elongation at break	%		M	M	Speed 200 mm/min
Stress at break	MPa		M	M	Speed 200 mm/min
Thermal properties					
Glass transition tem- perature		ISO 11357-1 and ISO 11357-2	Moulding com- pound	M	Record midpoint tempera- ture Use 10 °C/min
Other properties					
Density	g/cm ³	ISO 1183		M	
Moisture content	%	ISO 15512	Granules/mould- ing compound	Before and/or after drying	
^a M: Injection moulding					

Table 6 — Specialized properties and test conditions — Shore hardness classification D > 65

Property	Unit	Standard	Specimen type mm	Specimen prepara- tion ^a	Test conditions and sup- plementary instruc- tions
Mechanical properties					
Strain at break	%				Speed 200 mm/min
Tensile creep	MPa	ISO 899	ISO 3167A	M	To be agreed between customer and supplier. Times to be specified and documented
Charpy notched impact Strength	kJ/m ²		80 × 10 × 4 V-notch r=1	M	Method 1eA, Edgewise impact
Tear strength	kN/m	ISO 34-1	ISO 31-1 Bb		Speed 500 mm/min
Compression set	%	ISO 815	∅ 13 mm × 6 mm		23°C, 70°C
Abrasion loss	mm ³	ISO 4649 A	Thickness 6 mm		
Biological resistance		ISO 846 variant D and ISO 527-2	ISO 527-2 type 1BA thickness 2 mm	M	Tensile test for comparison purposes for ester containing TPU, but not needed for 100 % TPU-ARET or TPU-ALET
Thermal properties					
Burning behaviour		IEC 60695-11-10	125 × 13 × 3	M	0,91 mm, 3,0 mm
Electrical properties					
Relative permittivity		IEC 60250	≥ 60 × ≥ 60 × 2	M	100 Hz, 1 MHz
Dissipation factor tan		IEC 60250		M	100 Hz, 1 MHz
Volume resistivity	Ω m	IEC 60093		M	
Surface resistivity	Ω	IEC 60093		M	
Dielectrical strength	kV/mm	IEC 60243-1	≥ 60 × ≥ 60 × 1	M	
Comparative tracking index CTI	V	IEC 60112	≥ 20 × ≥ 20 × 4	M	
^a M: Injection moulding					

Annex A **(informative)**

Material identification

For material identification of thermoplastic polyurethane materials, infrared spectra can be used. Thermogravimetry can also be used and can be combined with density determination. Generally, this gives less information, but can easily be applied even in presence of carbon black without any sample preparation.

For quality control, other methods related to the molar mass of the polymer can be used in addition as solution viscosity measurements or gel permeation chromatography (GPC).

NOTE DSC usually is not considered as an adequate method for identity control of thermoplastic polyurethanes, because this method depends not only on the material used but also on processing and annealing conditions.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™