

BS ISO 16374:2016



BSI Standards Publication

# Evaluation method for cleanliness of magnesium and magnesium alloy ingots

**National foreword**

This British Standard is the UK implementation of ISO 16374:2016.

The UK participation in its preparation was entrusted to Technical Committee NFE/35, Light metals and their alloys.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.  
Published by BSI Standards Limited 2016

ISBN 978 0 580 78092 9

ICS 77.120.20

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 September 2016.

**Amendments/corrigenda issued since publication**

Date	Text affected
------	---------------

---

INTERNATIONAL  
STANDARD

BS ISO 16374:2016

**ISO**  
**16374**

First edition  
2016-09-01

---

---

**Evaluation method for cleanliness  
of magnesium and magnesium alloy  
ingots**

*Méthode d'évaluation de la propreté des lingots en magnésium et en  
alliages de magnésium*



Reference number  
ISO 16374:2016(E)

© ISO 2016



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

	Page
Foreword .....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions .....</b>	<b>1</b>
<b>4 Naked eye inspection .....</b>	<b>1</b>
<b>5 Chemical composition analysis .....</b>	<b>1</b>
<b>6 Brightness evaluation .....</b>	<b>2</b>
6.1 Principle of brightness evaluation .....	2
6.2 Specimen preparation .....	2
6.3 Shape of jig .....	3
6.4 Brightness evaluation of the fracture surface .....	4
6.5 Others .....	5
<b>7 Test report .....</b>	<b>5</b>
<b>Bibliography .....</b>	<b>6</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

The committee responsible for this document is ISO/TC 79, *Light metals and their alloys*, Subcommittee SC 5, *Magnesium and alloys of cast or wrought magnesium*.

# Evaluation method for cleanliness of magnesium and magnesium alloy ingots

## 1 Scope

This document describes a method to evaluate the cleanliness and the quality of magnesium and magnesium alloys ingots.

The method includes naked eye inspection, the composition analysis and a brightness evaluation procedure based on an ISO standard.

## 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2470-1, *Paper, board and pulps — Measurement of diffuse blue reflectance factor — Part 1: Indoor daylight conditions (ISO brightness)*

ISO 3116, *Magnesium and magnesium alloys — Wrought magnesium alloys*

ISO 8287, *Magnesium and magnesium alloys — Unalloyed magnesium — Chemical composition*

ISO 16220, *Magnesium and magnesium alloys — Magnesium alloy ingots and castings*

## 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

## 4 Naked eye inspection

Identify any presence of significant contraction or impurities on the surface of magnesium ingots. The decision on the quality of ingots by naked eye inspection should be agreed between the supplier and the purchaser.

## 5 Chemical composition analysis

Analyse the content of alloying elements of ingots. The chemical composition methods can be selected by agreement between the supplier and the purchaser and shall be mentioned in the testing report. The chemical composition of magnesium and magnesium alloys is specified in ISO 8287, ISO 16220 and ISO 3116. The range of the composition of unspecified alloys or alloying elements can be determined by an agreement between the supplier and the purchaser.


## 6 Brightness evaluation

### 6.1 Principle of brightness evaluation

The principle of the brightness evaluation is based on the specification given in ISO 2470-1. Diffused light beams from a standard testing machine are shed on a specimen. Beams reflected from the specimen surface pass through a specified glass filter and are subsequently measured by an optical cell or arranged diodes that respond to different effective wavelengths. The brightness can be evaluated directly from the output of the optical cell or obtained by assessment of the output from the diodes using an appropriate weight function.

### 6.2 Specimen preparation


In principle, the test specimen should be obtained directly from ingots or molten metals. The shape and dimension of the test specimen are shown in [Figure 1](#). The specimen is machined directly from the ingot in use. When the specimen is obtained from molten metals, it is prepared by pouring the melt in a mould having appropriate shape and dimensions. In this case, the dimensions can be slightly modified except that of the neck area, which shall have 8 mm diameter since it is the dimension area of the testing machine.

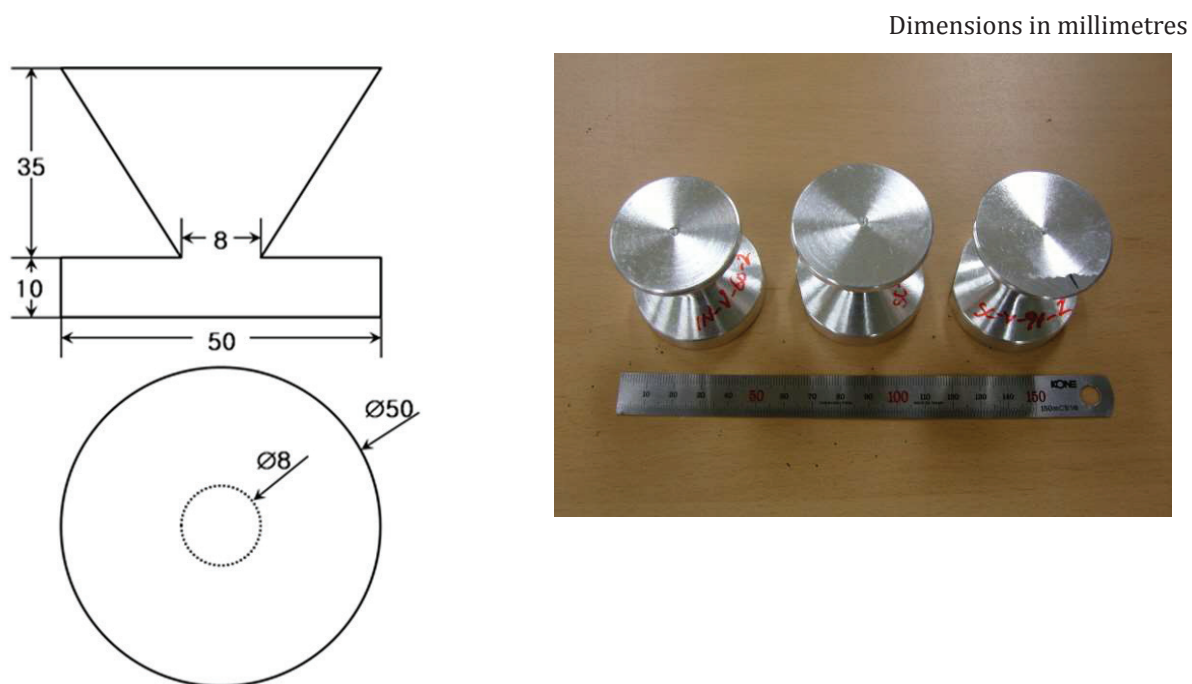

**Figure 1 — Shape and dimension of the test specimen obtained by machining from ingots**

[Figure 2](#) shows the shape and dimension of the mould to cast the brightness test specimen. The dimension of the inside area is the same as that shown in [Figure 1](#). The design of the mould can be modified freely; it can be designed as a separate type such that the specimen is easily released as shown below.




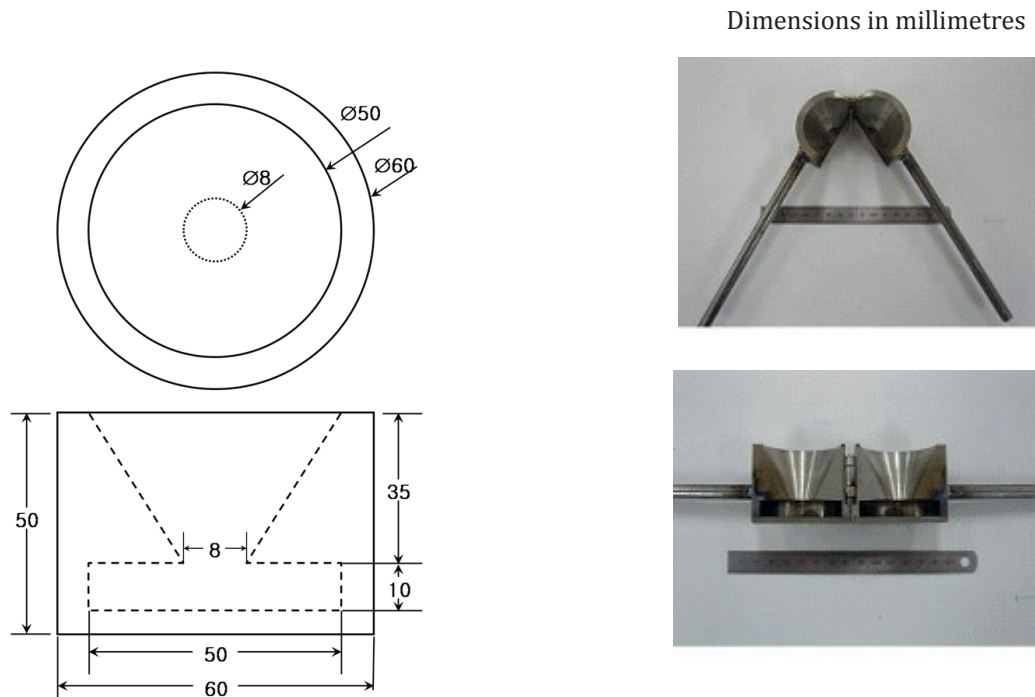

**Figure 2 — Shape and dimension of mould for brightness test specimen from molten metals**

### 6.3 Shape of jig

A jig is used to break the neck area for brightness tests. Such a jig can be prepared in various ways with freedom so that the neck area can be fractured by repeated impacts. The outline of the jig shape is shown in [Figure 3](#).

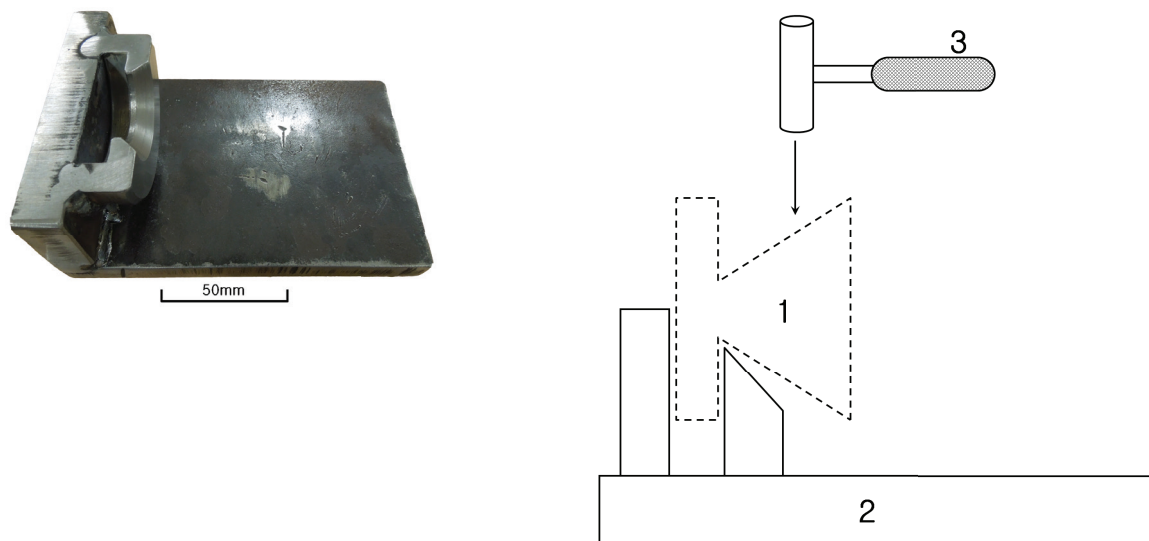

**Key**

- 1 specimen
- 2 jig for fracture
- 3 hammer

**Figure 3 — Shape of jig and setup for fracturing the test specimen**

**6.4 Brightness evaluation of the fracture surface**

Immediately after the fracture of the test specimen, the brightness of the fracture surface is evaluated by means of an appropriate instrument while rotating the specimen. The number of determination depends on rotation angles as shown in [Table 1](#). The final result is expressed by the average value of the test results obtained at each angle. The number of test specimen and determinations shall be specified by agreement between the supplier and the purchaser.

**Table 1 — Number of determinations and rotation angles to evaluate brightness of fracture surface**

No. of measurement	Rotation angle for each measurement
3	0°, 45°, 90°
8	0°, 45°, 90°, 135°, 180°, 225°, 270°, 315°

The criteria to evaluate brightness for each alloy is shown in [Table 2](#). The brightness data for alloys that are not shown in [Table 2](#) can be deduced from the contents of major alloying elements and finally determined according to the agreements between the deliverer and the acceptor.

**Table 2 — Criteria to evaluate brightness for each alloy**

Materials	Criteria for brightness	Major alloying element and its range	Alloy designation	
			ISO	ASTM
Mg-9Al-1Zn	above 48	Al 9,0 ~ 11,0	MgAl9Zn1(B)	AZ91C
			MgAl9Zn1(A)	AZ91E
				AZ91B
				AZ91D
Mg-6Al-0,5Mn, Mg-5Al-0,5Mn	above 50	Al 5,0 ~ 7,5	MgAl6Mn	AM60B
			MgAl5Mn	AM50A
Mg-3Al-1Zn	above 51	Al 3,0 ~ 5,0	MgAl3Zn1(A)	AZ31A
			MgAl3Zn1(B)	AZ31B

## 6.5 Others

In the case that there is a difficulty to obtain the full-specimen dimension by machining or casting, the brightness can be evaluated by directly breaking the ingots or castings after agreement between the supplier and the purchaser. In this case, the diameter of the fractured surface should be at least 8 mm and recorded in final report in detail.

## 7 Test report

The test report shall include the following information:

- a) the date of the test, identification of the testing organization and signature of the responsible person;
- b) the identification of the manufacturer, alloy designation, number of test specimens and number of test specimens;
- c) the identification of the sample;
- d) the specimen preparation method: casting, machining;
- e) the criteria for naked eye inspection and results;
- f) the chemical composition analysis method and results;
- g) the type of instrument used for the brightness evaluation: manufacturer, model;
- h) the conditions to evaluate the brightness of fractured surfaces;
- i) the results of brightness evaluation;
- j) any departure from this document or any circumstances or influences that may affect the results.

## Bibliography

- [1] ISO 2469, *Paper, board and pulps — Measurement of diffuse radiance factor (diffuse reflectance factor)*
- [2] ISO 7724-1, *Paints and varnishes — Colorimetry — Part 1: Principles*
- [3] ASTM E 1164, *Standard practice for obtaining spectrophotometric data for object — colour evaluation*







# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

## Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

## Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com).

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Useful Contacts

### Customer Services

**Tel:** +44 345 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 345 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)

### BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK