

BS ISO 16525-3:2014



BSI Standards Publication

# Adhesives — Test methods for isotropic electrically conductive adhesives

Part 3: Determination of heat-transfer properties

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of ISO 16525-3:2014.

The UK participation in its preparation was entrusted to Technical Committee PRI/52, Adhesives.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014.  
Published by BSI Standards Limited 2014

ISBN 978 0 580 74569 0  
ICS 83.180

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2014.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

INTERNATIONAL  
STANDARD

**ISO**  
**16525-3**

First edition  
2014-05-15

---

---

**Adhesives — Test methods for  
isotropic electrically conductive  
adhesives —**

**Part 3:  
Determination of heat-transfer  
properties**

*Adhésifs — Méthodes d'essai pour adhésifs à conductivité électrique  
isotrope —*

*Partie 3: Détermination des propriétés de transfert de chaleur*



Reference number  
ISO 16525-3:2014(E)

© ISO 2014



## **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>2</b>
<b>4 Principle</b> .....	<b>3</b>
<b>5 Scope of test</b> .....	<b>3</b>
<b>6 Apparatus</b> .....	<b>4</b>
<b>7 Cartridge-type specimen</b> .....	<b>6</b>
7.1 The cartridge-type specimen.....	6
7.2 Dimensions and tolerances of the cartridge-type specimen.....	6
7.3 Preparation of the cartridge-type specimen.....	8
<b>8 Standard rod</b> .....	<b>9</b>
8.1 Shape of standard rods.....	9
8.2 Dimensions and tolerance of standard rods.....	9
8.3 Material and thermal conductivity of standard rods.....	9
8.4 Surface roughness and flatness of the contact surface of the standard rods and parallelism of the upper/lower faces.....	10
8.5 Boring thermocouple holes through the standard rods.....	10
<b>9 Procedure</b> .....	<b>11</b>
9.1 Assembly of the cartridge-type specimen and the standard rod.....	11
9.2 Heating or cooling procedure of the cartridge-type specimen and the standard rod.....	11
9.3 Temperature measurement of the cartridge-type specimen and the standard rods.....	11
<b>10 Calculation of heat transfer property</b> .....	<b>11</b>
10.1 Effective thermal conductivity.....	11
10.2 Thermal resistance.....	14
10.3 Thermal conductance.....	15
<b>11 Test report</b> .....	<b>15</b>
<b>Bibliography</b> .....	<b>16</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2. [www.iso.org/directives](http://www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received. [www.iso.org/patents](http://www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

ISO 16525 consists of the following parts, under the general title *Adhesives — Test methods for isotropic electrically conductive adhesives*:

- *Part 1: General test methods*
- *Part 2: Determination of electric characteristics for use in electronic assemblies*
- *Part 3: Determination of heat-transfer properties*
- *Part 4: Determination of shear strength and electrical resistance using rigid-to-rigid bonded assemblies*
- *Part 5: Determination of shear fatigue*
- *Part 6: Determination of pendulum-type shear impact*
- *Part 7: Environmental test methods*
- *Part 8: Electrochemical migration test methods*
- *Part 9: Determination of high-speed signal-transmission characteristics*

# Adhesives — Test methods for isotropic electrically conductive adhesives —

## Part 3: Determination of heat-transfer properties

**SAFETY STATEMENT** — Persons using this part of ISO 16525 should be familiar with normal laboratory practice. This part of ISO 16525 does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory conditions.

**IMPORTANT** — Certain procedures specified in this part of ISO 16525 might involve the use or generation of substances, or the generation of waste, that could constitute a local environmental hazard. Reference should be made to appropriate documentation on safe handling and disposal after use.

### 1 Scope

This part of ISO 16525 specifies test methods for heat-transfer properties such as effective thermal conductivity and thermal resistance by a steady-state comparative longitudinal heat-flow method (SCHF method) using cartridge-type specimen for isotropic electrically conductive adhesives used in wiring, die attach, and surface assembly.

### 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3611, *Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics*

ISO 4287, *Geometrical Product Specifications (GPS) — Surface texture: Profile method — Terms, definitions and surface texture parameters*

ISO 13385-1, *Geometrical product specifications (GPS) — Dimensional measuring equipment — Part 1: Callipers; Design and metrological characteristics*

ISO 13385-2, *Geometrical product specifications (GPS) — Dimensional measuring equipment — Part 2: Calliper depth gauges; Design and metrological characteristics*

ISO 17212, *Structural adhesives — Guidelines for the surface preparation of metals and plastics prior to adhesive bonding*

ISO 80000-1, *Quantities and units — Part 1: General*

IEC 60584-1, *Thermocouples — Part 1: Reference tables*

### 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

NOTE Thermal conductivity of heterogeneous materials is called “apparent thermal conductivity”, “equivalent thermal conductivity” or “effective thermal conductivity”. For those materials whose compositions are nearly homogeneous, “thermal conductivity” can be used if it does not lead to confusion.

#### 3.1 heat flow rate

$Q$   
amount of thermal energy transferring from/to one system from/to another in a given time

Note 1 to entry: It is expressed in watts (W).

#### 3.2 heat flow rate over surface area

heat flux  
 $q$   
amount of thermal energy being transferred over a given surface area

Note 1 to entry: It is expressed in watts per square metre (W/m<sup>2</sup>).

#### 3.3 heat transfer property

collective term for thermal resistance, thermal conductivity, effective thermal conductivity and thermal conductance

#### 3.4 thermal resistance

$R$   
temperature difference between the front and back sides in the steady-state divided by heat flux

Note 1 to entry: It is expressed in square metre kelvin per watt (m<sup>2</sup>·K/W).

Note 2 to entry: This parameter indicates how heat is transferred, with a high value denoting reduced heat transfer.

#### 3.5 thermal conductance

$K$   
heat flux in the steady state divided by the temperature difference between front and back sides

Note 1 to entry: It is expressed in watt per square metre kelvin (W/m<sup>2</sup>·K).

Note 2 to entry: The reciprocal of thermal resistance.

#### 3.6 thermal conductivity

$k$   
proportionality coefficient that represents the relationship of heat flux and temperature gradient, where heat flux on an isothermal surface is proportional to the temperature gradient in the normal direction on the isothermal surface

Note 1 to entry: It is expressed in watt per metre kelvin (W/m·K).



### 3.7 effective thermal conductivity

$k_{\text{eff}}$

<system consisting of two substances or more> heat flux in the steady state that is divided by a temperature difference between the front and back sides, and multiplied by the distance between the front and back sides,  $L$

Note 1 to entry: It is expressed in watt per metre kelvin (W/m·K).

Note 2 to entry: Effective thermal conductivity includes interfacial thermal resistance.

Note 3 to entry: It is expressed by  $K \times L$ .

### 3.8 interfacial thermal resistance

$R_i$

specific type of thermal resistance arising on the contact surface of the material (contact thermal resistance), where thermal resistance caused by heat conduction of the filling between a gap and the material is removed

Note 1 to entry: It is expressed in square metre kelvin per watt (m<sup>2</sup>·K/W).

Note 2 to entry: It is generated mainly between the surface of the material and the contact surface.

### 3.9 mean temperature of specimen

$T_m$

arithmetic mean of temperatures of the high-temperature surface and the low-temperature surface of a specimen in the steady state

Note 1 to entry: It is expressed in kelvin (K).

Note 2 to entry: It is simply called mean temperature.

## 4 Principle

Effective thermal conductivity of isotropic electrically conductive adhesives is measured by the steady-state temperature distribution in the cartridge-type specimen and standard rods under longitudinal heat-flow condition. The cartridge-type specimen is sandwiched by the standard rods made of square or cylindrical poles with known thermal conductivity.

NOTE This method is called the steady-state comparative longitudinal heat-flow method (SCHF), which uses standard rods to measure heat flux,  $q$ , to calculate effective thermal conductivity. It is useful for isotropic electrically conductive adhesives whose thermal conductivity varies due to interfacial thermal resistance between the isotropic electrically conductive adhesive and the heating surface.

## 5 Scope of test

The measurement range of thermal conductivity of an isotropic electrically conductive adhesive is determined by its thermal conductance. The lower and upper limits of thermal conductance are calculated using Formulae (1) and (2), respectively.

$$K_s \geq 2760 t_r^{1.85} w_r^{-1.4} \quad (1)$$

where

$$25 \leq t_r \leq 60, 10 \leq w_r \leq 60$$

$$\begin{aligned} K_s &\leq 100\,000 & (k_{\text{eff}} > 20) \\ K_s &\leq 5\,000k_{\text{eff}} & (k_{\text{eff}} \leq 20) \end{aligned} \quad (2)$$

where

$K_s$  is the thermal conductance of the isotropic electrically conductive adhesive [ $\text{W}/(\text{m}^2\cdot\text{K})$ ]  
( $= k_{\text{eff}}/t_s$ );

$k_{\text{eff}}$  is the effective thermal conductivity of the isotropic electrically conductive adhesive [ $\text{W}/(\text{m}\cdot\text{K})$ ];

$t_r$  is the thickness of standard rods (mm);

$t_s$  is the thickness of the isotropic electrically conductive adhesive (mm);

$W_r$  is the length of the side of the specimen (mm).

**EXAMPLE** The lower limits of measurable thermal conductance of the isotropic electrically conductive adhesive with  $t_r$  of 25 mm are shown below:


- a) 2 000  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $W_r = 10$  mm;
- b) 800  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $W_r = 20$  mm;
- c) 400  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $W_r = 30$  mm;
- d) 200  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $W_r = 60$  mm.

**NOTE** The upper limit of measurable thermal conductance of the isotropic electrically conductive adhesive is shown below:

- a) 100 000  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $k_{\text{eff}} = 50$   $\text{W}/(\text{m}\cdot\text{K})$ ;
- b) 100 000  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $k_{\text{eff}} = 30$   $\text{W}/(\text{m}\cdot\text{K})$ ;
- c) 100 000  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $k_{\text{eff}} = 20$   $\text{W}/(\text{m}\cdot\text{K})$ ;
- d) 50 000  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $k_{\text{eff}} = 10$   $\text{W}/(\text{m}\cdot\text{K})$ ;
- e) 5 000  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $k_{\text{eff}} = 1$   $\text{W}/(\text{m}\cdot\text{K})$ ;
- f) 2 500  $\text{W}/(\text{m}^2\cdot\text{K})$ , when  $k_{\text{eff}} = 0,5$   $\text{W}/(\text{m}\cdot\text{K})$ .

## 6 Apparatus

**6.1 Apparatus** (general), consisting of measuring, heating, cooling and pressure-regulating devices. The cartridge-type specimen is sandwiched between the standard upper and lower rods with known thermal conductivity. Heat flows through the specimen longitudinally. An example of the test apparatus is shown in [Figure 1](#).

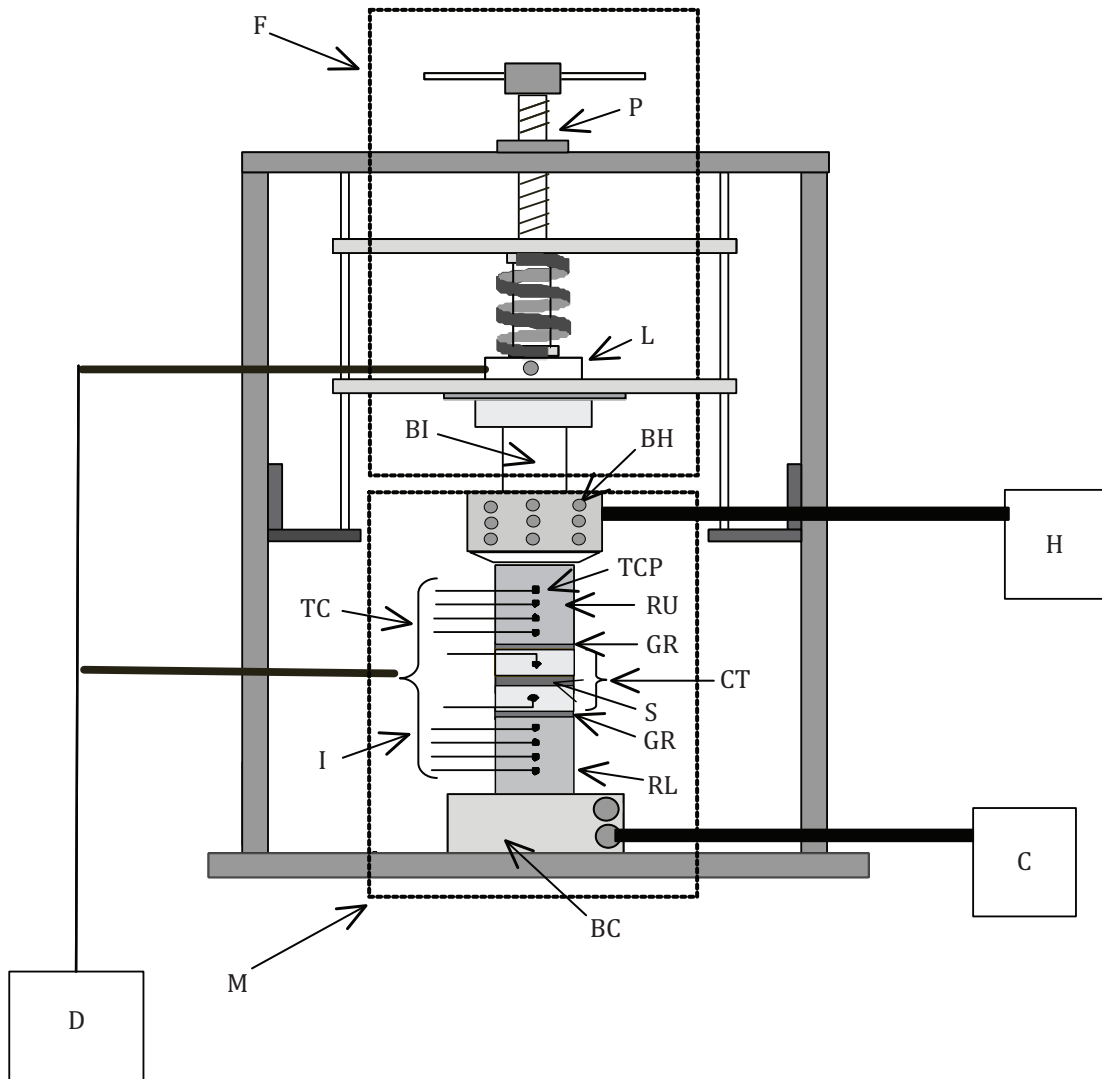

**Key**

- |    |                          |     |   |
|----|--------------------------|-----|---|
| BC | cooling block            | L   | load cell                                   |
| BH | heating block            | M   | measurement system                          |
| BI | insulating block         | P   | screw for pressure regulation               |
| CT | cartridge-type specimen  | RL  | lower rod                                   |
| C  | cooling equipment        | RU  | upper rod                                   |
| D  | data acquisition device  | S   | isotropic electrically conductive adhesives |
| F  | pressure adjustment unit | TC  | thermocouple                                |
| GR | thermal grease           | TCP | holes for temperature measurement           |
| H  | heating equipment        | I   | thermal insulator                           |

**Figure 1 — Example configuration of thermal conductivity test apparatus by SCHF method**

**6.2 Measurement system (M)**, consisting of a specimen (S), upper and lower rods (RU and RL), a heating block (BH) with a built-in heater, a cooling block (BC) and a thermal insulator (I), which covers these components. The upper/lower rods (RU/RL) and the specimen have thermocouple holes (TCPs)

in which thermocouples (TCs) are inserted to measure the temperature gradient. The depth of each thermocouple hole is no smaller than 5 mm.

The thermocouples are to measure the temperature distribution of the upper/lower rods (RU/RL) and specimen (S). Requirements for thermocouples are described below. When using thermoelectric devices, i.e. thermometers instead of thermocouples, they shall be equivalent to or surpass thermocouples in terms of performance.

- a) They shall be stable up to the temperature specified in IEC 60584;
- b) They shall have sufficient strength to be able to detect small fluctuations in temperature in a range where thermoelectromotive force does not change, and they shall have variance in the temperature displayed among thermocouples at  $\pm 0,5$  K.

### 6.3 Heating and cooling equipment (C, H).

- a) **Heating equipment (H)**, supplying the heater of the heating block (BH) in the measurement system (M) with power; its temperature fluctuation shall be within  $\pm 0,5$  K.
- b) **Cooling equipment (C)**, refrigerating the cooling block (BC) in the measuring system (M). The cooling equipment shall guarantee that the temperature of the specimen is within the range of room temperature to 125 °C and shall be able to control fluctuation of temperature of the specimen within  $\pm 0,5$  K.

**6.4 Pressure adjustment unit (F)**, pressurizing the measurement system (M) to measure its applied force. It is composed of a pressure adjustment screw (P), load cell (L) and insulating block (BI).

**6.5 Data acquisition device (D)**, recording steady-state temperature of the upper/lower standard rods (RU/RL) and cartridge-type specimen (CT), and applied force of the load cell (L).

## 7 Cartridge-type specimen

### 7.1 The cartridge-type specimen

The shape of the cartridge-type specimen is a square column. An example of the cartridge-type specimen is shown in [Figure 2](#). It consists of an isotropic electrically conductive adhesive sandwiched by metal blocks with three holes each for temperature measurement.

### 7.2 Dimensions and tolerances of the cartridge-type specimen

Dimensions and tolerance of the specimen are specified as follows:

- a) Length of the side of the specimen and its measurement: the range of the length of the side and its measurement are as follows:
  - 1) The length of the side of the specimen shall be within the range of 10 mm to 60 mm, and its tolerance shall be  $\pm 0,05$  mm.

NOTE Measurable heat conductance of a cartridge-type specimen can have a lower limit, depending on the length of its side (see [Clause 5](#)).

- 2) To measure the length of the side of the specimen, use vernier callipers with a precision of 0,05 mm as specified in ISO 13385-1 or those which are equivalent or higher in terms of precision.
- b) Cross-section: the cross-sectional area shall be obtained by multiplying the length of one side and the length of the other side.

- c) Thickness and its measurement: the range of thickness and its measurement are specified as follows.
- 1) The thickness of isotropic electrically conductive adhesives shall be within the range of 0,2 mm to 5 mm, and its lower limit is determined by Formula (3).

$$\begin{aligned} t_s &\geq 0,01k_{\text{eff}} && (k > 20) \\ t_s &\geq 0,2 && (k_{\text{eff}} \leq 20) \end{aligned} \quad (3)$$

EXAMPLE The lower limits of the isotropic electrically conductive adhesive are shown below:

- 0,5 mm, when  $k_{\text{eff}} = 50 \text{ W}/(\text{m}\cdot\text{K})$ ;
- 0,3 mm, when  $k_{\text{eff}} = 30 \text{ W}/(\text{m}\cdot\text{K})$ ;
- 0,2 mm, when  $k_{\text{eff}} = 20 \text{ W}/(\text{m}\cdot\text{K})$ ;
- 0,2 mm, when  $k_{\text{eff}} = 10 \text{ W}/(\text{m}\cdot\text{K})$ ;
- 0,2 mm, when  $k_{\text{eff}} = 1 \text{ W}/(\text{m}\cdot\text{K})$ ;
- 0,2 mm, when  $k_{\text{eff}} = 0.5 \text{ W}/(\text{m}\cdot\text{K})$ .


where the tolerance is  $\pm 0,010 \text{ mm}$ .

The accuracy of the measurement value of the thermal conductance depends on the measurement tolerances of the thickness with respect to the isotropic electrically conductive adhesive. When the measurement parameter is thermal resistance only, or the tolerance is lower than 0,010 mm, the limit of thickness is less than shown in the Note above.

When the measurement parameter is not thermal resistance, which includes interfacial resistance between specimen block and an isotropic electrically conductive adhesive, the hot disc method, the temperature wave analysis method, and the laser flash method (see ISO 22007-2, ISO 22007-3 and ISO 22007-4) are available for the thinner isotropic electrically conductive adhesive layers. The accuracy depends on the thickness tolerance. For example, if the thickness of the isotropic electrically conductive adhesive is 0,03 mm, the tolerance should be  $\pm 1,0 \mu\text{m}$ .

- 2) The thickness of the specimen block is within the range of 2 mm to 5 mm, and its tolerance is  $\pm 0,010 \text{ mm}$ .
  - 3) The thickness of the isotropic electrically conductive adhesive is obtained by subtracting the thickness of the specimen blocks from that of the cartridge-type specimen.
  - 4) Measure thickness at five points (the centre and four corners) using micrometer callipers with a precision of 0,001 mm as specified in ISO 3611 or those which are equivalent or higher in terms of precision.
- d) Surface roughness and flatness of the adherend of the specimen blocks and parallelism of the upper/lower faces: surface roughness and flatness of the adherend between the specimen blocks and the isotropic electrically conductive adhesive and parallelism of the upper/lower faces are specified as follows:
- 1) surface roughness of the adherend,  $R_a$ , as specified in ISO 4287, shall be no greater than  $5 \mu\text{m}$ ;
  - 2) flatness of the adherend and parallelism of the upper/lower faces shall be both no greater than  $5 \mu\text{m}$ .
- e) Types of specimen blocks: the specimen blocks shall be manufactured from a metal of known thermal conductivity.

- f) Diameter and depth of thermocouple holes: the diameter and depth of thermocouple holes are specified as follows:
- 1) the diameter of each thermocouple hole is within the range of 0,5 mm to 1 mm, allowing a thermocouple to be inserted;
  - 2) the depth of each thermocouple hole is not less than 5 mm.
- g) The number of thermocouple holes is one or three. Three holes make it possible to check the horizontal heat flow. When the difference in temperature between the holes is greater than 0,5 K, the specimen block should be reset.

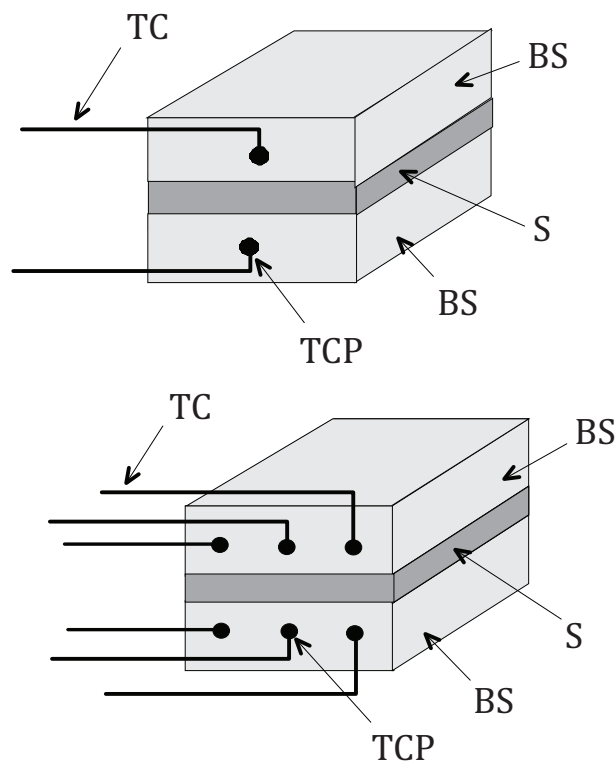

a) One-hole type

b) Three-hole type

**Key**

BS metal block

CT cartridge-type specimen

S isotropic electrically conductive adhesives

TC thermocouple

TCP holes for temperature measurement

**Figure 2 — Example configuration of cartridge-type specimen**

**7.3 Preparation of the cartridge-type specimen**

Prepare a cartridge-type specimen as follows.

- a) Wash the surface of the specimen blocks using a fresh solvent or cleaning agent, degrease it in compliance with ISO 17212, or follow the procedure recommended by the manufacturer.
- b) After measuring the thickness of the specimen blocks, apply an isotropic electrically conductive adhesive to the surface of the specimen blocks. For its application, stir the isotropic electrically

conductive adhesive sufficiently in accordance with the direction provided by its manufacturer; apply it to the specimen blocks using screen printing or a dispenser.

- c) Lay spacers of a specified thickness on the specimen blocks before placing the isotropic electrically conductive adhesive.

Spherical glass beads, metal or ceramic may be used as spacers. Lay spacers in the centre and four corners to make its thickness uniform, thus preventing the specimen from influencing the heat-transfer properties of the isotropic electrically conductive adhesive.

- d) Laminate the specimen blocks and apply pressure uniformly. Remove any excess isotropic electrically conductive adhesive immediately after lamination.

NOTE Preferably, use jig to align the specimens.

- e) Prepare a cartridge-type specimen cured under specified conditions while it is under pressure for the manufacturer's recommended curing conditions (curing temperature and setting time).

## 8 Standard rod

### 8.1 Shape of standard rods

The standard rods are square columns.

### 8.2 Dimensions and tolerance of standard rods

The dimensions and tolerance of standard rods are specified as follows.

- a) Length of the side of a standard rod and its measurement: see [7.2 a\)](#). The cross-sectional shape and length of the side of a standard rod are identical to those of the cartridge-type specimen.
- b) Cross-section: see [7.2 b\)](#).
- c) Thickness and its measurement: the range of thickness and its measurement are specified as follows:
  - 1) the thickness is within the range of 25 mm to 60 mm, and its tolerance is  $\pm 0,05$  mm;
  - 2) to measure thickness, use vernier callipers with a precision of 0,05 mm as specified in ISO 13385-1 and ISO 13385-2 or those which are equivalent or higher in terms of precision.

NOTE The measurable heat conductance of a cartridge-type specimen can have a lower limit, depending on the thickness of standard rods (see [Clause 5](#)).

### 8.3 Material and thermal conductivity of standard rods

Choose a material for standard rods of known thermal conductivity and satisfying Formula (4). (See [Table 1](#).)

When the effective thermal conductivity of the specimen is estimated to be  $3 \text{ W}/(\text{m}\cdot\text{K})$ , when thickness of the specimen resin is 0,3 mm, and when effective thickness of standard rods is 15 mm, Formula (4) is

$0,1 \times 3 \times (15/0,3) = 15 < k_r < 4 \times 3 \times (15/0,3) = 600 \text{ W/(m}\cdot\text{K)}$ . Therefore, aluminium alloy (A5052), pure aluminium (A1100) or pure copper (C1100) may be used for standard rods.

$$0,1k_{\text{eff}} \left( \frac{t_{\text{eff}}}{t_s} \right) < k_r < 4k_{\text{eff}} \left( \frac{t_{\text{reff}}}{t_s} \right) \quad (4)$$

where

$k_{\text{eff}}$  is the effective thermal conductivity of the isotropic electrically conductive adhesive [W/(m·K)];

$k_r$  is the thermal conductivity of the standard rods [W/(m·K)];

$t_{\text{reff}}$  is the effective thickness of the standard rods [= thickness of the portion for temperature measurement in the standard rods (m)];

$t_s$  is the thickness of the isotropic electrically conductive adhesive (m).

**Table 1 — Examples of material for standard rods**

Rod material (mark)	Thermal conductivity of rods $k_r$ (300K), W/(m K)
pure copper (C1100)	398
pure aluminium (A1100)	222
aluminium alloy (A5052)	140
stainless steel (SUS304)	16,0

#### 8.4 Surface roughness and flatness of the contact surface of the standard rods and parallelism of the upper/lower faces

Surface roughness and flatness of the contact surface between the standard rods and the cartridge-type specimen and parallelism of the upper/lower faces are specified as follows:

- for surface roughness of the contact surface, see [7.2 d](#) 1);
- for flatness of the contact surface and parallelism of the upper/lower faces, see [7.2 d](#) 2).

#### 8.5 Boring thermocouple holes through the standard rods

Bore thermocouple holes through the standard rods.

The diameter and depth of thermocouple holes are specified as follows:

- the diameter of each thermocouple hole is within the range of 0,5 mm to 1 mm, allowing a thermocouple to be inserted;
- the depth of each thermocouple hole is not less than 5 mm so that a thermocouple can be inserted to a point as near the centre of the specimen blocks as possible. Taking standard rods with the thickness of 25 mm as an example, bore four 0,8 mm holes at intervals of 5 mm.



## 9 Procedure

### 9.1 Assembly of the cartridge-type specimen and the standard rod

The assembly of a cartridge-type specimen and standard rods is specified as follows.

- a) Place the lower standard rod on the cooling block then place the cartridge-type specimen, the upper standard rod, the heating block, the insulating block, and finally the load cell (see [Figure 1](#)). Next, apply grease or other agent to reduce contact thermal resistance to each contact surface to an extent where its thickness is approximately 100 µm.
- b) To minimize the thermal resistance, apply a pressure of 0,1 MPa or higher using a pressure adjustment screw. Measure the applied force using the load cell installed in the upper part.

### 9.2 Heating or cooling procedure of the cartridge-type specimen and the standard rod

Heating and cooling of the cartridge-type specimen and standard rods are specified as follows.

- a) For cooling the specimen and standard rods, use the cooling equipment to refrigerate the cooling block of the measurement system.
- b) For heating the cartridge-type specimen and the standard rods, use the heating equipment to heat the measurement system. Set a calorific value of the heater so that the following conditions will be met: temperature difference,  $\Delta T_s$ , of the isotropic electrically conductive adhesive in the specimen block will exceed 5 K and temperature difference,  $\Delta T_{\text{reff}}$ , of effective thickness,  $t_{\text{reff}}$ , of the upper and lower standard rods will exceed 5 K (see [Figure 4](#).)

### 9.3 Temperature measurement of the cartridge-type specimen and the standard rods

The temperature measurement of the cartridge-type specimen and the standard rods are specified as follows.

- a) Steady state: the temperature fluctuation of,  $\Delta T_s$ , of the isotropic electrically conductive adhesive not greater than 0,4 K per minute is regarded as the steady state.
- b) Temperature of the isotropic electrically conductive adhesive: the temperature of the isotropic electrically conductive adhesive is defined as the arithmetic mean of the temperatures of the lower and upper ends of the isotropic electrically conductive adhesive that is obtained through the temperature of the specimen block and standard rods.

## 10 Calculation of heat transfer property

### 10.1 Effective thermal conductivity

Calculate effective thermal conductivity of the isotropic electrically conductive adhesive using Formulae (5) to (9).

The temperature gradient of the upper and lower standard rods contained in each formula is obtained from the temperature distribution of the upper and lower standard rods in the steady state (see Figures 3 and 4.). For displaying a calculation result, round off the result to 0,1 [W/(m·K)] in accordance with ISO 80000-1.

$$k_{\text{eff}} = \frac{q_s t_s}{\Delta T_s} \quad (5)$$

$$q_s = (q_1 + q_2) / 2 \quad (6)$$

$$q_1 = -k_r \cdot \left( \frac{dT}{dX} \right)_1 \quad (7)$$

$$q_2 = -k_r \cdot \left( \frac{dT}{dX} \right)_2 \quad (8)$$

$$\Delta T_s = \Delta T_c - \frac{q_s t_b}{k_b} \quad (9)$$

where

$k_{\text{eff}}$  is the effective thermal conductivity of the isotropic electrically conductive adhesive [W/(m·K)];

$k_r$  is the thermal conductivity of standard rods [W/(m·K)];

$k_b$  is the thermal conductivity of the specimen block [W/(m·K)];

$x$  is the distance from the top face of the upper standard rod (m);

$q_s$  is the heat flux in the isotropic electrically conductive adhesive (W/m<sup>2</sup>);

$q_1$  is the heat flux in the upper standard rod (W/m<sup>2</sup>);

$q_2$  is the heat flux in the lower standard rod (W/m<sup>2</sup>);

$(dT/dx)_1$  is the temperature gradient of the upper standard rod (K/m);


$(dT/dx)_2$  is the temperature gradient of the lower standard rod (K/m);

$\Delta T_c$  is the temperature difference of the cartridge-type specimen (K);

$\Delta T_s$  is the temperature difference of the isotropic electrically conductive adhesive (K);

$t_b$  is the thickness of the specimen block (m);


$t_s$  is the thickness of the isotropic electrically conductive adhesive.

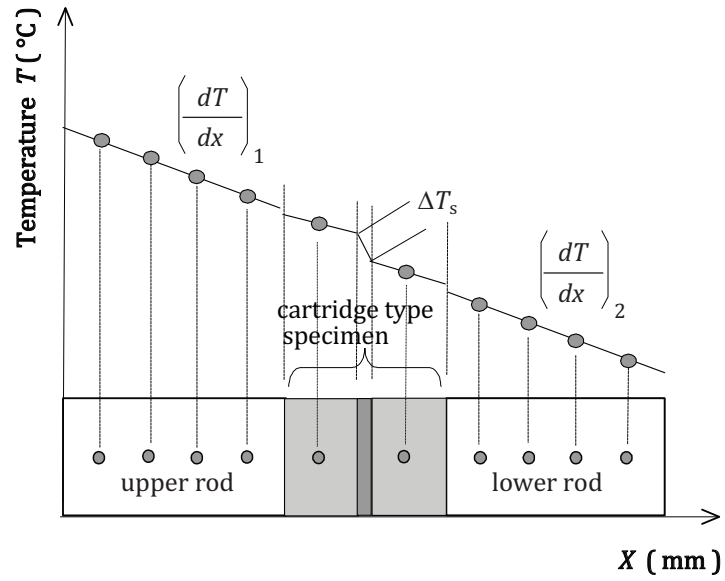

**Key**

- 1 cartridge-type specimen
- 2 lower rod
- 3 upper rod

**Figure 3 — Temperature distribution in the upper/lower standard rods and cartridge-type specimen**

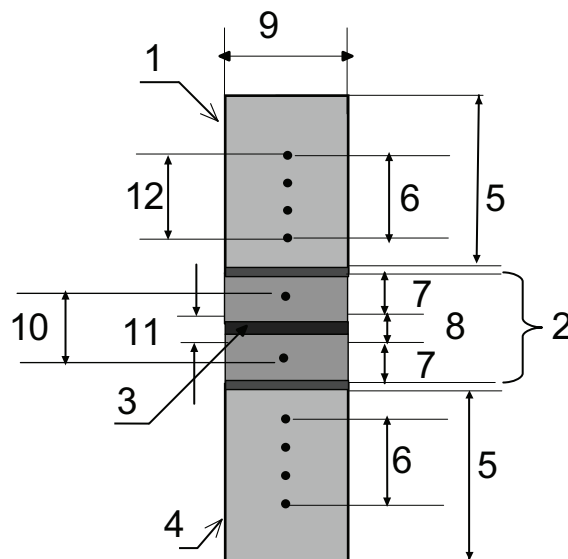

Key			
1	upper rod (thermal conductivity $k_r$ )	7	thickness of the specimen block $t_b$
2	cartridge-type specimen	8	thickness of the isotropic electrically conductive adhesive $t_s$
3	isotropic electrically conductive adhesives (thermal conductivity $k_s$ )	9	width of the rod $W_r$
4	lower rod (thermal conductivity $k_r$ )	10	temperature difference of the cartridge type specimen $\Delta T_c$
5	thickness of the rod $t_r$	11	temperature difference of the isotropic electrically conductive adhesives $\Delta T_s$
6	distance between first hole and fourth hole of the rod $t_{\text{reff}}$	12	temperature difference of the first hole and fourth hole of the rod $\Delta T_{\text{reff}}$

Figure 4 — Meaning of symbols

## 10.2 Thermal resistance

Calculate the thermal resistance,  $R_s$ , between the upper and lower faces of the isotropic electrically conductive adhesive using Formula (10).

$$R_s = \frac{t_s}{k_{\text{eff}}} \quad (10)$$

where

$R_s$  is the thermal resistance between the upper and lower faces of the isotropic electrically conductive adhesive ( $\text{K}\cdot\text{m}^2/\text{W}$ );

$t_s$  is the thickness of the isotropic electrically conductive adhesive (m);

$k_{\text{eff}}$  is the effective thermal conductivity of the isotropic electrically conductive adhesive obtained through Formula (5) [ $\text{W}/(\text{m}\cdot\text{K})$ ].

### 10.3 Thermal conductance

Calculate the thermal conductance,  $K_s$ , between the upper and lower faces of the specimen using Formula (11):

$$K_s = \frac{1}{R_s} \quad (11)$$

where

$K_s$  is the thermal conductance between the upper and lower faces of the isotropic electrically conductive adhesive [ $W/(K \cdot m^2)$ ];

$R_s$  is the thermal conductivity obtained through Formula (10) ( $K \cdot m^2/W$ ).

## 11 Test report

The test report shall contain the following items. Some items may be selected from items b) to j) upon agreement between the delivering and receiving parties:

- a) a reference to this part of ISO 16525, i.e. ISO 16525-3;
- b) type and data of an isotropic electrically conductive adhesive (type of resin, filler material, manufacturer's code number);
- c) assembly procedure of the cartridge-type specimen (curing temperature, setting time, temperature and pressure of the adhesive procedure);
- d) shape of the cartridge-type specimen (the length of the sides, the average thickness of the adhesive layer after curing) and quantity of specimens;
- e) measurement date and measurement organization;
- f) effective thermal conductivity, thermal resistance and thermal conductance;
- g) specimen temperature;
- h) type of standard rod (materials and thermal conductivity);
- i) dimensions of standard rod (the length of the sides and thickness);
- j) calculation conditions of the heat-transfer property (pressure, heat flow rate over a given surface area and temperature distribution).

## Bibliography

- [1] ISO 22007-1, *Plastics — Determination of thermal conductivity and thermal diffusivity — Part 1: General principles*
- [2] ISO 22007-2, *Plastics — Determination of thermal conductivity and thermal diffusivity — Part 2: Transient plane heat source (hot disc) method*
- [3] ISO 22007-3, *Plastics — Determination of thermal conductivity and thermal diffusivity — Part 3: Temperature wave analysis method*
- [4] ISO 22007-4, *Plastics — Determination of thermal conductivity and thermal diffusivity — Part 4: Laser flash method*
- [5] ASTM D5470-01, *Standard Test Method for Thermal Transmission Properties of Thin Thermally Conductive Solid Electrical Insulation Materials*









# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™