

BS ISO 16574:2015



BSI Standards Publication

Determination of percentage of resolvable pearlite in high carbon steel wire rod

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 16574:2015.

The UK participation in its preparation was entrusted to Technical Committee ISE/101/7, Methods of physical and metallographic testing.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015.

Published by BSI Standards Limited 2015

ISBN 978 0 580 80113 6

ICS 77.040.99

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 September 2015.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

**Determination of percentage of
resolvable pearlite in high carbon
steel wire rod**

*Détermination du pourcentage de perlite résoluble dans les fils
machine en acier à haut carbone*





COPYRIGHT PROTECTED DOCUMENT

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Symbols and abbreviated terms	1
5 Principle	2
6 Selection and preparation of samples	2
6.1 Test location	2
6.2 Grinding and polishing.....	2
6.3 Etching	2
7 Evaluation of the percentage of resolvable pearlite	3
7.1 Parameters of optical microscope.....	3
7.2 Determination of measuring field of view.....	3
7.2.1 Determination of measuring locations.....	3
7.3 Measuring methods	4
7.3.1 Manual point count method.....	4
7.3.2 Automatic image analysis method.....	4
7.4 Reporting of results	4
Bibliography	5

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 17, *Steel*, Subcommittee SC 7, *Methods of testing (other than mechanical tests and chemical analysis)*.

Introduction

This test method produces an estimate of the percentage of pearlite resolvable at 500x magnification in wire rod as a function of the cooling method after hot rolling to rod. The drawability of high-carbon pearlitic rod is influenced by the amount of resolvable pearlite present. As the percentage of resolvable pearlite increases, drawability decreases. The methods are used to check if the content of resolvable pearlite can fulfil the requirement of the wire rod with improved characteristics intended for drawing.

Determination of percentage of resolvable pearlite in high carbon steel wire rod

1 Scope

This International Standard defines resolvable pearlite and specifies two methods of determining the percentage of resolvable pearlite.

The methods are applicable for wire rod made from control cooling steel with carbon content greater than 0,65 % C.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 9042, *Steels — Manual point counting method for statistically estimating the volume fraction of a constituent with a point grid*

ISO 16120-1, *Non-alloy steel wire rod for conversion to wire — Part 1: General requirements*

3 Terms and definitions

For the purpose of this document, the terms and definitions given in ISO 9042 and ISO 16120-1 apply.

4 Symbols and abbreviated terms

The symbols and corresponding designations are given in [Table 1](#).

Table 1 — Symbols and designations

Symbol	Designation
O_1	the 1st measuring location
O_2	the 2nd measuring location
O_3	the 3rd measuring location
O_4	the 4th measuring location
O_i	the i^{th} measuring location, $i = 1, 2, 3$ and 4
S_{i1}	percentage of resolvable pearlite in the first field of view of the O_i measuring location
S_{i2}	percentage of resolvable pearlite in the second field of view of the O_i measuring location
S_{i3}	percentage of resolvable pearlite in the third field of view of the O_i measuring location
\bar{S}	average percentage of resolvable pearlite in the cross-section of wire rod

5 Principle

5.1 This International Standard defines resolvable pearlite as pearlite where the ferrite and iron carbide lamellae can be observed at 500x magnification under optical microscopy with 0,8 or higher numerical aperture. The light source shall typically be white light, but another light source can be used.

5.2 Resolvable pearlite is revealed by chemical etching of a polished section of the wire rod using an appropriate etchant. The choice of etchant shall refer to [6.3](#).

5.3 This International Standard specifies two methods of measuring the percentage of resolvable pearlite: manual point count method and automatic image analysis method.

5.3.1 The manual point count method: a grid with a number of regularly arrayed points, which can be a clear plastic test grid or eyepiece reticule, is superimposed over the image, or a projection of the image, produced by a light microscope, and the number of points falling within the constituent of interest are counted and divided by the total number of grid points yielding a point fraction, usually expressed as a percentage, for that field.

5.3.2 Automatic image analysis method: constituents with different microstructure are separated by grey-level intensity differences; for example, pearlites with smaller width between ferrite and iron carbide lamellae are darker than pearlites with bigger width. Thus, the measurement of the content of different constituents can be made on each field by the image analyser on the nature of the discriminated picture point elements in the image.

5.3.3 In case of a dispute, manual point count method shall be the referee method.

6 Selection and preparation of samples

6.1 Test location

If the order, or the International Standard defining the product, does not specify the number of specimens and the point at which they are to be taken from the product, these are left to the manufacturer. It is recommended that two or more sections be assessed. Care shall be taken to ensure that the specimens are representative of the bulk of the product.

Unless otherwise stated by the product standard or by agreement with the customer, the polished face of the specimen shall be transversal.

6.2 Grinding and polishing

The specimens should be prepared metallographically using a well-conceived method, starting with sectioning with a device that imparts minimal damage, mounting with a good resin with either a hot compression mounting press or cast resins, followed by an appropriate sequence of grinding and polishing steps, finishing with an abrasive of at least 1 μm , to yield a flat surface with minimal preparation-induced damage. After polishing, the specimen should be carefully washed with water, cleaned with alcohol and finally dried.

6.3 Etching

The following two etchants are recommended:

- a) a picral etchant, which is a solution of 4 g of picric acid in 100 ml of ethanol;
- b) a nital etchant, which is a solution of a 2 ml of nitric acid ($\rho_{20} = 1,33 \text{ g/ml}$) in 100 ml of ethanol.

NOTE Nital is orientation sensitive and can reveal the pearlite in different colonies in different contrast. Picral can reveal pearlite uniformly and can be superior to nital for most high carbon wire rod.

The polished surface is etched at ambient temperature in the etching solution for a minimum of 10 s or until the surface is etched clearly.

After etching, wash the specimen under a stream of lukewarm water to stop the etching reaction and to remove the etchant from the surface. Then, squirt ethanol onto the surface to displace the water and dry the specimen using either clean compressed air or a flow of hot air from a device similar to a hair dryer or a hand dryer. If bleed out occurs during drying, it may be necessary to clean the mounted specimen in an ultrasonic cleaner.

7 Evaluation of the percentage of resolvable pearlite

7.1 Parameters of optical microscope

The etched surface shall be observed with an optical microscope using the following conditions:

- magnification: 500x;
- numerical aperture: 0,8 or higher;
- light source: white or another light source.

7.2 Determination of measuring field of view

7.2.1 Determination of measuring locations

The measuring locations of the cross-section of wire rod are defined as the following. Four measuring locations, which are designated as O_1 , O_2 , O_3 and O_4 , are equally spaced in the circle being $D/4$ away from the centre of wire rod (mid-radius, as shown in [Figure 1](#)).

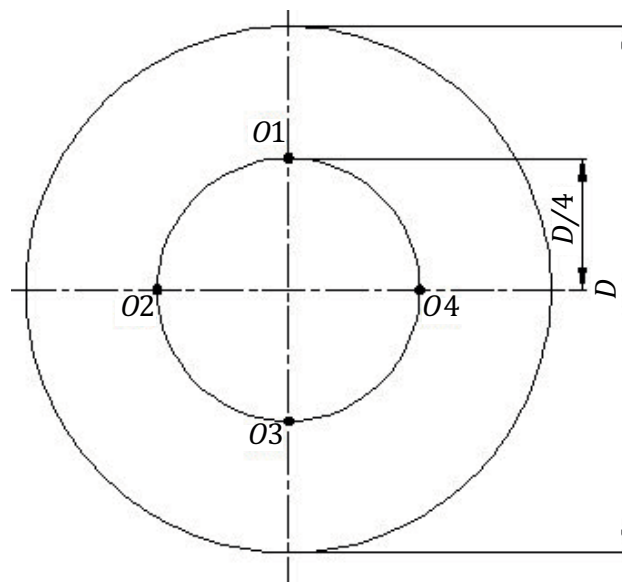


Figure 1 — The schematic diagram of measuring locations

7.2.2 Determination of measuring fields of view

On each measuring locations O_i ($i = 1, 2, 3$ and 4), three continuous fields of view are taken to measure the percentage of resolvable pearlite and recorded as S_{i1} , S_{i2} , S_{i3} .

7.3 Measuring methods

7.3.1 Manual point count method

At each measuring location O_i ($i=1, 2, 3$ and 4) (see [Figure 1](#)), at least three continuous fields of view are taken to measure the percentage of resolvable pearlite in accordance with ISO 9042 and recorded as Si_1, Si_2, Si_3 . The percentage of resolvable pearlite of the whole cross-section of the wire rod, \bar{S} , is the average value of total 12 individual measurements.

7.3.2 Automatic image analysis method

At each measuring location O_i (see [Figure 1](#)), at least three continuous fields of view are taken. The metallographic microstructure photos have to be clearly shown on the image analyser. The brightness has to be adjusted in order to covering all the measured phase. The measurements are made on each field of view selected. Si_1, Si_2 and Si_3 are obtained from the first three fields of view, respectively. The percentage of resolvable pearlite of the whole cross-section of the wire rod, \bar{S} , is the average value of total 12 individual measurements.

7.4 Reporting of results

The report shall include at least the following information unless otherwise agreed by the parties concerned:

- a) the steel grade examined, heat number, rod diameter, test locations and number;
- b) the magnification, numerical aperture, type of light and etchant used;
- c) the measuring method used;
- d) the result of the test (the average percentage of resolvable pearlite examined and the standard deviation).

Bibliography

- [1] GB 13298, *Metal-Inspection method of microstructure*
- [2] ASTM E3, *Standard guide for preparation of metallographic specimens*
- [3] ASTM E407, *Standard practice for microetching metals and alloys*
- [4] VANDER VOORT G.F. etc., Measurement of interlamellar spacing of pearlite. *Metallography*. 1984, **17** pp. 1-17

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™