



BSI Standards Publication

Textiles — Test method for assessing the matting appearance of napped fabrics after cleansing

National foreword

This British Standard is the UK implementation of ISO 16847:2016.

The UK participation in its preparation was entrusted to Technical Committee TCI/82, Textiles care labelling, dry cleaning, domestic laundering and drying.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.
Published by BSI Standards Limited 2016

ISBN 978 0 580 88922 6

ICS 59.080.30

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 December 2016.

Amendments/Corrigenda issued since publication

Date	Text affected
------	---------------

**Textiles — Test method for assessing
the matting appearance of napped
fabrics after cleansing**

*Textiles — Méthode d'essai pour l'évaluation de l'aspect du
moutonnement des étoffes grattées après nettoyage*



COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
6 Test specimens	3
7 Procedure	3
8 Expression of results	4
9 Test report	4

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 38, *Textiles*, Subcommittee SC 2, *Cleansing, finishing and water resistance tests*.

Introduction

With use, the surface of napped fabrics changes significantly. This change in appearance, known as matting, is more or less severe and is related to the fibre, fabric or finishing characteristics.

Based on the structure of other ISO standards dealing with the change in appearance after cleansing, this document has been elaborated to solve this situation.

Textiles — Test method for assessing the matting appearance of napped fabrics after cleansing

1 Scope

This document specifies a method for assessing the matting appearance of the napped fabrics (fleece fabrics) tested, after one or several cleansing treatments.

This method has been developed for use primarily with Type B domestic washing machines, as defined in ISO 6330, in the cleansing process. However, it is possible to use it with Type A machines, as defined in ISO 6330. This test method can be used for judging matting appearance after other cleansing processes.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 105-A03, *Textiles — Tests for colour fastness — Part A03: Grey scale for assessing staining*

ISO 139, *Textiles — Standard atmospheres for conditioning and testing*

ISO 3175 (all parts), *Textiles — Professional care, drycleaning and wetcleaning of fabrics and garments*

ISO 6330, *Textiles — Domestic washing and drying procedures for textile testing*

ISO 15797, *Textiles — Industrial washing and finishing procedures for testing of workwear*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp/ui/>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

matting

disorientation of the raised fibres of a napped fabric, which produces a visible surface change

Note 1 to entry: See Figure 1.

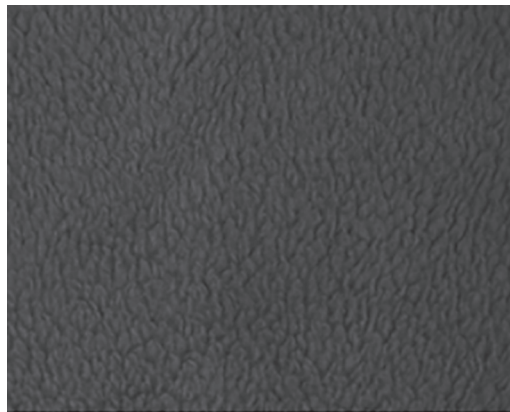


Figure 1 — Example of matting appearance of napped fabric

4 Principle

Fabric specimens are subjected to procedures simulating cleansing practices. One of the domestic washing and drying procedures specified in ISO 6330, one of the professional procedures specified in the series of ISO 3175 or one of the industrial procedures as specified in ISO 15797 is used, as agreed between the interested parties. If the interested parties decide that other cleansing processes are to be used, this fact shall be reported.

5 Apparatus

5.1 Washing and drying apparatus, as specified in ISO 6330, professional care apparatus, as specified in ISO 3175 or industrial laundering apparatus as specified in ISO 15797.

5.2 Lighting.


The evaluation area shall be a darkened room, using the overhead lighting arrangement shown in Figure 2 and comprising the following items. Lamp dimensions should be chosen to extend beyond the overall surface of a test specimen and replicas, when used for the assessment.

5.2.1 Two CW (cool white) fluorescent lamps, placed side by side, without baffle or glass, a minimum of 2 m in length each.

5.2.2 One white enamel reflector, without baffle or glass.

5.2.3 One specimen holder.

5.2.4 One thick plywood viewing board, painted grey to match the grade 2 on the grey scale for assessing staining specified in ISO 105-A03.

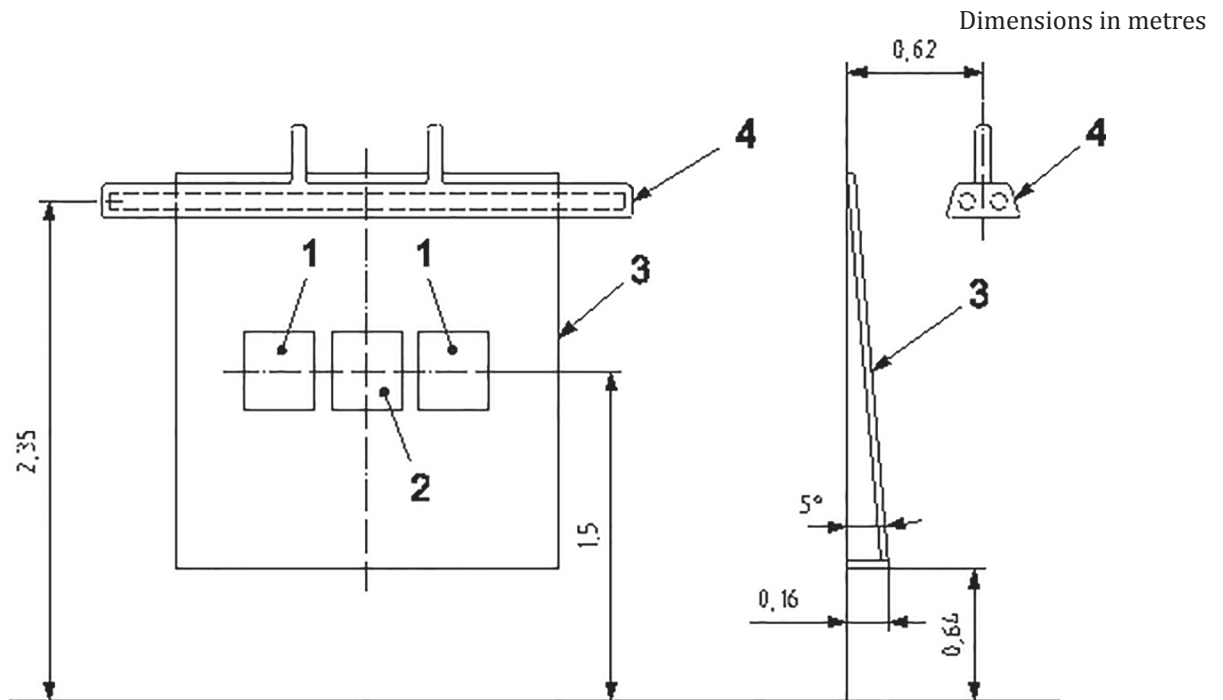

Key

- 1 replica
- 2 test specimen
- 3 board for viewing
- 4 example of fluorescent lamp placement

Figure 2 — Lighting equipment for viewing test specimens

6 Test specimens

Prepare three test specimens, each measuring 38 cm x 38 cm, cut parallel to the length direction, pinked to prevent fraying and marked to indicate the length direction.

If the matting appearance shall be assessed on both faces, mark the front face.

7 Procedure

7.1 Treat each specimen according to one of the cleansing procedures specified in ISO 6330, ISO 3175 or ISO 15797, as agreed between the interested parties.

7.2 If required, repeat the selected treatment four times, to give a total of five cycles (one cycle consists of one washing and one drying).

7.3 Condition the test specimens in the standard atmosphere according to ISO 139 for a minimum of 4 h by hanging each specimen unfolded with the length direction vertical to avoid distortion.

7.4 For the evaluation, carry out steps 7.5 to 7.11.

7.5 Three observers shall rate each treated test specimen independently.

7.6 Mount the test specimen on the viewing board (5.2.4) as illustrated in Figure 2, with the length direction vertical. If the matting appearance shall be assessed on both faces, proceed to 7.6 to 7.11 with the marked front faces, and then repeat 7.6 to 7.11 with the other faces.

7.7 The overhead fluorescent light (5.2.1) shall be the only light source for the viewing board, and all other lights in the room shall be turned off. It has been the experience of many observers that the light reflected from the side walls near the viewing board can interfere with the rating results. It is recommended that the side walls be painted black or that blackout curtains be mounted on either side of the viewing board to eliminate the reflective interference.

7.8 The observer shall stand directly in front of the specimen, 1,2 m away from the board. It has been found that normal variations in the height of the observer above and below the arbitrary 1,5 m eye level have no significant effect on the rating given.

7.9 Assign the number of the grade which most nearly matches the appearance of the test specimen, or assign ratings midway between those whole-number standards which have no half-number standards separating them if the appearance of the specimens warrants it (see Table 1).

7.10 A 5 rating represents the best retention of original appearance, while a 1 rating represents the poorest retention of original appearance.

7.11 Similarly, the observer shall independently rate each of the other two test specimens. The other two observers shall proceed in the same manner, assigning ratings independently.

Table 1 — Matting grading scheme

Grade	Description
5	No change
4	Slight surface matting
3	Moderate surface matting
2	Distinct surface matting
1	Dense surface matting

8 Expression of results

Calculate the median of the nine observations made by the three observers on the set of three test specimens for the concerned face. Report the median to the nearest half rating.

9 Test report

The test report shall include the following information:

- a) a reference to this International Standard (ISO 16847:2016);
- b) details of the sample evaluated;
- c) details of the cleansing procedures used;
- d) the number of cleansing cycles used;
- e) for each concerned face, the fabric matting rating as calculated according to Clause 8 associated to the description as stated in Table 1;
- f) details of any deviation from the specified procedure.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK