

BS ISO 17139:2014



BSI Standards Publication

# Fine ceramics (advanced ceramics, advanced technical ceramics) — Thermophysical properties of ceramic composites — Determination of thermal expansion

**bsi.**

...making excellence a habit.™

### **National foreword**

This British Standard is the UK implementation of ISO 17139:2014.

The UK participation in its preparation was entrusted to Technical Committee RPI/13, Advanced technical ceramics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 77171 2

ICS 81.060.30

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 June 2014.

### **Amendments issued since publication**

Date	Text affected
------	---------------

---

INTERNATIONAL  
STANDARD

**ISO**  
**17139**

First edition  
2014-06-15

---

---

**Fine ceramics (advanced ceramics,  
advanced technical ceramics) —  
Thermophysical properties of ceramic  
composites — Determination of  
thermal expansion**

*Céramiques techniques — Propriétés thermophysiques des composites  
céramiques — Détermination de la dilatation thermique*



Reference number  
ISO 17139:2014(E)



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>2</b>
4.1 General.....	2
4.2 Direct measurement.....	2
4.3 Differential method.....	2
<b>5 Apparatus</b> .....	<b>2</b>
5.1 Construction materials.....	2
5.2 Heating and cooling device.....	2
5.3 Temperature measurement.....	2
5.4 Test piece mounting.....	2
5.5 System for measuring and recording the thermal expansion.....	3
5.6 Test piece measurement.....	3
<b>6 Specimens</b> .....	<b>3</b>
6.1 Test pieces.....	3
6.2 Reference pieces.....	3
6.3 Dimensions.....	3
<b>7 Procedure</b> .....	<b>4</b>
<b>8 Calculations</b> .....	<b>5</b>
8.1 Direct measurement.....	5
8.2 Differential method.....	5
<b>9 Test report</b> .....	<b>6</b>
<b>Annex A (normative) Direct measurement apparatus</b> .....	<b>9</b>
<b>Annex B (normative) Differential type measurement apparatus</b> .....	<b>11</b>
<b>Bibliography</b> .....	<b>12</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 206, *Fine ceramics*.

# Fine ceramics (advanced ceramics, advanced technical ceramics) — Thermophysical properties of ceramic composites — Determination of thermal expansion

## 1 Scope

This International Standard describes methods for the determination of linear thermal expansion characteristics of ceramic matrix composite materials up to 2 300 K, and is applicable to 1D, 2D, and nD materials.

The method describes general principles of construction, calibration, and operation of the equipment.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO/IEC 17025, *General requirements for the competence of testing and calibration laboratories*

IEC 60584-1, *Thermocouples — Part 1: Reference tables*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### **linear thermal expansion**

positive or negative change in one dimension that occurs when a material is subjected to a change in temperature

### 3.2

#### **linear thermal expansion coefficient at temperature $T$**

derivative of the length  $L$  with respect to temperature at the temperature  $T$ , divided by the length at temperature  $T$

$$\alpha_T = \frac{1}{L} \left( \frac{dL}{dT} \right)$$

### 3.3

#### **mean linear thermal expansion coefficient between temperatures $T_1$ and $T_2$**

linear thermal expansion between temperatures  $T_1$  and  $T_2$  divided by the temperature increment  $T_1$  to  $T_2$  and the length at temperature  $T_1$

$$\alpha(T_1, T_2) = \frac{L(T_2) - L(T_1)}{L(T_1)} \times \frac{1}{(T_2 - T_1)}$$

### 3.4

#### **representative volume element**

#### **RVE**

minimum volume which is representative of the material considered

## 4 Principle

### 4.1 General

A test piece is heated and subsequently cooled, either at a specified uniform rate or using defined temperature increments. Its change of length and its temperature are measured continuously, or at regular frequent intervals during the imposed temperature cycle.

One of two methods can be used to determine the linear thermal expansion coefficient, either by direct measurement or by a differential method.

### 4.2 Direct measurement

In this method, the variation in length of the test piece is measured directly. It is necessary to know the change in dimensions of the test piece support system by previous calibration.

The test piece is placed in a specimen holder and is made to contact a displacement transducer by using a push rod, made of the same material as the holder. This assembly is put in a furnace. The differential expansion between the test piece and the test piece holder is measured during the increase and the decrease in temperature.

The apparatus is shown in [Figure 1](#).

### 4.3 Differential method

This method consists of measuring the changes in length between a reference piece ([6.2](#)) and the test piece. It is not therefore necessary to know the change in dimensions of the test piece support system.

The apparatus is shown in [Figure 2](#).

## 5 Apparatus

### 5.1 Construction materials

The test piece holder and the push rod shall be made from thermomechanically stable materials of the same type, which shall be chemically inert and thermally compatible with the test piece material under the environmental conditions of the test.

NOTE For temperatures above 1 400 °C, it is necessary to employ a vacuum or inert gas atmosphere, with a non-oxide material appropriate for the test environment, such as a grade of dense graphite.

### 5.2 Heating and cooling device

Furnace, capable of working in a controlled atmosphere when required, and of controlling the temperature of the test piece to within 1 % of its mean temperature, expressed in K.

### 5.3 Temperature measurement

Thermocouples, in accordance with IEC 60584-1, subject to the upper temperature requirements and environmental consideration, except for tungsten-rhenium couples which may be used at higher temperatures but are not covered by IEC 60584-1, should be individually calibrated. For temperature in excess of 2 000 K, infrared detectors or any suitable device may be used.

### 5.4 Test piece mounting

The device used shall allow free axial movement of the test piece and of the reference piece in case of differential measurement. The mechanical environment shall minimize stresses. For vertical



measurement apparatus, the test pieces shall be free standing and mechanically stable on the end-plate. For measuring apparatus which is horizontal or inclined to the horizontal, the sideways movement or twist of the test piece shall be restricted, without any restriction of axial movement, by a suitable arrangement.

## 5.5 System for measuring and recording the thermal expansion

System, capable of measuring displacements to an accuracy better than 0,1  $\mu\text{m}$ . The system shall allow recording of the test piece temperature and the displacement simultaneously. The system for measuring of displacements shall be periodically calibrated in accordance with [Annex A](#) for direct measurement or [Annex B](#) for differential measurement.

## 5.6 Test piece measurement

Device for measuring the test piece dimensions, with an accuracy better than 0,05 mm (e.g. micrometer in accordance with ISO 3611 or callipers in accordance with ISO 6906).

# 6 Specimens

## 6.1 Test pieces

The dimensions of the test pieces depend on the type of apparatus used. For differential measurements, the test piece and the reference piece ([6.2](#)) shall have the same length  $L_0$  (see [Table 1](#)).

The test piece shall be cut in such a way that the axis of desired measurement is related to the principal fibre orientations in accordance with agreement between parties to the measurement.

The end-faces of the length of the test piece shall be plane, parallel to each other, and perpendicular to the long axis.

## 6.2 Reference pieces

Reference materials shall be chosen so that their properties are as close as possible to the properties of the material to be tested. The reference piece shall have a volume of the same order and, if possible, shall have the same dimensions as the test piece (see [Table 1](#)).

For measurement at high temperature (over 2 000 K) under inert atmosphere, reference materials generally used are either tungsten or highly purified graphite. Reference materials shall be procured from a certified laboratory.

## 6.3 Dimensions

See [Table 1](#).

**Table 1 — Recommended test piece dimensions**

Dimensions in millimetres

	Material with small RVE (3.4) such as 1D or 2D	Material with large RVE (3.4) such as nD ( $n \geq 3$ )	Tolerances
$L_0$ , total length	30	70	$\pm 0,2$
B, width	7	Depending on material and equipment	—
h, thickness	Depending on material and equipment	Depending on material and equipment	Depending on material and equipment
$\phi$ , diameter	-	30	—
Parallelism	$\pm 0,01$	$\pm 0,01$	—

A test piece volume of a minimum of 5 RVE (3.4) is recommended.

The shape and dimensions of the test piece depend on the structure of reinforcement. In the case of material such as 3D, a large test piece is often necessary when the representative volume element is important.

For nD ( $n \geq 3$ ) composites with large RVE, thick beam specimens or cylinders with diameter  $\phi$  are recommended.

If dimensions different from the recommended ones are used, specimen volume shall be larger than 5 RVE. Tolerances: dimensions:  $\pm 0,2$  - Parallelism:  $\pm 0,05$ .

## 7 Procedure

In order to simplify calibration procedures, test pieces and reference pieces of the same length should be used. If reference and test pieces have different lengths, then it is necessary to take into account a base line shift. In this case, refer to EN 821-1.

- Measure the original length of the test piece at room temperature with devices (5.6).  
 The accuracy shall be better than
  - 0,05 mm for length of 10 mm and above, and
  - 0,02 mm for length lower than 10 mm.
- Make sure that the equipment has been calibrated for the type of material prior to the test, according to the procedure described in Annex A for direct measurement [determination of  $S$  and  $\bar{\alpha}(A)$ ], and in Annex B for differential measurement ( $S$  and  $\delta$ ).
- Introduce the test piece in test system and provide a good contact between the push rod and the test piece. The force to apply on the specimen depends on the test system and material, but values lower than 1 N are generally sufficient.
- Proceed with heating or cooling at a rate of between 1 K/min and 5 K/min, ensuring a fairly constant temperature gradient along the test piece. If the temperature is changed by steps, the hold temperature shall be maintained until the length of the test piece shows no change for at least 5 min before the measure.
- Record temperature  $T$  and displacement  $\Delta x$ .

In case of large test pieces, a stepwise temperature rise is recommended.

The mean linear thermal expansion coefficient shall be calculated as the average from the results of tests on three test pieces.

Push rod for test should not have any reaction with the test piece and the reference.

## 8 Calculations

### 8.1 Direct measurement

Calculate the change in length,  $\Delta l$ , of a length of the sample holder material equal to the original test piece length  $L_0$ , from Formula (1):

$$\Delta l = L_0 \bar{\alpha}_A (T_2 - T_1) \quad (1)$$

using the calculated value of  $\Delta l$ , the change in length of  $\Delta L$  of the specimen is obtained from the measured displacement  $S\Delta x$ :

$$\Delta L = S\Delta x + \Delta l \quad (2)$$

Calculate the mean linear thermal expansion coefficient of the test piece material from Formula (3):

$$\bar{\alpha} = \frac{\Delta L}{L_0 (T_2 - T_1)} \quad (3)$$

where

- $\bar{\alpha}$  is the mean linear thermal expansion coefficient of the test piece material, in K<sup>-1</sup>;
- $\bar{\alpha}_A$  is the mean linear thermal expansion coefficient correction for the apparatus over the temperature range used. It is determined from calibration (see [Annex A](#));
- $L_0$  is the initial length of the test piece at room temperature, in mm;
- $\Delta x$  is the recorded displacement (in mm, volt, etc.) over the temperature range;
- $S$  is the measurement sensitivity of the displacement recording system;
- $\Delta l$  is the change in length of the sample holder material, in mm;
- $\Delta L$  is the change in length of the test piece, in mm;
- $T_2 - T_1$  is the temperature interval in K for which the change in length is measured.

A curve of  $\frac{\Delta L}{L_0}$  versus  $T$  may be constructed.

### 8.2 Differential method

Calculate the mean linear thermal expansion coefficient of the test piece material from Formula (4):

$$\bar{\alpha} = \frac{S\Delta x - \delta}{L_0 (T_2 - T_1)} + \bar{\alpha}(R) \times \frac{L(R)}{L_0} \quad (4)$$

where


- $\delta$  is the baseline correction over the temperature range, which is introduced because of the possibility of unequal response from the two pushrods;
- $L(R)$  is the initial reference piece length at room temperature, in mm;
- $\bar{\alpha}(R)$  is the mean linear thermal expansion coefficient of the reference piece, in K<sup>-1</sup>.

Other terms are as in [8.1](#).

## 9 Test report

The results shall be reported in accordance with ISO/IEC 17025 and the test report shall include the following information:


- a) the name of the testing establishment;
- b) the date of the test; a unique identification of the report and on each page, the name and address of the customer, and a signatory of the report;
- c) a reference to this International Standard, i.e. "Determined in accordance with ISO 17139";
- d) general description of the method used, i.e. Direct or Differential (see [Clause 4](#));
- e) method of calibration;
- f) description of the test piece: dimensions, preparation method, orientation, mass, volume;
- g) thermal cycle(s), number of hold periods, time at hold periods, and temperature interval between holds;
- h) maximum temperature testing;
- i) testing atmosphere;
- j) hysteresis between the heating and cooling cycle for materials which show a repeatable behaviour;
- k) indication of the thermal cycles carried out on the test piece prior to the measurement;
- l) table of the mean linear thermal expansion coefficient at the temperature required;
- m) any features identifiable as phase changes or softening under load of the measuring device;
- n) all other relevant information and all incidents that can affect the results, including comments on the test or test results.

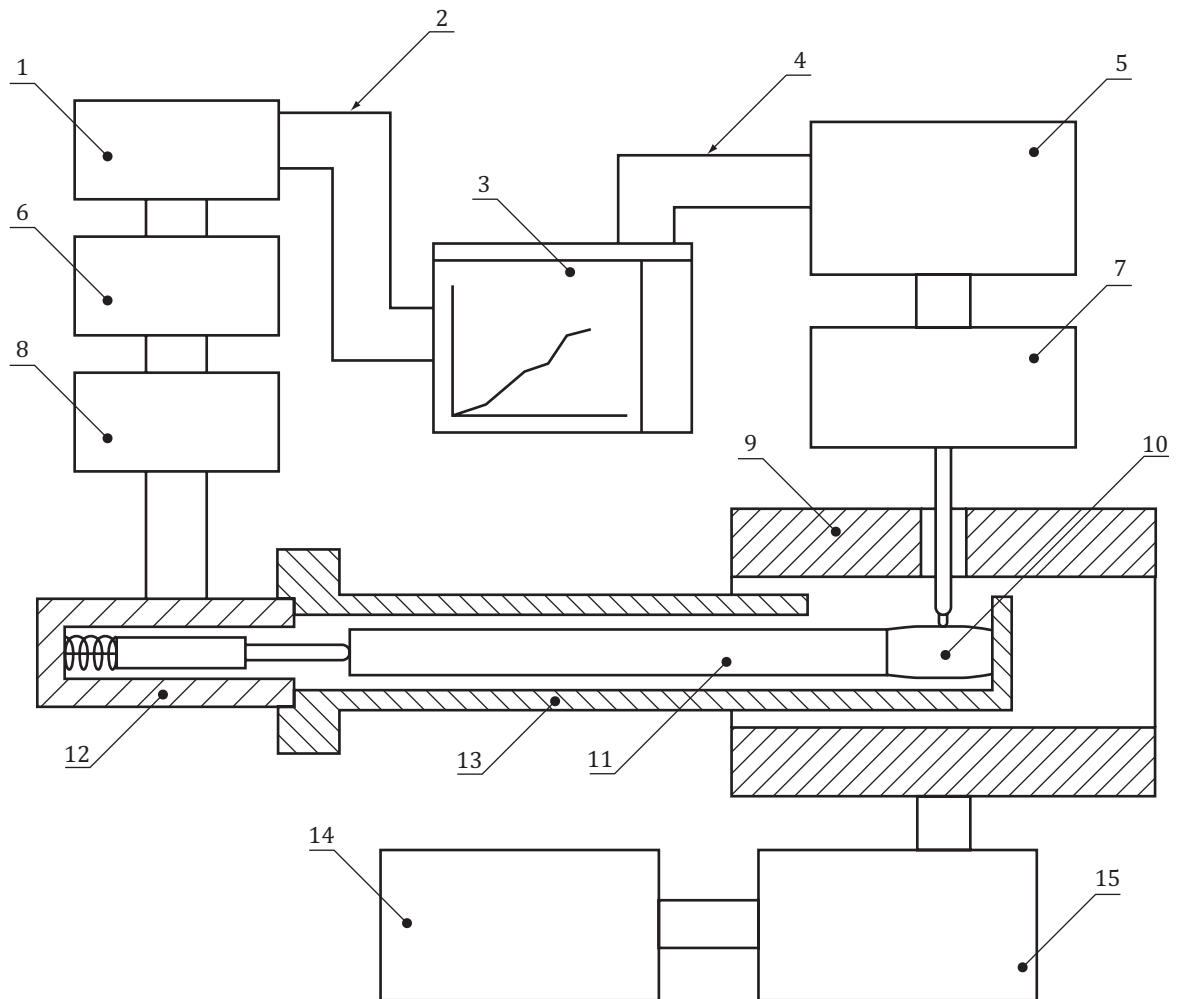

**Key**

- |                       |  |
|-----------------------|--|
| 1 expansion ranging   | 9 furnace  |
| 2 y-axis              | 10 sample  |
| 3 X-Y recorder        | 11 push rod  |
| 4 x-axis              | 12 linear variable differential transformer (LVDT) |
| 5 temperature ranging | 13 sample holder                                   |
| 6 correction factor   | 14 programmer                                      |
| 7 0 °C reference      | 15 furnace power control                           |
| 8 expansion amplifier |  |

**Figure 1 — Schematic of a direct measurement system**

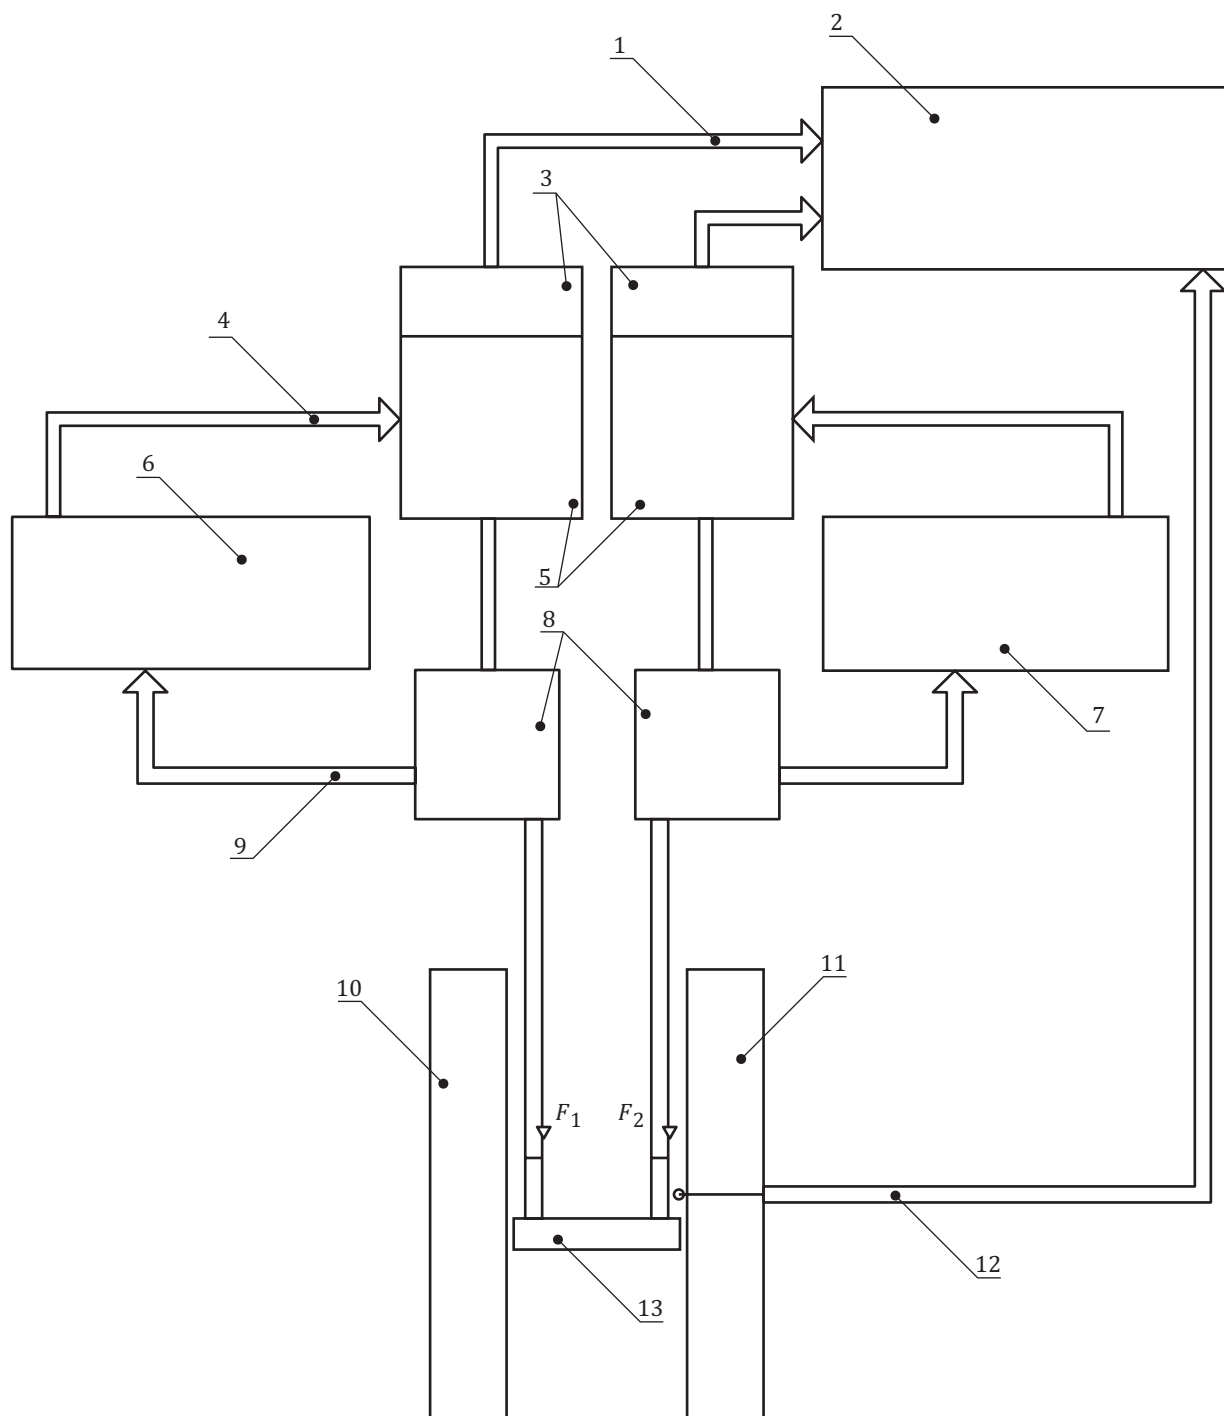

**Key**

- |   |                            |
|---|----------------------------|
| 1 displacement measurement  | 8 strength transducer      |
| 2 data treatment (analog or digital)                                  | 9 strength measurement     |
| 3 encoders  | 10 sample                  |
| 4 displacement signal   | 11 reference               |
| 5 displacement modules  | 12 temperature measurement |
| 6 control in order to have $F_1 = C_1$ ( $C_1 =$ adjustable constant) | 13 furnace                 |
| 7 control in order to have $F_2 = C_2$ ( $C_2 =$ adjustable constant) |                            |

**Figure 2 — Schematic of a differential measurement system**

## Annex A (normative)

### Direct measurement apparatus

#### A.1 Determination of measurement sensitivity

The sensitivity of the measurement device,  $S$ , requires to be calibrated if it is not based on a direct-reading dial gauge or micrometer. This can be done either by using direct mechanical movement produced by using a certified micrometer of sufficient accuracy, or by use of two certified thermal expansion reference materials as test pieces.

Calibration tests shall be made for mechanical movement in both directions, and then the mean value of sensitivity taken. Calibration should take place in the same environment and at the same heating rate as the measurements on the test piece. Any nonlinearity shall be reported, and the apparatus shall be calibrated over the same range of displacement as that to be used for any series of tests.

NOTE This procedure applies to linear displacement transducer measuring devices in particular.

When two certified thermal expansion reference materials are available, the sensitivity is determined using Formula (A.1):

$$\bar{\alpha} = \frac{S\Delta x}{L_0\Delta T} + \bar{\alpha}_A \quad (\text{A.1})$$

for the two materials:

$$\bar{\alpha}_1 = \frac{S\Delta x_1}{L_0\Delta T} + \bar{\alpha}_A \quad (\text{A.2})$$

$$\bar{\alpha}_2 = \frac{S\Delta x_2}{L_0\Delta T} + \bar{\alpha}_A \quad (\text{A.3})$$

and by subtracting:

$$S = \frac{(\bar{\alpha}_1 - \bar{\alpha}_2)L_0\Delta T}{\Delta x_1 - \Delta x_2} \quad (\text{A.4})$$

where

$\bar{\alpha}_1$  and  $\bar{\alpha}_2$  are the mean thermal expansion coefficients of the two reference materials over the temperature range  $\Delta T$ ;

$L_0$  is the initial length, in mm, of the two reference pieces at room temperature;

$\Delta x_1, \Delta x_2$  are the recorded displacements (in mm, volts...) over the temperature range  $\Delta T$ ;

$\Delta T$  is the temperature interval for which the changes in length are measured;

$S$  is the measured sensitivity of the displacement recording system;

$\bar{\alpha}_A$  is the mean thermal expansion coefficient correction for the apparatus.

#### A.2 Determination of $\bar{\alpha}_A$

$$\bar{\alpha}_A = \bar{\alpha}(R) - \frac{S\Delta x}{L_0\Delta T} \quad (\text{A.5})$$

where

- $\bar{\alpha}_A$  is the mean linear thermal expansion coefficient correction for the apparatus over the temperature range used;
- $\bar{\alpha}(R)$  is the mean linear thermal expansion coefficient of the reference piece material;
- $\Delta x$  is the recorded displacement (in mm, volts, etc.) over the temperature range  $\Delta T$ ;
- $S$  is the measurement sensitivity of the displacement recording system;
- $L_0$  is the initial length of the test piece, in mm;
- $\Delta T$  is the temperature range, in K, over which the change in length is measured.

The mean linear thermal expansion coefficient  $\bar{\alpha}_A$  is obtained by using a certified reference material of similar thermal expansion to that of the material of the test piece holder and the push rod, and carrying out measurement in accordance with the procedure given in [Clause 7](#). The value of  $\bar{\alpha}_A$  is obtained by inserting calibrated and experimental data for the reference material in Formula (A.5).

The calibrated reference piece is certified by approved organizations. The dimensions of the test piece to be measured and of the reference piece are identical within machining tolerances.

The physical properties of the material to be measured and the reference material (thermal expansion coefficient, thermal conductivity, emissivity) should be as close as possible. Measurements on the reference material and on the specimen should be performed under identical experimental conditions: type of environment, measuring kinetics, material for the specimen holder, temperature measurement device.



## Annex B (normative)

### Differential type measurement apparatus

#### B.1 Determination of measurement sensitivity, $S$

Because of the differences between the differential dilatometers which can be used, the manufacturer's instructions should be referred to for the determination of measurement sensitivity.

#### B.2 Determination of $\delta$

The calibration is carried out with two reference test pieces, one having significantly different thermal expansion characteristics from the other.

The recorded displacement corresponds to the difference in expansion:

$$S\Delta x_1 = (L_0\bar{\alpha}_1 - L_0\bar{\alpha}_2)\Delta T + \delta \quad (\text{B.1})$$

By exchanging the positions of the reference pieces and by carrying a new cycle, the displacement is now:

$$S\Delta x_2 = (L_0\bar{\alpha}_2 - L_0\bar{\alpha}_1)\Delta T + \delta \quad (\text{B.2})$$

The baseline correction is obtained by addition of the two formulae:

$$\delta = \frac{1}{2}S(\Delta x_1 + \Delta x_2) \quad (\text{B.3})$$

## Bibliography

- [1] ISO 31-4, *Quantities and units — Part 4: Heat*
- [2] ISO 3611, *Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics*
- [3] ISO 6906:1984, *Vernier callipers reading to 0,02 mm*
- [4] ISO 13385-1:2011, *Geometrical product specifications (GPS) — Dimensional measuring equipment — Part 1: Callipers; Design and metrological characteristics*
- [5] ISO 17562, *Fine ceramics (advanced ceramics, advanced technical ceramics) - Test method for linear thermal expansion of monolithic ceramics by push-rod technique*
- [6] EN 821-1, *Advanced technical ceramics — Monolithic ceramics — Thermo-physical properties — Part 1: Determination of thermal expansion*







# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK



...making excellence a habit.™