

BS ISO 17324:2014



BSI Standards Publication

# Rubber hoses for automotive turbochargers — Specification

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of ISO 17324:2014.

The UK participation in its preparation was entrusted to Technical Committee PRI/66, Rubber and plastics tubing, hoses and hose assemblies.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 79655 5

ICS 43.040.01; 83.140.40

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 September 2014.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

INTERNATIONAL  
STANDARD

**ISO**  
**17324**

First edition  
2014-09-15

---

---

**Rubber hoses for automotive  
turbochargers — Specification**

*Tuyaux en caoutchouc pour turbocompresseurs automobiles —  
Spécifications*



Reference number  
ISO 17324:2014(E)

© ISO 2014



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Case postale 56 • CH-1211 Geneva 20  
Tel. + 41 22 749 01 11  
Fax + 41 22 749 09 47  
E-mail [copyright@iso.org](mailto:copyright@iso.org)  
Web [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Classification</b> .....	<b>2</b>
4.1 Types and classes.....	2
4.2 Grades.....	2
<b>5 Materials and construction</b> .....	<b>2</b>
5.1 Materials.....	2
5.2 Construction.....	3
<b>6 Dimensions and tolerances</b> .....	<b>3</b>
6.1 Inside diameter, wall thickness, and length tolerance.....	3
6.2 Hose end squareness.....	4
<b>7 Physical properties</b> .....	<b>5</b>
7.1 Rubber compounds.....	5
7.2 Hose.....	7
<b>8 Frequency of testing</b> .....	<b>8</b>
<b>9 Marking</b> .....	<b>9</b>
<b>10 Storage</b> .....	<b>9</b>
<b>Annex A (normative) Fatigue resistance test</b> .....	<b>10</b>
<b>Annex B (normative) Type and routine tests</b> .....	<b>12</b>
<b>Annex C (informative) Recommended production tests</b> .....	<b>13</b>
<b>Bibliography</b> .....	<b>15</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 1, *Rubber and plastics hoses and hose assemblies*.

# Rubber hoses for automotive turbochargers — Specification

## 1 Scope

This International Standard specifies requirements of rubber hoses used in the automotive turbocharger system to connect turbocharger, intercooler, and internal combustion engine at the working temperatures from  $-40^{\circ}\text{C}$  to  $+250^{\circ}\text{C}$  and the working pressures from  $-0,01\text{MPa}(-0,1\text{bar})$  to  $0,5\text{MPa}(5\text{bar})$ . Hoses covered by this International Standard may be straight or shaped.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 188, *Rubber, vulcanized or thermoplastic — Accelerated ageing and heat resistance tests*

ISO 812, *Rubber, vulcanized or thermoplastic — Determination of low-temperature brittleness*

ISO 1402, *Rubber and plastics hoses and hose assemblies — Hydrostatic testing*

ISO 1431-1, *Rubber, vulcanized or thermoplastic — Resistance to ozone cracking — Part 1: Static and dynamic strain testing*

ISO 1629, *Rubber and latices — Nomenclature*

ISO 1817, *Rubber, vulcanized or thermoplastic — Determination of the effect of liquids*

ISO 4671, *Rubber and plastics hoses and hose assemblies — Methods of measurement of the dimensions of hoses and the lengths of hose assemblies*

ISO 7233:2006, *Rubber and plastics hoses and hose assemblies — Determination of resistance to vacuum*

ISO 8033, *Rubber and plastics hoses — Determination of adhesion between components*

ISO 8330, *Rubber and plastics hoses and hose assemblies — Vocabulary*

ISO 8331, *Rubber and plastics hoses and hose assemblies — Guidelines for selection, storage, use and maintenance*

ISO 28702, *Rubber and plastics hoses and tubing — Textile-reinforced types — Sub-ambient temperature crush test*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 8330 and the abbreviated terms given in ISO 1629 apply.

## 4 Classification

### 4.1 Types and classes

The hoses are classified into three types as per the intended operating conditions.

- Type A: hose for connecting air filter and turbocharger, to transfer filtered atmospheric air. Working temperature from  $-40^{\circ}\text{C}$  to  $+100^{\circ}\text{C}$ , and vacuum pressure low to  $-0,01\text{MPa}(-0,1\text{bar})$ .
- Type B: hose for connecting turbocharger and intercooler, to transfer the pressurized and heated air. Working temperature from  $-40^{\circ}\text{C}$  to  $+250^{\circ}\text{C}$ .

Type B is subdivided into three subtypes as per working temperature and further classified into classes as per maximum working pressures. The subtypes and classes are shown in [Table 1](#).

**Table 1 — Subtypes and classes for Type B**

Type	Working temperature $^{\circ}\text{C}$	Class		
		1	2	3
		Maximum working pressure MPa(bar)		
B1	$-40$ approximately $+180$	0,16(1,6)	0,22(2,2)	0,28(2,8)
B2	$-40$ approximately $+220$	0,20(2,0)	0,28(2,8)	0,34(3,4)
B3	$-40$ approximately $+250$	0,30(3,0)	0,40(4,0)	0,50(5,0)

- Type C: hose for connecting intercooler and internal combustion engine, to transfer the pressurized and cooled air. Working temperature from  $-40^{\circ}\text{C}$  to  $+140^{\circ}\text{C}$  and maximum working pressure  $0,3\text{MPa}$  (3bar).

### 4.2 Grades

Type B and C of hose are classified into 2 grades as per fatigue resistance:

- Grade 200 — 200 000 impulse cycles;
- Grade 400 — 400 000 impulse cycles.

## 5 Materials and construction

### 5.1 Materials

The typical materials for the types of hoses are listed in [Table 2](#).



**Table 2 — Hose type and typical material**

Dimensions in millimetres

Type	Lining	Reinforcement	Cover
A/C	EPDM	PET <sup>a</sup> PA <sup>b</sup> wire	EPDM
	CM		CM
	CR		CR
	ECO		ECO
	AEM		AEM
	ACM		ACM
	VMQ		VMQ
B1	AEM	PET <sup>a</sup> AR <sup>c</sup>	AEM
	ACM		ACM
	VMQ		VMQ
B2/B3	FKM	AR <sup>c</sup>	VMQ
	FVMQ		VMQ
NOTE — All the abbreviated words are defined in ISO 1629 excluded PET, PA, and AR. a PET — poly(ethylene terephthalate) fibre b PA — polyamide c AR — Aramid			

## 5.2 Construction

The hoses shall consist of:

- a flexible polymeric elastomers lining;
- a synthetic textile reinforcement or other reinforcements, applied by any suitable technique;
- a flexible polymeric elastomers cover.

Hose body may have a smooth or corrugated finish, and be further reinforced with wire at suitable positions, and may be covered with glass fibre cloth with aluminium-foil paper, or heat insulation or abrasion resistant jacket made of thermoplastic material on suitable position.

NOTE Type A may be rubber tubing without reinforcement.

## 6 Dimensions and tolerances

### 6.1 Inside diameter, wall thickness, and length tolerance

Unless otherwise specified, when measured in accordance with ISO 4671, inside diameters and wall thicknesses tolerances are given in [Table 3](#) and length tolerances are given in [Table 4](#).

**Table 3 — Inside diameter, wall thickness tolerance**

Dimensions in millimetres

Inside diameter and tolerance		Tolerance of wall thickness	
Inside diameter	Tolerance	Extruded hose	Wrapped hose <sup>a</sup>
≤ 35	+0,5 -1,3	±0,3	±0,5
> 35 and ≤ 50			
> 50 and ≤ 80	+0,5 -1,3	±0,8	±1,0
> 80 and ≤ 110	+0,8 -1,7		
> 110 and ≤ 150	+1,2 -2,0	±1,0	±1,2
> 150	+1,6 -2,5		

<sup>a</sup> Overlap zone excluded

**Table 4 — Length tolerance**

Dimensions in millimetres

Length	Tolerance
≤ 300	±3
> 300 and ≤ 600	±4,5
> 600	±1 %


## 6.2 Hose end squareness

All the points on the end surface of a hose shall be in the tolerance zone, given in [Table 5](#), which is defined by two planes vertical to the longitudinal axis of the hose (see [Figure 1](#)).

**Table 5 — Hose end squareness**

Dimensions in millimetres

I.D.	Tolerance zone
< 25,4	2,5
≥ 25,4	10 % of I.D.

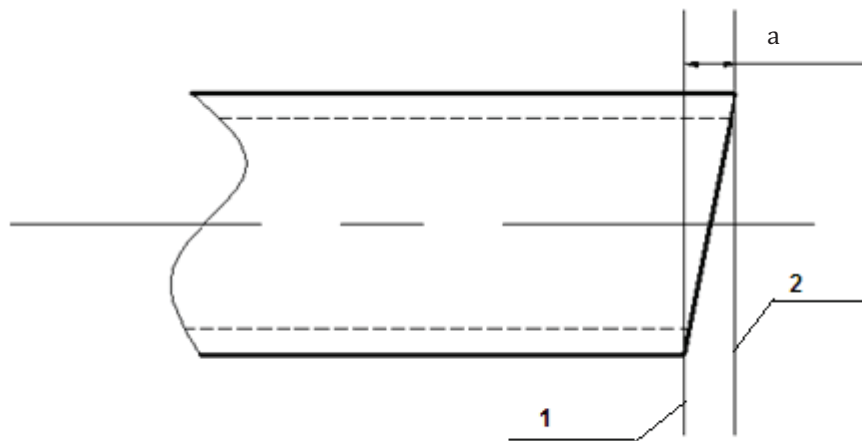

**Key**

- 1 plane
- 2 plane
- a Tolerance zone.

**Figure 1 — Hose end squareness**

## 7 Physical properties

### 7.1 Rubber compounds

Physical properties of rubber compounds used for the lining, cover and tubing shall conform to the values given in [Table 6](#), [Table 7](#), [Table 8](#), [Table 9](#), and [Table 10](#). Tests shall be carried out on samples (taken from the hose or from moulded sheets of rubber compound, 2 mm thick or moulded test pieces) in all cases vulcanized to the same cured state as the production hose.

**Table 6 — Lining, cover, and tubing for type A**

Property	Requirement	Test method
Heat aging resistance, 100 °C × 168 h		
Change in hardness, shore A	±10	ISO 188
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Oil resistance <sup>a</sup> , IRM 901 Oil, 100 °C × 70 h		
Change in hardness, shore A	±10	ISO 1817
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Change in volume, %	±10	
Brittleness temperature, at -40 °C	No brittleness	ISO 812
Ozone resistance, 100pphm × 40 °C × 72 h × 20 %	No cracks	ISO 1431-1
<sup>a</sup> not applicable for EPDM		

**Table 7 — Lining, cover, and tubing for type B1**

Property	Requirement	Test method
Heat aging resistance, 180 °C × 168 h		
Change in hardness, shore A	±10	ISO 188
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Oil resistance, IRM 901 Oil, 150 °C × 70 h		
Change in hardness, shore A	±10	ISO 1817
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Change in volume, %	±10	
Brittleness temperature, at -40 °C,	No brittleness	ISO 812
Ozone resistance, 100pphm × 40 °C × 72 h × 20 %	No cracks	ISO 1431-1

**Table 8 — Lining, cover, and tubing for type B2**

Property	Requirement	Test method
Heat aging resistance, 220 °C × 168 h		
Change in hardness, shore A	±10	ISO 188
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Oil resistance, 150 °C × 70 h, IRM 901 Oil excluding lining, IRM 903 Oil for lining		
Change in hardness, shore A	±10	ISO 1817
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Change in volume, %	±10	
Brittleness temperature, at -40 °C	No brittleness	ISO 812
Ozone resistance, 100pphm × 40 °C × 72 h × 20 %	No cracks	ISO 1431-1

**Table 9 — Lining, cover, and tubing for type B3**

Property	Requirement	Test method
Heat aging resistance, 250 °C × 168 h		
Change in hardness, shore A	±10	ISO 188
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Oil Resistance, 150 °C × 70 h, IRM 901 Oil excluding lining IRM 903 Oil for lining		

Table 9 (continued)

Property	Requirement	Test method
Change in hardness, Shore A	±10	ISO 1817
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Change in volume, %	±10	
Brittleness temperature, at -40 °C	No brittleness	ISO 812
Ozone resistance, 100pphm × 40 °C × 72 h × 20 %	No cracks	ISO 1431-1

Table 10 — Lining, cover, and tubing for type C

Property	Requirement	Test method
Heat aging resistance, 140 °C × 168 h		
Change in hardness, shore A	±10	ISO 188
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Oil resistance <sup>a</sup> , IRM 901 Oil, 100 °C × 70 h		
Change in hardness, shore A	±10	ISO 1817
Change in tensile strength, %	±30	
Change in elongation at break, %	±40	
Change in volume, %	±10	
Brittleness temperature, at -40 °C	No brittleness	ISO 812
Ozone resistance, 100pphm × 40 °C × 72 h × 20 %	No cracks	ISO 1431-1
<sup>a</sup> not applicable for EPDM		

## 7.2 Hose

### 7.2.1 Appearance

When checked with 1x magnification, hose cover and bore surface shall show no visible defects such as kinking, porosity, blister, foreign inclusions, damages, and scratches. Marks such as wrapper marks on the cover surface may be acceptable. Reinforcement shall not be exposed other than on the end surfaces of hose.

Delivery hoses shall be clean and qualified, free from impurity, grease, or any contamination that may affect the function of the hose.

### 7.2.2 Vacuum resistance (only for Type A)

When tested in accordance with method C in ISO 7233:2006, the change in hose length ( $\Delta L_t$ ) shall be 0~5 %, and the change in OD ( $\Delta D_t$ ) shall be 0~-8 %, measured while vacuum pressure maintained at -0,015 MPa for 10 min.

The lines A and B should be at 25 mm apart from ends of the hose if the length of the hose to be tested is less than 500 mm.

### 7.2.3 Proof pressure (for Type B and C)

When tested in accordance with ISO 1402 at the proof pressures given in [Table 11](#), no leakage or other signs of weakness nor abrupt twisting shall be shown.

#### 7.2.4 Minimum burst Pressure (for Type B and C)

When tested in accordance with ISO 1402, the minimum burst pressures for the hoses of Type B and C shall be in accordance with the values given in [Table 11](#).

**Table 11 — Maximum working pressure, proof pressure, and minimum burst pressure**

Type	Class	Maximum working pressure MPa(bar)	Proof pressure MPa(bar)	Minimum burst pressure MPa(bar)
B1	1	0,16(1,6)	0,32(3,2)	0,64(6,4)
	2	0,22(2,2)	0,44(4,4)	0,88(8,8)
	3	0,28(2,8)	0,56(5,6)	1,12(11,2)
B2	1	0,20(2,0)	0,40(4,0)	0,80(8,0)
	2	0,28(2,8)	0,56(5,6)	1,12(11,2)
	3	0,34(3,4)	0,68(6,8)	1,36(13,6)
B3	1	0,30(3,0)	0,60(6,0)	1,20(12,0)
	2	0,40(4,0)	0,80(8,0)	1,60(16,0)
	3	0,50(5,0)	1,00(10,0)	2,00(20,0)
C	—	0,30(3,0)	0,60(6,0)	1,20(12,0)

#### 7.2.5 Adhesion

When tested in accordance with ISO 8033, adhesion between layers shall be no less than 1,0 kN/m.

#### 7.2.6 Fatigue resistance (for Type B and C)

When tested in accordance with [Annex A](#) and subjected to the impulse cycles given in [Table 12](#), the hoses shall show no leakage, cracking, and other evidence of failure. Burst pressure and adhesion values after fatigue resistance shall be in accordance with the agreement between the customer and manufacturer.

**Table 12 — The impulse cycles for Type B and C**

Grade 200	Grade 400
200 000	400 000

#### 7.2.7 Sub-ambient crush resistance

When tested in accordance with ISO 28702, if required and applicable, at  $-40\text{ °C} \pm 2\text{ °C}$  or at the test temperature agreed by customer and manufacturer, any abnormalities such as cracks, fractures, or separation of layers on interior and exterior of the test piece shall not be observed.

## 8 Frequency of testing

Type tests and routine tests shall be as specified in [Annex B](#).

Type tests are those tests required to confirm that a particular hose or hose assembly design, manufactured by a particular method from particular materials, meets all the requirements of this International Standard. The tests shall be repeated at a maximum of one year intervals, or whenever a change in the method of manufacture or materials used occurs. They shall be performed on all sizes, and on all types except those of the same size and construction.

Routine tests are those tests required to be carried out on each length of finished hose prior to dispatch.

Production tests are non-mandatory and the recommended frequencies are given in [Annex C](#) for guidance only.

## 9 Marking

The hose shall be continuously, indelibly, and legibly marked, with at least the following information:

- a) the manufacturer's name or mark (and serial No. if applicable), e.g. MAN;
- b) the number and year of this standard, i.e. ISO 17324:2014;
- c) hose type, class, and grade, e.g. B1-1-200;
- d) ID of the hose, e.g. 35;
- e) maximum working pressure, MPa(bar), e.g. 0,3MPa(3bar);
- f) quarter and year of manufacture, e.g. 2Q14.

EXAMPLE     MAN/ISO 17324:2014 /B1-1-200/35/0,3MPa/2Q14

## 10 Storage

Recommendations for storage are detailed in ISO 8331.

## Annex A (normative)

### Fatigue resistance test

**WARNING — Persons using this International Standard should be familiar with normal laboratory practice. This standard does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any national regulatory conditions.**

#### A.1 General

This method simulates the practical operating condition at ambient temperature of  $100^{\circ}\text{C} \pm 10^{\circ}\text{C}$ , and subjects a hose to alternate pressures of 0MPa(0bar) and 0,25MPa(2,5bar) (or 133 % maximum working pressure) and simultaneously to vibration of a certain amplitude and frequency by using a cycle pump and an actuator.

#### A.2 Test rig

**A.2.1** An impulse-vibration test can be carried out on the test rig. If vibration is not required, only impulse test shall be carried.

**A.2.2** A protective device, capable of interrupting the test immediately when leakage, burst, or any other failures happen.

**A.2.3** A pressure-cycle pump for gas cycling. Cycling medium is the compressed air flowing continuously in the hose.

**A.2.4** An actuator, capable of providing vibration.

**A.2.5** A temperature-control device, allowing medium and ambient temperature to be controlled.

**A.2.6** A recorder, capable of recording the impulse cycle number and vibration.

#### A.3 Procedure

**A.3.1** Attach a hose to the test rig, adjust the clamp and torque to keep a tightly sealed state.

**A.3.2** Rise the temperature of the cycling compressed air to the value given in [Table A.1](#).

**Table A.1 — Cycling gas temperature**

Type	Test temperature
B1	$180^{\circ}\text{C} \pm 5^{\circ}\text{C}$
B2	$220^{\circ}\text{C} \pm 5^{\circ}\text{C}$
B3	$250^{\circ}\text{C} \pm 5^{\circ}\text{C}$
C	$140^{\circ}\text{C} \pm 5^{\circ}\text{C}$



**A.3.3** Raise ambient temperature to  $100\text{ °C} \pm 10\text{ °C}$ .

**A.3.4** Regulate the pressure cycle (and vibration) frequency to the specified value.

**A.3.5** Start the pressure cycle pump and apply pressure cycles as following sequence to the specified cycle number:

- from 0MPa to 0,25MPa(2,5bar) (or 133 % maximum working pressure) in 1 s;
- maintain 0,25MPa(2,5bar) (or 133 % maximum working pressure) for 2 s;
- from 0,25MPa(2,5bar) (or 133 % maximum working pressure) to 0MPa(0bar) in 1 s;
- maintain 0 MPa(0bar) for 2 s.

The duration of one cycle shall be 6 s.

Continue the test until the failure occurs.

**A.3.6** If vibration is required, start vibration at the same time ([A.3.5](#)). Vibration amplitude and frequency shall conform to the agreement between the customer and manufacturer.

**A.3.7** Check the hose for failures when completing the specified cycles (and vibration) and continue the test till failure occurs.

**A.3.8** Record the number of cycles completed to failure.

**A.3.9** Leakage may occur because of the hose clamp. In this case, test results shall be ignored.

**A.3.10** At least three test pieces shall be tested.

## **A.4 Test report**

The test report shall include at least the following information:

- a) a reference to this International Standard (i.e. ISO 17324:2014);
- b) type of the tested hose;
- c) test temperature;
- d) test pressure, MPa(bar);
- e) pressure cycle rate, vibration amplitude and frequency;
- f) number of test for undamaged hose;
- g) details of any failures which affect the test results.

## Annex B (normative)

### Type and routine tests

Type tests and routine tests are given in [Table B.1](#).

**Table B.1 — Type and routine tests**

Property	Type tests	Routine tests
<b>Rubber compounds</b>		
Heat aging resistance	×	N/A
Oil resistance	×	N/A
Brittleness temperature	×	N/A
Ozone resistance	×	N/A
<b>Hose</b>		
Inside diameter	×	×
Wall thickness	×	×
Length	×	×
Hose end squareness	×	×
Appearance	×	×
Vacuum resistance	×	N/A
Proof pressure	×	×
Burst pressure	×	N/A
Adhesion	×	N/A
Fatigue resistance	×	N/A
Sub-ambient crush resistance	×	N/A
× Test shall be carried out.		
N/A Test not applicable.		

## Annex C (informative)

### Recommended production tests

The recommended production tests are given in [Table C.1](#).

For rubber compounds, the frequency should be every 6 months of production for each type and hose size. For hose, the production tests should be carried on each batch which is defined as 1 000 lengths of hose.

**Table C.1 — Recommended production tests**

Property	Production tests
<b>Rubber compounds</b>	
Heat aging resistance	×
Oil resistance	×
Brittleness temperature	×
Ozone resistance	×
<b>Hose</b>	
Inside diameter	×
Wall thickness	×
Length	×
Hose end squareness	×
Appearance	×
Vacuum resistance (only for Type A)	×
Proof pressure	×
Minimum burst pressure (for Type B and C)	×
Adhesion	×
Fatigue resistance (for Type B and C)	N/A
Sub-ambient crush resistance	×
× Test shall be carried out. N/A Test not applicable.	



## Bibliography

- [1] ISO 2393, *Rubber test mixes — Preparation, mixing and vulcanization — Equipment and procedures*





# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™