



BSI Standards Publication

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for elastic moduli of monolithic ceramics at room temperature by sonic resonance

National foreword

This British Standard is the UK implementation of ISO 17561:2016.

The UK participation in its preparation was entrusted to Technical Committee RPI/13, Advanced technical ceramics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.
Published by BSI Standards Limited 2016

ISBN 978 0 580 90629 9

ICS 81.060.30

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 June 2016.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

**Fine ceramics (advanced ceramics,
advanced technical ceramics) —
Test method for elastic moduli
of monolithic ceramics at room
temperature by sonic resonance**

*Céramiques techniques — Méthode d'essai des modules d'élasticité
des céramiques monolithiques, à température ambiante, par
résonance acoustique*





COPYRIGHT PROTECTED DOCUMENT

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Summary of test method	2
5 Apparatus	3
5.1 General.....	3
5.2 Oscillator.....	5
5.3 Amplifier.....	5
5.4 Driver.....	5
5.5 Detector.....	5
5.6 Frequency counter.....	6
5.7 Specimen suspension means.....	6
5.8 Micrometer.....	6
5.9 Vernier calliper.....	7
5.10 Balance.....	7
6 Test pieces	7
7 Test procedure	7
7.1 Measurement of the size and the mass.....	7
7.2 Positioning of the specimen.....	7
7.3 Measurement of resonant frequency.....	8
8 Calculations	9
9 Test report	11
Bibliography	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 206, *Fine ceramics*.

This second edition cancels and replaces the first edition (ISO 17561:2002), which has been technically revised. It also incorporates the Technical Corrigendum ISO 17561:2002/Cor.1:2007.

Fine ceramics (advanced ceramics, advanced technical ceramics) — Test method for elastic moduli of monolithic ceramics at room temperature by sonic resonance

1 Scope

This International Standard describes the method of test for determining the dynamic elastic moduli of fine ceramics at room temperature by sonic resonance. This International Standard is for fine ceramics that are elastic, homogeneous and isotropic.^[2]

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3611, *Geometrical product specifications (GPS) — Dimensional measuring equipment: Micrometers for external measurements — Design and metrological characteristics*

ISO 13385 (all parts), *Geometrical product specifications (GPS) — Dimensional measuring equipment*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

dynamic elastic moduli

adiabatic elastic moduli, which are dynamic Young's modulus, shear modulus and Poisson's ratio

Note 1 to entry: Adiabatic elastic moduli are obtained by the sonic resonance method.

3.1.1

Young's modulus

E

elastic modulus in tension or compression

$$E = \sigma / \varepsilon$$

where

E is Young's modulus in pascals;

σ is the tension or compression stress in pascals;

ε is the tension or compression strain.

3.1.2

shear modulus

G

elastic modulus in shear or torsion

$$G = \tau / \gamma$$

where

G is the shear modulus in pascals;

τ is the shear or torsional stress in pascals;

γ is the shear or torsional strain.

3.1.3

Poisson's ratio

ν

ratio of transverse strain to the corresponding axial strain resulting from uniformly distributed axial stress below the proportional limit of the material

Note 1 to entry: In isotropic materials, Young's modulus (E), shear modulus (G) and Poisson's ratio (ν) are related by the following formula:

$$\nu = E / (2G) - 1$$

3.2 vibration

3.2.1

flexural vibration

vibration apparent when the oscillation in a slender bar is in plane normal to the length dimension

Note 1 to entry: Also defined as vibration in a flexural mode.

3.2.2

torsional vibration

vibration apparent when the oscillation in each cross-section plane of a slender bar is such that the plane twists around the length dimension axis

Note 1 to entry: Also defined as vibration in a torsional mode.

3.3

resonance

state if, when a slender bar driven into one of the above modes of vibration, the imposed frequency is such that the resultant displacements for a given amount of driving force are at a maximum

Note 1 to entry: The resonant frequencies are natural vibration frequencies which are determined by the elastic modulus, mass and dimensions of the test piece.

3.4

fundamental frequency

lowest frequency of a periodic waveform

3.5

nodes

location(s) in slender rod or bar in *resonance* (3.3) having a constant zero displacement

Note 1 to entry: For the fundamental flexural resonance, the nodes are located at 0,224 L from each end, where L is the length of the rod or bar.

4 Summary of test method

This test method measures the flexural or torsional frequencies of test specimens of rectangular prism or cylindrical geometry by exciting them at continuously variable frequencies. Mechanical excitation of the specimens is provided through the use of a transducer that transforms a cyclic electrical signal into a cyclic mechanical force on the test piece. A second transducer senses the resulting mechanical vibrations of the test piece and transforms them into an electrical signal. The amplitude and the


frequency of the signal are measured by an oscilloscope or other means to detect resonance. The peak response is obtained at the resonant frequency. The fundamental resonant frequencies, dimensions and mass of the specimen are used to calculate the dynamic elastic moduli. The Young's modulus is determined from the flexural resonance frequency, and the shear modulus is determined from the torsional resonance frequency, together with the test piece dimensions and mass. Poisson's ratio is determined from the Young's modulus and the shear modulus.

5 Apparatus

5.1 General

There are various techniques that may be used to determine the resonant frequency of the test piece. The test piece may be excited by direct mechanical contact of a vibrator, or it may be suspended by a wire from a vibrator. It may be driven electromagnetically by attaching thin foils of magnetic material to one surface, or electrostatically by attaching an electrode to one surface.


One example of the test apparatus is shown in [Figure 1](#). The driving circuit consists of an oscillator, an amplifier, a driver and a frequency counter. The detecting circuit consists of a detector, an amplifier and an oscilloscope. [Figure 1](#) shows the suspension style of the apparatus. The direct contact support style of the test apparatus, shown in [Figure 2](#), is also possible. It consists of a variable-frequency audio oscillator, used to generate a sinusoidal voltage, and a power amplifier and suitable transducer to convert the electrical signal to a mechanical driving vibration. A frequency meter (preferably digital) monitors the audio oscillator output to provide accurate frequency determination. A suitable suspension coupling system supports the test piece. A transducer detector acts to detect mechanical vibration in the specimen and to convert it into an electrical signal which is passed through an amplifier and displayed on an indicating meter. The meter may be a voltmeter, a microammeter or an oscilloscope. An oscilloscope is recommended because it enables the operator to positively identify resonances, including higher order harmonics, by Lissajous figure analysis, which is a superposition of two perpendicular harmonics. If a Lissajous figure is desired, the output of the oscillator is also coupled to the horizontal plates of the oscilloscope.

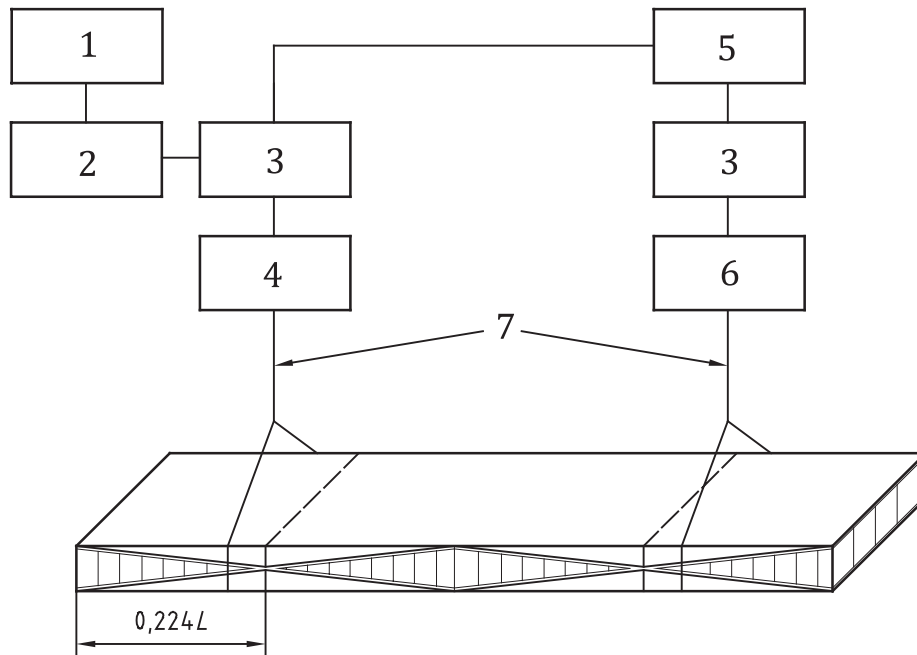

Key

- 1 frequency counter
- 2 oscillator
- 3 amplifier
- 4 driver
- 5 oscilloscope
- 6 detector
- 7 suspending string

Figure 1 — Example of the test apparatus and the suspension for fundamental flexural resonance

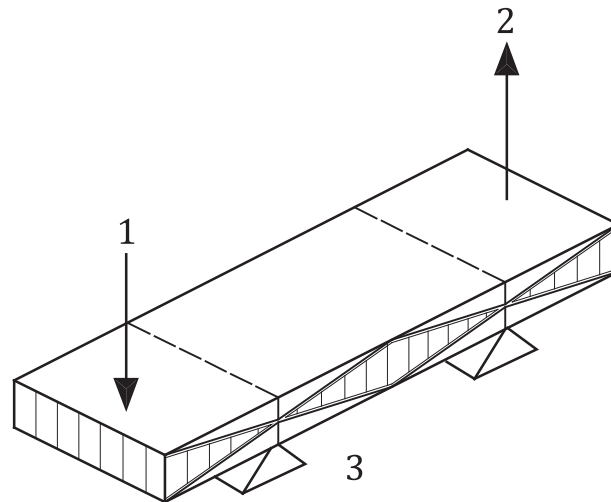

Key

- 1 driving
- 2 detecting
- 3 flexural

Figure 2 — Example of the direct contact support of the test piece for fundamental flexural resonance

5.2 Oscillator

The oscillator shall be able to vary the frequency from 100 Hz to at least 30 kHz, with a frequency resolution of 1 Hz and a maximum frequency drift of 1 Hz/min.

5.3 Amplifier

The audio amplifier shall have a power output sufficient to ensure that the type of transducer used can excite any specimen, the mass of which falls within a specified range. A power amplifier in the detector circuit shall be impedance-matched with the type of detector transducer selected and shall serve as a prescope amplifier.

5.4 Driver

The driver shall be able to convert electrical vibration to mechanical vibration. The frequency response of the driver transducer across the frequency range of interest shall have at least a 6,5 kHz bandwidth before -3 dB power loss occurs.

NOTE For flexibility in testing, the bandwidth can, with advantage, be at least as large as the frequency range given in [Table 1](#).

5.5 Detector

The detector shall generate a voltage proportional to the amplitude, velocity or acceleration of the mechanical vibration of the specimen. The frequency response of the detector across the frequency range of interest shall have at least a 6,5 kHz bandwidth before a -3 dB power loss occurs.

NOTE For flexibility in testing, the bandwidth can, with advantage, be at least as large as the frequency range given in [Table 1](#).

Table 1 — Examples of the test piece size and the calculated resonant frequencies

Where the density = 3 g/cm ³			
$L \times b (d) \times t$	$E = 200 \text{ GPa}$ $\nu = 0,25$	$E = 300 \text{ GPa}$ $\nu = 0,25$	$E = 400 \text{ GPa}$ $\nu = 0,25$
75 × 15 × 3	$f_f = 4\,453 \text{ Hz}$ $f_t = 12\,706 \text{ Hz}$	5 453 Hz 15 561 Hz	6 297 Hz 17 969 Hz
100 × 20 × 2	$f_f = 1\,676 \text{ Hz}$ $f_t = 5\,016 \text{ Hz}$	2 053 Hz 6 143 Hz	2 371 Hz 7 094 Hz
75 × 20 × 2	$f_f = 2\,977 \text{ Hz}$ $f_t = 6\,688 \text{ Hz}$	3 646 Hz 8 191 Hz	4 210 Hz 9 458 Hz
Where the density = 6 g/cm ³			
$L \times b (d) \times t$	$E = 200 \text{ GPa}$ $\nu = 0,25$	$E = 300 \text{ GPa}$ $\nu = 0,25$	$E = 400 \text{ GPa}$ $\nu = 0,25$
75 × 15 × 3	$f_f = 3\,148 \text{ Hz}$ $f_t = 8\,984 \text{ Hz}$	3 856 Hz 11 004 Hz	4 453 Hz 12 706 Hz
100 × 20 × 2	$f_f = 1\,185 \text{ Hz}$ $f_t = 3\,547 \text{ Hz}$	1 452 Hz 4 344 Hz	1 676 Hz 5 016 Hz
75 × 20 × 2	$f_f = 2\,105 \text{ Hz}$ $f_t = 4\,729 \text{ Hz}$	2 578 Hz 5 792 Hz	2 977 Hz 6 688 Hz
where			
L is the length in millimetres;			
b is the width in millimetres;			
d is the diameter in millimetres;			
t is the thickness in millimetres;			
f_f is the fundamental flexural resonant frequency in Hertz;			
f_t is the fundamental torsional resonant frequency in Hertz.			

5.6 Frequency counter

The frequency counter, preferably digital, shall be able to measure frequencies to within ± 1 Hz.

5.7 Specimen suspension means

Any method of specimen support that permits the free vibration of the test piece with no significant effect on the vibration frequencies shall be used. Test pieces are commonly supported either by suspension from threads or wires or on direct contact supports. If the test piece is to be supported from beneath, the support shall be made of rubber, cork or similar material, and shall have a minimum contact area with the test piece. If the test piece is suspended from the driving and detecting transducers, fine thread or metal wires shall be used. The vibrating mass of the suspension system shall be less than 0,1 % of the mass of the test piece. For the electromagnetic or electrostatic method, the mass of any magnetic foil or electrode attached to the test piece shall be negligible compared with the mass of the test piece.

5.8 Micrometer

A micrometer with a resolution of 0,002 mm or 0,1 % of the specimen, in accordance with ISO 3611, shall be used to measure the thickness, width and diameter of the test piece. Alternative dimension measuring instruments that have a resolution of 0,002 mm or finer may be used.

5.9 Vernier calliper

A vernier calliper with a resolution of 0,05 mm or 0,1 % of the specimen, in accordance with ISO 13385 (all parts), shall be used to measure the length of the test piece. Alternative dimension measuring instruments that have a resolution of 0,05 mm or finer may be used.

5.10 Balance

A balance with a resolution of 1 mg or 0,1 % of the specimen or finer, shall be used to measure the weight of the test piece.

6 Test pieces

The test piece shall be a rectangular prism or a bar with a circular cross section. This test method is not satisfactory for test pieces that have major discontinuities, such as large cracks (surface or internal) or internal voids.

- a) For flexural resonance, the length of the specimen (L) shall be greater than 40 mm, and the ratio of length to thickness (t), L/t , or length to diameter (d), L/d , shall be greater than 20.
- b) For torsional resonance, L shall be greater than 40 mm, L/t shall be greater than 20, and the ratio of the width (b) to the thickness, b/t , shall be in the range of 3 to 10 (5 is recommended).
- c) The parallelism of the specimen shall be within 0,1 % across the length and the width, and shall be within 0,5 % across the thickness.
- d) The surface of the test piece shall be smooth and flat. The surface shall be finished using a fine grind (400 grit or finer). The machining procedure shall not affect the test results.
- e) The edges of the specimen shall not be chamfered. However, if the chipping of the specimen from the edges affects the results, the edges may be chamfered, but the amount of the chamfering shall be as small as possible.

NOTE ASTM C1259, Annex A2 describes correction for edge chamfers or radii in rectangular beams in the calculation of Young's Modulus.

- f) For the suspension method, the mass of the specimen is, with advantage, at least 5 g in order to assist keeping a suspension system straight.

7 Test procedure

7.1 Measurement of the size and the mass


Dry the specimen until the mass is constant. Weigh the specimen to the nearest 1 mg or 0,1 % (whichever is greater). Measure the thickness and the width, or the diameter, to the nearest 0,002 mm or 0,1 % (whichever is greater) at three points on the test piece, and determine the average of the three measurements. Measure the length to the nearest 0,05 mm or 0,1 % (whichever is greater).

7.2 Positioning of the specimen

Position the specimen properly. If the fundamental mode of the flexural resonance is measured, the vibration nodes appear at a distance of 0,224 of the total length from each end. If the specimen is suspended by threads or wires that will be used to drive and detect vibration, position the threads outside the nodal points, as shown in [Figure 1](#) (distance of 0,2 of the length from each end is recommended). If the specimen is to be supported from below, position two supports at the nodal points, as shown in [Figure 2](#). If the fundamental mode of the torsional resonance is measured, the vibration nodes appear as shown in [Figure 3](#). If the specimen is supported from below, position one support at the centre of the specimen, as shown in [Figure 3](#). If the specimen is suspended by threads, position the

supports at diagonally opposed corners of the specimen, as shown in [Figure 4](#). The suspending devices shall permit the free vibration of the test piece.


Cotton thread is recommended for suspending the specimen. Cork or rubber is recommended for supporting the specimen.

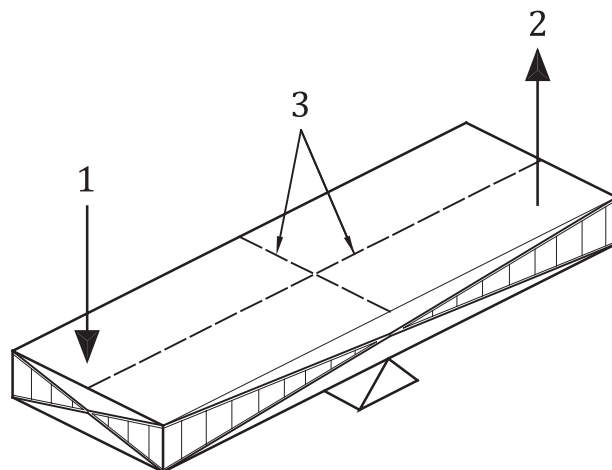

Key

- 1 driving
- 2 detecting
- 3 nodal

Figure 3 — Nodes and direct contact support on the fundamental torsional resonance

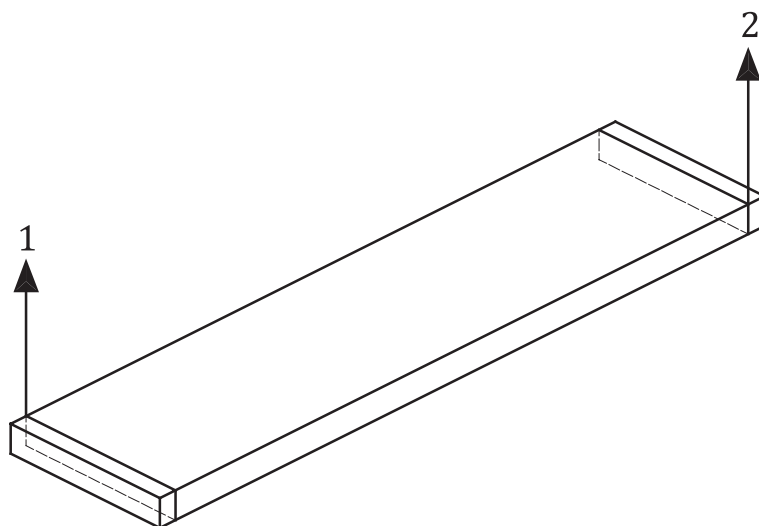

Key

- 1 driving
- 2 detecting

Figure 4 — Suspension for the fundamental torsional resonance

7.3 Measurement of resonant frequency

Activate the equipment so that the power adequate to excite the specimen is delivered to the driving transducer. Set the gain of the detector circuit high enough to detect vibration in the specimen and to display it on the oscilloscope screen with sufficient amplitude to accurately measure the frequency at

which the signal amplitude is maximized. Adjust the oscilloscope so that a sharply defined horizontal baseline exists when the test piece is not excited. Scan frequencies with the audio oscillator until test piece resonance (flexural or torsional) is indicated by a sinusoidal pattern of maximum amplitude on the oscilloscope or by a single closed loop Lissajous pattern. It is recommended that the frequency scan start at a low frequency and then increase. To verify that the frequency is fundamental and not an overtone, either the node/antinode locations or one or more overtones should be identified. If a determination of the shear modulus is made, offset the coupling to the transducers so that the torsional mode of vibration may be induced and detected (see [Figure 3](#) and [Figure 4](#)).

Currently, no certified reference artefacts for checking this measurement are available. Measurement system calibration for frequency should be undertaken using a suitable traceably certified frequency source. Laboratories should retain an identified test-piece for intermittent system repeatability checks, and for staff training.

NOTE The proper identification of the fundamental flexural mode is important as spurious frequencies inherent in the system may interfere, especially when greater excitation power and detection sensitivity are required for work with a specimen that has a poor response. One method of locating the nodes on the test piece is to move the detector along the length of the test piece; a node is indicated when the output amplitude goes to zero. An anti-node is indicated when the output amplitude reaches a local maximum. Another node location method (used often with string suspensions) is to lay a thin rod across the test piece at a presumed node or anti-node location. If the output amplitude is not affected, then the rod is on a node; if the output amplitude goes to zero, then the location is an anti-node. It is also possible to locate the nodes by spreading fine, free-flowing powder on the top surface of the test piece and observe its alignment at the nodal points. When several resonant flexural frequencies have been identified, the lowest frequency can be verified as the fundamental if the numerical ratios of the first three overtone frequencies to the lowest frequency are: 2,7, 5,4 and 8,9. Note that these ratios are for a Bernoulli-Euler (simple) beam under ideal conditions. Typically, the ratios will be slightly lower. A further possibility is localizing the nodes on the test piece by means of laser vibrometer.

8 Calculations

8.1 Calculate the dynamic Young's modulus for a rectangular prism from [Formula \(1\)](#):^[3]

$$E = 0,946\ 5 \frac{mf_f^2}{b} \left(\frac{L}{t}\right)^3 \left[1 + 6,585 \left(\frac{t}{L}\right)^2 \right] \quad (1)$$

where

- E is the dynamic Young's modulus in pascals;
- m is the mass of the specimen in kilograms;
- f_f is the fundamental flexural resonant frequency in hertz;
- b is the width of the specimen in metres;
- L is the length of the specimen in metres;
- t is the thickness of the specimen in metres.

8.2 Calculate the dynamic Young's modulus for a bar with a circular cross section from [Formula \(2\)](#):^[3]

$$E = 1,606\ 7 (mf_f^2) \left(\frac{L^3}{d^4}\right) \left[1 + 4,939 \left(\frac{d}{L}\right)^2 \right] \quad (2)$$

where d is the diameter of the specimen in metres.

8.3 Calculate the dynamic shear modulus for a rectangular prism from [Formula \(3\)](#):^[4]

$$G = \frac{4Lmf_t^2}{bt} \left(\frac{B}{1+A} \right) \quad (3)$$

where

G is the dynamic shear modulus in pascals;

f_t is the fundamental torsional resonant frequency in hertz;

B is a shape factor given by

$$B = \left[(b/t) + (t/b) \right] / \left[4(t/b) - 2,52(t/b)^2 + 0,21(t/b)^6 \right];$$

A is an empirical correction factor, given by [Figure 5](#) or by

$$A = \left[0,5062 - 0,8776(b/t) + 0,3504(b/t)^2 - 0,0078(b/t)^3 \right] / \left[12,03(b/t) + 9,892(b/t)^2 \right].$$


8.4 Calculate the dynamic shear modulus for a bar with a circular cross section from [Formula \(4\)](#):^[4]

$$G = 16mf_t^2 \left(\frac{L}{\pi d^2} \right) \quad (4)$$

8.5 Calculate the dynamic Poisson's ratio from [Formula \(5\)](#):

$$\nu = \frac{E}{2G} - 1 \quad (5)$$

where ν is the dynamic Poisson's ratio.

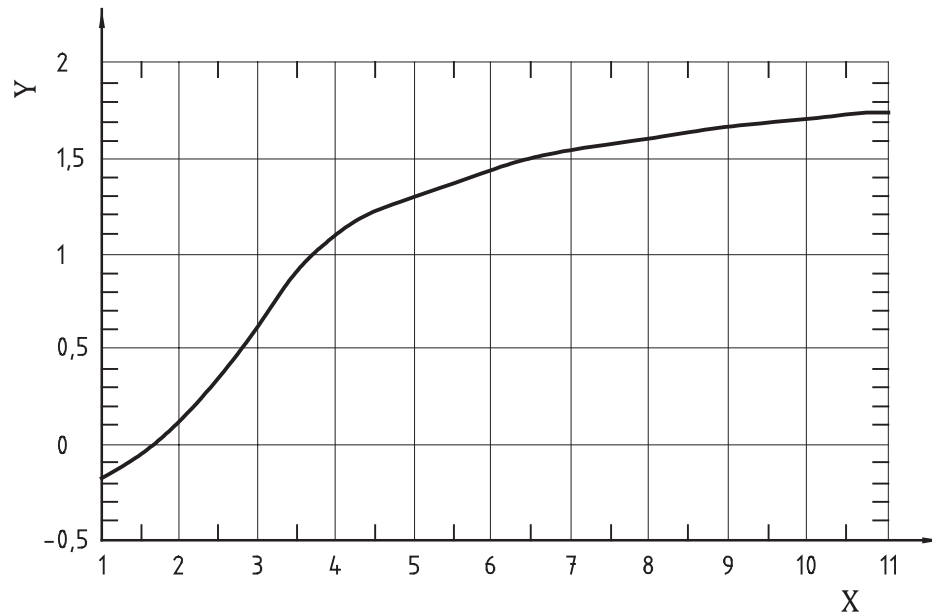

Key

X width to thickness ratio, b/t
Y correction term, A , %

NOTE Shear modulus correction term, A . $G = G_{\text{measured}}/(1 + A)$.

Figure 5 — Empirical correction factor, A , for the calculation of shear modulus

9 Test report

The test report shall include the following information:

- a) the name of the testing establishment;
- b) the apparatus used;
- c) the date of the test;
- d) the number of specimens;
- e) the specimen geometry and mass;
- f) the name of the person performing the test;
- g) the identification of the specific test;
- h) the values of resonant frequencies;
- i) the values of dynamic Young's modulus, dynamic shear modulus and dynamic Poisson's ratio;
- j) the description of test piece:
 - 1) the composition and source;
 - 2) the machining condition, surface finish and edge conditions;
 - 3) any other information (test piece history, treatments);
- k) any other relevant comments.

Bibliography

- [1] ASTM C1259, *Standard Test Method for Dynamic Young's Modulus, Shear Modulus, and Poisson's Ratio for Advanced Ceramics by Impulse Excitation of Vibration*
- [2] SPINNER S., & TEFFT W.E. A Method for Determining Mechanical Resonance Frequencies and for Calculating Elastic Moduli from These Frequencies. *Proceedings, ASTM*, 1961, pp. 1221-1238
- [3] SPINNER S., REICHARD T.W., TEFFT W.E. A Comparison of Experimental and Theoretical Relations Between Young's Modulus and the Flexural and Longitudinal Resonance Frequencies of Uniform Bars. *J. Res. Natl. Bur. Stand., A Phys. Chem.* 1960, **64A** (2)
- [4] PICKETT G Equations for Computing Elastic Constants from Flexural and Torsional Resonant Frequencies of Vibration of Prisms and Cylinders. *Proceedings ASTM*, (**45**), 1945, pp. 846-865

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK