

BS ISO 18550:2016



BSI Standards Publication

# Fine ceramics (advanced ceramics, advanced technical ceramics) — Testing method for macro-heterogeneity in microstructure

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of ISO 18550:2016.

The UK participation in its preparation was entrusted to Technical Committee RPI/13, Advanced technical ceramics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.  
Published by BSI Standards Limited 2016

ISBN 978 0 580 81869 1

ICS 81.060.30

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2016.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

---

---

**Fine ceramics (advanced ceramics,  
advanced technical ceramics) —  
Testing method for macro-  
heterogeneity in microstructure**

*Céramiques techniques — Méthode d'essai relative aux macro-  
hétérogénéités dans la microstructure*



## **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2016, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

	Page
<b>Foreword</b> .....	<b>iv</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>1</b>
<b>5 Apparatus</b> .....	<b>1</b>
<b>6 Test specimen</b> .....	<b>2</b>
<b>7 Procedure</b> .....	<b>2</b>
7.1 Measurement of specimen thickness.....	2
7.2 Observation.....	2
7.3 Magnification.....	2
<b>8 Measurement of macro-heterogeneities</b> .....	<b>3</b>
8.1 Determination of specimen volume under examination.....	3
8.2 Measurement of the size of macro-heterogeneities.....	3
<b>9 Analysis</b> .....	<b>3</b>
9.1 Maximum and minimum size.....	3
9.2 Size interval.....	3
9.3 Size and population of defect.....	3
9.4 Graph.....	4
<b>10 Test report</b> .....	<b>4</b>
<b>Annex A (informative) Refractive indices of solid and liquids</b> .....	<b>5</b>
<b>Annex B (informative) Examples of macro-heterogeneities observed in transmission mode</b> .....	<b>6</b>
<b>Bibliography</b> .....	<b>9</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 206, *Fine ceramics*.

# Fine ceramics (advanced ceramics, advanced technical ceramics) — Testing method for macro-heterogeneity in microstructure

## 1 Scope

This International Standard specifies a test method for determining macro-heterogeneities within the microstructure of fine ceramics that are above a certain size within the volume of the material and affect materials mechanical strength properties. This method is limited to fine ceramics with a porosity of less than 10 vol% and that are transparent for visible light in the form of a thin specimen.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO/IEC 17025, *General requirements for the competence of testing and calibration laboratories*

## 3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

### 3.1

#### **coarse macro-heterogeneity**

macro-heterogeneity, e.g. agglomerates, pores, inclusion, grains, with a size above 10 µm significantly affecting the mechanical strength

### 3.2

#### **coarse macro-heterogeneity distribution**

size distribution of coarse macro-heterogeneities

### 3.3

#### **equivalent circle diameter**

diameter of a circle having the same area as the coarse macro-heterogeneity

## 4 Principle

A variety of ceramics are composed of transparent materials and their macro-heterogeneity is observed in the transmission mode on a thin specimen.

## 5 Apparatus

**5.1 Microscope**, enabling the observation in the transmission mode. The microscope shall have a maximum magnification of the objective lens of  $\times 10$  and an illumination system with an adjustable aperture. A certified graticule shall be used for the calibration of the magnification.

**5.2 Cutting machine**, suitable machine capable of cutting the ceramics.

**5.3 Grinding machine**, suitable machine capable of grinding the ceramics.

**5.4 Polishing machine**, suitable machine capable of polishing the ceramics.

**5.5 Micrometer**, capable of measuring the thickness of the polished ceramic section with an accuracy of 2  $\mu\text{m}$ .

**5.6 Microscope slide**, suitable transparent microscope slide for mounting the test-piece in the microscope.

**5.7 Transparent film with circles of various diameter**, to determine the equivalent circle diameter of defects.

## 6 Test specimen

The specimen shall be thin enough for observation in the transmission mode of the microscope. The typical thickness depends on the material and its porosity, and is between 30  $\mu\text{m}$  and 200  $\mu\text{m}$ .

The specimen shall be prepared as follows.

- a) Cut a thin slab from the ceramic using a cutting machine. A thickness of the slab of more than 1 mm plus the final thickness is recommended. For a ceramic with thickness of less than 2 mm, this process can be omitted.
- b) One face of the slab shall be ground using a grinding machine and polished with a polishing machine by using polishing grains of a sequence of decreasing sizes with the finishing grit size of less than 1  $\mu\text{m}$ .
- c) The other face of the slab shall be ground to adjust the thickness of the slab appropriately. Finally, the ground face shall be polished with the polishing machine by using polishing grains of a sequence of decreasing sizes as mentioned above to prepare a thin specimen for observation.
- d) Finally, mount the thin specimen on the microscope slide for observation. Transparent thermoplastic resin is recommended for mounting.
- e) The thickness of the specimen must be adjusted for adequate transparency before examination. With a specimen of adequate transparency, defects located at any depth in the specimen can be well focused. Scratches on both front and back surfaces are conveniently used to examine the applicability of this International Standard. If they are clearly seen from the opposite side, this International Standard can be applied.

## 7 Procedure

### 7.1 Measurement of specimen thickness

The thickness of the specimen shall be measured at the centre of the specimen with a micrometer to the nearest 0,002 mm.

### 7.2 Observation

Adjust the microscope as follows; set the numerical aperture of the condenser lens in the illumination system 0,1 or less. The objective lens used for observation should have the magnification under  $\times 10$ .

### 7.3 Magnification

The minimum sizes of defects subjected for examination is 10  $\mu\text{m}$  equivalent circle diameter. With the numerical aperture of the lens of 0,1, the maximum thicknesses of specimens which can be examined in one micrograph will be 48  $\mu\text{m}$  and 28  $\mu\text{m}$  multiplied by the refractive index of the specimen, for the objective lenses of magnifications  $\times 4$  and  $\times 10$ , respectively.



The position of focus should be at half of the specimen thickness from the top surface. The refractive index of major phase shall be used for a specimen with multiple phases.

If the specimen is highly transparent, a thicker specimen can be used. A series of micrographs shall be taken by changing the position of focus through the depth direction of specimen. The interval in the position of focus shall be less than  $48\ \mu\text{m}$  and  $28\ \mu\text{m}$  multiplied by the refractive index of the specimen, for the objective lenses of magnifications  $\times 4$  and  $\times 10$ , respectively.

The photographed areas shall not overlap and micrographs should cover at least 100 macro-heterogeneities which shall be analysed.

## 8 Measurement of macro-heterogeneities

### 8.1 Determination of specimen volume under examination

The volume,  $V$ , under examination is given by the image area,  $A_i$ , the thickness,  $t$ , of the slab, and the number,  $n_L$ , of locations under examination.

$$V = A_i \times t \times n_L \quad (1)$$

### 8.2 Measurement of the size of macro-heterogeneities

The net magnification shall be adjusted to make the defect of the minimum size appear to be over 5 mm equivalent circle diameter on the micrograph. A transparent film with circles of various diameters shall be used to determine the equivalent circle diameter. Determine the size for at least 100 macro-heterogeneities.

## 9 Analysis

### 9.1 Maximum and minimum size

Determine the largest and smallest macro-heterogeneity.

### 9.2 Size interval

At least five size intervals shall be taken between the size of the largest and smallest defects in the analysis. The intervals may not be equal, but at least five macro-heterogeneities should be present in each interval, except in the interval containing the largest macro-heterogeneity.

### 9.3 Size and population of defect

The size and the population of macro-heterogeneities for each size interval are given by Formulae (2) and (3).

$$d_{i,m} = (d_{i,l} + d_{i,u})/2 \quad (2)$$

where

$d_{i,m}$  is the mean size of interval  $i$ ;

$d_{i,l}$  is the lower limit of the interval  $i$ ;

$d_{i,u}$  is the upper limit of the interval  $i$ .

$$p_i = n_i / (d_{i,u} - d_{i,l}) V \quad (3)$$

where

$p_i$  is the population on interval  $i$ ;

$n_i$  is the number of defects belonging to interval  $i$ .

The unit to express population is the number of macro-heterogeneities/mm<sup>3</sup>/μm.

## 9.4 Graph

Plot the logarithm of the population as a function of the size of macro-heterogeneities.

## 10 Test report

The test report shall be in accordance with the provisions of ISO/IEC 17025 and shall include at least the following information:

- a) a reference to this International Standard, i.e. ISO 18550;
- b) the name of the specimen;
- c) the preparation method of specimen:
  - 1) machining method;
  - 2) thickness of specimen;
- d) the observation method:
  - 1) name of microscope;
  - 2) objective lens (type, magnification, optical system);
  - 3) numerical aperture in observation;
- e) the micrographs [micrographs of specimen and microscale taken at the magnification of observation and the results (e), if required];
- f) the measured results for size distribution of coarse non-uniform structure:
  - 1) size distribution of non-uniform structure (equivalent circle diameter);
  - 2) volume for observation.

## Annex A (informative)

### Refractive indices of solid and liquids

Refractive index (R.I.) varies with the wave length. It decreases with increasing wave length. Materials of crystallographically cubic symmetry have a single value at each wave length. Those of non-cubic crystal structures have multiple values. Average values are given for them in [Table A.1](#). Values at the wave length of 632,8 nm are listed in [Table A.1](#).

**Table A.1 — Refractive indices (R.I.) of various materials at the wave length 632,8 nm**


Materials	R.I.
Al <sub>2</sub> O <sub>3</sub>	1,770
AlN	2,165
MgO	1,735
SiC	2,635
SiO <sub>2</sub>	1,457
Si <sub>3</sub> N <sub>4</sub>	2,023
BaTiO <sub>3</sub>	2,411
TiO <sub>2</sub>	2,874
ZrO <sub>2</sub>	2,208

Source: <http://www.filmetrics.com/refractive-index-database>

## Annex B (informative)

### Examples of macro-heterogeneities observed in transmission mode


Macro-heterogeneities, e.g. agglomerates, pores, inclusion, grains, are found in essentially any ceramic. [Figure B.1](#) shows the structure of alumina ceramics observed with a transmission optical microscope. Dark features of various shapes correspond to heterogeneities in the structure. [Figure B.2](#) shows the population of macro-heterogeneities determined through the analysis of micrographs taken at various locations of the ceramics. A linear relationship is noted in this log-log plot. This relationship was noted in all other systems examined so far.

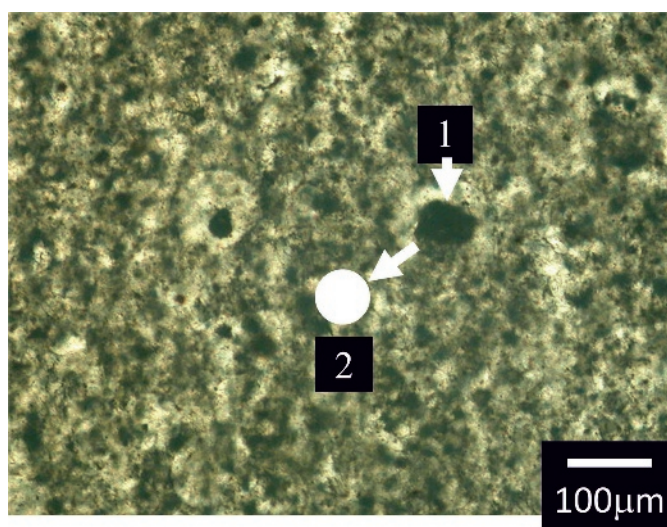

#### Key

- 1 flaw
- 2 equivalent circle, flaw size = equivalent circle diameter

**Figure B.1 — Optical micrograph of a ceramic and the determination of equivalent circle diameter of a flaw**

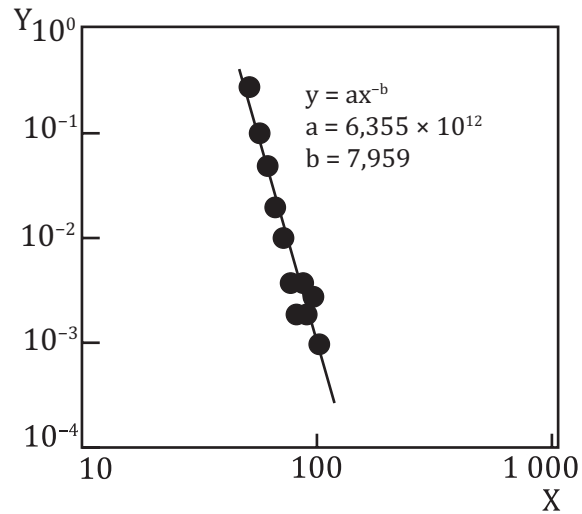


**Key**


- X flaw equivalent circle diameter/ $\mu\text{m}$
- Y population of flaw/ $\text{mm}^{-3} \mu\text{m}^{-1}$

**Figure B.2 — Size distribution of macro-heterogeneities in an alumina ceramic**

Examples of other macro-heterogeneities are shown in [Figures B.3](#) and [B.4](#) for a silicon nitride ceramic and a zirconia ceramic, respectively.

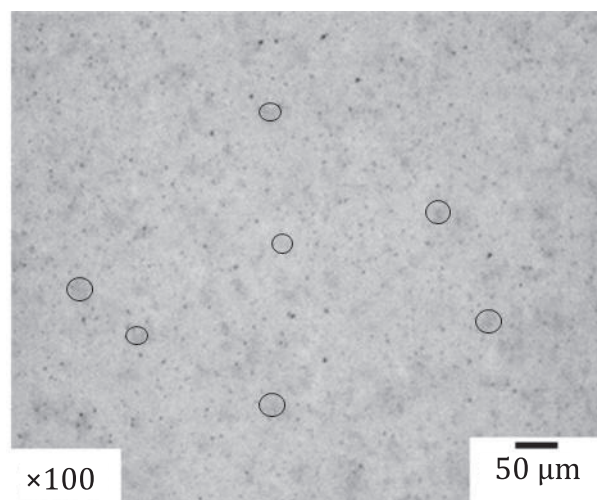

**Figure B.3 — Macro-heterogeneities in a silicon nitride ceramic (100  $\mu\text{m}$  thick)**

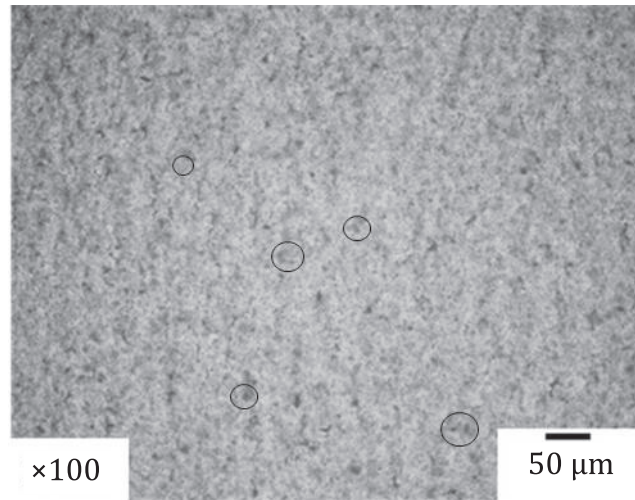

**Figure B.4 — Macro-heterogeneities in a zirconia ceramic (100 μm thick)**

## Bibliography

- [1] ISO 13383-1, *Fine ceramics (advanced ceramics, advanced technical ceramics) — Microstructural characterization — Part 1: Determination of grain size and size distribution*
- [2] JIS R1666, *Testing method for macro-heterogeneity in microstructure of fine ceramics*
- [3] ABE H., HOTTA T., NAITO M., SHINOHARA N., OKUMIYA M., KAMIYA H. Origin of strength variation of silicon nitride ceramics with CIP condition in powder compaction process. *Powder Technol.* 2000, **119** pp. 194–200
- [4] ABE H., HOTTA T., NAITO M., SHINOHARA N., UEMATSU K. Direct observation of detrimental defects in ceramics. *Am. Ceram. Soc. Bull.* 2002, **81** (1) pp. 31–34
- [5] HOTTA T., NAKAHIRA K., NAITO M., SHINOHARA N., OKUMIYA M., UEMATSU K. Origin of strength change in ceramics associated with the alteration of spray dryer. *J. Mater. Res.* 1999, **14** (7) pp. 2974–2979
- [6] HOTTA T., NAKAHIRA K., NAITO M., SHINOHARA N., OKUMIYA M., UEMATSU K. Origin of strength change of silicon nitride ceramics with the alteration of spray drying conditions. *J. Eur. Ceram. Soc.* 2001, **21** pp. 603–610
- [7] NAKAMURA S., TANAKA S., KATO Z., UEMATSU K. Strength-processing defects relationship based on micrographic analysis and fracture mechanics in alumina ceramics. *J. Am. Ceram. Soc.* 2009, **92** (3) pp. 688–693
- [8] SHINOHARA N., OKUMIYA M., HOTTA T., NAKAHIRA K., NAITO M., UEMATSU K. Effect of seasons on density, strength of alumina. *Am. Ceram. Soc. Bull.* 1999, **78** (2) pp. 81–84
- [9] SHINOHARA N., OKUMIYA M., HOTTA T., NAKAHIRA K., NAITO M., UEMATSU K. Seasonal variation of microstructure and sintered strength of dry-pressed alumina. *J. Am. Ceram. Soc.* 1999, **82** (12) pp. 3441–3446
- [10] UEMATSU K., SEKIGUCHI M., KIM J.-Y., SATO K., MUTOH Y., INOUE M. Effect of process conditions on the characteristics of pores in hot isostatically pressed alumina. *J. Mater. Sci.* 1993, **28** (4) pp. 1788–1792







# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

