

BS ISO 18843:2015



BSI Standards Publication

# Aluminium oxide primarily used for the production of aluminium — Method for the determination of flow time

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of ISO 18843:2015.

The UK participation in its preparation was entrusted to Technical Committee CII/24, Raw materials for the aluminium industry.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015. Published by BSI Standards Limited 2015

ISBN 978 0 580 84997 8

ICS 71.100.10

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 June 2015.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

INTERNATIONAL  
STANDARD

**ISO**  
**18843**

First edition  
2015-06-01

---

---

**Aluminium oxide primarily used for the  
production of aluminium — Method for  
the determination of flow time**

*Oxyde d'aluminium principalement utilisé pour la production  
d'aluminium — Méthode de détermination du temps d'écoulement*



Reference number  
ISO 18843:2015(E)

© ISO 2015



**COPYRIGHT PROTECTED DOCUMENT**

© ISO 2015, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
Ch. de Blandonnet 8 • CP 401  
CH-1214 Vernier, Geneva, Switzerland  
Tel. +41 22 749 01 11  
Fax +41 22 749 09 47  
copyright@iso.org  
www.iso.org

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Principle</b> .....	<b>1</b>
<b>4 Apparatus</b> .....	<b>1</b>
<b>5 Sample preparation</b> .....	<b>1</b>
<b>6 Procedure</b> .....	<b>2</b>
6.1 General.....	2
6.2 Number of determinations.....	2
6.3 Determination.....	2
<b>7 Reporting of results</b> .....	<b>2</b>
<b>8 Precision</b> .....	<b>2</b>
<b>9 Test report</b> .....	<b>3</b>
<b>Annex A (informative) Results of planned trial</b> .....	<b>5</b>
<b>Bibliography</b> .....	<b>6</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 226, *Materials for the production of primary aluminium*.

## Introduction

This International Standard is based on Australian Standard, AS 2879.9, *Alumina—Determination of flow time*.





# Aluminium oxide primarily used for the production of aluminium — Method for the determination of flow time

## 1 Scope

This International Standard sets out a method for determining the amount of time taken for a given quantity of smelter-grade alumina to flow by gravity through a precisely constructed standard funnel.

NOTE Variations in the apparatus and other test variables can create significant inter-laboratory differences in results. (See [Table A.1](#).)

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

AS 4538.2, *Guide to the sampling of alumina — Part 2: Preparation of samples*

## 3 Principle

The standard funnel is loaded with a specified mass of alumina. The time for the alumina to flow out of the funnel is determined.

## 4 Apparatus

### 4.1 General

The test may be carried out using manual or automatic timing. An automatic device is shown in [Figure 1](#).

**4.2 Funnel**, precisely constructed of a corrosion resistant metal, e.g. brass or aluminium, as shown in [Figure 2](#) with an abrasion resistant material, e.g. hardened stainless steel, insert with an outlet diameter of (3,95 to 4,00) mm; this diameter is critical.

**4.3 Stand**, a suitable device for supporting the funnel.

**4.4 Timing device**, either a stop watch or automated device capable of an accuracy of 1 s.

**4.5 Top-loading balance**, capable of weighing 100 g to the nearest 0,1 g.

**4.6 Sieve**, with apertures within the range (300 to 400)  $\mu\text{m}$  to remove abnormal oversize material.

**4.7 Container**, suitable for containing the test sample.

**4.8 Sealable container**, suitable for containing and storing the funnel.

## 5 Sample preparation

The analytical sample shall be conditioned by exposure to the laboratory atmosphere for a minimum of 2 h in a layer of 5 mm maximum thickness. The sample shall then be split as per AS 4538.2 into three

portions of approximately (105 to 120) g for testing. The sample shall then be screened through a sieve (4.6) and the oversize material discarded.

## 6 Procedure

### 6.1 General

This procedure is for manually timed determinations.

### 6.2 Number of determinations

Three determinations shall be carried out.

### 6.3 Determination

Each determination shall be carried out as follows.

- a) Ensure the funnel is clean with no surface oxides present and dry prior to use; otherwise flow times will not be reproducible. Frequent use has usually been found to be an adequate cleaning method.
- b) Set up the apparatus by placing the funnel (4.2) on the stand (4.3) in a vibration-free environment.
- c) Ensure that the funnel is secure on the stand and that the upper surface is precisely level.
- d) For apparatus not in frequent use, clean the funnel by passing several portions of alumina through it [see a)]. Discard this material prior to testing.
- e) Take one of the prepared samples (see [Clause 5](#)) and accurately weigh a test portion of  $(100 \pm 0,1)$  g and place into the container (4.7). (See [Clause 5](#).)
- f) Pour the test portion uniformly into the funnel while manually obstructing the outlet.
- g) Start the flow by removing the outlet obstruction and immediately commence timing. Stop the timing as soon as all the sample has passed through the funnel. Never tap the funnel.
- h) Repeat the procedure with the other two test portions ([Clause 5](#)).
- i) Remove the funnel from the stand and wipe the funnel clean with a dry cloth. Replace it in the sealable container (4.8) to prevent damage to the outlet orifice and minimize atmospheric oxidation of the inner surface.

## 7 Reporting of results

Report the average of the three results to the nearest second.

## 8 Precision

A test programme of the method in this International Standard was carried out in accordance with AS 2850. From the results of this programme, a within-laboratory repeatability ( $r$ ) and between-laboratory reproducibility ( $R$ ) at the 95 % confidence level as given in [Table 1](#) should be achieved.

NOTE Results of the test programme are given in [Annex A](#).

**Table 1 — Precision data for flow time**

Repeatability ( $r$ )	Reproducibility ( $R$ )
2,7	9,7

## 9 Test report


The test report shall include the following information:

- a) identification of the sample;
- b) a reference to this International Standard, i.e. ISO 18843;
- c) average flow time for the sample;
- d) the date on which the test was carried out;
- e) any factors during the course of the test which may have had an effect on the results.



**Figure 1 — Automatic flow funnel time apparatus**

Dimensions in millimetres

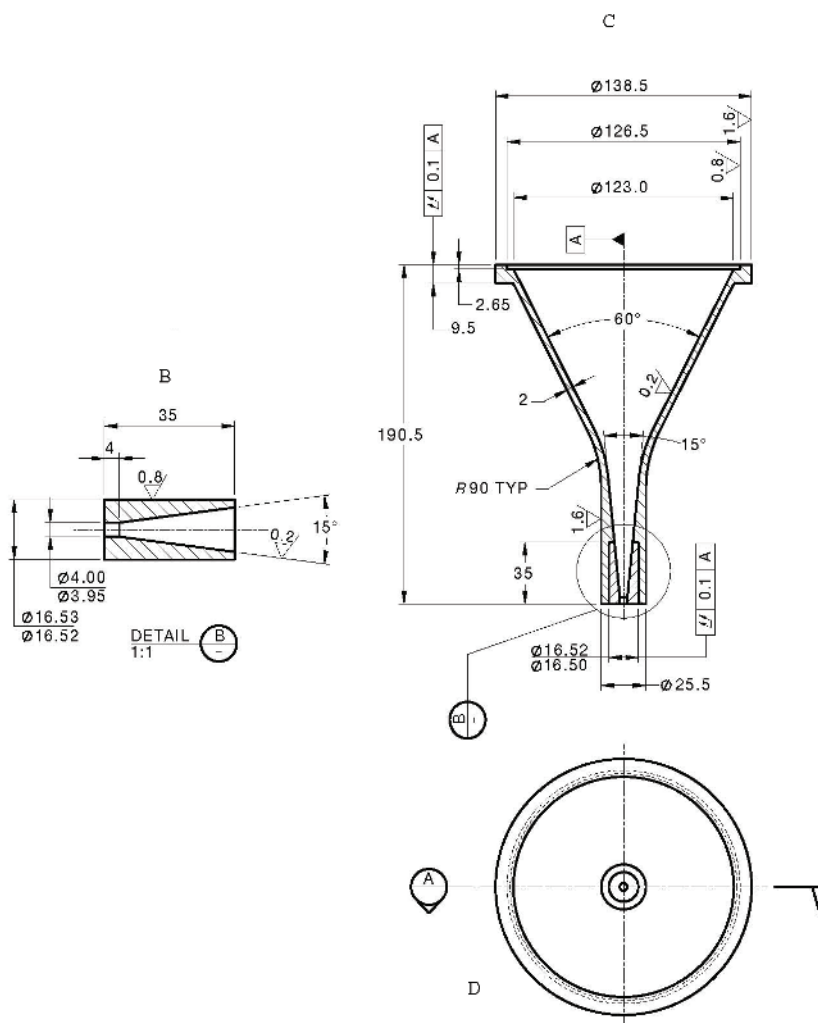

**Key**

- A datum line through the funnel
- B hardened insert with orifice shown *in situ* and as detail
- C vertical cross section
- D top view

R90 TYP = Radius 90 typical

$\boxed{A}$  = Datum line

$\sqrt{\quad}$  = Total run out (i.e. radius tolerance is 0,1 mm)

$\varnothing$  = Diameter

$\sqrt{\quad}$  = Finish (0,2 Fine, 1,6 Standard)

$\frac{\varnothing 4.00}{\varnothing 3.95}$  = Tolerance Max./Min.

FINISH 3,2 UND

TOLERANCE  $\pm 0,3$  UND

**Figure 2 — Flow funnel**

## Annex A (informative)

### Results of planned trial

A planned trial of the method in this International Standard was carried out in accordance with AS 2850. Samples of three smelter grade aluminas were analysed. Results were provided in quadruplicate by six laboratories. The within-laboratory ( $r$ ) and between-laboratory ( $R$ ) precision data (at 95 % confidence limits) and mean flow time values calculated from the results are given in [Table A.1](#).

**Table A.1 — Precision data obtained using test samples**

Sample	Mean flow time $s$	Repeatability $(r)$	Reproducibility $(R)$
S-109	47	1,5	7,3
S-110	68	3,3	10,7
S-111	82	2,9	10,8

## Bibliography

- [1] AS 4538.1, *Guide to the sampling of alumina — Part 1: Sampling procedures*
- [2] AS 2879.9, *Alumina—Determination of flow time*









# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™