

BS ISO 21048:2014



BSI Standards Publication

Plastics — Epoxy resins — Determination of 1,2-glycol content

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of ISO 21048:2014. It supersedes BS ISO 21048:2004 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/42, Fibre reinforced thermosetting plastics and prepregs.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 81810 3

ICS 83.080.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2014.

Amendments issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

ISO
21048

Second edition
2014-02-15

**Plastics — Epoxy resins —
Determination of 1,2-glycol content**

*Plastiques — Résines époxydes — Détermination de la teneur en
1,2-glycol*



Reference number
ISO 21048:2014(E)

© ISO 2014



COPYRIGHT PROTECTED DOCUMENT

© ISO 2014

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword.....	iv
Introduction.....	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Reagents	2
6 Apparatus	4
7 Procedure	4
8 Expression of results	5
9 Precision	5
10 Test report	6

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: Foreword - Supplementary information.

The committee responsible for this document is ISO/TC 61, *Plastics*, Subcommittee SC 12, *Thermosetting materials*.

This second edition cancels and replaces the first edition (ISO 21048:2004), which has been technically revised.

Introduction

In producing epoxy resin based on epichlorohydrin, impurities containing 1,2-glycol may be formed. Owing to the hydrophilic characteristics of 1,2-glycol, it is necessary to control the level of these impurities, since they could affect final properties such as electrical insulation. Additionally, these impurities could affect the speed of the curing reaction when using curing agents such as amines and acid anhydrides. Therefore, it is important to determine the 1,2-glycol content in epoxy resins for both resin manufacture and customer use.

Plastics — Epoxy resins — Determination of 1,2-glycol content

SAFETY STATEMENT — Persons using this document should be familiar with normal laboratory practice, if applicable. This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to ensure compliance with any regulatory requirements.

1 Scope

This International Standard specifies a method for the determination of the 1,2-glycol content in epoxy resins.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

ISO 5725-2, *Accuracy (trueness and precision) of measurement methods and results — Part 2: Basic method for the determination of repeatability and reproducibility of a standard measurement method*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

1,2-glycol

the 1,2-glycol group [-CH(OH)CH₂OH] in epoxy resins, the content of which is expressed in moles per kilogram of the epoxy resin

Note 1 to entry: This moiety is chemically equivalent to two OH groups.


Note 2 to entry: Other possible nomenclatures are vicinal-OH group, 1,2-dihydroxyl group, α -glycol group.

4 Principle

1,2-glycol is determined on the basis of the following reactions.

1,2-glycol is oxidized to aldehyde compounds by an excess of orthoperiodic acid (reaction 1), then potassium iodide is added to the reaction mixture in the presence of sulfuric acid (reaction 2). The generated iodine is then titrated by standardized sodium thiosulfate solution (reaction 3). The 1,2-glycol content is calculated from the sodium thiosulfate consumption.

Reaction 1

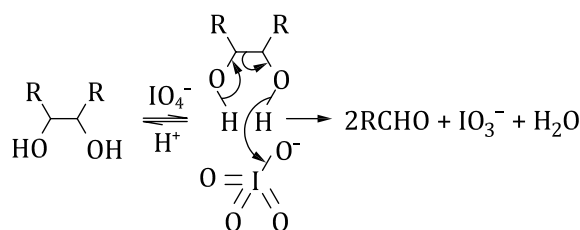

5 Reagents

Use reagents of recognized analytical grade, and water of grade 3 (as defined in ISO 3696) or better.

5.1 Chloroform.

WARNING — Chloroform is toxic. Avoid inhalation of its vapour. Prevent skin and eye contact. Work in a fume hood or in a well ventilated area. The threshold limit is 10 µg/g.

5.2 Methanol.

WARNING — Methanol is toxic. Avoid inhalation of its vapour. Prevent skin and eye contact. Work in a fume hood or in a well ventilated area. The threshold limit is 200 µg/g.

5.3 Benzyltrimethylammonium hydroxide, 40 % (by mass) solution in methanol.

5.4 Acetic acid.

5.5 Orthoperiodic acid.

5.6 Orthoperiodic acid, 0,2 mol/l solution.

5.6.1 Preparation

Weigh 2,70 g to 2,75 g of orthoperiodic acid into a 500 ml beaker (6.7) and dissolve in 450 ml of methanol (5.2), mixing with a magnetic stirrer (6.2). Place the pH electrode (6.3) into the solution. Neutralize the solution to pH 7,0 by adding benzyltrimethylammonium hydroxide solution (5.3) slowly with stirring. Add 15 ml of acetic acid (5.4) and 5 ml of water, using a 20 ml graduated glass cylinder (6.8), and, using a 500 ml volumetric flask (6.9), fill to the mark with methanol.

5.7 Sulfuric acid, 10 % (by mass) solution.

Add 10 g of sulfuric acid dropwise to 90 g of water with stirring.

5.8 Potassium iodide, 20 % (by mass) solution.

Dissolve 20 g of potassium iodide in 80 g of water.

5.9 Anhydrous sodium carbonate.

5.10 Potassium iodate.

5.11 Oxygen-free water.

5.11.1 Preparation

Put grade 3 water (as specified in ISO 3696) into the conical flask (6.5), boil it for about 5 min to expel dissolved oxygen and allow it to cool to room temperature by sealing with nitrogen gas. Alternatively, it is permissible to expel dissolved oxygen by sparging high purity nitrogen gas for about 15 min.

5.12 Sodium thiosulfate, 0,1 mol/l solution.

5.12.1 Preparation

Weigh out 26,0 g of sodium thiosulfate 5-hydrate and 0,20 g of anhydrous sodium carbonate (5.9). Add 1 l of oxygen-free water (5.11) and store in an airtight container. Allow to stand for two days before using.

5.12.2 Standardization

Heat the required amount of potassium iodate (reference material for volumetric analysis) (5.10) at 130 °C for about 2 h, and allow it to cool in a desiccator. Weigh 0,9 g to 1,1 g of the dried KIO_3 to the nearest 0,1 mg into a 250 ml volumetric flask (6.9), dissolve in water and fill to the mark with water. Using a pipette, place 25 ml of the solution in a 300 ml conical flask (6.5). Add 2 g of potassium iodide and 2 ml of sulfuric acid (1 + 1) to the conical flask, stopper immediately, shake gently, and allow to stand for 5 min in the dark. As an indicator, add 0,5 ml of starch solution (5.13), and titrate with 0,1 mol/l sodium thiosulfate solution (5.12). Add another 0,5 ml of the starch solution when nearing the end point. Continue to titrate until the blue colour of the solution just disappears.

Separately, measure 25 ml of water (using a pipette) and 2 g of potassium iodide into a 300 ml conical flask (6.5), then add 2 ml of sulfuric acid (1 + 1), stopper immediately, shake gently, and allow to stand for 5 min in the dark. Carry out a blank titration by the same procedure as described, and use the result to correct the volume needed for the standardization titration.

5.12.3 Calculation of concentration

Calculate the concentration from the following equation:

$$c = \frac{a \times p}{0,003\,566\,7 \times (V_2 - V_1) \times 10\,000} \quad (1)$$

where

- c is the concentration of the sodium thiosulfate solution, expressed in moles per litre;
- a is the mass of potassium iodate, expressed in grams;
- p is the purity of the potassium iodate, expressed in percent;
- 0,003 566 7 is the mass of potassium iodate equivalent to 1 ml of 0,1 mol/l sodium thiosulfate solution;
- V_1 is the volume of sodium thiosulfate solution used in the titration, expressed in millilitres;
- V_2 is the volume of sodium thiosulfate solution used in the blank titration, expressed in millilitres.

Round the result to three significant figures.

5.13 Starch solution, 1 % (by mass).

Dissolve 1 g of water-soluble starch in 99 g of hot water.

6 Apparatus

Usual laboratory apparatus, plus the following.

6.1 **Analytical balance**, accurate to 0,1 mg.

6.2 **Magnetic stirrer**, equipped with a polytetrafluoroethylene-coated bar.

6.3 **pH-meter**, accurate to 0,1 pH-units, calibrated in advance, equipped with a glass combination electrode and electrode stand.

6.4 **Burette**, 50 ml.

6.5 **Conical flask**, 300 ml, with a ground-glass stopper.

6.6 **Pipettes**, 5 ml, 20 ml and 25 ml.

6.7 **Beaker**, 500 ml.

6.8 **Graduated glass cylinders**, 20 ml and 100 ml.

6.9 **Volumetric flasks**, 250 ml and 500 ml.

7 Procedure

7.1 Select the mass of the test portion in accordance with the expected 1,2-glycol content (see [Table 1](#)).

Table 1 — Mass of test portion

1,2-glycol content, w mol/kg	Mass of test portion g
$w < 0,01$	10
$0,01 \leq w < 0,05$	8
$0,05 \leq w < 0,1$	4
$0,1 \leq w < 0,2$	2
$0,2 \leq w$	1

7.2 Weigh the test portion to the nearest 0,1 mg into a 300 ml conical flask ([6.5](#)). Add 25 ml of chloroform ([5.1](#)) and warm the mixture to obtain a clear solution. Then cool to ambient temperature.

7.3 Using a pipette, add 25 ml of 0,2 mol/l orthoperiodic acid solution ([5.6](#)) to the conical flask. Wet a ground-glass stopper with water and stopper the conical flask tightly. Mix well and allow the reaction mixture to stand at room temperature for 2 h.

7.4 Add 100 ml of cold water to the conical flask and then stopper again. Mix vigorously, using a magnetic stirrer, for 30 s.

7.5 Wash the inside of the conical flask and the glass stopper with a small quantity of water. Using a pipette, add 5 ml of 10 % sulfuric acid solution (5.7).

7.6 Using a pipette, add 20 ml of 20 % potassium iodide solution (5.8).

7.7 Mix well for 30 s with a magnetic stirrer. Titrate with 0,1 mol/l sodium thiosulfate solution (5.12), with stirring. As an indicator, add about 1 ml of starch solution (5.13) when the colour of the solution becomes pale yellow which shows the end point is near.

7.8 Continue to titrate until the blue colour of the solution just disappears.

7.9 Carry out a blank test, following the same procedure and using the same reagents, but omitting the test portion.

8 Expression of results

Calculate the 1,2-glycol content of the sample from the following equation:

$$w = \frac{(V_2 - V_1) \times c}{2m_0} \quad (2)$$

where

w is the 1,2-glycol content of the sample, expressed in moles per kilogram;

m_0 is the mass of the test portion, expressed in grams;

V_1 is the volume of sodium thiosulfate solution used in the titration of the test portion, expressed in millilitres;

V_2 is the volume of sodium thiosulfate solution used in the blank titration, expressed in millilitres;

c is the concentration of the sodium thiosulfate solution, expressed in moles per litre.

9 Precision

Precision data were determined from a round-robin experiment organized in January 2000 involving eight laboratories in Japan. Three commercial epoxy resins with different levels of 1,2-glycol content were tested and the results were analysed in accordance with ISO 5725-2.

The repeatability and reproducibility calculated from the experiments are given in [Table 2](#).

Table 2 — Precision data

Sample	1,2-glycol content (averaged) mol/kg	Repeatability s_r	Reproducibility s_R
Sample A (liquid BPA type epoxy resin)	0,029	0,002	0,003
Sample B (liquid BPA type epoxy resin)	0,063	0,002	0,002
Sample C (solid BPA type epoxy resin)	0,24	0,02	0,02

10 Test report

The test report shall include the following:

- a) a reference to this International Standard;
- b) all details necessary for identification of the sample;
- c) the test result;
- d) the date of the test;
- e) any other relevant information.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™