

Wood preservatives — Accelerated ageing of treated wood prior to biological testing —

Part 1: Evaporative ageing procedure

This European Standard EN 73 has the status of a
British Standard

UDC 674.04:620.193

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW



Cooperating organizations

The European Committee for Standardization, under whose supervision this European Standard was prepared, comprises the national standards organizations of the following Western European countries.

Austria	Oesterreichisches Normungsinstitut
Belgium	Institut belge de normalisation
Denmark	Dansk Standardiseringsraad
Finland	Suomen Standardisoimisliitto, r.y.
France	Association française de normalisation
Germany	Deutsches Institut für Normung e.V.
Greece	Hellenic Organization for Standardization
Iceland	Icelandic Council for Standardization
Ireland	National Standards Authority of Ireland
Italy	Ente Nazionale Italiano di Unificazione
Luxemburg	Inspection des travaux et des mines
Netherlands	Nederlands Normalisatie-instituut
Norway	Norges Standardiseringsforbund
Portugal	Instituto Português de Qualidade
Spain	Instituto Español de Normalización
Sweden	Standardiseringskommissionen i Sverige
Switzerland	Association suisse de normalisation
United Kingdom	British Standards Institution

This British Standard, having been prepared under the direction of the Wood Preservations Standards Policy Committee, was published under the authority of the Board of BSI and comes into effect on 31 May 1989

© BSI 12-1999

First published January 1979
First revision May 1989

The following BSI references relate to the work on this standard:
Committee reference WPC/10
Draft for comment 85/52681 DC

ISBN 0 580 17300 3

Amendments issued since publication

Amd. No.	Date of issue	Comments

Contents

	Page
Cooperating organizations	Inside front cover
National foreword	ii
Brief history	2
Text of EN 73	3
National appendix A	Inside back cover

National foreword

This Part of BS 5761 has been published under the direction of the Wood Preservation Standards Policy Committee.

This Part of BS 5761 was first published in 1979. This revision supersedes the 1979 edition which is withdrawn.

This Part of BS 5761 is identical with EN 73:1988 “*Wood preservatives; Accelerated ageing of treated wood prior to biological testing; Evaporative ageing procedure*”, published by the European Committee for Standardization (CEN).

EN 73:1988 was prepared as a result of discussions in CEN Technical Committee 38 “Methods of test of wood preservatives”, in which the UK participated.

National appendix A gives the constitution of the committee responsible for the UK participation in the preparation of this standard.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN title page, pages 2 to 6, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

Key words: Wood, wood preservatives, protection against the pest, ageing tests, materials, evaporation, test specimen.

English version

Wood preservatives —
Accelerated ageing of treated wood
prior to biological testing —
Evaporative ageing procedure

Produits de préservation des bois; Epreuves de
vieillesse accélérée des bois traités avant
essais biologiques; Epreuve d'évaporation

Holzschutzmittel; Beschleunigte Alterung von
behandeltem Holz vor biologischen Prüfungen;
Verdunstungsbeanspruchung

This European Standard was accepted by CEN on 4 December 1987. CEN members are bound to comply with the requirements of the CEN/CENELEC Rules which stipulate the condition for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Central Secretariat or to any CEN member.

This European Standard exists in the official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to CEN Central Secretariat has the same status as the official versions.

CEN members are the national standards organizations of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxemburg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Brief history

This European Standard was drawn up by the Technical Committee CEN/TC 38 "Methods of test for wood preservatives", the Secretariat of which is held by AFNOR.

According to the Common CEN/CENELEC Rules, the following countries are bound to implement this European Standard:

Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxemburg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

Contents

	Page
Brief history	2
1 Object	3
2 Principle	3
3 Equipment	3
4 Test specimens	3
5 Procedure	3
6 Destination of the test specimens after the evaporative ageing procedure	4
7 Reference in the test reports	4
Figure 1 — Movement of test specimens in a compartment containing more than one test specimen	4
Figure 2 — Rotation of test specimen with four treated surfaces through an angle of 180° on its small horizontal axis	5
Figure 3 — Rotation of test specimen with only one treated surface through an angle of 180° on its vertical axis	5

1 Object

This European Standard describes an evaporative ageing procedure, applicable to test specimens of wood which have previously been treated with a preservative, in order to evaluate any loss in effectiveness when these test specimens are subsequently subjected to biological tests, as compared with test specimens which have not undergone any evaporative ageing procedure.

2 Principle

Exposure, for a specified period, in a dust-free current of air of a defined velocity and temperature, of test specimens which have been prepared for biological testing of their effectiveness against either fungi or insects using the appropriate standard methods.

3 Equipment

3.1 Wind tunnel, compartmented and fitted with devices for heating and distributing air.

The air shall be dust-free and shall not be polluted by chemical products which could have an effect on the test results.

The heating and distribution devices shall be such that the temperature and air velocity are maintained constant and uniform in each compartment.

The air leaving the tunnel shall be led away in such a manner that it cannot re-enter the tunnel.

3.2 Temperature recorder capable of measuring a temperature of $40\text{ °C} \pm 2\text{ °C}$.

3.3 Anemometer capable of measuring an air velocity of $1\text{ m/s} \pm 0,1\text{ m/s}$.

3.4 Conditioning room or environmental chamber at a temperature of $20\text{ °C} \pm 2\text{ °C}$ and $65\% \pm 5\%$ relative humidity for conditioning the test specimens after evaporative ageing.

4 Test specimens

4.1 Definition and origin

The test specimens and their preparation are defined in the standards concerning the biological tests to which they are intended to be subjected.

The evaporative procedure is carried out, at the latest, 3 months after the end of the conditioning period that follows the treatment of the test specimens described in the relevant biological test standard.

4.2 Number of test specimens

The number of test specimens shall allow the relevant biological tests to be carried out in accordance with the instructions in the appropriate standards, bearing in mind that the evaporative ageing procedure shall be applied equally to treated test specimens which are subjected to biological agents and to control test specimens. The control test specimens shall be of the following kinds:

- treated control test specimens that will not be subjected to attack by biological agents after the evaporative ageing procedure. These will serve as controls for changes in mass in those tests in which this factor is taken into consideration.
- untreated control specimens which, after evaporative ageing, are subjected to the test by biological agents, to check any variation in the behaviour of untreated wood. These test specimens are only necessary for biological tests using insects.
- control test specimens of timber treated with solvent or diluent if necessary.

5 Procedure

5.1 Arrangement of the test specimens

Place the test specimens in the compartments, resting them with one of their faces on the base so that none of the other faces is less than 10 mm from the side partitions. The faces parallel to the grain of the wood shall be parallel to the general direction of air flow and they shall be at least 10 mm from the corresponding faces of the adjacent test specimens. Do not place in the same compartment either test specimens treated with different products or with different concentrations of the same product or treated and control specimens. Arrange the test specimens according to type, as follows.

5.1.1 Test specimens treated on all surfaces¹⁾

Rest the test pieces on one of the small faces parallel to the grain of wood with the faces that are perpendicular to the grain of wood at least 20 mm away from the corresponding faces of adjacent test pieces.

5.1.2 Test pieces for which the faces perpendicular to the grain of wood are sealed before treatment²⁾

Arrange the test pieces as in 5.1.1. The sealed faces may, however, be brought closer together.

¹⁾ For example, test specimens intended for tests determining the toxic values (basidiomycetes, soft rot fungi, *Anobium punctatum* by larval transfer and by observing egg-laying, and the rate of survival of larvae, *Hylotrupes bajulus*, termites).

²⁾ For example, test specimens intended for tests for determining the preventive action against *Lyctus brunneus* or *Hylotrupes bajulus*.

5.1.3 Test specimens with one treated face only³⁾

Rest the test specimens on the opposite face to that which has been treated.

5.2 Starting and adjustment of the apparatus

With the test specimens in position, establish an air current controlled at a temperature of $40\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ which emerges at a speed of $1\text{ m/s} \pm 0,1\text{ m/s}$. Check this velocity with an anemometer, at the outlet, on the axis of each compartment.

5.3 Procedure

Maintain the test specimens in the arrangement specified in 5.1 and under the conditions specified in 5.2 for a complete week (7 days).

In order to obtain homogeneous evaporation from all the treated faces of a test specimen, rotate the test specimen through an angle of 180° on its small horizontal axis on the first day of each week (see 5.4) (see Figure 2).

Test specimens with only one treated surface shall be rotated through an angle of 180° on their vertical axis (see Figure 3).

If a compartment contains more than one test specimen, at the same time as rotating the test specimens, change the position of the specimens within this compartment, the method depending on the number of test specimens which it contains and on the duration of the procedure (see Figure 1).

5.4 Exposure period in the tunnel

The duration of the exposure period is 12 weeks. For certain specific applications, alternative periods of ageing may be used, in which case, the ageing period should be mentioned in the report of the biological test concerned.

5.5 Conditioning of the test specimens

At the end of the exposure period (5.4) allow the specimens to stabilize in the conditioning room (3.4) for a week.


6 Destination of the test specimens after the evaporative ageing procedure

After completion of the ageing procedure, tests specimens shall be subjected to biological tests within three months. Such biological tests shall be carried out in accordance with the procedures described in the relevant standard, commencing with the clause entitled "Exposure of the test specimens to insects (or fungi)".



7 Reference in the test reports

Quote the evaporative ageing procedure by giving the number of this European Standard (i.e. EN 73) and the duration(s) of evaporative ageing in the test report of each biological test.

The duration and conditions of storage of the test specimen between initial preparation and the start of the ageing procedure shall also be reported.

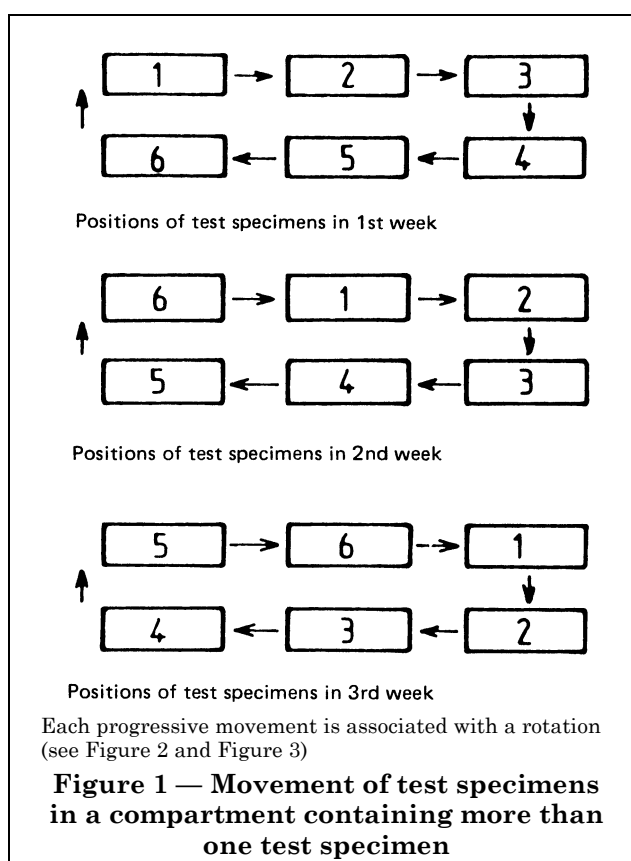

³⁾ For example, test specimens intended for the test determining preventive action against termites.

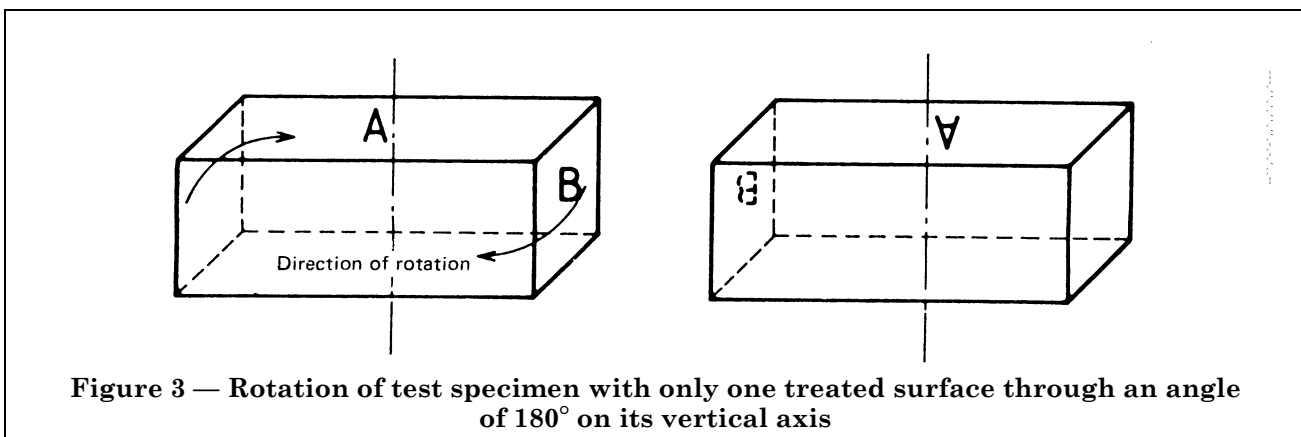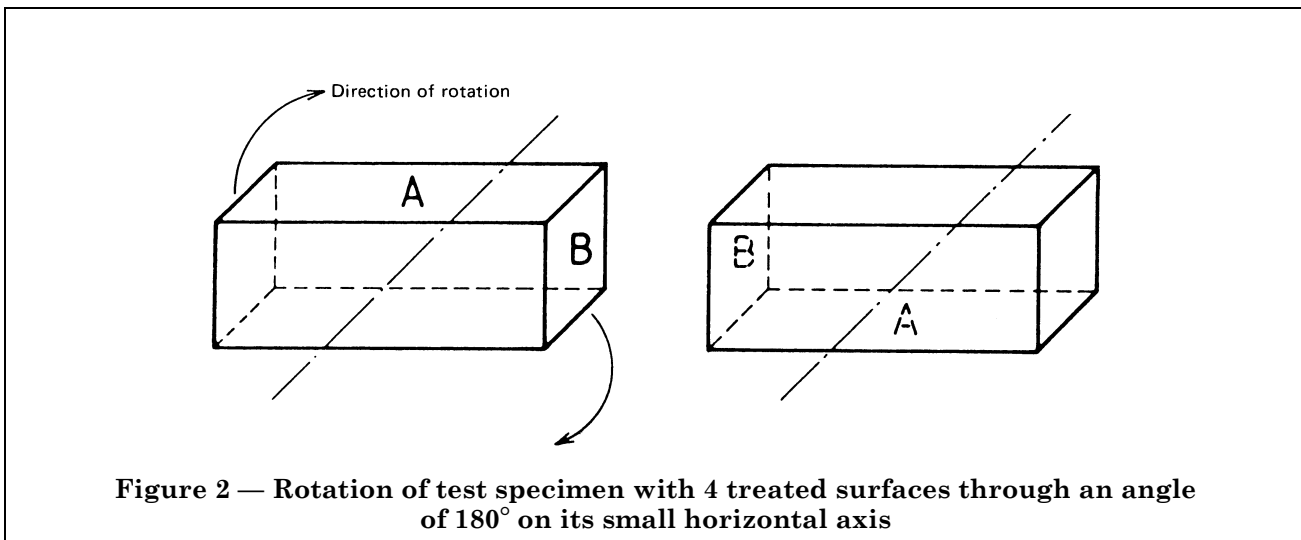

National appendix A

The United Kingdom participation in the preparation of this European Standard was entrusted by the Wood Preservation Standards Policy Committee (WPC/-) to Technical Committee WPC/10, upon which the following bodies were represented:

Association of Consulting Scientists
British Pest Control Association
British Wood Preserving Association
Chemical Industries Association
Department of the Environment — Building Research Establishment
Timber Research and Development Association

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.