

Methods of

# Sampling and test for sodium and potassium silicates for industrial use —

## Part 4: Determination of carbonate content

[ISO title: Sodium and potassium silicates for industrial use —  
Determination of carbonates content — Gas-volumetric method]

NOTE It is recommended that this Part be read in conjunction with the information in the  
“*General introduction*” published separately as BS 6092-0.

UDC 661.683/.684:[546.32'284 + 546.33'284]:543.279.062:546.264

# National foreword

This Part of BS 6092 is identical with ISO 1691 “*Sodium and potassium silicates for industrial use — Determination of carbonates content — Gas-volumetric method*”, published in 1976 by the International Organization for Standardization (ISO).

**Terminology and conventions.** The text of the International Standard has been approved as suitable for publication as a British Standard without deviation. Some terminology and certain conventions are not identical with those used in British Standards; attention is especially drawn to the following.

The comma has been used throughout as a decimal marker. In British Standards it is current practice to use a full point on the baseline as the decimal marker.

Wherever the words “International Standard” appear, referring to this standard, they should be read as “British Standard”.

## Cross-references

There is no British Standard corresponding directly to ISO 1686 to which reference is made in 3.3. Technically equivalent information on sampling is given in BS 6092-0.

The standards listed in the Annex are intended for information only. Corresponding British Standards are listed in BS 6092-0.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

## Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, pages 1 to 6, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

This British Standard, having been prepared under the direction of the Chemicals Standards Committee, was published under the authority of the Executive Board and comes into effect on 27 February 1981

© BSI 11-1999

The following BSI references relate to the work on this standard:  
Committee reference CIC/22  
Draft for comment 73/55424 DC

ISBN 0 580 12038 4

## Amendments issued since publication

| Amd. No. | Date of issue | Comments |
|----------|---------------|----------|
|          |               |          |
|          |               |          |
|          |               |          |
|          |               |          |

# Contents

|  | Page               |
|--|--------------------|
| National foreword  | Inside front cover |
| 1 Scope and field of application   | 1                  |
| 2 Reference  | 1                  |
| 3 Preliminary test   | 1                  |
| 4 Sodium or potassium silicates containing neither sulphides nor chlorates           | 1                  |
| 5 Sodium or potassium silicates containing sulphides                                 | 4                  |
| 6 Sodium or potassium silicates containing chlorates                                 | 5                  |
| 7 Test report  | 5                  |
| Annex ISO Publications relating to sodium and potassium silicates for industrial use | 6                  |
| Figure — Apparatus for gas-volumetric determination of carbonates content            | 3                  |
| Publications referred to   | Inside back cover  |



## 1 Scope and field of application

This International Standard specifies a gas-volumetric method for the determination of the carbonates content, expressed, respectively, as sodium carbonate or potassium carbonate, of sodium and potassium silicates for industrial use.

Three cases, defined by a preliminary test, are envisaged:

**1.1** Sodium or potassium silicates containing neither sulphides nor chlorates.

**1.2** Sodium or potassium silicates containing sulphides.

**1.3** Sodium or potassium silicates containing chlorates.

## 2 Reference

ISO 1686, *Sodium and potassium silicates for industrial use — Samples and methods of test — General*.

## 3 Preliminary test

### 3.1 Principle

Boiling of an acidified test portion containing methyl orange and with a lead acetate paper strip in the vapour. The presence of sulphides produces blackening of the paper and the presence of chlorates decolorizes the methyl orange.

### 3.2 Reagents

During the analysis, use only reagents of recognized analytical grade and only distilled water or water of equivalent purity, free from carbon dioxide.

**3.2.1** *Hydrochloric acid*, approximately 6 N solution.

**3.2.2** *Methyl orange*, 0,5 g/l solution.

**3.2.3** *Lead acetate paper*, cut into strips about 15 mm × 80 mm.

### 3.3 Procedure

Place about 5 g of the test sample (see ISO 1686) in a 300 ml conical flask. Add 150 ml of water and 3 drops of the methyl orange solution (**3.2.2**).

Neutralize with the hydrochloric acid solution (**3.2.1**) and add an excess of 5 ml of this acid.

Fix a lead acetate paper strip (**3.2.3**) inside the neck of the conical flask, curling it over the outside of the flask.

Boil the solution for 5 min and select the procedure to be followed according to the following table.

| Appearance |           | Case number | Procedure |
|------------|-----------|-------------|-----------|
| solution   | paper     |             |           |
| red        | white     | 1.1         | Clause 4  |
| red        | blackened | 1.2         | Clause 5  |
| colourless | white     | 1.3         | Clause 6  |

## 4 Sodium or potassium silicates containing neither sulphides nor chlorates

### 4.1 Principle

Measurement of the volume of carbon dioxide evolved from a test portion by reaction with a hydrochloric acid solution.

### 4.2 Reagents

Reagents specified in **3.2** and

**4.2.1** *Distilled water*, or water of equal purity, free from carbon dioxide at ambient temperature.

Eliminate any carbon dioxide present either by boiling the water for 10 min and cooling in the absence of atmospheric carbon dioxide or, more simply, by bubbling air free from carbon dioxide through it for 15 min: (Free the air from carbon dioxide by passing it through a column containing pellets of sodium hydroxide.)

Store the water in the absence of atmospheric carbon dioxide.

**4.2.2** *Hydrochloric acid*,  $\rho$  approximately 1,19 g/ml, about 38 % (m/m) or approximately 12 N solution.

**4.2.3** *Sodium chloride*, coloured acid solution.

Dissolve 263 g of sodium chloride in water. Add 5 ml of a sulphuric acid solution,  $\rho$  approximately 1,84 g/ml, about 96 % (m/m) or approximately 36 N solution. Dilute to 1 000 ml, add a small amount of the methyl orange solution (**3.2.2**) and mix.

**4.2.4** *Sodium hydroxide*,  $\rho$  approximately 1,22 g/ml, about 20 % (m/m) or approximately 6 N solution.

Dissolve 120 g of sodium hydroxide in water. Cool to ambient temperature, dilute to 500 ml and mix thoroughly.

### 4.3 Apparatus

Ordinary laboratory apparatus and

**4.3.1** *Apparatus* as shown in the Figure.

## 4.4 Procedure

### 4.4.1 Test portion

Weigh, to the nearest 0,001 g, 4,9 to 5,1 g of the test sample (see ISO 1686).

### 4.4.2 Determination

#### 4.4.2.1 PREPARATION OF THE APPARATUS

Fill the burette (B) of the apparatus (4.3.1) with the sodium chloride solution (4.2.3), through the levelling bottle (F).

Pour into the absorber (C) the sodium hydroxide solution (4.2.4). (Renew this solution after approximately 100 determinations.)

The burette (B) and the absorber (C) being filled up to the stopcock ( $R_1$ ) and the mark ( $a$ ) respectively, and the stopcocks ( $R_1$ ) and ( $R_2$ ) being closed, quantitatively transfer the test portion (4.4.1), previously mixed with 10 ml of water, to the flask (A). Dilute to approximately 40 ml so as to reduce the dead space to a volume slightly greater than 100 ml [volume above the level of the liquid in the flask (A) plus the volume of the condenser tube (D) up to the cock ( $R_1$ )].

Place in the flask (A) three porcelain or glass beads of diameter approximately 2 mm, together with a few pieces of pumice stone, the volume of which should be approximately equal to that of the beads. Close the flask and the stopcock (R).

Open the stopcock ( $R_1$ ) to connect the flask (A) and the burette (B) and lower the levelling bottle (F).

Check the tightness of the apparatus by appropriately handling the cocks and the levelling bottle.

#### 4.4.2.2 EVOLUTION AND MEASUREMENT OF CARBON DIOXIDE


By means of the dropping funnel, pour 20 ml of the hydrochloric acid solution (4.2.2) into the flask (A), taking care to avoid loss of gas.

Heat the flask and maintain the solution at boiling point for 5 min while running cold water through the condenser. Then stop heating and add sodium chloride solution (4.2.3) by means of the funnel, lowering the levelling bottle (F) still further so as to make the solution in the flask (A) rise in the condenser tube up to the cock ( $R_1$ ). Then close the latter and wait 5 min to allow the gas to reach the temperature of the water-jacket.

Measure the volume of gas,  $V_0$ , at atmospheric pressure  $P$  and at the temperature  $t$  of the water in the jacket. For this purpose, move the levelling bottle (F) so as to bring the sodium chloride solution (4.2.3) to the same level both in the flask and in the burette (B); read the volume of the latter.

Adjust the cocks ( $R_1$ ) and ( $R_2$ ) so that the burette (B) and the absorber (C) are connected, then raise the levelling bottle (F) so that the gas is transferred to the absorber where the carbon dioxide is absorbed. Then transfer the non-absorbed gas back to the burette (B) by lowering the levelling bottle (F) and, after adjusting the level of the sodium hydroxide solution (4.2.4) to the gauge mark ( $a$ ) on the absorber (C), close the cock ( $R_2$ ) and read the volume of the residual gas. Repeat these operations until a constant volume  $V_1$  is obtained.

The difference ( $V_0 - V_1$ ) represents the volume of the carbon dioxide contained in the test portion, measured at atmospheric pressure and at the temperature of the water-jacket.

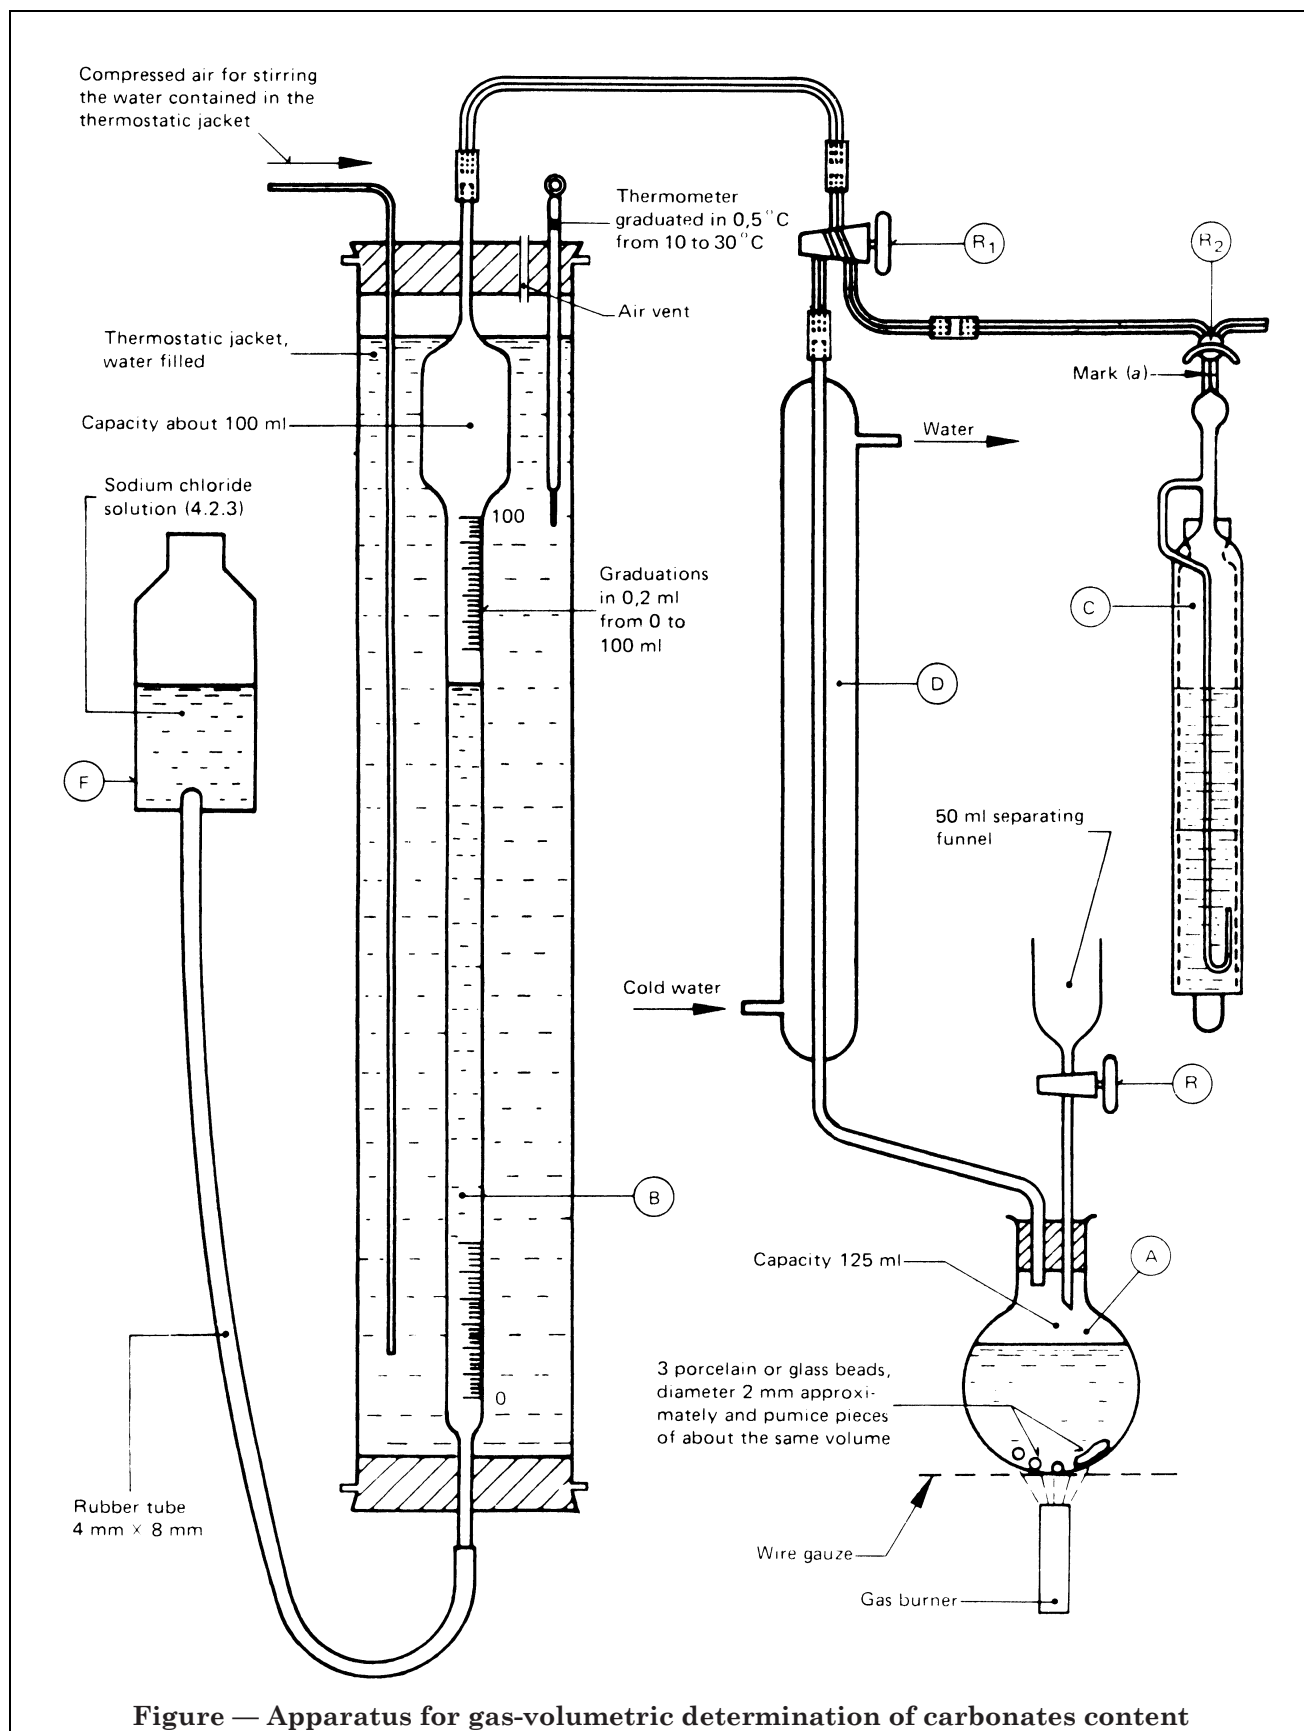

#### 4.5 Expression of results

The content of sodium carbonate ( $\text{Na}_2\text{CO}_3$ ) or of potassium carbonate ( $\text{K}_2\text{CO}_3$ ), expressed as a percentage by mass, is given, according to the case, by the formulae

$$\begin{aligned} \text{Na}_2\text{CO}_3, \% (m/m) \\ &= (V_0 - V_1) \times \frac{273}{273 + t} \times \frac{P - p}{1013} \times 0,001\,98 \times \frac{106}{44} \times \frac{100}{m} \\ &= 0,128 \times \frac{P - p}{273 + t} \times \frac{V_0 - V_1}{m} \end{aligned}$$

$$\begin{aligned} \text{K}_2\text{CO}_3, \% (m/m) \\ &= (V_0 - V_1) \times \frac{273}{273 + t} \times \frac{P - p}{1013} \times 0,001\,98 \times \frac{138,2}{44} \times \frac{100}{m} \\ &= 0,167 \times \frac{P - p}{273 + t} \times \frac{V_0 - V_1}{m} \end{aligned}$$

where

$V_0$  is the volume, in millilitres, of the gas before absorption of the carbon dioxide;

$V_1$  is the volume, in millilitres, of the gas after absorption of the carbon dioxide;

$t$  is the temperature, in degrees Celsius, of the water contained in the water-jacket;

$P$  is the atmospheric pressure, in millibars, during the determination;

NOTE If the atmospheric pressure  $P$  is measured in pascals (or kilopascals), multiply this value by 0,01 (or by 10) to convert it to millibars.

$p$  is the vapour pressure, in millibars, of the solution sodium chloride (4.2.3) at the temperature of the water contained in the jacket. Vapour pressures are given in the table below for temperatures from 10 to 30 °C:

| Temperature, $t$ °C       | 10 | 12 | 14 | 16 | 18 | 20 | 22 | 24 | 26 | 28 | 30 |
|---------------------------|----|----|----|----|----|----|----|----|----|----|----|
| Vapour pressure, $p$ mbar | 11 | 12 | 13 | 15 | 17 | 19 | 21 | 24 | 27 | 30 | 33 |

$m$  is the mass, in grams, of the test portion (4.4.1);

0,001 98 is the factor for the conversion of the volume of carbon dioxide, in millilitres, to the mass of carbon dioxide, in grams;

$\frac{106}{44}$  is the factor for the conversion of the mass of carbon dioxide to the corresponding mass of  $\text{Na}_2\text{CO}_3$ ;

$\frac{138,2}{44}$  is the factor for the conversion of the mass of carbon dioxide to the corresponding mass of  $\text{K}_2\text{CO}_3$ .

#### 4.6 Precision of the method

The results obtained with this method are reproducible to the nearest  $\pm 0,04$  % ( $m/m$ ) in absolute value.

### 5 Sodium or potassium silicates containing sulphides

In the case of sodium or potassium silicates containing sulphides, the acidification of the product causes the liberation of hydrogen sulphide which is absorbed in the sodium hydroxide solution at the same time as the carbon dioxide, giving a result in excess of the true value. A preliminary treatment of the test portion is therefore necessary. The method is applicable to products containing up to 5 g of sulphides, expressed as  $\text{Na}_2\text{S}$ , per kilogram.

#### 5.1 Principle

Oxidation of the sulphides by hydrogen peroxide and boiling of the test portion before acidification.

Determination according to the method specified in clause 4.

#### 5.2 Reagents

Reagents specified in 3.2 and 4.2, and:

5.2.1 Hydrogen peroxide, 30 % ( $m/m$ ).

#### 5.3 Apparatus

See 4.3.

#### 5.4 Procedure

Follow the procedure specified in 4.4, applying the following modifications:

— in 4.4.2.1, 4th paragraph, place in the flask (A), before the porcelain or glass beads, 5 drops of the hydrogen peroxide solution (5.2.1);

— at the end of 4.4.2.1, open the cock ( $R_1$ ), lower the levelling bottle (F) and boil the contents of the flask (A) for 5 min, while running cold water through the condenser. Cool to a temperature slightly above ambient temperature, to prevent the liquid in the burette from being drawn into the condenser.

#### 5.5 Expression of results

See 4.5.



## 6 Sodium or potassium silicates containing chlorates

In the case of sodium or potassium silicates containing chlorates, acidification of the product causes the liberation of chlorine, which is absorbed in the sodium hydroxide solution at the same time as the carbon dioxide, giving a result in excess of the true value. A preliminary treatment of the test portion is therefore necessary.

The method is applicable to products containing up to 10 g of chlorates, expressed as  $\text{NaClO}_3$ , per kilogram.

### 6.1 Principle

Prior reduction of the chlorates to chlorides by addition of iron(II) sulphate.

Determination according to the method specified in clause 4.

### 6.2 Reagents

Reagents specified in 3.2 and 4.2, and:

**6.2.1** *Iron(II) sulphate* solution, containing 28 g of iron(II) sulphate heptahydrate ( $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ ) and 4 drops of the hydrochloric acid solution (3.2.1) in 100 ml.

### 6.3 Apparatus

See 4.3.

### 6.4 Procedure

Follow the procedure specified in 4.4.3, applying the following modification:

— in 4.4.2.1, 3rd paragraph, place in the flask (A), after the test portion (4.4.1), 5 ml of the iron(II) sulphate solution (6.2.1).

### 6.5 Expression of results

See 4.5.

## 7 Test report

The test report shall include the following particulars:

- a) the reference of the method used;
- b) the results and the method of expression used;
- c) any unusual features noted during the determination;
- d) any operation not included in this International Standard or in the International Standard to which reference is made, or regarded as optional.

**Annex ISO publications relating to sodium and potassium silicates for industrial use**

ISO 1686, *Samples and methods of test — General.*

ISO 1687, *Determination of density at 20 °C of samples in solution — Methods using density hydrometer and pycnometer.*

ISO 1688, *Determination of dry matter — Gravimetric method.*

ISO 1689, *Calculation of the ratio  $\frac{\text{SiO}_2}{\text{Na}_2\text{O}}$  or  $\frac{\text{SiO}_2}{\text{K}_2\text{O}}$ .*

ISO 1690, *Determination of silica content — Gravimetric method by insolubilization.*

ISO 1691, *Determination of carbonates content — Gas-volumetric method.*

ISO 1692, *Determination of total alkalinity — Titrimetric method.*

ISO 2122, *Preparation of solution of products not easily soluble in boiling water and determination of matter insoluble in water.*

ISO 2123, *Determination of dynamic viscosity.*

ISO 2124, *Determination of silica content — Titrimetric method.*

ISO 3200, *Determination of sulphates content — Barium sulphate gravimetric method.*

ISO 3201, *Determination of iron content — 1,10-Phenanthroline photometric method.*

## Publications referred to

See national foreword.

---

---

# **BSI — British Standards Institution**

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

## **Revisions**

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.  
Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

## **Buying standards**

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

## **Information on standards**

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.  
Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.  
Tel: 020 8996 7002. Fax: 020 8996 7001.

## **Copyright**

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager.  
Tel: 020 8996 7070.